

Optical Filter Glass

Data Sheets
Version June 2026

Introduction

This is a data sheet collection for our portfolio glasses in 2024. We have revised the layout of our data sheets: you can find data about the Knoop hardness for all filter glasses, which is given in the section “Mechanical properties” of each data sheet.

The date of the current data status is indicated on each data sheet.

Resistance against humidity

Group “resistant glasses”

No substantial surface change occurs in the filter glass types. A change in the surface is only possible under extreme conditions such as 85 °C and 85 % relative humidity over hundreds of hours.

Group “robust glasses”

These glass types withstand the warm humidity testing at 60 °C and 90 % relative humidity for more than 48 hours.

Group “sensitive glasses”

These glass types should be used and stored in a moderate climate or in closed work and store rooms (constant temperature below 35 °C, relative humidity less than 60 %). A desiccant is to be used when wetness is a possibility. For use and storage in open air and tropical climates, it is advisable to apply protective coatings by which SCHOTT can provide on request.

Group “delicate glasses”

For these types of optical filter glass, changes in the glass surface are possible after several months of normal storage. These glasses are to be handled with care: Any contact with water or warm humidity should be avoided. A desiccant is to be used for long-term storage of unprotected glass. For this reason, protective coatings are recommended which SCHOTT can provide upon request.

Refractive index

The refractive indices of the glass types are stated as reference values. Due to different annealing conditions, there are deviations from batch to batch. Any refractive indices within the defined wavelength range can be calculated from the Sellmeier dispersion formula.

Note that the wavelength must be entered into the Sellmeier dispersion formula in units of μm in order to calculate the correct refractive index from the given coefficients.

$$n^2 - 1 = \frac{B_1 \lambda^2}{\lambda^2 - C_1} + \frac{B_2 \lambda^2}{\lambda^2 - C_2} + \frac{B_3 \lambda^2}{\lambda^2 - C_3}$$

Transmission

The internal transmittance τ_i is given for the respective reference thickness d .

$$\tau_{i,d_1} = (\tau_{i,d})^{\left(\frac{d_1}{d}\right)}$$

The formula can be used to calculate the internal transmittance for any other thickness d_1 .



Nomenclature

AR	Alkali resistance class in accordance with ISO 10629
d	Reference thickness
B ₁ , B ₂ , B ₃	Coefficients of the Sellmeier dispersion formula
C ₁ , C ₂ , C ₃	Coefficients of the Sellmeier dispersion formula
FR	Stain resistance class in accordance with catalog “SCHOTT Optical Filter Glass”
HK[0,1/20]	Knoop hardness in accordance with ISO 9385
n _d	Refractive index at the d-line
P _e	Excitation purity
SR	Acid resistance class in accordance with ISO 8424
T _g	Transformation temperature in accordance with ISO 7884-8
Tk	Temperature coefficient longpass filter
x, y	Chromaticity coordinates
Y	Tristimulus value of brightness
$\alpha_{-30^{\circ}\text{C}/+70^{\circ}\text{C}}$	Linear coefficient of thermal expansion in 10 ⁻⁶ /K in the temperature range [– 30 °C to + 70 °C]
$\alpha_{20^{\circ}\text{C}/200^{\circ}\text{C}}$	Linear coefficient of thermal expansion in 10 ⁻⁶ /K in the temperature range [+ 20 °C to + 200 °C]
$\alpha_{20^{\circ}\text{C}/300^{\circ}\text{C}}$	Linear coefficient of thermal expansion in 10 ⁻⁶ /K in the temperature range [+ 20 °C to + 300 °C]. Some glasses have such a low T _g , that the measurement for those glass types is not feasible.
λ	Wavelength
λ_d	Dominant wavelength
τ_i	Internal transmittance
ρ	Density
P _d	Reflection Factor at the d-line

For further explanations, see the catalog “SCHOTT Optical Filter Glass”.

Table of contents


Filter type	Glass type	Filter type	Glass type
Bandpass filter	BG3	Longpass filter	N-WG205
	BG7		N-WG280
	BG18		N-WG295
	BG25		N-WG305
	BG38		N-WG320
	BG39		N-WG360
	BG40		GG395
	BG42		GG400
	BG47 NEW		GG420
	BG55		GG435
	BG59		GG455
	BG60		GG475
	BG60HT		GG495
	BG61		OG515
	BG62		OG530
	BG62HT		OG550
	BG63		OG570
	BG64		OG590
	BG66		RG610
	BG66HS		RG630
	BG67		RG645
	BG67HT		RG665
	S8022		RG695
	S8023		RG715
	S8612		RG9
	VG9		RG780
	VG20		RG830
UV-Bandpass filter	UG1		RG850
	UG2A		RG905
	UG5		RG1000
	UG11		S7000
Multi-Bandpass filter	BG36	Shortpass filter	KG1
	S7005		KG2
	S7010N		KG3
	S8008G		KG5
	S8802	Neutral density filter	NG1
	S8806A		NG3
	S8808		NG4
	S8809		NG5
	S8851		NG9
			NG11

BG3


Optical properties	
Reflection factor	
$P_d = 0,921$	
Spectral values guaranteed	
τ_i (365 nm)	$\geq 0,94$
τ_i (633 nm)	$\leq 0,00005$
Refractive indices	
n_F (486 nm)	$= 1,516$
n_e (546 nm)	$= 1,512$
n_d (587,6 nm)	$= 1,51$
Sellmeier coefficients	
valid from 300 nm to 1600 nm	
B_1	0,8735
B_2	0,3716
B_3	1,1076
C_1	9,390E-03 μm^2
C_2	1,0998E-02 μm^2
C_3	145,898 μm^2
Internal quality	
Bubble class	1

Mechanical properties	
Reference thickness	
$d = 1,00$ mm	
Density	
$\rho = 2,55$ g/cm ³	
Knoop hardness	
HK[0.1/20] = 438	
Thermal properties	
Transformation temperature	
$T_g = 478$ °C	
Thermal expansion in $10^{-6}/K$	
$\alpha_{(-30^\circ C/+70^\circ C)} = 8,8$	
$\alpha_{(20^\circ C/300^\circ C)} = 10,1$	
Chemical properties	
Chemical resistance	
FR class = 0	
SR class = 1	
AR class = 1	
Resistance against humidity	
Sensitive glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colorimetric properties		1 mm	2 mm	3 mm
Illuminant D65	x	0,154	0,160	0,163
	y	0,029	0,018	0,014
	Y	2,0	0,8	0,5
	λ_d	455 nm	448 nm	444 nm
	P_e	0,979	0,993	0,996
Illuminant A	x	0,160	0,166	0,170
	y	0,042	0,024	0,020
	Y	0,9	0,3	0,2
	λ_d	458 nm	447 nm	440 nm
	P_e	0,958	0,977	0,978
Notes				
UV				
Transmission changes are possible under the action of intense ultraviolet radiation.				
Ionically colored glass				
Bandpass filter / Shortpass filter				
ISO 23364:2021				
Disclaimer				
All data without tolerances are to be understood to be reference values.				

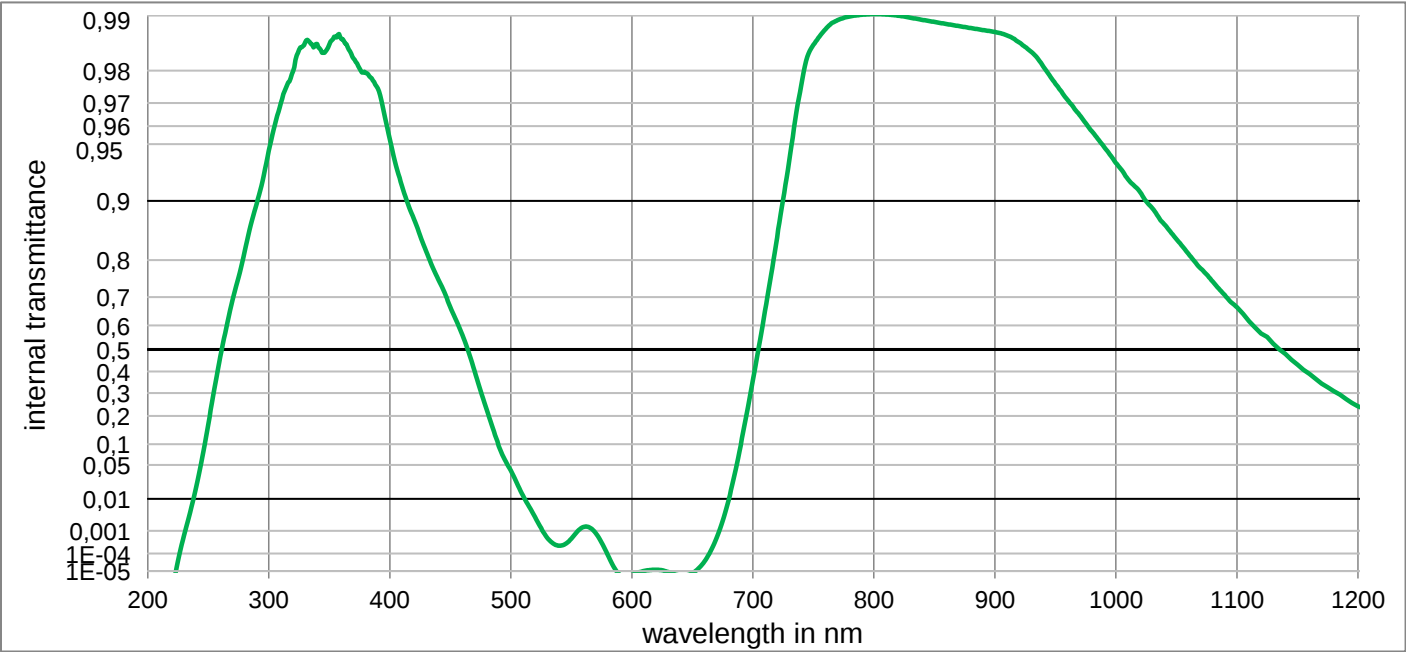


BG3

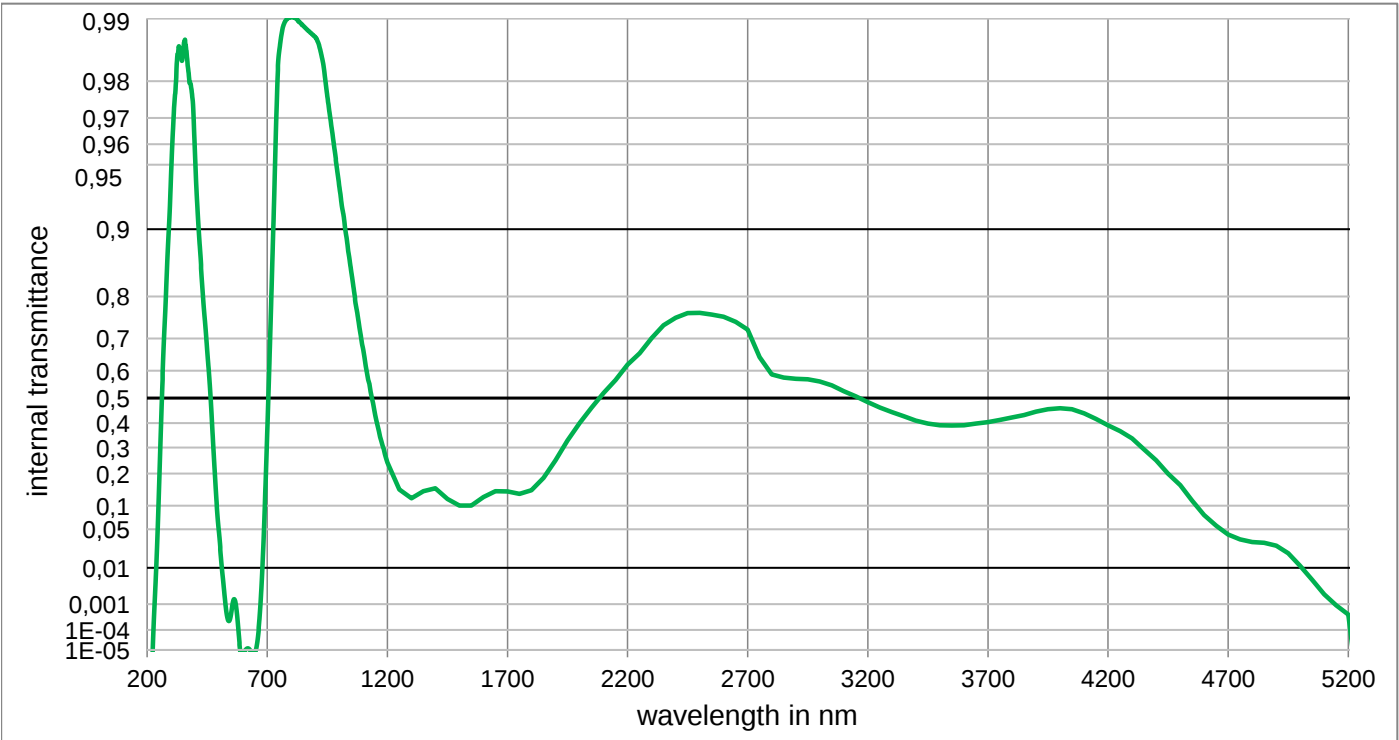


Internal transmittance τ_i at reference thickness											
The internal transmittance values, tabulated and graphically represented, are reference values only											
λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	4,007E-02	800	9,902E-01	1100	6,665E-01	2200	6,200E-01	3700	4,038E-01
210	< 1,000E-05	510	1,201E-02	810	9,901E-01	1110	6,152E-01	2250	6,566E-01	3750	4,132E-01
220	< 1,000E-05	520	2,977E-03	820	9,900E-01	1120	5,680E-01	2300	7,009E-01	3800	4,226E-01
230	6,761E-04	530	5,426E-04	830	9,897E-01	1130	5,247E-01	2350	7,349E-01	3850	4,330E-01
240	1,924E-02	540	2,394E-04	840	9,895E-01	1140	4,800E-01	2400	7,538E-01	3900	4,462E-01
250	1,690E-01	550	4,902E-04	850	9,892E-01	1150	4,319E-01	2450	7,642E-01	3950	4,557E-01
260	4,698E-01	560	1,401E-03	860	9,889E-01	1160	3,884E-01	2500	7,651E-01	4000	4,600E-01
270	6,903E-01	570	8,404E-04	870	9,886E-01	1170	3,432E-01	2550	7,613E-01	4050	4,557E-01
280	8,188E-01	580	8,776E-05	880	9,883E-01	1180	3,081E-01	2600	7,557E-01	4100	4,400E-01
290	8,972E-01	590	< 1,000E-05	890	9,880E-01	1190	2,727E-01	2650	7,434E-01	4150	4,170E-01
300	9,457E-01	600	< 1,000E-05	900	9,877E-01	1200	2,412E-01	2700	7,236E-01	4200	3,915E-01
310	9,700E-01	610	1,013E-05	910	9,872E-01	1250	1,462E-01	2750	6,443E-01	4250	3,670E-01
320	9,798E-01	620	1,227E-05	920	9,860E-01	1300	1,200E-01	2800	5,868E-01	4300	3,368E-01
330	9,859E-01	630	< 1,000E-05	930	9,842E-01	1350	1,406E-01	2850	5,764E-01	4350	2,925E-01
340	9,857E-01	640	< 1,000E-05	940	9,810E-01	1400	1,500E-01	2900	5,717E-01	4400	2,500E-01
350	9,856E-01	650	< 1,000E-05	950	9,764E-01	1450	1,179E-01	2950	5,698E-01	4450	2,000E-01
360	9,865E-01	660	3,783E-05	960	9,712E-01	1500	1,000E-01	3000	5,623E-01	4500	1,600E-01
370	9,829E-01	670	5,207E-04	970	9,651E-01	1550	1,000E-01	3050	5,481E-01	4550	1,132E-01
380	9,794E-01	680	9,561E-03	980	9,574E-01	1600	1,236E-01	3100	5,264E-01	4600	7,780E-02
390	9,750E-01	690	9,566E-02	990	9,484E-01	1650	1,406E-01	3150	5,066E-01	4650	5,610E-02
400	9,527E-01	700	3,590E-01	1000	9,369E-01	1700	1,400E-01	3200	4,840E-01	4700	4,159E-02
410	9,169E-01	710	6,550E-01	1010	9,230E-01	1750	1,330E-01	3250	4,632E-01	4750	3,483E-02
420	8,758E-01	720	8,460E-01	1020	9,099E-01	1800	1,443E-01	3300	4,443E-01	4800	3,170E-02
430	8,192E-01	730	9,380E-01	1030	8,909E-01	1850	1,849E-01	3350	4,274E-01	4850	3,076E-02
440	7,520E-01	740	9,760E-01	1040	8,680E-01	1900	2,500E-01	3400	4,100E-01	4900	2,729E-02
450	6,672E-01	750	9,856E-01	1050	8,428E-01	1950	3,283E-01	3450	3,981E-01	4950	2,004E-02
460	5,617E-01	760	9,881E-01	1060	8,133E-01	2000	4,000E-01	3500	3,915E-01	5000	1,099E-02
470	4,022E-01	770	9,894E-01	1070	7,800E-01	2050	4,623E-01	3550	3,896E-01	5050	5,082E-03
480	2,258E-01	780	9,899E-01	1080	7,463E-01	2100	5,200E-01	3600	3,915E-01	5100	2,032E-03
490	9,487E-02	790	9,901E-01	1090	7,060E-01	2150	5,670E-01	3650	3,981E-01	5150	9,099E-04

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm 2 mm 3 mm				
P _d = 0,919		d = 1,00 mm		Illuminant D65	x	0,191	0,152	0,138
Spectral values guaranteed		Density			y	0,272	0,229	0,200
τ _i (365 nm)	≥ 0,25	ρ = 2,60 g/cm³			Y	37,9	20,6	12,7
τ _i (488 nm)	≥ 0,78	Knoop hardness			λ _d	486 nm	484 nm	482 nm
τ _i (633 nm)	≤ 0,08	HK[0.1/20] = 441			P _e	0,493	0,675	0,758
				Illuminant A	x	0,262	0,179	0,145
		Thermal properties			y	0,406	0,360	0,317
Refractive indices		Transformation temperature			Y	30,1	14,5	8,2
n _F (486 nm)	= 1,526	Tg = 447 °C			λ _d	495 nm	492 nm	490 nm
n _e (546 nm)	= 1,521	Thermal expansion in 10 ⁻⁶ /K			P _e	0,438	0,654	0,755
n _d (587,6 nm)	= 1,519	α _(-30°C/+70°C) = 8,7		Notes				
		α _(20°C/300°C) = 10,0						
Sellmeier coefficients		Chemical properties		Ionically colored glass				
valid from 440 nm to 1550 nm		Chemical resistance		Bandpass filter / Shortpass filter				
B ₁	0,5574	FR class = 0						
B ₂	0,7122	SR class = 1						
B ₃	37,3513	AR class = 1		ISO 23364:2021				
		Resistance against humidity						
C ₂	1,8447E-02 μm²	Robust glass		Disclaimer				
C ₃	5502,533 μm²	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		All data without tolerances are to be understood to be reference values.				
Internal quality								
Bubble class	1							

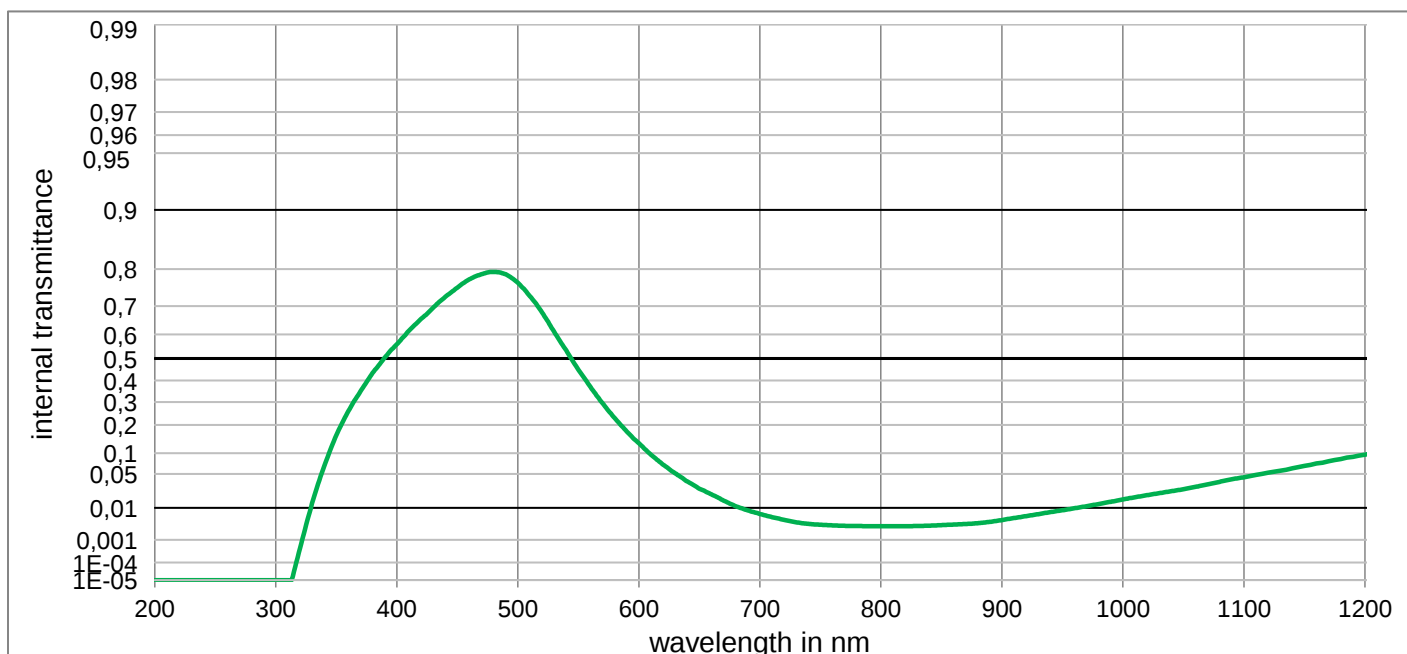


BG7

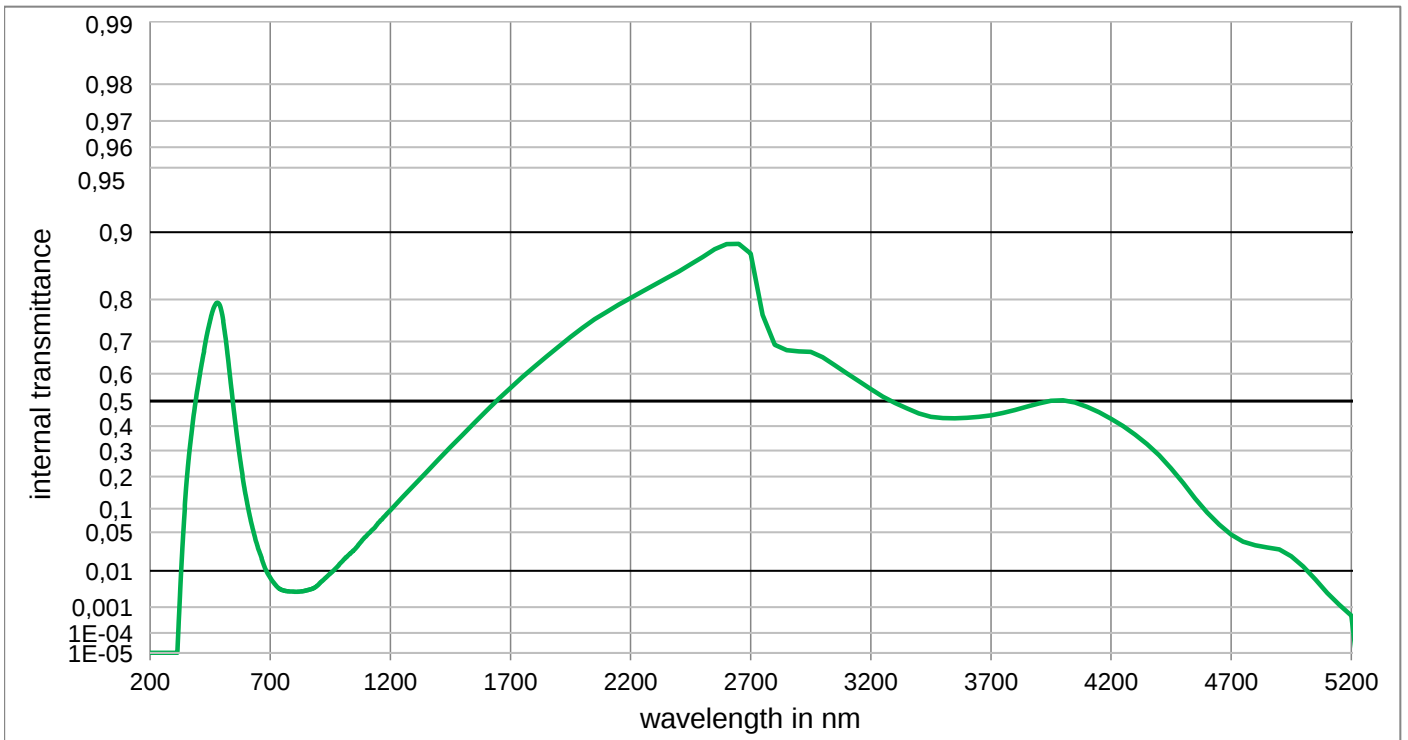Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	7,670E-01	800	2,994E-03	1100	4,400E-02	2200	8,025E-01	3700	4,437E-01
210	< 1,000E-05	510	7,300E-01	810	2,991E-03	1110	4,807E-02	2250	8,157E-01	3750	4,531E-01
220	< 1,000E-05	520	6,790E-01	820	3,000E-03	1120	5,220E-02	2300	8,274E-01	3800	4,648E-01
230	< 1,000E-05	530	6,110E-01	830	3,035E-03	1130	5,630E-02	2350	8,386E-01	3850	4,779E-01
240	< 1,000E-05	540	5,350E-01	840	3,117E-03	1140	6,164E-02	2400	8,493E-01	3900	4,903E-01
250	< 1,000E-05	550	4,500E-01	850	3,240E-03	1150	6,717E-02	2450	8,600E-01	3950	5,013E-01
260	< 1,000E-05	560	3,690E-01	860	3,370E-03	1160	7,262E-02	2500	8,704E-01	4000	5,034E-01
270	< 1,000E-05	570	2,950E-01	870	3,515E-03	1170	7,810E-02	2550	8,805E-01	4050	4,947E-01
280	< 1,000E-05	580	2,290E-01	880	3,723E-03	1180	8,353E-02	2600	8,866E-01	4100	4,778E-01
290	< 1,000E-05	590	1,740E-01	890	4,074E-03	1190	8,971E-02	2650	8,869E-01	4150	4,560E-01
300	< 1,000E-05	600	1,310E-01	900	4,627E-03	1200	9,577E-02	2700	8,749E-01	4200	4,300E-01
310	< 1,000E-05	610	9,600E-02	910	5,299E-03	1250	1,317E-01	2750	7,671E-01	4250	3,997E-01
320	4,675E-04	620	7,000E-02	920	5,997E-03	1300	1,713E-01	2800	6,908E-01	4300	3,656E-01
330	1,289E-02	630	5,100E-02	930	6,812E-03	1350	2,151E-01	2850	6,751E-01	4350	3,263E-01
340	6,592E-02	640	3,700E-02	940	7,737E-03	1400	2,635E-01	2900	6,716E-01	4400	2,809E-01
350	1,600E-01	650	2,700E-02	950	8,668E-03	1450	3,140E-01	2950	6,698E-01	4450	2,297E-01
360	2,600E-01	660	2,070E-02	960	9,771E-03	1500	3,629E-01	3000	6,536E-01	4500	1,774E-01
370	3,490E-01	670	1,500E-02	970	1,100E-02	1550	4,125E-01	3050	6,281E-01	4550	1,280E-01
380	4,350E-01	680	1,103E-02	980	1,244E-02	1600	4,621E-01	3100	6,016E-01	4600	9,050E-02
390	5,040E-01	690	8,610E-03	990	1,407E-02	1650	5,077E-01	3150	5,741E-01	4650	6,410E-02
400	5,610E-01	700	6,910E-03	1000	1,593E-02	1700	5,497E-01	3200	5,456E-01	4700	4,610E-02
410	6,140E-01	710	5,620E-03	1010	1,784E-02	1750	5,885E-01	3250	5,170E-01	4750	3,580E-02
420	6,570E-01	720	4,710E-03	1020	1,981E-02	1800	6,238E-01	3300	4,930E-01	4800	3,122E-02
430	6,950E-01	730	3,974E-03	1030	2,181E-02	1850	6,562E-01	3350	4,715E-01	4850	2,870E-02
440	7,280E-01	740	3,550E-03	1040	2,396E-02	1900	6,854E-01	3400	4,512E-01	4900	2,660E-02
450	7,540E-01	750	3,317E-03	1050	2,634E-02	1950	7,124E-01	3450	4,376E-01	4950	2,000E-02
460	7,755E-01	760	3,182E-03	1060	2,928E-02	2000	7,365E-01	3500	4,328E-01	5000	1,250E-02
470	7,881E-01	770	3,080E-03	1070	3,273E-02	2050	7,569E-01	3550	4,316E-01	5050	6,300E-03
480	7,936E-01	780	3,032E-03	1080	3,649E-02	2100	7,736E-01	3600	4,338E-01	5100	2,760E-03
490	7,880E-01	790	3,009E-03	1090	4,051E-02	2150	7,893E-01	3650	4,378E-01	5150	1,210E-03

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm 2 mm 3 mm				
P _d = 0,915		d = 1,00 mm		Illuminant D65	x	0,255	0,225	0,206
Spectral values guaranteed		Density			y	0,335	0,340	0,346
τ _i (350 nm)	≥ 0,3	ρ = 2,68 g/cm³			Y	67,6	54,2	45,1
τ _i (405 nm)	≥ 0,65	Knoop hardness			λ _d	493 nm	493 nm	493 nm
τ _i (514 nm)	≥ 0,88	HK[0.1/20] = 462			P _e	0,205	0,312	0,376
τ _i (633 nm)	≤ 0,25	Thermal properties		Illuminant A	x	0,361	0,309	0,275
τ _i (694 nm)	≤ 0,03	Transformation temperature			y	0,441	0,459	0,472
τ _i (1060 nm)	≤ 0,0005	Tg = 457 °C			Y	60,8	46,0	36,7
Refractive indices		Thermal expansion in 10 ⁻⁶ /K			λ _d	502 nm	501 nm	501 nm
n _F (486 nm) = 1,539	α _(-30°C/+70°C) = 7,4	α _(20°C/300°C) = 8,9			P _e	0,197	0,315	0,392
n _e (546 nm) = 1,536				Notes				
n _d (587,6 nm) = 1,534								
Sellmeier coefficients		Chemical properties		Ionically colored glass				
valid from 440 nm to 1550 nm		Chemical resistance		Bandpass filter / Shortpass filter				
B ₁ 1,2546		FR class = 0		NIR cutoff filter				
B ₂ 0,0793		SR class = 2						
B ₃ 90,1178		AR class = 2		ISO 23364:2021				
C ₁ 1,531E-03 μm²		Resistance against humidity						
C ₂ 7,2019E-02 μm²		Sensitive glass		Disclaimer				
C ₃ 8112,428 μm²		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		All data without tolerances are to be understood to be reference values.				
Internal quality								
Bubble class 2								

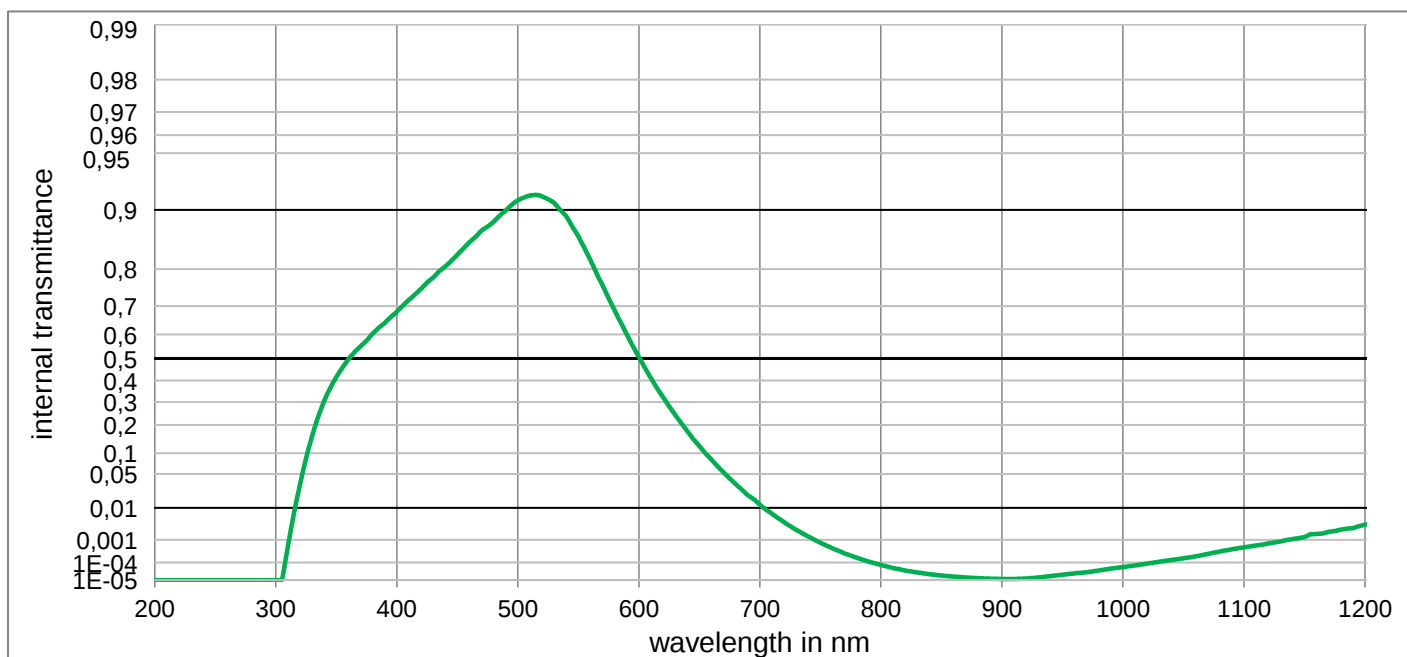


BG18

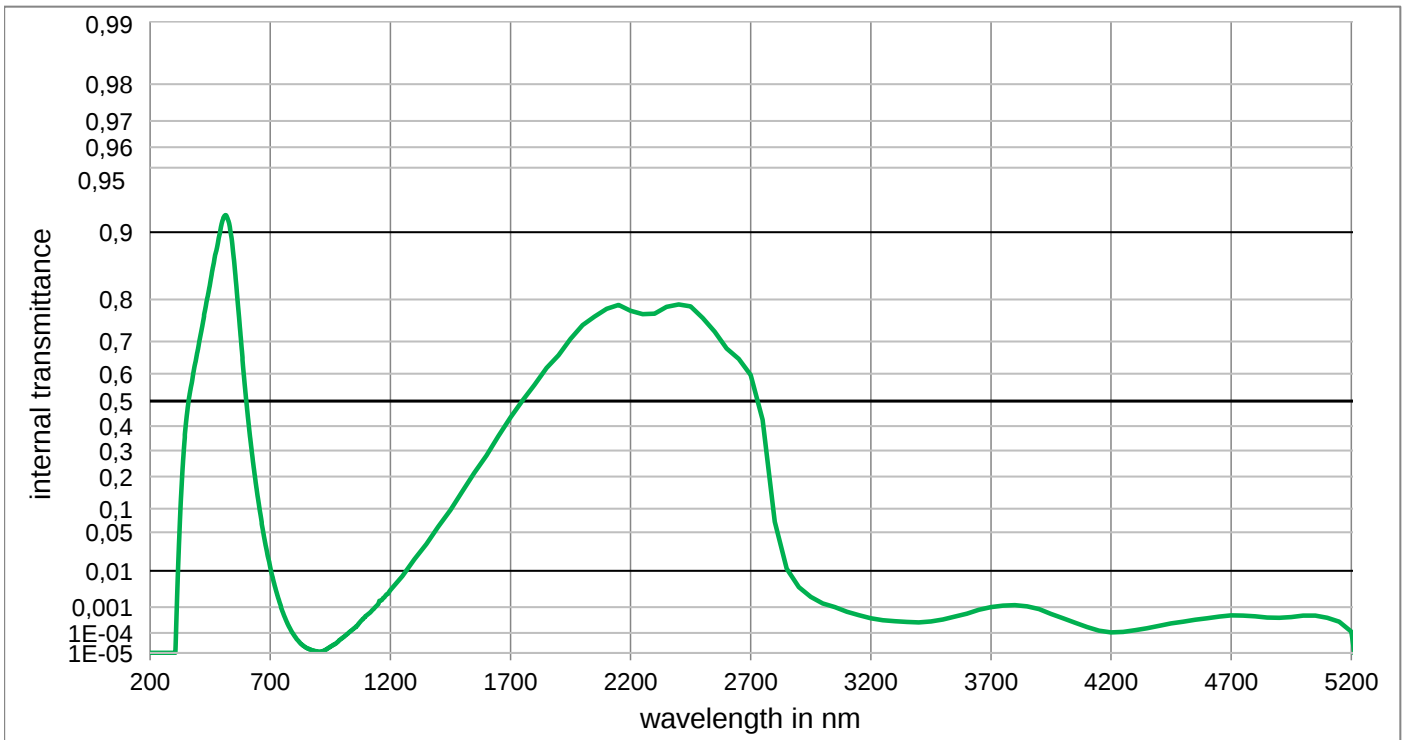Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,109E-01	800	7,603E-05	1100	5,023E-04	2200	7,765E-01	3700	1,000E-03
210	< 1,000E-05	510	9,159E-01	810	5,164E-05	1110	5,957E-04	2250	7,690E-01	3750	1,117E-03
220	< 1,000E-05	520	9,150E-01	820	3,784E-05	1120	7,145E-04	2300	7,700E-01	3800	1,156E-03
230	< 1,000E-05	530	9,081E-01	830	2,904E-05	1130	8,591E-04	2350	7,849E-01	3850	1,072E-03
240	< 1,000E-05	540	8,920E-01	840	2,323E-05	1140	1,056E-03	2400	7,900E-01	3900	8,650E-04
250	< 1,000E-05	550	8,630E-01	850	1,907E-05	1150	1,260E-03	2450	7,858E-01	3950	5,821E-04
260	< 1,000E-05	560	8,190E-01	860	1,661E-05	1160	1,624E-03	2500	7,600E-01	4000	4,000E-04
270	< 1,000E-05	570	7,610E-01	870	1,474E-05	1170	1,940E-03	2550	7,263E-01	4050	2,735E-04
280	< 1,000E-05	580	6,860E-01	880	1,331E-05	1180	2,299E-03	2600	6,800E-01	4100	1,803E-04
290	< 1,000E-05	590	6,000E-01	890	1,245E-05	1190	2,572E-03	2650	6,484E-01	4150	1,256E-04
300	< 1,000E-05	600	5,060E-01	900	1,188E-05	1200	3,303E-03	2700	5,956E-01	4200	1,064E-04
310	5,636E-04	610	4,110E-01	910	1,184E-05	1250	7,500E-03	2750	4,255E-01	4250	1,102E-04
320	3,300E-02	620	3,220E-01	920	1,265E-05	1300	1,760E-02	2800	7,000E-02	4300	1,327E-04
330	1,560E-01	630	2,420E-01	930	1,465E-05	1350	3,270E-02	2850	1,117E-02	4350	1,614E-04
340	3,050E-01	640	1,750E-01	940	1,771E-05	1400	6,000E-02	2900	4,000E-03	4400	2,000E-04
350	4,160E-01	650	1,220E-01	950	2,149E-05	1450	9,630E-02	2950	2,113E-03	4450	2,553E-04
360	4,970E-01	660	8,200E-02	960	2,560E-05	1500	1,500E-01	3000	1,318E-03	4500	2,972E-04
370	5,520E-01	670	5,300E-02	970	3,000E-05	1550	2,136E-01	3050	1,000E-03	4550	3,508E-04
380	6,030E-01	680	3,300E-02	980	3,747E-05	1600	2,800E-01	3100	7,000E-04	4600	4,000E-04
390	6,430E-01	690	1,992E-02	990	4,756E-05	1650	3,594E-01	3150	5,248E-04	4650	4,667E-04
400	6,820E-01	700	1,200E-02	1000	5,807E-05	1700	4,356E-01	3200	4,000E-04	4700	5,140E-04
410	7,190E-01	710	6,990E-03	1010	7,070E-05	1750	5,018E-01	3250	3,412E-04	4750	5,000E-04
420	7,510E-01	720	4,000E-03	1020	8,810E-05	1800	5,600E-01	3300	3,097E-04	4800	4,699E-04
430	7,800E-01	730	2,294E-03	1030	1,098E-04	1850	6,191E-01	3350	2,871E-04	4850	4,266E-04
440	8,060E-01	740	1,333E-03	1040	1,337E-04	1900	6,600E-01	3400	2,793E-04	4900	4,169E-04
450	8,300E-01	750	7,750E-04	1050	1,622E-04	1950	7,070E-01	3450	3,034E-04	4950	4,477E-04
460	8,530E-01	760	4,570E-04	1060	2,000E-04	2000	7,430E-01	3500	3,606E-04	5000	5,000E-04
470	8,720E-01	770	2,754E-04	1070	2,573E-04	2050	7,631E-01	3550	4,634E-04	5050	5,000E-04
480	8,850E-01	780	1,734E-04	1080	3,317E-04	2100	7,807E-01	3600	6,000E-04	5100	4,198E-04
490	8,991E-01	790	1,109E-04	1090	4,133E-04	2150	7,891E-01	3650	8,185E-04	5150	2,931E-04

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm 2 mm 3 mm				
P _d = 0,920		d = 1,00 mm		Illuminant D65	x	0,150	0,153	0,157
Spectral values guaranteed		Density			y	0,055	0,027	0,021
τ _i (334 nm)	≤ 0,8	ρ = 2,56 g/cm³			Y	5,0	1,8	1,1
τ _i (405 nm)	≥ 0,93	Knoop hardness			λ _d	463 nm	455 nm	451 nm
τ _i (488 nm)	≤ 0,39	HK[0.1/20] = 434			P _e	0,934	0,985	0,993
τ _i (725 nm)	≤ 0,36	Thermal properties		Illuminant A	x	0,155	0,151	0,155
Refractive indices		Transformation temperature			y	0,093	0,035	0,024
n _F (486 nm)	= 1,518	Tg = 459 °C			Y	2,6	0,7	0,4
n _e (546 nm)	= 1,514	Thermal expansion in 10 ⁻⁶ /K			λ _d	470 nm	459 nm	454 nm
n _d (587,6 nm)	= 1,512	α (-30°C/+70°C) = 8,9	α (20°C/300°C) = 10,2		P _e	0,903	0,981	0,992
Sellmeier coefficients		Chemical properties		Notes				
valid from 400 nm to 1550 nm		Chemical resistance		UV				
B ₁	0,8738	FR class = 0		Transmission changes are possible under the action of intense ultraviolet radiation.				
B ₂	0,3772	SR class = 1		Ionically colored glass				
B ₃	1,1188	AR class = 1		Bandpass filter / Shortpass filter				
C ₁	9,601E-03 μm²	Resistance against humidity		ISO 23364:2021				
C ₂	1,1147E-02 μm²	Robust glass		Disclaimer				
C ₃	145,493 μm²	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		All data without tolerances are to be understood to be reference values.				
Internal quality								
Bubble class	1							

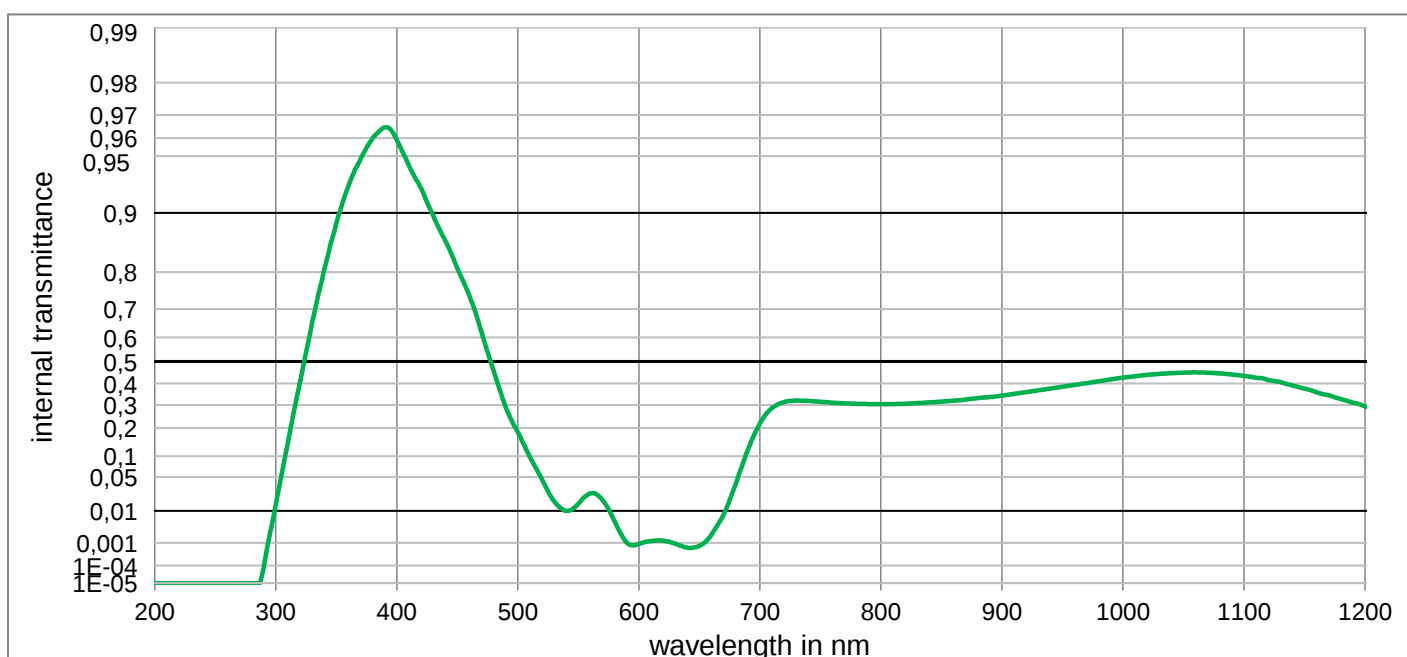


BG25

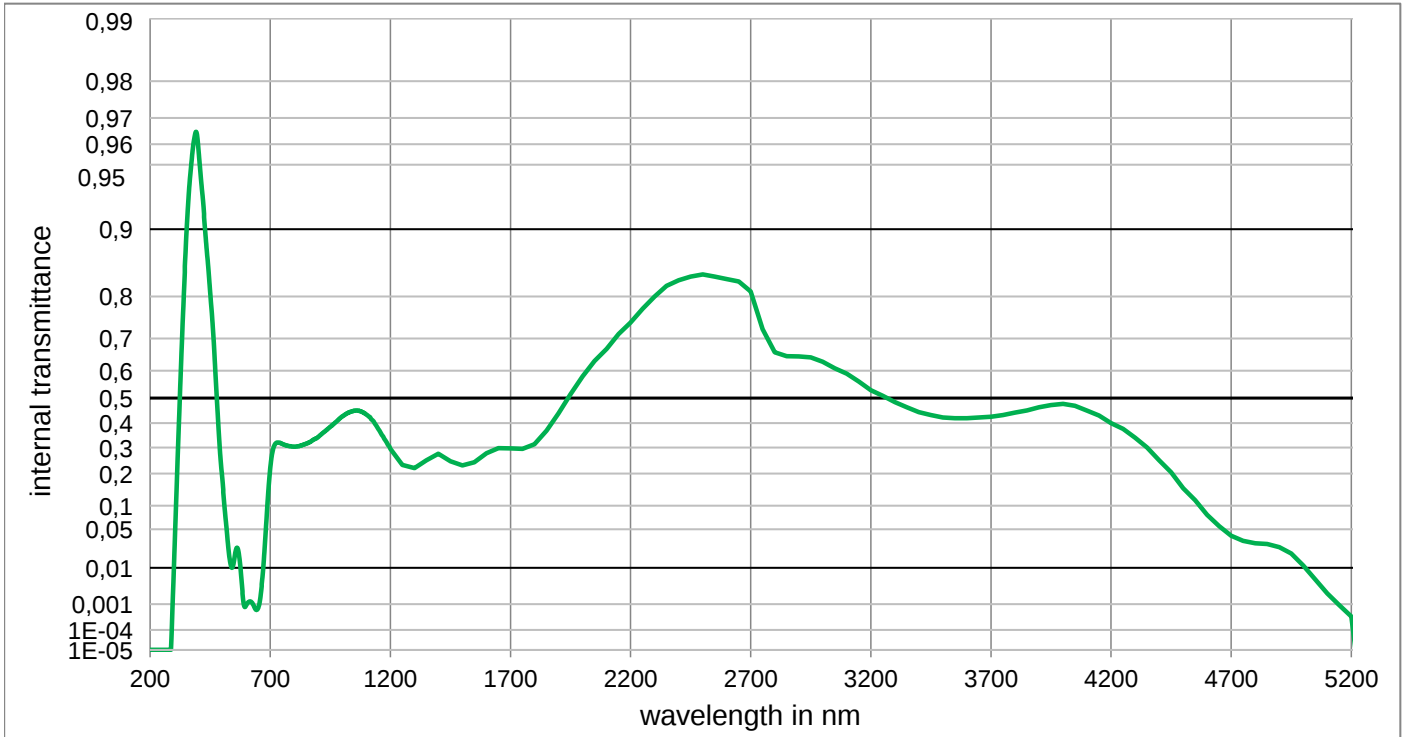Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	1,830E-01	800	3,037E-01	1100	4,350E-01	2200	7,421E-01	3700	4,262E-01
210	< 1,000E-05	510	9,700E-02	810	3,043E-01	1110	4,263E-01	2250	7,743E-01	3750	4,322E-01
220	< 1,000E-05	520	4,500E-02	820	3,060E-01	1120	4,160E-01	2300	8,000E-01	3800	4,424E-01
230	< 1,000E-05	530	1,700E-02	830	3,089E-01	1130	4,069E-01	2350	8,200E-01	3850	4,517E-01
240	< 1,000E-05	540	1,000E-02	840	3,122E-01	1140	3,915E-01	2400	8,300E-01	3900	4,636E-01
250	< 1,000E-05	550	1,500E-02	850	3,157E-01	1150	3,759E-01	2450	8,363E-01	3950	4,721E-01
260	< 1,000E-05	560	2,499E-02	860	3,200E-01	1160	3,598E-01	2500	8,400E-01	4000	4,772E-01
270	< 1,000E-05	570	1,800E-02	870	3,250E-01	1170	3,452E-01	2550	8,363E-01	4050	4,700E-01
280	< 1,000E-05	580	5,153E-03	880	3,320E-01	1180	3,280E-01	2600	8,321E-01	4100	4,500E-01
290	8,492E-05	590	1,014E-03	890	3,368E-01	1190	3,108E-01	2650	8,278E-01	4150	4,305E-01
300	1,400E-02	600	9,099E-04	900	3,438E-01	1200	2,943E-01	2700	8,100E-01	4200	4,000E-01
310	1,439E-01	610	1,170E-03	910	3,517E-01	1250	2,318E-01	2750	7,251E-01	4250	3,761E-01
320	4,080E-01	620	1,212E-03	920	3,598E-01	1300	2,200E-01	2800	6,600E-01	4300	3,400E-01
330	6,550E-01	630	9,256E-04	930	3,683E-01	1350	2,496E-01	2850	6,478E-01	4350	3,006E-01
340	8,050E-01	640	6,433E-04	940	3,764E-01	1400	2,751E-01	2900	6,470E-01	4400	2,500E-01
350	8,870E-01	650	7,603E-04	950	3,850E-01	1450	2,462E-01	2950	6,436E-01	4450	2,046E-01
360	9,280E-01	660	1,998E-03	960	3,932E-01	1500	2,300E-01	3000	6,300E-01	4500	1,500E-01
370	9,480E-01	670	7,995E-03	970	4,017E-01	1550	2,420E-01	3050	6,079E-01	4550	1,146E-01
380	9,600E-01	680	3,800E-02	980	4,106E-01	1600	2,768E-01	3100	5,900E-01	4600	7,834E-02
390	9,650E-01	690	1,180E-01	990	4,192E-01	1650	2,980E-01	3150	5,621E-01	4650	5,508E-02
400	9,590E-01	700	2,190E-01	1000	4,270E-01	1700	2,963E-01	3200	5,300E-01	4700	4,000E-02
410	9,440E-01	710	2,860E-01	1010	4,338E-01	1750	2,946E-01	3250	5,086E-01	4750	3,296E-02
420	9,260E-01	720	3,140E-01	1020	4,398E-01	1800	3,133E-01	3300	4,840E-01	4800	3,000E-02
430	8,970E-01	730	3,205E-01	1030	4,442E-01	1850	3,693E-01	3350	4,636E-01	4850	2,924E-02
440	8,610E-01	740	3,190E-01	1040	4,475E-01	1900	4,400E-01	3400	4,449E-01	4900	2,576E-02
450	8,090E-01	750	3,150E-01	1050	4,501E-01	1950	5,145E-01	3450	4,330E-01	4950	1,968E-02
460	7,400E-01	760	3,109E-01	1060	4,513E-01	2000	5,800E-01	3500	4,228E-01	5000	1,132E-02
470	6,200E-01	770	3,079E-01	1070	4,498E-01	2050	6,325E-01	3550	4,200E-01	5050	5,236E-03
480	4,570E-01	780	3,057E-01	1080	4,465E-01	2100	6,700E-01	3600	4,200E-01	5100	2,178E-03
490	2,910E-01	790	3,043E-01	1090	4,416E-01	2150	7,124E-01	3650	4,228E-01	5150	9,397E-04

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm 2 mm 3 mm				
P _d = 0,916		d = 1,00 mm		Illuminant D65	x	0,288	0,268	0,253
Spectral values guaranteed		Density			y	0,328	0,326	0,323
τ _i (350 nm)	≥ 0,8	ρ = 2,66 g/cm³			Y	83,2	76,4	70,8
τ _i (405 nm)	≥ 0,93	Knoop hardness			λ _d	491 nm	491 nm	490 nm
τ _i (514 nm)	≥ 0,95	HK[0.1/20] = 472			P _e	0,092	0,164	0,223
τ _i (633 nm)	≤ 0,67	Thermal properties		Illuminant A	x	0,413	0,384	0,360
τ _i (694 nm)	≤ 0,32	Transformation temperature			y	0,419	0,427	0,433
τ _i (1060 nm)	≤ 0,06	Tg = 482 °C			Y	79,7	70,7	63,7
Refractive indices		Thermal expansion in 10 ⁻⁶ /K			λ _d	501 nm	500 nm	500 nm
n _F (486 nm) = 1,533		α _(-30°C/+70°C) = 7,5			P _e	0,078	0,144	0,200
n _e (546 nm) = 1,529		α _(20°C/300°C) = 8,9		Notes				
n _d (587,6 nm) = 1,527				Ionically colored glass Bandpass filter / Shortpass filter NIR cutoff filter				
Sellmeier coefficients		Chemical properties						
valid from 440 nm to 1550 nm		Chemical resistance						
B ₁	0,3382	FR class = 0		ISO 23364:2021				
B ₂	0,9643	SR class = 2		Disclaimer All data without tolerances are to be understood to be reference values.				
B ₃	1,7959	AR class = 2						
C ₁	3,475E-03 μm²	Resistance against humidity						
C ₂	1,0319E-02 μm²	Sensitive glass						
C ₃	190,755 μm²	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5						
Internal quality								
Bubble class	2							

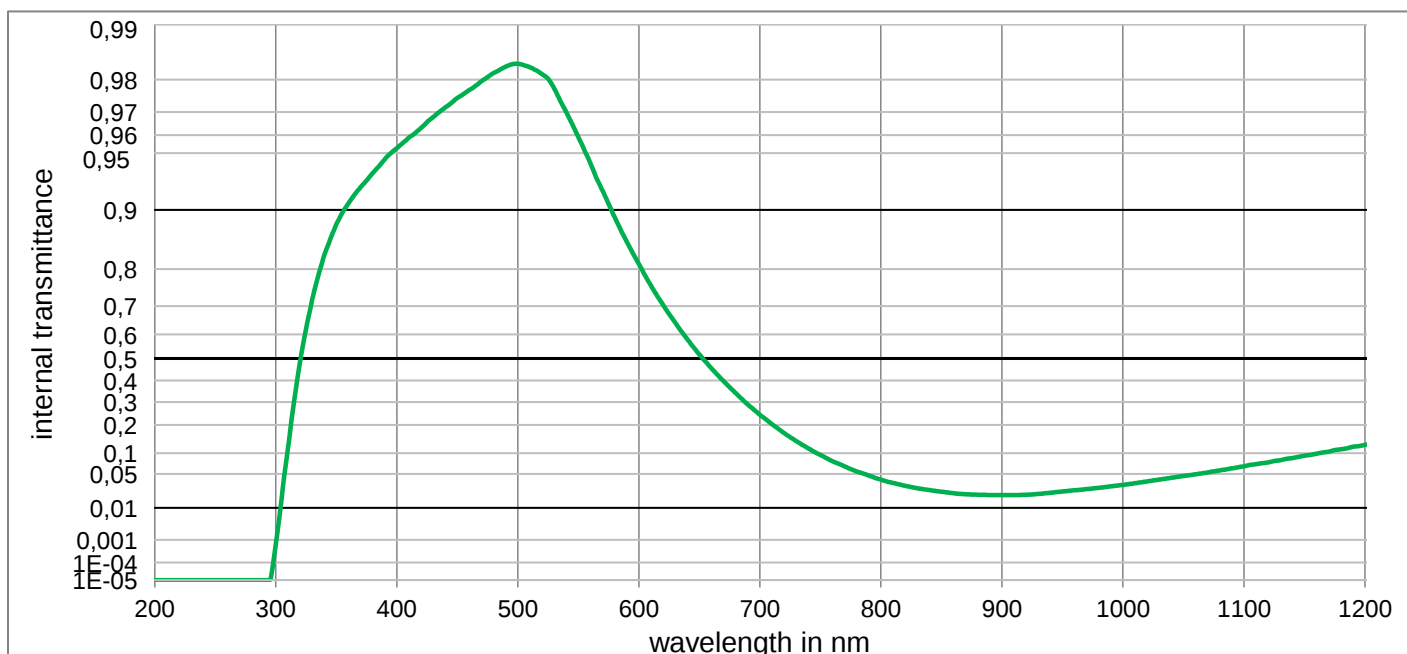

BG38

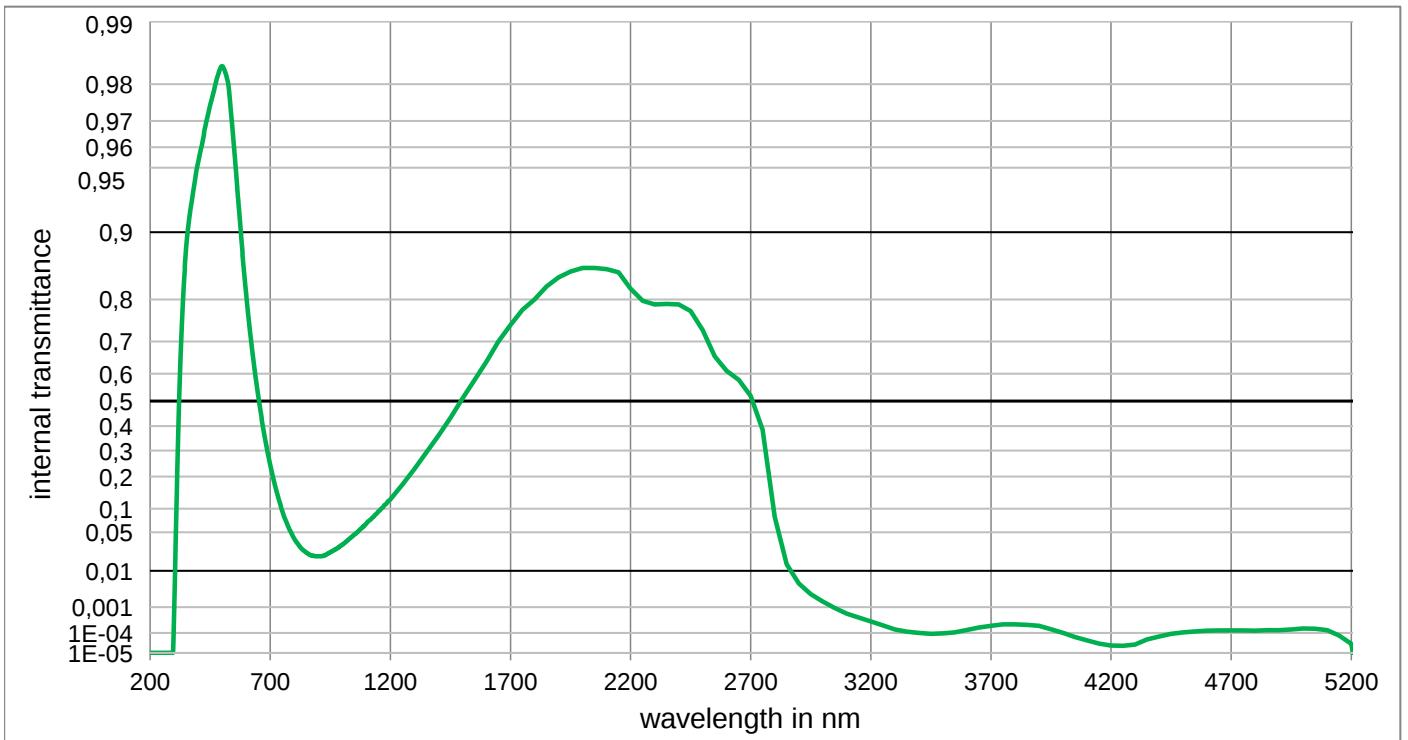Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,836E-01	800	4,002E-02	1100	6,593E-02	2200	8,208E-01	3700	2,000E-04
210	< 1,000E-05	510	9,829E-01	810	3,491E-02	1110	7,111E-02	2250	7,973E-01	3750	2,296E-04
220	< 1,000E-05	520	9,813E-01	820	3,080E-02	1120	7,524E-02	2300	7,897E-01	3800	2,317E-04
230	< 1,000E-05	530	9,777E-01	830	2,761E-02	1130	8,054E-02	2350	7,907E-01	3850	2,193E-04
240	< 1,000E-05	540	9,700E-01	840	2,539E-02	1140	8,631E-02	2400	7,897E-01	3900	2,000E-04
250	< 1,000E-05	550	9,590E-01	850	2,341E-02	1150	9,319E-02	2450	7,756E-01	3950	1,449E-04
260	< 1,000E-05	560	9,430E-01	860	2,183E-02	1160	9,869E-02	2500	7,300E-01	4000	1,000E-04
270	< 1,000E-05	570	9,210E-01	870	2,077E-02	1170	1,044E-01	2550	6,569E-01	4050	6,471E-05
280	< 1,000E-05	580	8,910E-01	880	2,026E-02	1180	1,113E-01	2600	6,100E-01	4100	4,436E-05
290	< 1,000E-05	590	8,540E-01	890	2,000E-02	1190	1,198E-01	2650	5,786E-01	4150	3,090E-05
300	6,457E-04	600	8,110E-01	900	1,991E-02	1200	1,258E-01	2700	5,200E-01	4200	2,500E-05
310	1,140E-01	610	7,600E-01	910	1,996E-02	1250	1,715E-01	2750	3,854E-01	4250	2,410E-05
320	4,870E-01	620	7,040E-01	920	2,020E-02	1300	2,281E-01	2800	8,000E-02	4300	2,818E-05
330	7,180E-01	630	6,440E-01	930	2,103E-02	1350	2,931E-01	2850	1,384E-02	4350	5,047E-05
340	8,290E-01	640	5,810E-01	940	2,227E-02	1400	3,600E-01	2900	5,000E-03	4400	6,776E-05
350	8,813E-01	650	5,180E-01	950	2,371E-02	1450	4,335E-01	2950	2,547E-03	4450	9,036E-05
360	9,077E-01	660	4,560E-01	960	2,505E-02	1500	5,100E-01	3000	1,531E-03	4500	1,047E-04
370	9,239E-01	670	3,970E-01	970	2,650E-02	1550	5,768E-01	3050	9,290E-04	4550	1,169E-04
380	9,359E-01	680	3,410E-01	980	2,805E-02	1600	6,400E-01	3100	6,000E-04	4600	1,247E-04
390	9,460E-01	690	2,890E-01	990	3,000E-02	1650	7,000E-01	3150	4,236E-04	4650	1,294E-04
400	9,530E-01	700	2,430E-01	1000	3,196E-02	1700	7,436E-01	3200	3,000E-04	4700	1,294E-04
410	9,587E-01	710	2,030E-01	1010	3,434E-02	1750	7,784E-01	3250	2,133E-04	4750	1,282E-04
420	9,634E-01	720	1,680E-01	1020	3,707E-02	1800	8,000E-01	3300	1,422E-04	4800	1,259E-04
430	9,680E-01	730	1,390E-01	1030	4,006E-02	1850	8,246E-01	3350	1,138E-04	4850	1,330E-04
440	9,717E-01	740	1,150E-01	1040	4,300E-02	1900	8,400E-01	3400	1,000E-04	4900	1,330E-04
450	9,748E-01	750	9,500E-02	1050	4,610E-02	1950	8,491E-01	3450	9,120E-05	4950	1,409E-04
460	9,772E-01	760	7,800E-02	1060	4,929E-02	2000	8,548E-01	3500	9,550E-05	5000	1,560E-04
470	9,796E-01	770	6,600E-02	1070	5,297E-02	2050	8,548E-01	3550	1,057E-04	5050	1,531E-04
480	9,816E-01	780	5,500E-02	1080	5,700E-02	2100	8,529E-01	3600	1,358E-04	5100	1,318E-04
490	9,830E-01	790	4,700E-02	1090	6,123E-02	2150	8,482E-01	3650	1,694E-04	5150	7,516E-05

Optical properties	
Reflection factor	
P _d = 0,914	
Spectral values guaranteed	
τ _i (350 nm)	≥ 0,6
τ _i (405 nm)	≥ 0,85
τ _i (514 nm)	≥ 0,93
τ _i (633 nm)	≤ 0,3
τ _i (694 nm)	≤ 0,03
τ _i (1060 nm)	≤ 0,001
Refractive indices	
n _F (486 nm)	= 1,542
n _e (546 nm)	= 1,538
n _d (587,6 nm)	= 1,536
Sellmeier coefficients	
valid from 440 nm to 1550 nm	
B ₁	0,4382
B ₂	0,8900
B ₃	7,4825
C ₁	2,508E-02 μm ²
C ₂	1,2201E-04 μm ²
C ₃	973,996 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,74 g/cm ³	
Knoop hardness	
HK[0.1/20] = 386	

Thermal properties	
Transformation temperature	
T _g = 322 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _(-30°C/+70°C) = 11,6	
α _(20°C/200°C) = 13,1	


Chemical properties	
Chemical resistance	
FR class = 0	
SR class = 5.1	
AR class = 3	
Resistance against humidity	
Delicate glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colormetric properties				
	1 mm	2 mm	3 mm	
Illuminant D65	x	0,257	0,226	0,207
	y	0,326	0,322	0,318
	Y	72,8	62,3	55,1
	λ _d	491 nm	490 nm	490 nm
	P _e	0,207	0,321	0,395
Illuminant A	x	0,365	0,314	0,279
	y	0,434	0,445	0,450
	Y	65,9	53,3	45,2
	λ _d	500 nm	500 nm	499 nm
	P _e	0,188	0,305	0,385

Notes
Ionically colored glass
Bandpass filter / Shortpass filter
NIR cutoff filter
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

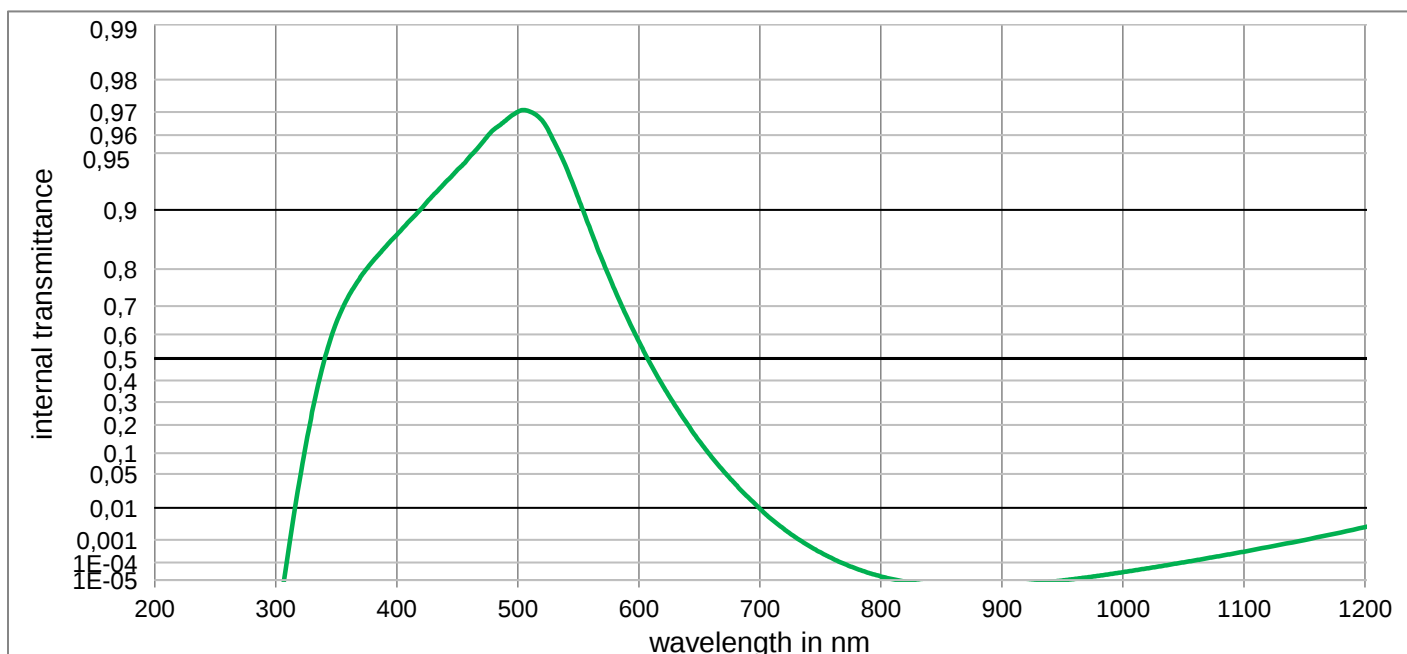


BG39

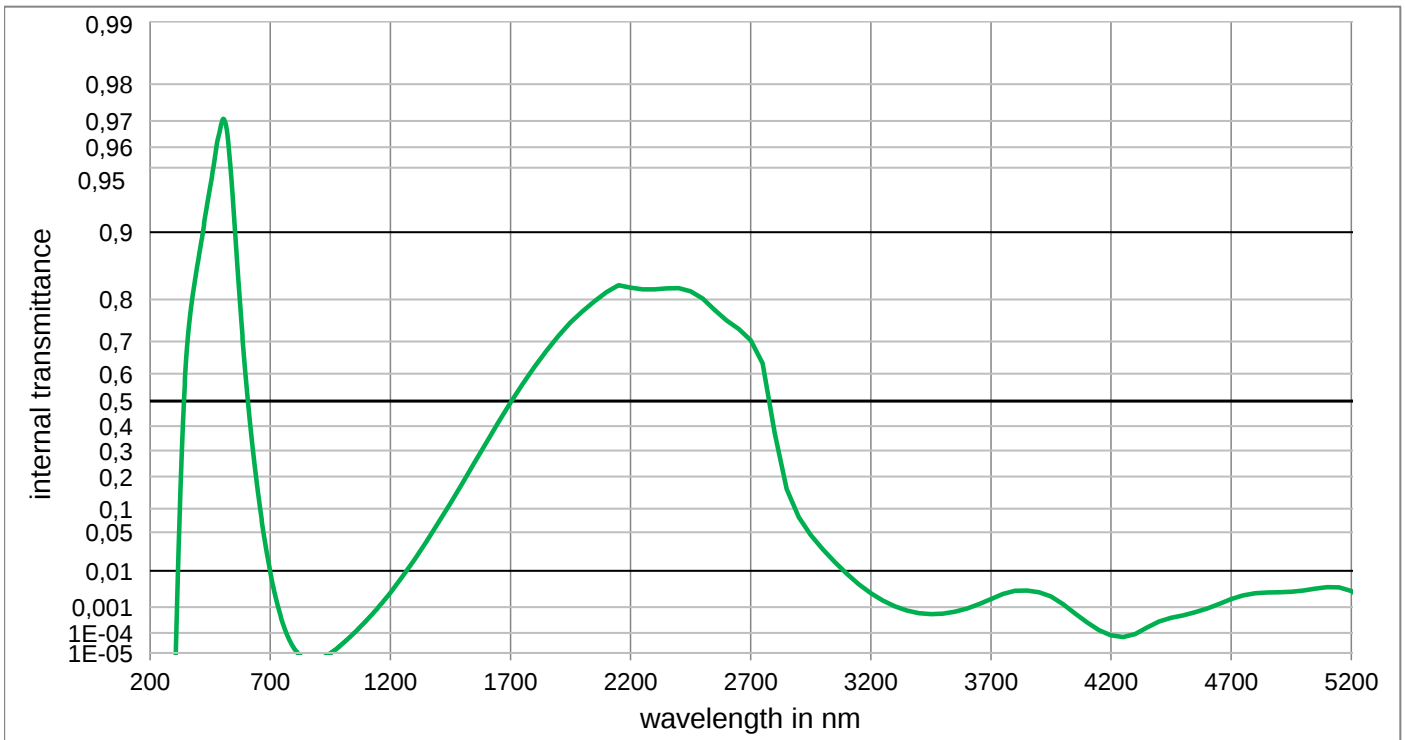Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,701E-01	800	1,679E-05	1100	3,264E-04	2200	8,223E-01	3700	1,829E-03
210	< 1,000E-05	510	9,702E-01	810	1,129E-05	1110	4,120E-04	2250	8,194E-01	3750	2,580E-03
220	< 1,000E-05	520	9,667E-01	820	< 1,000E-05	1120	5,116E-04	2300	8,195E-01	3800	3,154E-03
230	< 1,000E-05	530	9,566E-01	830	< 1,000E-05	1130	6,423E-04	2350	8,210E-01	3850	3,205E-03
240	< 1,000E-05	540	9,404E-01	840	< 1,000E-05	1140	7,952E-04	2400	8,214E-01	3900	2,858E-03
250	< 1,000E-05	550	9,132E-01	850	< 1,000E-05	1150	9,899E-04	2450	8,158E-01	3950	2,168E-03
260	< 1,000E-05	560	8,728E-01	860	< 1,000E-05	1160	1,222E-03	2500	8,015E-01	4000	1,246E-03
270	< 1,000E-05	570	8,184E-01	870	< 1,000E-05	1170	1,508E-03	2550	7,779E-01	4050	6,041E-04
280	< 1,000E-05	580	7,488E-01	880	< 1,000E-05	1180	1,853E-03	2600	7,542E-01	4100	2,775E-04
290	< 1,000E-05	590	6,653E-01	890	< 1,000E-05	1190	2,274E-03	2650	7,335E-01	4150	1,304E-04
300	< 1,000E-05	600	5,718E-01	900	< 1,000E-05	1200	2,781E-03	2700	7,036E-01	4200	7,747E-05
310	2,473E-04	610	4,724E-01	910	< 1,000E-05	1250	7,276E-03	2750	6,343E-01	4250	6,541E-05
320	4,316E-02	620	3,743E-01	920	< 1,000E-05	1300	1,708E-02	2800	3,706E-01	4300	8,895E-05
330	2,547E-01	630	2,834E-01	930	< 1,000E-05	1350	3,605E-02	2850	1,569E-01	4350	1,733E-04
340	4,905E-01	640	2,037E-01	940	< 1,000E-05	1400	6,784E-02	2900	7,906E-02	4400	3,052E-04
350	6,442E-01	650	1,392E-01	950	< 1,000E-05	1450	1,147E-01	2950	4,535E-02	4450	4,169E-04
360	7,297E-01	660	8,981E-02	960	1,176E-05	1500	1,765E-01	3000	2,671E-02	4500	5,160E-04
370	7,811E-01	670	5,537E-02	970	1,474E-05	1550	2,513E-01	3050	1,536E-02	4550	6,651E-04
380	8,163E-01	680	3,258E-02	980	1,859E-05	1600	3,332E-01	3100	8,588E-03	4600	9,006E-04
390	8,436E-01	690	1,825E-02	990	2,366E-05	1650	4,155E-01	3150	4,772E-03	4650	1,277E-03
400	8,658E-01	700	9,545E-03	1000	3,013E-05	1700	4,949E-01	3200	2,711E-03	4700	1,805E-03
410	8,849E-01	710	4,770E-03	1010	3,852E-05	1750	5,633E-01	3250	1,632E-03	4750	2,353E-03
420	9,011E-01	720	2,404E-03	1020	4,902E-05	1800	6,229E-01	3300	1,062E-03	4800	2,719E-03
430	9,162E-01	730	1,205E-03	1030	6,271E-05	1850	6,739E-01	3350	7,617E-04	4850	2,853E-03
440	9,283E-01	740	6,007E-04	1040	7,974E-05	1900	6,158E-01	3400	6,129E-04	4900	2,887E-03
450	9,384E-01	750	3,062E-04	1050	1,018E-04	1950	7,492E-01	3450	5,650E-04	4950	2,973E-03
460	9,475E-01	760	1,568E-04	1060	1,287E-04	2000	7,754E-01	3500	5,886E-04	5000	3,218E-03
470	9,556E-01	770	8,431E-05	1070	1,640E-04	2050	7,963E-01	3550	6,906E-04	5050	3,616E-03
480	9,626E-01	780	4,649E-05	1080	2,067E-04	2100	8,145E-01	3600	8,896E-04	5100	3,971E-03
490	9,666E-01	790	2,707E-05	1090	2,611E-04	2150	8,268E-01	3650	1,246E-03	5150	3,909E-03

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm 2 mm 3 mm				
P _d = 0,916		d = 1,00 mm		Illuminant D65	x	0,283	0,262	0,246
Spectral values guaranteed		Density			y	0,327	0,324	0,321
τ _i (350 nm) ≥ 0,8		ρ = 2,74 g/cm³			Y	82,1	74,8	69,0
τ _i (405 nm) ≥ 0,93		Knoop hardness			λ _d	491 nm	490 nm	490 nm
τ _i (514 nm) ≥ 0,97		HK[0.1/20] = 383			P _e	0,108	0,188	0,250
τ _i (633 nm) ≤ 0,57		Thermal properties		Illuminant A	x	0,406	0,374	0,348
τ _i (694 nm) ≤ 0,16		Transformation temperature			y	0,421	0,430	0,436
τ _i (1060 nm) ≤ 0,02		T _g = 313 °C			Y	78,0	68,4	61,3
Refractive indices		Thermal expansion in 10 ⁻⁶ /K			λ _d	501 nm	500 nm	500 nm
n _F (486 nm) = 1,536		α _(-30°C/+70°C) = 11,9			P _e	0,094	0,168	0,227
n _e (546 nm) = 1,532		α _(20°C/200°C) = 13,7		Notes				
n _d (587,6 nm) = 1,53		Chemical properties		Ionically colored glass Bandpass filter / Shortpass filter NIR cutoff filter				
Sellmeier coefficients		Chemical resistance						
valid from 435 nm to 1550 nm		FR class = 0		ISO 23364:2021				
B ₁ 0,9300		SR class = 5.1						
B ₂ 0,3779		AR class = 3		Disclaimer				
B ₃ 1,0478		Resistance against humidity						
C ₁ 8,617E-03 μm²		Sensitive glass		All data without tolerances are to be understood to be reference values.				
C ₂ 1,0398E-02 μm²		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5						
C ₃ 149,651 μm²		Internal quality						
Bubble class 1								

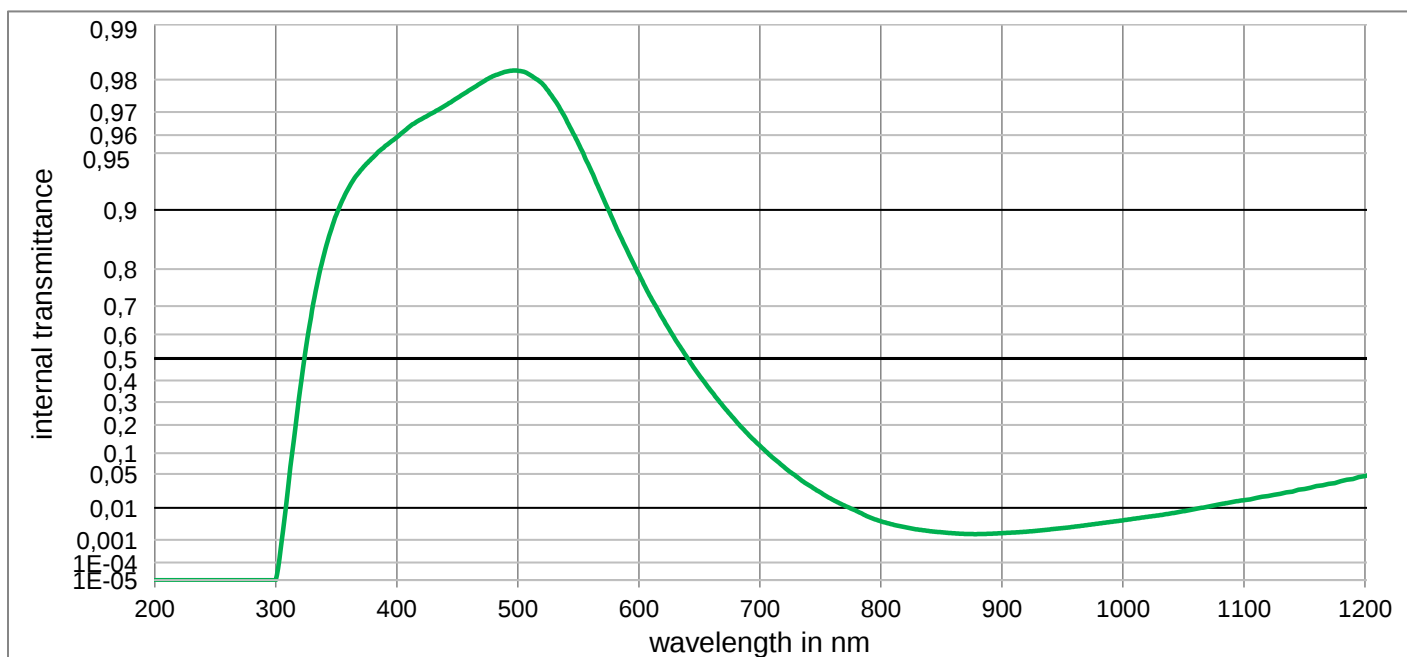


BG40

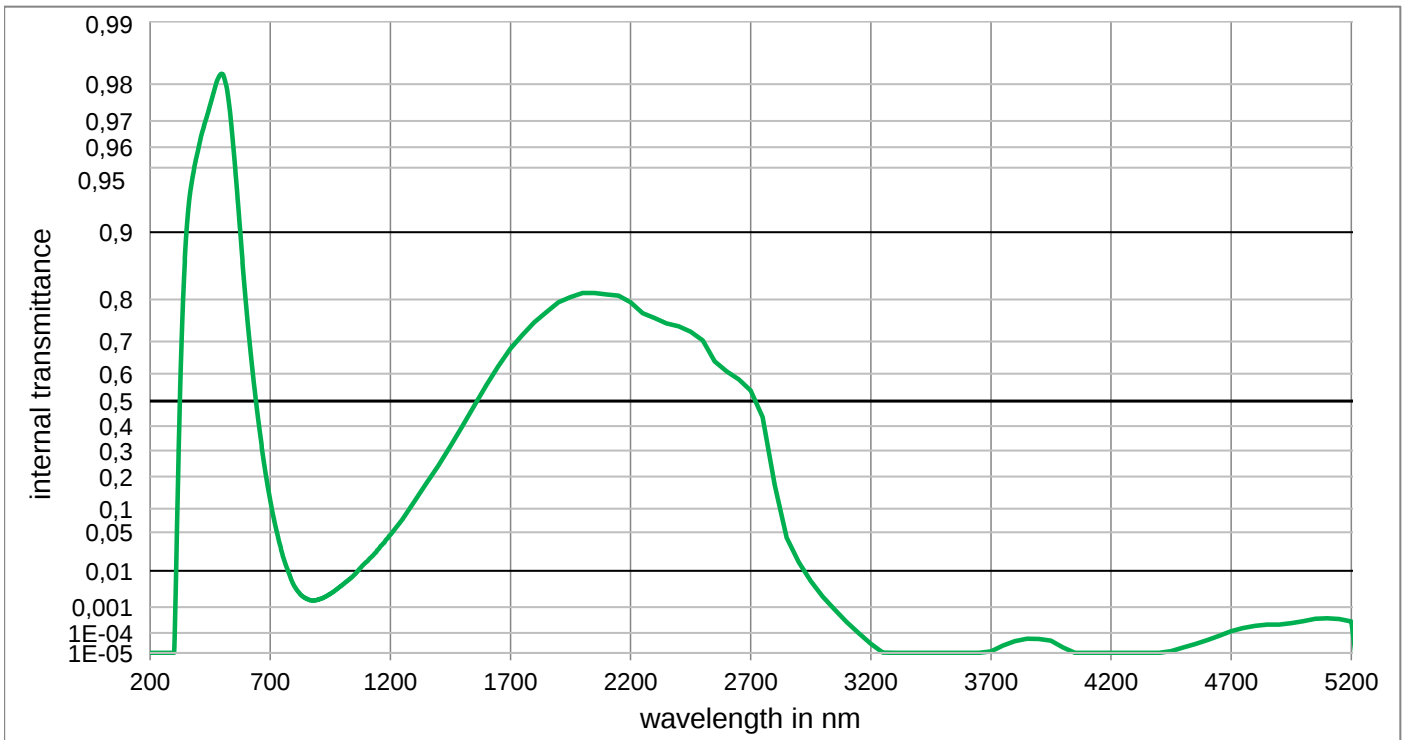Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,821E-01	800	4,252E-03	1100	1,533E-02	2200	7,945E-01	3700	1,213E-05
210	< 1,000E-05	510	9,812E-01	810	3,366E-03	1110	1,712E-02	2250	7,709E-01	3750	2,518E-05
220	< 1,000E-05	520	9,790E-01	820	2,780E-03	1120	1,901E-02	2300	7,600E-01	3800	4,169E-05
230	< 1,000E-05	530	9,745E-01	830	2,340E-03	1130	2,123E-02	2350	7,473E-01	3850	5,395E-05
240	< 1,000E-05	540	9,670E-01	840	2,062E-03	1140	2,354E-02	2400	7,400E-01	3900	5,333E-05
250	< 1,000E-05	550	9,556E-01	850	1,880E-03	1150	2,665E-02	2450	7,266E-01	3950	4,335E-05
260	< 1,000E-05	560	9,390E-01	860	1,734E-03	1160	3,051E-02	2500	7,030E-01	4000	2,000E-05
270	< 1,000E-05	570	9,150E-01	870	1,644E-03	1170	3,350E-02	2550	6,408E-01	4050	< 1,000E-05
280	< 1,000E-05	580	8,820E-01	880	1,622E-03	1180	3,747E-02	2600	6,079E-01	4100	< 1,000E-05
290	< 1,000E-05	590	8,400E-01	890	1,670E-03	1190	4,112E-02	2650	5,805E-01	4150	< 1,000E-05
300	< 1,000E-05	600	7,880E-01	900	1,752E-03	1200	4,588E-02	2700	5,400E-01	4200	< 1,000E-05
310	2,600E-02	610	7,260E-01	910	1,850E-03	1250	7,450E-02	2750	4,363E-01	4250	< 1,000E-05
320	3,560E-01	620	6,570E-01	920	1,964E-03	1300	1,200E-01	2800	1,700E-01	4300	< 1,000E-05
330	6,860E-01	630	5,810E-01	930	2,136E-03	1350	1,762E-01	2850	4,150E-02	4350	< 1,000E-05
340	8,320E-01	640	5,030E-01	940	2,360E-03	1400	2,400E-01	2900	1,510E-02	4400	< 1,000E-05
350	8,940E-01	650	4,240E-01	950	2,607E-03	1450	3,185E-01	2950	5,754E-03	4450	1,256E-05
360	9,230E-01	660	3,490E-01	960	2,880E-03	1500	4,000E-01	3000	2,153E-03	4500	2,000E-05
370	9,380E-01	670	2,790E-01	970	3,228E-03	1550	4,825E-01	3050	8,072E-04	4550	2,958E-05
380	9,470E-01	680	2,170E-01	980	3,631E-03	1600	5,600E-01	3100	2,818E-04	4600	4,645E-05
390	9,540E-01	690	1,650E-01	990	4,064E-03	1650	6,258E-01	3150	9,840E-05	4650	7,362E-05
400	9,590E-01	700	1,230E-01	1000	4,527E-03	1700	6,800E-01	3200	3,000E-05	4700	1,197E-04
410	9,638E-01	710	8,900E-02	1010	5,091E-03	1750	7,181E-01	3250	1,033E-05	4750	1,618E-04
420	9,671E-01	720	6,400E-02	1020	5,708E-03	1800	7,500E-01	3300	< 1,000E-05	4800	2,000E-04
430	9,698E-01	730	4,570E-02	1030	6,370E-03	1850	7,737E-01	3350	< 1,000E-05	4850	2,286E-04
440	9,723E-01	740	3,200E-02	1040	7,145E-03	1900	7,945E-01	3400	< 1,000E-05	4900	2,286E-04
450	9,748E-01	750	2,267E-02	1050	8,180E-03	1950	8,048E-01	3450	< 1,000E-05	4950	2,600E-04
460	9,771E-01	760	1,580E-02	1060	9,350E-03	2000	8,124E-01	3500	< 1,000E-05	5000	3,126E-04
470	9,792E-01	770	1,138E-02	1070	1,068E-02	2050	8,124E-01	3550	< 1,000E-05	5050	3,802E-04
480	9,809E-01	780	8,250E-03	1080	1,221E-02	2100	8,100E-01	3600	< 1,000E-05	5100	3,981E-04
490	9,819E-01	790	5,710E-03	1090	1,384E-02	2150	8,076E-01	3650	< 1,000E-05	5150	3,758E-04

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,914$	$d = 1,00 \text{ mm}$	
Spectral values guaranteed	Density	
$\tau_i (350 \text{ nm}) \geq 0,4$	$\rho = 2,69 \text{ g/cm}^3$	
$\tau_i (405 \text{ nm}) \geq 0,65$	Knoop hardness	
$\tau_i (514 \text{ nm}) \geq 0,88$	$HK[0.1/20] = 467$	
$\tau_i (633 \text{ nm}) \leq 0,27$		
$\tau_i (694 \text{ nm}) \leq 0,03$	Thermal properties	
$\tau_i (1060 \text{ nm}) \leq 0,002$	Transformation temperature	
	$T_g = 475 \text{ }^\circ\text{C}$	
	Thermal expansion in $10^{-6}/\text{K}$	
Refractive indices	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,3$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 8,7$	
Sellmeier coefficients	Chemical properties	
on request	Chemical resistance	
	FR class = 0	
	SR class = 2	
	AR class = 2	
	Resistance against humidity	
	Sensitive glass	
Internal quality	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
Bubble class 2		
		Notes
		Ionically colored glass
		Bandpass filter / Shortpass filter
		NIR cutoff filter
		ISO 23364:2021
		Disclaimer
		All data without tolerances are to be understood to be reference values.

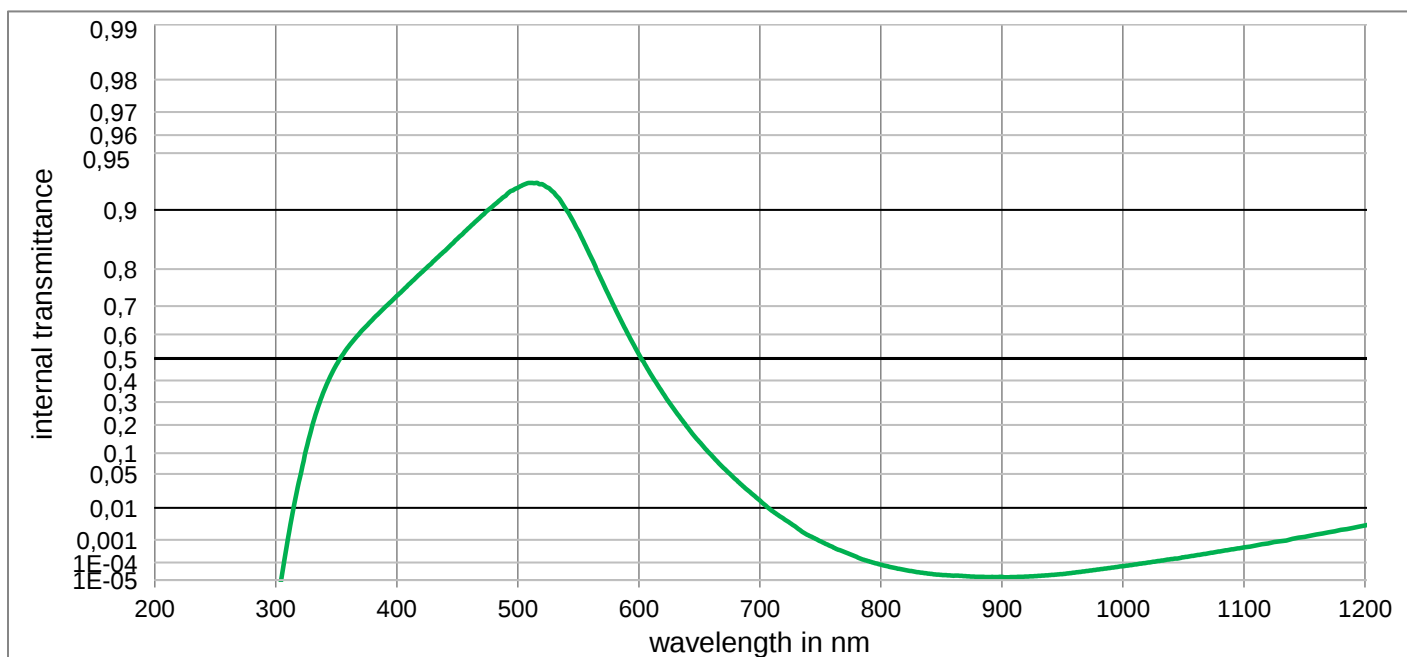

BG42

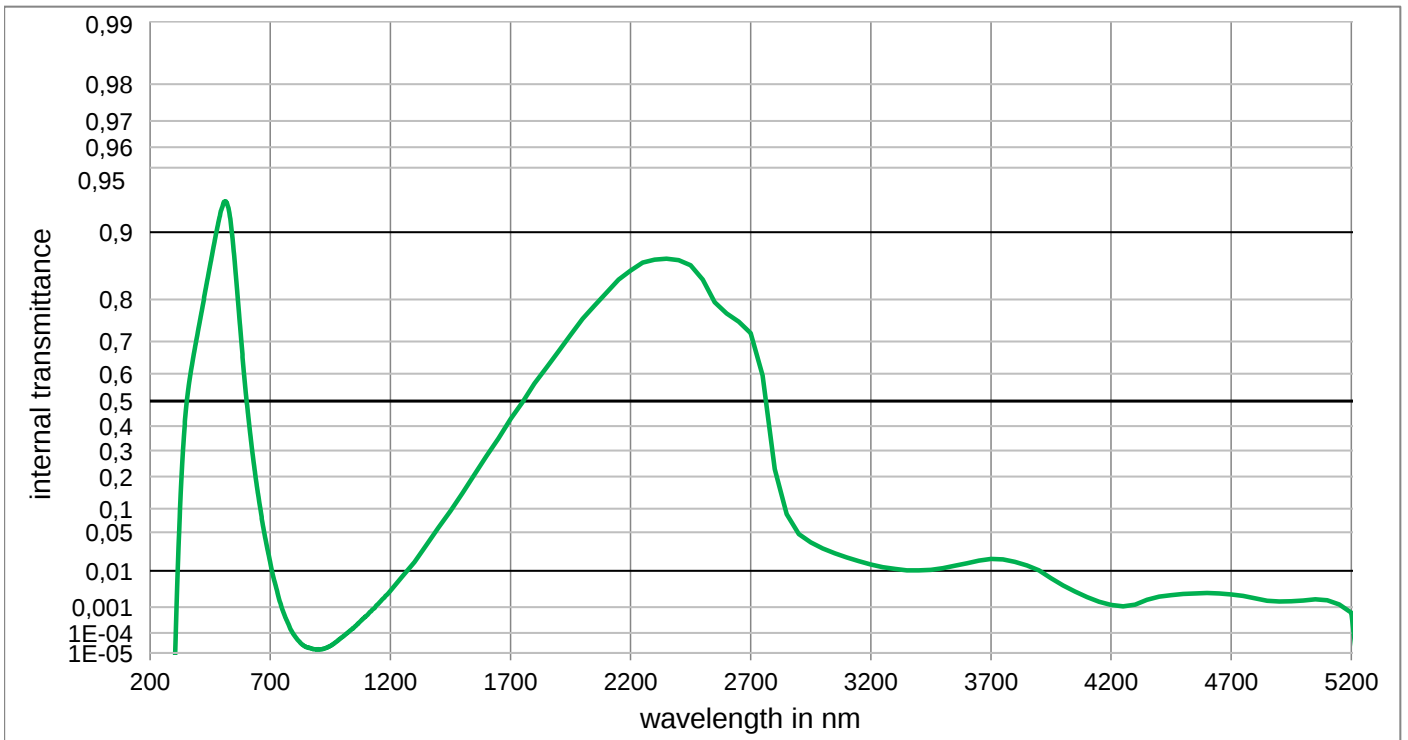Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,234E-01	800	7,768E-05	1100	4,963E-04	2200	8,507E-01	3700	1,775E-02
210	< 1,000E-05	510	9,279E-01	810	5,462E-05	1110	6,033E-04	2250	8,624E-01	3750	1,729E-02
220	< 1,000E-05	520	9,267E-01	820	3,995E-05	1120	7,275E-04	2300	8,665E-01	3800	1,543E-02
230	< 1,000E-05	530	9,188E-01	830	3,059E-05	1130	8,722E-04	2350	8,678E-01	3850	1,301E-02
240	< 1,000E-05	540	9,003E-01	840	2,447E-05	1140	1,095E-03	2400	8,660E-01	3900	1,018E-02
250	< 1,000E-05	550	8,716E-01	850	2,086E-05	1150	1,277E-03	2450	8,588E-01	3950	6,779E-03
260	< 1,000E-05	560	8,276E-01	860	1,861E-05	1160	1,563E-03	2500	8,362E-01	4000	4,415E-03
270	< 1,000E-05	570	7,687E-01	870	1,773E-05	1170	1,864E-03	2550	7,946E-01	4050	3,031E-03
280	< 1,000E-05	580	6,953E-01	880	1,585E-05	1180	2,255E-03	2600	7,705E-01	4100	2,085E-03
290	< 1,000E-05	590	6,101E-01	890	1,546E-05	1190	2,633E-03	2650	7,512E-01	4150	1,498E-03
300	< 1,000E-05	600	5,178E-01	900	1,593E-05	1200	3,171E-03	2700	7,228E-01	4200	1,191E-03
310	1,094E-03	610	4,287E-01	910	1,546E-05	1250	7,380E-03	2750	5,938E-01	4250	1,063E-03
320	4,416E-02	620	3,398E-01	920	1,658E-05	1300	1,533E-02	2800	2,270E-01	4300	1,199E-03
330	1,931E-01	630	2,598E-01	930	1,816E-05	1350	3,166E-02	2850	8,630E-02	4350	1,720E-03
340	3,537E-01	640	1,909E-01	940	2,045E-05	1400	5,808E-02	2900	4,698E-02	4400	2,140E-03
350	4,717E-01	650	1,366E-01	950	2,350E-05	1450	9,389E-02	2950	3,497E-02	4450	2,362E-03
360	5,508E-01	660	9,400E-02	960	2,852E-05	1500	1,440E-01	3000	2,755E-02	4500	2,572E-03
370	6,085E-01	670	6,215E-02	970	3,496E-05	1550	2,069E-01	3050	2,263E-02	4550	2,675E-03
380	6,549E-01	680	4,026E-02	980	4,313E-05	1600	2,781E-01	3100	1,895E-02	4600	2,729E-03
390	6,954E-01	690	2,523E-02	990	5,297E-05	1650	3,496E-01	3150	1,605E-02	4650	2,641E-03
400	7,309E-01	700	1,516E-02	1000	6,464E-05	1700	4,287E-01	3200	1,362E-02	4700	2,506E-03
410	7,626E-01	710	8,398E-03	1010	7,923E-05	1750	4,958E-01	3250	1,195E-02	4750	2,256E-03
420	7,909E-01	720	4,946E-03	1020	9,752E-05	1800	5,652E-01	3300	1,104E-02	4800	1,914E-03
430	8,164E-01	730	2,764E-03	1030	1,198E-04	1850	6,214E-01	3350	1,027E-02	4850	1,621E-03
440	8,385E-01	740	1,476E-03	1040	1,471E-04	1900	6,717E-01	3400	1,018E-02	4900	1,518E-03
450	8,590E-01	750	8,860E-04	1050	1,815E-04	1950	7,173E-01	3450	1,055E-02	4950	1,548E-03
460	8,769E-01	760	5,196E-04	1060	2,215E-04	2000	7,583E-01	3500	1,139E-02	5000	1,632E-03
470	8,923E-01	770	3,134E-04	1070	2,726E-04	2050	7,873E-01	3550	1,284E-02	5050	1,777E-03
480	9,053E-01	780	1,872E-04	1080	3,342E-04	2100	8,136E-01	3600	1,445E-02	5100	1,675E-03
490	9,158E-01	790	1,157E-04	1090	4,095E-04	2150	8,362E-01	3650	1,637E-02	5150	1,231E-03

Data Sheet


BG47




Optical properties
Reflection factor
$P_d = 0,914$
Spectral values guaranteed
τ_i (405 nm) $\geq 0,65$
τ_i (430 nm) $\geq 0,7$
τ_i (514 nm) $\geq 0,87$
τ_i (565 nm) $\geq 0,5$
τ_i (633 nm) $\leq 0,1$
τ_i (1500 nm) $\leq 0,08$
Refractive indices
n_F (486 nm) = 1,546
n_e (546 nm) = 1,542
n_d (587,6 nm) = 1,54
Sellmeier coefficients
valid from 250 nm to 1700 nm
B_1 0,3196
B_2 1,0166
B_3 0,7150
C_1 2,355E-02 μm^2
C_2 4,6055E-03 μm^2
C_3 100,494 μm^2
Internal quality
Bubble class

Mechanical properties
Reference thickness
$d = 1,00$ mm
Density
$\rho = 2,74$ g/cm ³
Knoop hardness
HK[0.1/20] = 409
Thermal properties
Transformation temperature
$T_g = 416$ °C
Thermal expansion in 10 ⁻⁶ /K
α (-30°C/+70°C) = 10,0
α (20°C/300°C) = 11,9
Chemical properties
Chemical resistance
FR class = 0
SR class = 4.3
AR class = 3.3
Resistance against humidity
Delicate glass
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5

Colormetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,221	0,189	0,172
	y	0,328	0,329	0,335
	Y	56,6	41,8	32,6
	λ_d	491 nm	492 nm	492 nm
	P _e	0,336	0,452	0,510
Illuminant A	x	0,303	0,243	0,211
	y	0,452	0,466	0,474
	Y	47,7	32,8	24,6
	λ_d	500 nm	500 nm	500 nm
	P _e	0,328	0,466	0,540
Notes				
Ionically colored glass				
Bandpass filter / Shortpass filter				
NIR cutoff filter				
$\lambda_{50\%}(d = 0,20 \text{ mm}) = 633 \text{ nm}$				
ISO 23364:2021				
Disclaimer				
All data without tolerances are to be understood to be reference values.				

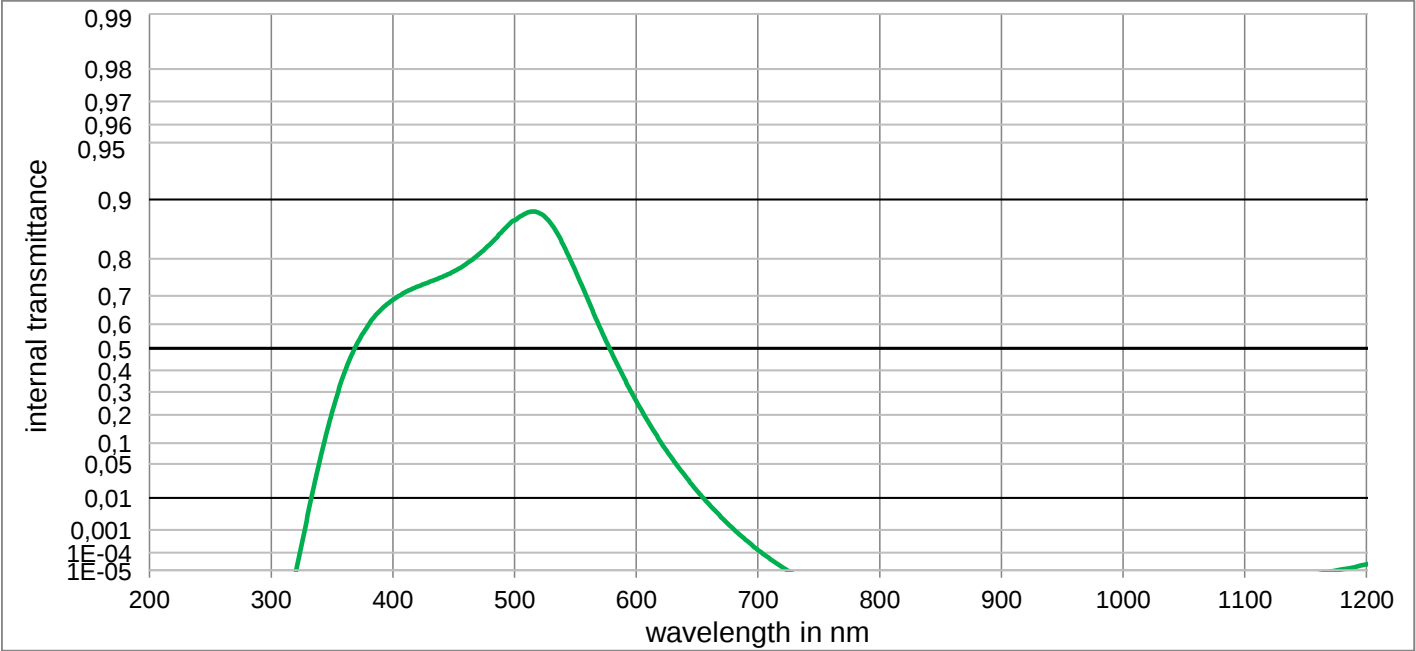

BG47

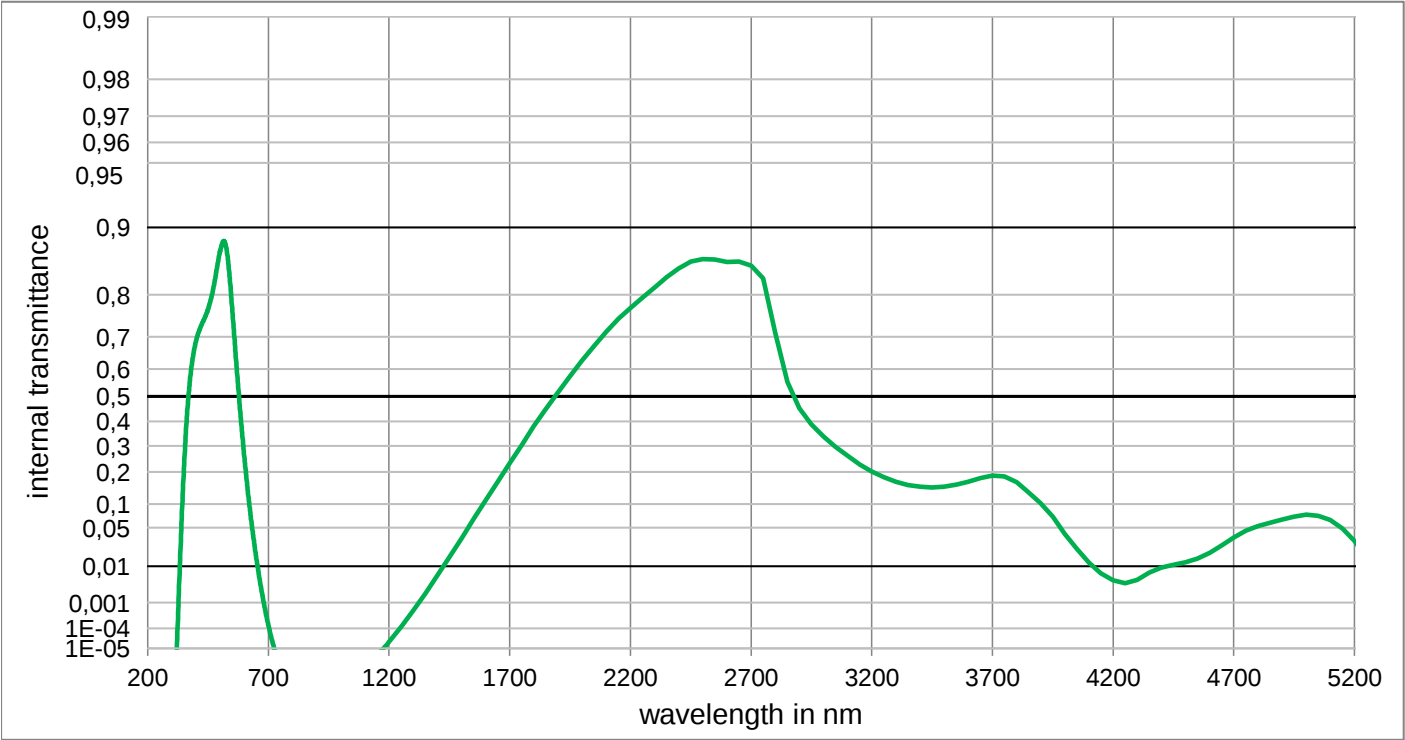

Internal transmittance τ_i at reference thickness													
The internal transmittance values, tabulated and graphically represented, are reference values only													
λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	8,712E-01	800	< 1,000E-05	1100	< 1,000E-05	2200	7,724E-01	3700	1,875E-01		
210	< 1,000E-05	510	8,826E-01	810	< 1,000E-05	1110	< 1,000E-05	2250	7,942E-01	3750	1,847E-01		
220	< 1,000E-05	520	8,828E-01	820	< 1,000E-05	1120	< 1,000E-05	2300	8,143E-01	3800	1,640E-01		
230	< 1,000E-05	530	8,664E-01	830	< 1,000E-05	1130	< 1,000E-05	2350	8,322E-01	3850	1,327E-01		
240	< 1,000E-05	540	8,301E-01	840	< 1,000E-05	1140	< 1,000E-05	2400	8,467E-01	3900	1,027E-01		
250	< 1,000E-05	550	7,713E-01	850	< 1,000E-05	1150	< 1,000E-05	2450	8,569E-01	3950	7,051E-02		
260	< 1,000E-05	560	6,902E-01	860	< 1,000E-05	1160	< 1,000E-05	2500	8,607E-01	4000	4,036E-02		
270	< 1,000E-05	570	5,895E-01	870	< 1,000E-05	1170	< 1,000E-05	2550	8,603E-01	4050	2,220E-02		
280	< 1,000E-05	580	4,777E-01	880	< 1,000E-05	1180	1,128E-05	2600	8,567E-01	4100	1,201E-02		
290	< 1,000E-05	590	3,640E-01	890	< 1,000E-05	1190	1,573E-05	2650	8,574E-01	4150	6,789E-03		
300	< 1,000E-05	600	2,590E-01	900	< 1,000E-05	1200	2,240E-05	2700	8,513E-01	4200	4,526E-03		
310	< 1,000E-05	610	1,704E-01	910	< 1,000E-05	1250	1,173E-04	2750	8,303E-01	4250	3,851E-03		
320	< 1,000E-05	620	1,042E-01	920	< 1,000E-05	1300	5,203E-04	2800	7,127E-01	4300	4,717E-03		
330	3,175E-03	630	5,917E-02	930	< 1,000E-05	1350	1,934E-03	2850	5,538E-01	4350	7,098E-03		
340	5,681E-02	640	3,088E-02	940	< 1,000E-05	1400	6,071E-03	2900	4,528E-01	4400	9,395E-03		
350	2,113E-01	650	1,489E-02	950	< 1,000E-05	1450	1,552E-02	2950	3,877E-01	4450	1,075E-02		
360	3,848E-01	660	6,663E-03	960	< 1,000E-05	1500	3,436E-02	3000	3,388E-01	4500	1,210E-02		
370	5,139E-01	670	2,763E-03	970	< 1,000E-05	1550	6,538E-02	3050	2,970E-01	4550	1,458E-02		
380	5,989E-01	680	1,072E-03	980	< 1,000E-05	1600	1,094E-01	3100	2,598E-01	4600	1,900E-02		
390	6,524E-01	690	3,923E-04	990	< 1,000E-05	1650	1,661E-01	3150	2,275E-01	4650	2,606E-02		
400	6,876E-01	700	1,382E-04	1000	< 1,000E-05	1700	2,323E-01	3200	2,010E-01	4700	3,540E-02		
410	7,108E-01	710	4,699E-05	1010	< 1,000E-05	1750	3,047E-01	3250	1,807E-01	4750	4,489E-02		
420	7,278E-01	720	1,561E-05	1020	< 1,000E-05	1800	3,818E-01	3300	1,659E-01	4800	5,252E-02		
430	7,415E-01	730	< 1,000E-05	1030	< 1,000E-05	1850	4,505E-01	3350	1,556E-01	4850	5,874E-02		
440	7,544E-01	740	< 1,000E-05	1040	< 1,000E-05	1900	5,163E-01	3400	1,496E-01	4900	6,502E-02		
450	7,696E-01	750	< 1,000E-05	1050	< 1,000E-05	1950	5,754E-01	3450	1,478E-01	4950	7,108E-02		
460	7,876E-01	760	< 1,000E-05	1060	< 1,000E-05	2000	6,282E-01	3500	1,500E-01	5000	7,464E-02		
470	8,083E-01	770	< 1,000E-05	1070	< 1,000E-05	2050	6,744E-01	3550	1,567E-01	5050	7,269E-02		
480	8,314E-01	780	< 1,000E-05	1080	< 1,000E-05	2100	7,136E-01	3600	1,662E-01	5100	6,377E-02		
490	8,540E-01	790	< 1,000E-05	1090	< 1,000E-05	2150	7,474E-01	3650	1,780E-01	5150	4,872E-02		

Optical properties	
Reflection factor	
P _d = 0,914	
Spectral values guaranteed	
τ _i (405 nm)	≥ 0,76
τ _i (514 nm)	≥ 0,93
τ _i (633 nm)	≥ 0,18
τ _i (694 nm)	≤ 0,016
τ _i (1060 nm)	≤ 0,0005
Refractive indices	
n _F (486 nm)	= 1,546
n _e (546 nm)	= 1,542
n _d (587,6 nm)	= 1,54
Sellmeier coefficients	
valid from 400 nm to 1550 nm	
B ₁	1,3373
B ₂	0,0002
B ₃	0,8117
C ₁	9,095E-03 μm ²
C ₂	1,4952E-02 μm ²
C ₃	100,000 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,65 g/cm ³	
Knoop hardness	
HK[0.1/20] = 504	

Thermal properties	
Transformation temperature	
T _g = 453 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _{-30°C/+70°C} = 7,2	
α _{20°C/300°C} = 9,1	


Chemical properties	
Chemical resistance	
FR class = 0	
SR class = 2	
AR class = 2	
Resistance against humidity	
Sensitive glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colorimetric properties				
	1 mm	2 mm	3 mm	
Illuminant D65	x	0,252	0,220	0,201
	y	0,329	0,328	0,328
	Y	68,9	56,6	48,2
	λ _d	492 nm	491 nm	491 nm
	P _e	0,223	0,339	0,409
Illuminant A	x	0,356	0,302	0,267
	y	0,438	0,452	0,460
	Y	61,7	47,6	39,0
	λ _d	501 nm	500 nm	500 nm
	P _e	0,208	0,331	0,413

Notes
Ionically colored glass
Bandpass filter / Shortpass filter
NIR cutoff filter
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

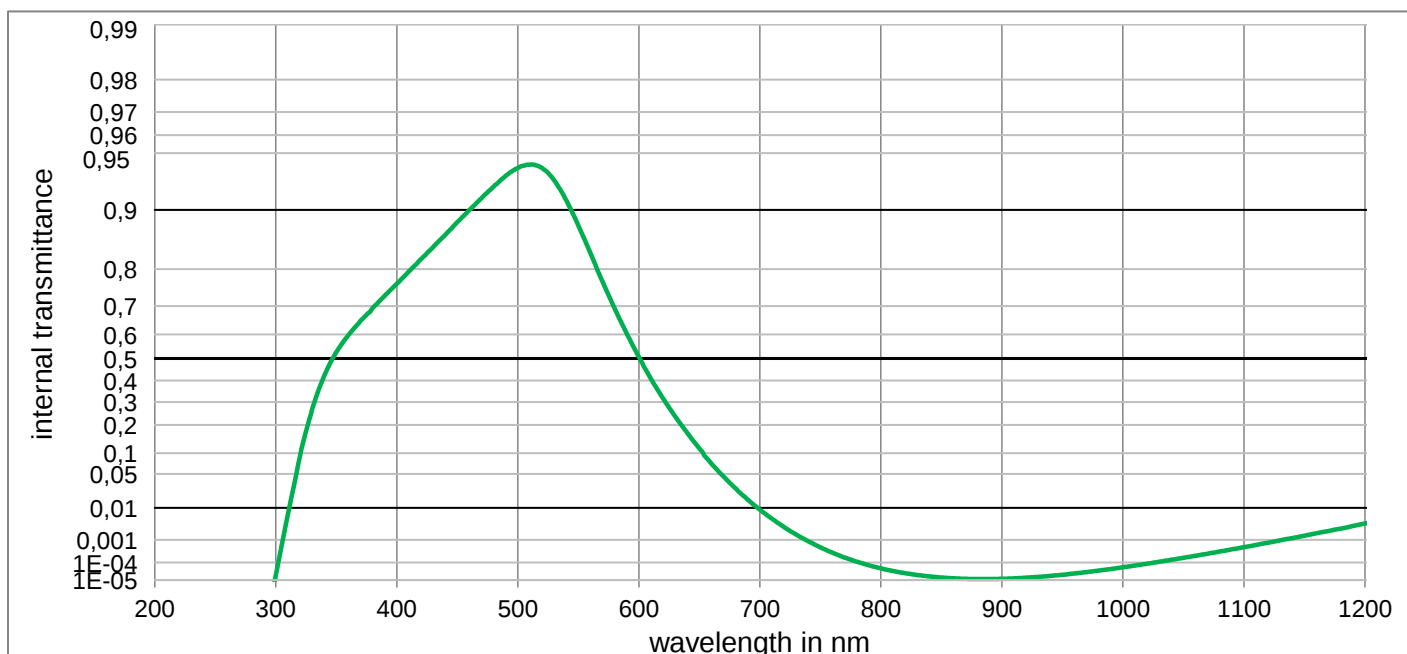


BG55

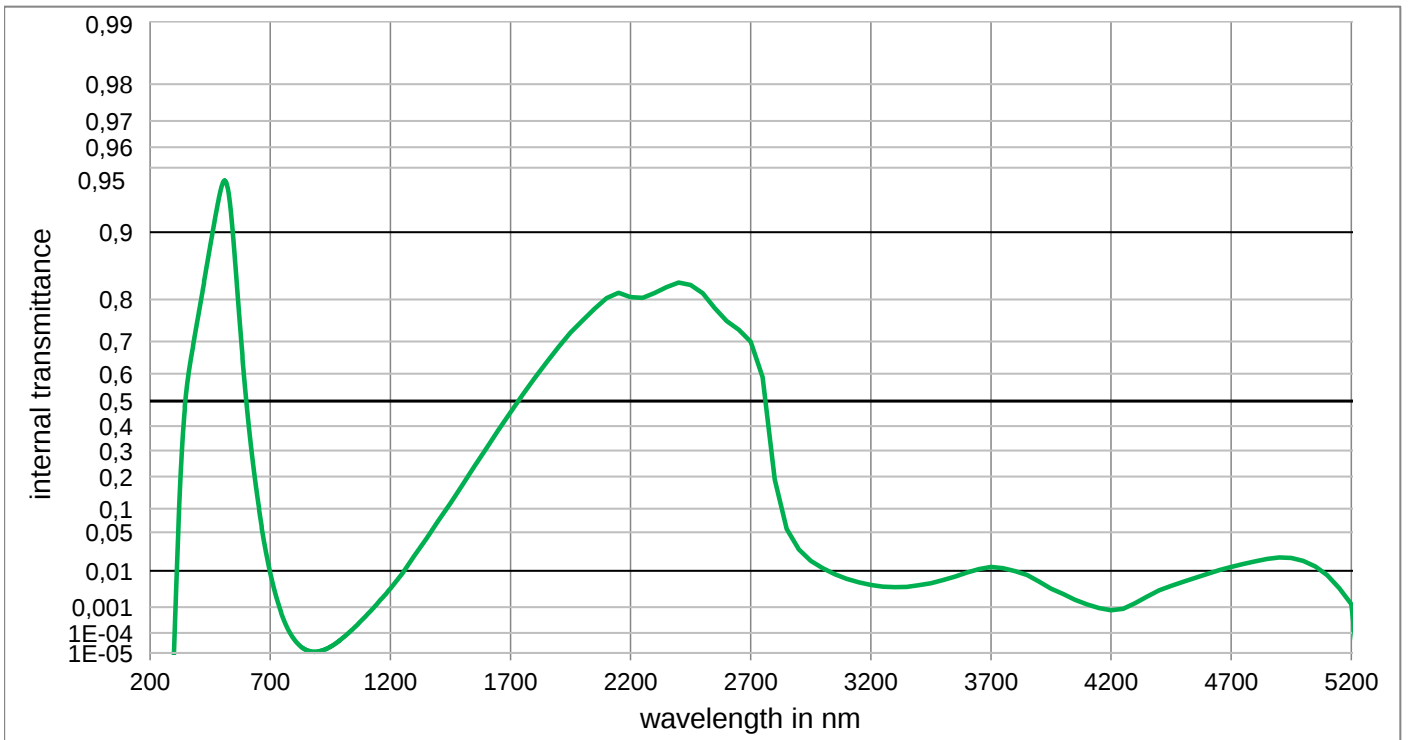Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,399E-01	800	4,934E-05	1100	5,093E-04	2200	8,044E-01	3700	1,209E-02
210	< 1,000E-05	510	9,424E-01	810	3,526E-05	1110	6,294E-04	2250	8,032E-01	3750	1,149E-02
220	< 1,000E-05	520	9,400E-01	820	2,638E-05	1120	7,757E-04	2300	8,123E-01	3800	9,901E-03
230	< 1,000E-05	530	9,303E-01	830	2,067E-05	1130	9,532E-04	2350	8,232E-01	3850	8,076E-03
240	< 1,000E-05	540	9,110E-01	840	1,694E-05	1140	1,167E-03	2400	8,313E-01	3900	5,598E-03
250	< 1,000E-05	550	8,792E-01	850	1,452E-05	1150	1,424E-03	2450	8,272E-01	3950	3,651E-03
260	< 1,000E-05	560	8,329E-01	860	1,297E-05	1160	1,739E-03	2500	8,119E-01	4000	2,558E-03
270	< 1,000E-05	570	7,701E-01	870	1,207E-05	1170	2,078E-03	2550	7,821E-01	4050	1,710E-03
280	< 1,000E-05	580	6,928E-01	880	1,167E-05	1180	2,505E-03	2600	7,532E-01	4100	1,227E-03
290	< 1,000E-05	590	6,029E-01	890	1,169E-05	1190	3,047E-03	2650	7,316E-01	4150	9,269E-04
300	1,878E-05	600	5,057E-01	900	1,211E-05	1200	3,660E-03	2700	6,993E-01	4200	7,882E-04
310	6,724E-03	610	4,085E-01	910	1,292E-05	1250	8,670E-03	2750	5,881E-01	4250	8,827E-04
320	9,213E-02	620	3,166E-01	920	1,416E-05	1300	2,062E-02	2800	1,888E-01	4300	1,344E-03
330	2,650E-01	630	2,354E-01	930	1,590E-05	1350	4,003E-02	2850	5,554E-02	4350	2,158E-03
340	4,212E-01	640	1,677E-01	940	1,824E-05	1400	7,197E-02	2900	2,645E-02	4400	3,245E-03
350	5,277E-01	650	1,149E-01	950	2,132E-05	1450	1,148E-01	2950	1,629E-02	4450	4,293E-03
360	5,980E-01	660	7,208E-02	960	2,533E-05	1500	1,710E-01	3000	1,137E-02	4500	5,522E-03
370	6,500E-01	670	4,508E-02	970	3,049E-05	1550	2,371E-01	3050	8,398E-03	4550	6,840E-03
380	6,932E-01	680	2,711E-02	980	3,711E-05	1600	3,093E-01	3100	6,519E-03	4600	8,465E-03
390	7,313E-01	690	1,583E-02	990	4,557E-05	1650	3,844E-01	3150	5,315E-03	4650	1,031E-02
400	7,648E-01	700	9,032E-03	1000	5,634E-05	1700	4,561E-01	3200	4,538E-03	4700	1,220E-02
410	7,945E-01	710	5,056E-03	1010	7,000E-05	1750	5,236E-01	3250	4,113E-03	4750	1,406E-02
420	8,214E-01	720	2,809E-03	1020	8,728E-05	1800	5,841E-01	3300	3,971E-03	4800	1,587E-02
430	8,447E-01	730	1,576E-03	1030	1,090E-04	1850	6,379E-01	3350	4,064E-03	4850	1,775E-02
440	8,657E-01	740	8,774E-04	1040	1,363E-04	1900	6,841E-01	3400	4,457E-03	4900	1,892E-02
450	8,842E-01	750	5,015E-04	1050	1,705E-04	1950	7,241E-01	3450	5,018E-03	4950	1,854E-02
460	8,999E-01	760	2,924E-04	1060	2,130E-04	2000	7,545E-01	3500	6,034E-03	5000	1,629E-02
470	9,131E-01	770	1,764E-04	1070	2,657E-04	2050	7,807E-01	3550	7,359E-03	5050	1,249E-02
480	9,246E-01	780	1,106E-04	1080	3,308E-04	2100	8,029E-01	3600	9,128E-03	5100	7,925E-03
490	9,338E-01	790	7,226E-05	1090	4,110E-04	2150	8,131E-01	3650	1,095E-02	5150	3,751E-03

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm		2 mm	3 mm	
P _d = 0,911		d = 1,00 mm		Illuminant D65	x	0,200	0,172	0,157
Spectral values guaranteed		Density			y	0,356	0,395	0,440
τ _i (405 nm)	≥ 0,37	ρ = 2,82 g/cm³			Y	42,8	26,7	17,9
τ _i (430 nm)	≥ 0,42	Knoop hardness			λ _d	494 nm	497 nm	500 nm
τ _i (514 nm)	≥ 0,72	HK[0.1/20] = 431			P _e	0,393	0,474	0,510
τ _i (565 nm)	≥ 0,42	Thermal properties		Illuminant A	x	0,261	0,208	0,183
τ _i (633 nm)	≤ 0,02	Transformation temperature			y	0,484	0,523	0,559
τ _i (1500 nm)	≤ 0,02	T _g = 411 °C			Y	34,3	20,1	13,1
Refractive indices		Thermal expansion in 10 ⁻⁶ /K			λ _d	502 nm	503 nm	505 nm
n _F (486 nm)	= 1,56	α _{-30°C/+70°C} = 9,7			P _e	0,421	0,539	0,597
n _e (546 nm)	= 1,553	α _{20°C/300°C} = 11,6		Notes				
n _d (587,6 nm)	= 1,55							
Sellmeier coefficients		Chemical properties		Ionically colored glass				
valid from 440 nm to 1550 nm		Chemical resistance		Bandpass filter / Shortpass filter				
B ₁	1,3353	FR class		NIR cutoff filter				
B ₂	0,0436	SR class = 5.2		λ _{50%} (d=0.11mm) @ 636 nm				
B ₃	122,4367	AR class = 3		ISO 23364:2021				
C ₂	1,3411E-01 μm²	Resistance against humidity						
C ₃	13784,523 μm²	Sensitive glass		Disclaimer				
Internal quality		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		All data without tolerances are to be understood to be reference values.				
Bubble class	0							

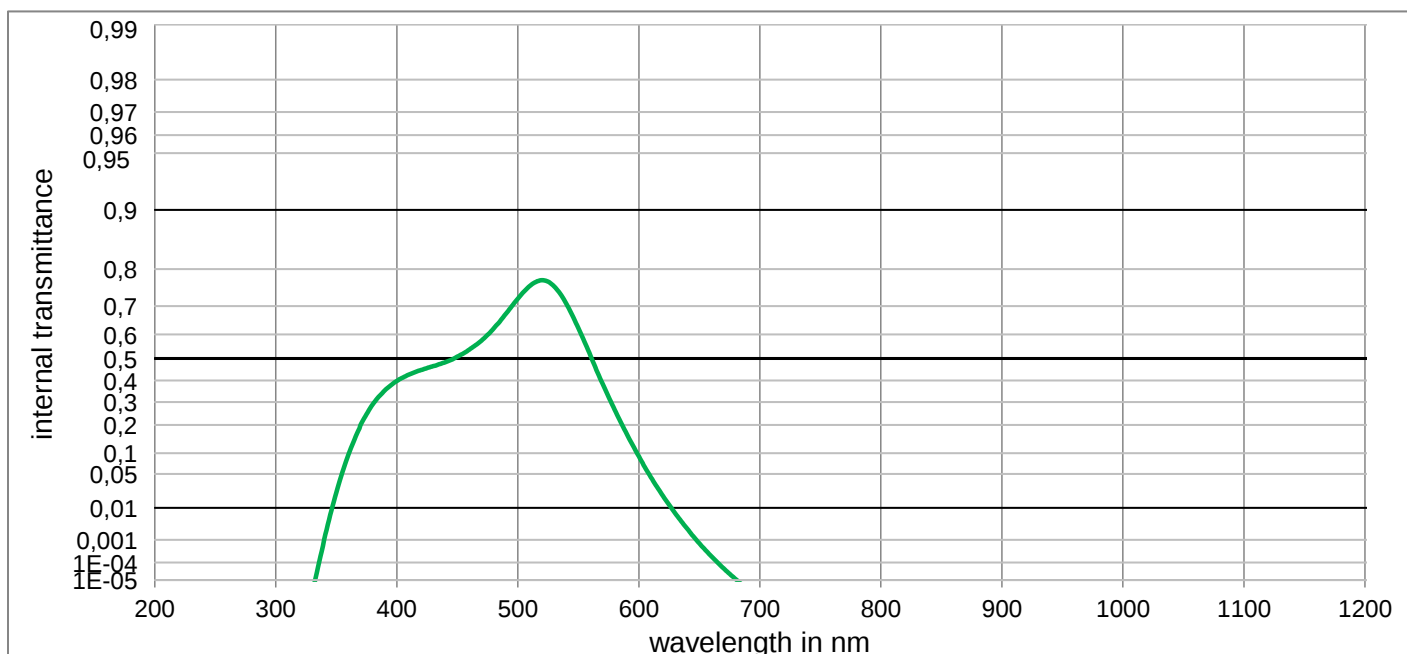

BG59

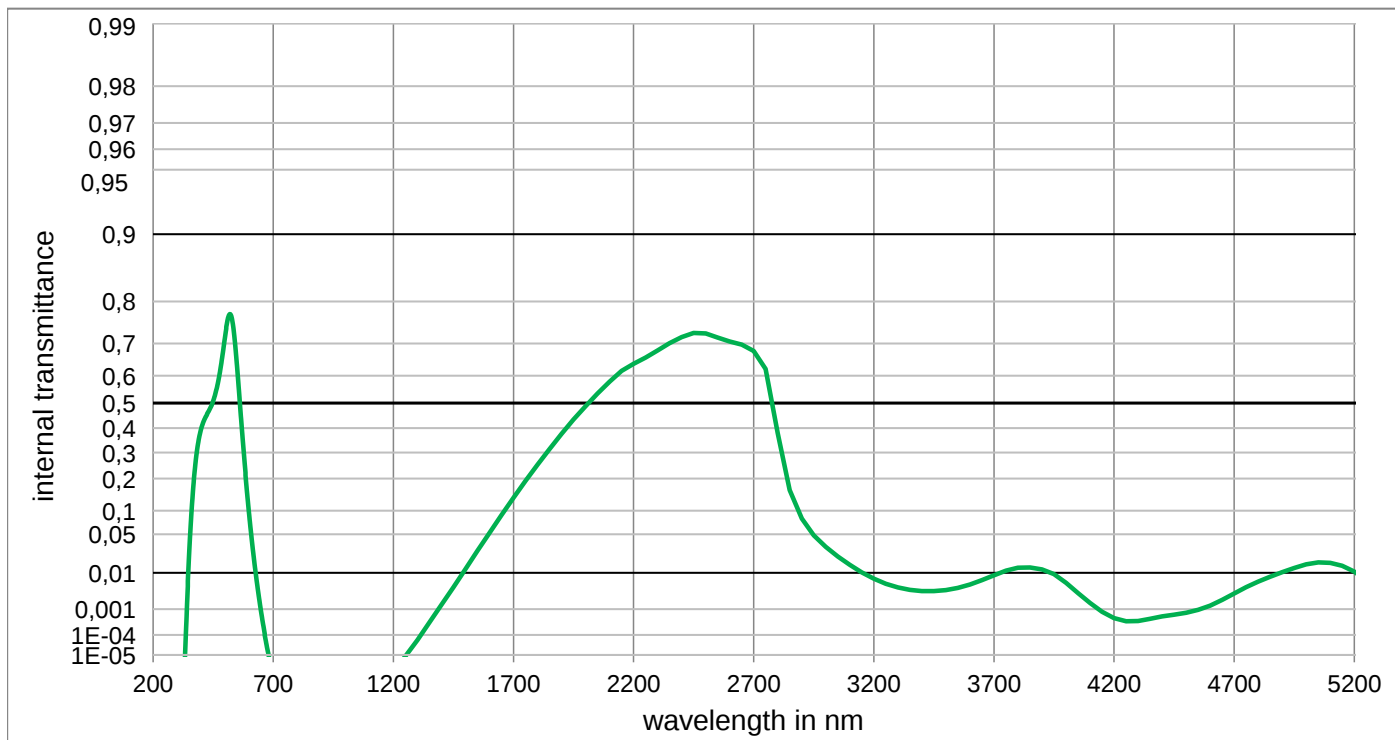Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	7,226E-01	800	< 1,000E-05	1100	< 1,000E-05	2200	6,389E-01	3700	8,820E-03
210	< 1,000E-05	510	7,591E-01	810	< 1,000E-05	1110	< 1,000E-05	2250	6,587E-01	3750	1,117E-02
220	< 1,000E-05	520	7,735E-01	820	< 1,000E-05	1120	< 1,000E-05	2300	6,798E-01	3800	1,287E-02
230	< 1,000E-05	530	7,579E-01	830	< 1,000E-05	1130	< 1,000E-05	2350	7,007E-01	3850	1,311E-02
240	< 1,000E-05	540	7,078E-01	840	< 1,000E-05	1140	< 1,000E-05	2400	7,176E-01	3900	1,192E-02
250	< 1,000E-05	550	6,239E-01	850	< 1,000E-05	1150	< 1,000E-05	2450	7,281E-01	3950	9,336E-03
260	< 1,000E-05	560	5,117E-01	860	< 1,000E-05	1160	< 1,000E-05	2500	7,270E-01	4000	5,822E-03
270	< 1,000E-05	570	3,863E-01	870	< 1,000E-05	1170	< 1,000E-05	2550	7,160E-01	4050	3,096E-03
280	< 1,000E-05	580	2,657E-01	880	< 1,000E-05	1180	< 1,000E-05	2600	7,055E-01	4100	1,568E-03
290	< 1,000E-05	590	1,642E-01	890	< 1,000E-05	1190	< 1,000E-05	2650	6,965E-01	4150	8,159E-04
300	< 1,000E-05	600	9,059E-02	900	< 1,000E-05	1200	< 1,000E-05	2700	6,787E-01	4200	4,886E-04
310	< 1,000E-05	610	4,407E-02	910	< 1,000E-05	1250	< 1,000E-05	2750	6,223E-01	4250	3,681E-04
320	< 1,000E-05	620	1,888E-02	920	< 1,000E-05	1300	5,930E-05	2800	3,784E-01	4300	3,728E-04
330	< 1,000E-05	630	7,188E-03	930	< 1,000E-05	1350	3,273E-04	2850	1,604E-01	4350	4,568E-04
340	1,027E-03	640	2,439E-03	940	< 1,000E-05	1400	1,361E-03	2900	8,072E-02	4400	5,594E-04
350	2,251E-02	650	7,312E-04	950	< 1,000E-05	1450	4,512E-03	2950	4,828E-02	4450	6,493E-04
360	9,632E-02	660	1,998E-04	960	< 1,000E-05	1500	1,204E-02	3000	3,175E-02	4500	7,558E-04
370	1,987E-01	670	4,929E-05	970	< 1,000E-05	1550	2,697E-02	3050	2,156E-02	4550	9,438E-04
380	2,886E-01	680	1,139E-05	980	< 1,000E-05	1600	5,205E-02	3100	1,474E-02	4600	1,304E-03
390	3,537E-01	690	< 1,000E-05	990	< 1,000E-05	1650	8,870E-02	3150	1,021E-02	4650	1,959E-03
400	3,982E-01	700	< 1,000E-05	1000	< 1,000E-05	1700	1,363E-01	3200	7,304E-03	4700	3,029E-03
410	4,273E-01	710	< 1,000E-05	1010	< 1,000E-05	1750	1,914E-01	3250	5,506E-03	4750	4,508E-03
420	4,480E-01	720	< 1,000E-05	1020	< 1,000E-05	1800	2,513E-01	3300	4,428E-03	4800	6,243E-03
430	4,655E-01	730	< 1,000E-05	1030	< 1,000E-05	1850	3,140E-01	3350	3,805E-03	4850	8,173E-03
440	4,836E-01	740	< 1,000E-05	1040	< 1,000E-05	1900	3,758E-01	3400	3,515E-03	4900	1,037E-02
450	5,076E-01	750	< 1,000E-05	1050	< 1,000E-05	1950	4,342E-01	3450	3,501E-03	4950	1,279E-02
460	5,386E-01	760	< 1,000E-05	1060	< 1,000E-05	2000	4,878E-01	3500	3,751E-03	5000	1,509E-02
470	5,759E-01	770	< 1,000E-05	1070	< 1,000E-05	2050	5,362E-01	3550	4,305E-03	5050	1,650E-02
480	6,225E-01	780	< 1,000E-05	1080	< 1,000E-05	2100	5,797E-01	3600	5,247E-03	5100	1,628E-02
490	6,740E-01	790	< 1,000E-05	1090	< 1,000E-05	2150	6,165E-01	3650	6,721E-03	5150	1,419E-02

Optical properties	
Reflection factor	
P _d = 0,914	
Spectral values guaranteed	
τ _i (405 nm)	≥ 0,8
τ _i (514 nm)	≥ 0,91
τ _i (633 nm)	≥ 0,1
τ _i (694 nm)	≤ 0,008
τ _i (1060 nm)	≤ 0,0015
Refractive indices	
n _F (486 nm)	= 1,544
n _e (546 nm)	= 1,54
n _d (587,6 nm)	= 1,538
Sellmeier coefficients	
valid from 340 nm to 1550 nm	
B ₁	1,3298
B ₂	0,0004
B ₃	2,5598
C ₁	9,241E-03 μm ²
C ₂	1,0918E-01 μm ²
C ₃	450,591 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,83 g/cm ³	
Knoop hardness	
HK[0.1/20] = 362	

Thermal properties	
Transformation temperature	
T _g = 411 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _(-30°C/+70°C) = 12,0	
α _(20°C/300°C) = 13,9	


Chemical properties	
Chemical resistance	
FR class = 1	
SR class = 52.3	
AR class = 3.3	
Resistance against humidity	

Colorimetric properties				
	1 mm	2 mm	3 mm	
Illuminant D65	x	0,236	0,201	0,181
	y	0,318	0,306	0,297
	Y	63,8	49,9	41,0
	λ _d	490 nm	489 nm	489 nm
	P _e	0,286	0,425	0,506
Illuminant A	x	0,334	0,271	0,232
	y	0,436	0,441	0,437
	Y	55,7	40,5	31,7
	λ _d	499 nm	498 nm	497 nm
	P _e	0,259	0,406	0,498

Notes
Ionically colored glass
Bandpass filter / Shortpass filter
NIR cutoff filter
lambda_50%(d=0.3mm) = 633 nm
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

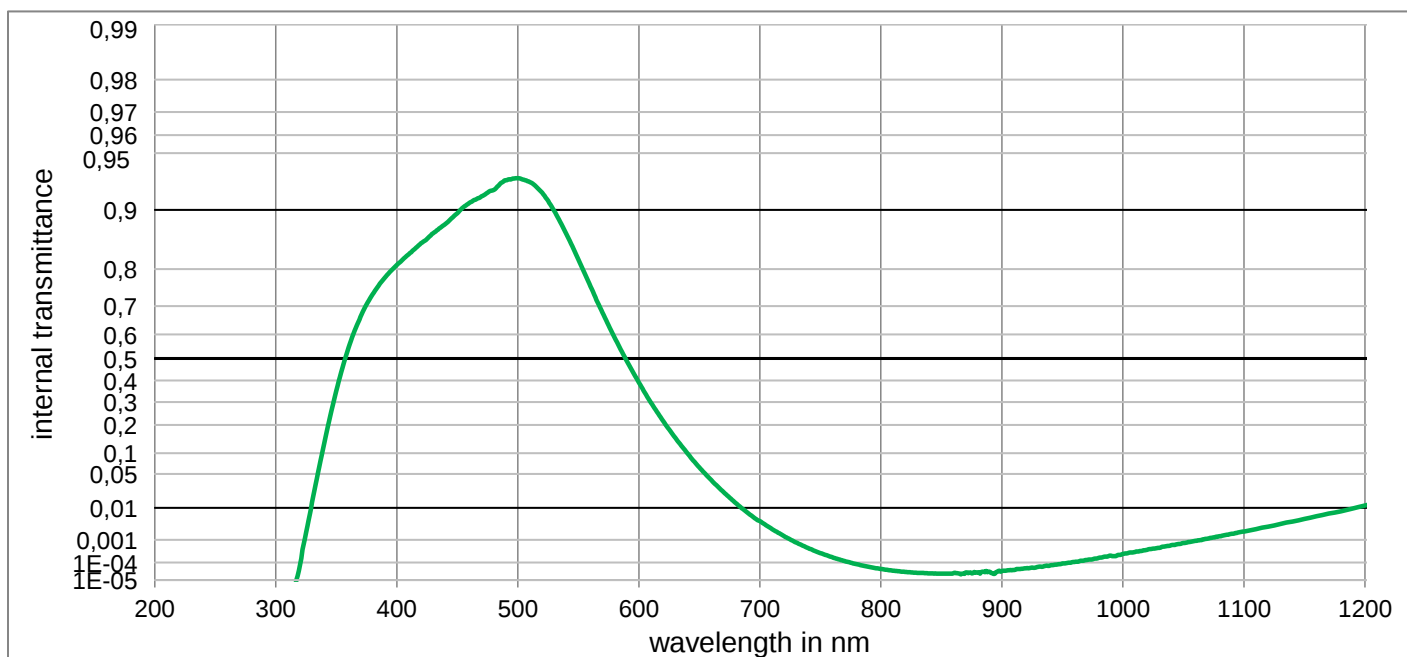

BG60

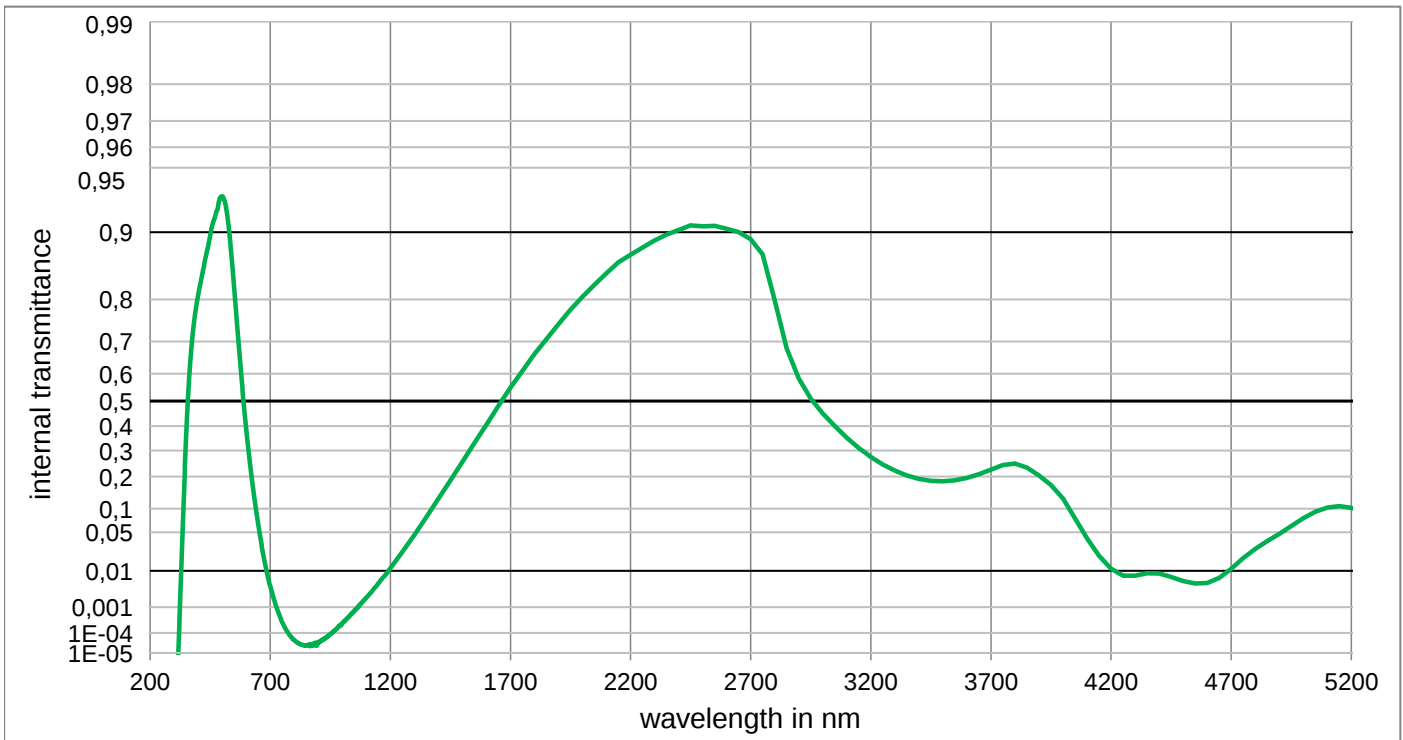Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,319E-01	800	4,553E-05	1100	1,992E-03	2200	8,733E-01	3700	2,259E-01
210	< 1,000E-05	510	9,286E-01	810	3,683E-05	1110	2,416E-03	2250	8,825E-01	3750	2,432E-01
220	< 1,000E-05	520	9,187E-01	820	3,115E-05	1120	2,902E-03	2300	8,910E-01	3800	2,484E-01
230	< 1,000E-05	530	8,991E-01	830	2,752E-05	1130	3,528E-03	2350	8,974E-01	3850	2,331E-01
240	< 1,000E-05	540	8,673E-01	840	2,593E-05	1140	4,192E-03	2400	9,023E-01	3900	2,041E-01
250	< 1,000E-05	550	8,208E-01	850	2,497E-05	1150	4,976E-03	2450	9,069E-01	3950	1,707E-01
260	< 1,000E-05	560	7,573E-01	860	2,632E-05	1160	5,967E-03	2500	9,061E-01	4000	1,275E-01
270	< 1,000E-05	570	6,790E-01	870	2,877E-05	1170	7,049E-03	2550	9,064E-01	4050	7,682E-02
280	< 1,000E-05	580	5,874E-01	880	2,856E-05	1180	8,166E-03	2600	9,035E-01	4100	4,036E-02
290	< 1,000E-05	590	4,892E-01	890	3,182E-05	1190	9,653E-03	2650	9,000E-01	4150	2,037E-02
300	< 1,000E-05	600	3,905E-01	900	3,559E-05	1200	1,142E-02	2700	8,923E-01	4200	1,121E-02
310	< 1,000E-05	610	2,979E-01	910	3,967E-05	1250	2,400E-02	2750	8,737E-01	4250	7,748E-03
320	7,831E-05	620	2,168E-01	920	4,945E-05	1300	4,588E-02	2800	7,977E-01	4300	7,701E-03
330	1,360E-02	630	1,505E-01	930	5,977E-05	1350	7,977E-02	2850	6,805E-01	4350	8,815E-03
340	1,301E-01	640	1,000E-01	940	7,197E-05	1400	1,268E-01	2900	5,825E-01	4400	8,635E-03
350	3,524E-01	650	6,356E-02	950	8,963E-05	1450	1,867E-01	2950	5,097E-01	4450	7,195E-03
360	5,453E-01	660	3,882E-02	960	1,064E-04	1500	2,557E-01	3000	4,513E-01	4500	5,756E-03
370	6,642E-01	670	2,294E-02	970	1,346E-04	1550	3,305E-01	3050	3,996E-01	4550	4,996E-03
380	7,356E-01	680	1,314E-02	980	1,709E-04	1600	4,056E-01	3100	3,524E-01	4600	5,132E-03
390	7,795E-01	690	7,409E-03	990	2,146E-04	1650	4,814E-01	3150	3,104E-01	4650	6,813E-03
400	8,093E-01	700	4,338E-03	1000	2,576E-04	1700	5,511E-01	3200	2,744E-01	4700	1,106E-02
410	8,314E-01	710	2,421E-03	1010	3,170E-04	1750	6,093E-01	3250	2,449E-01	4750	1,826E-02
420	8,515E-01	720	1,378E-03	1020	3,967E-04	1800	6,632E-01	3300	2,218E-01	4800	2,702E-02
430	8,678E-01	730	7,905E-04	1030	4,818E-04	1850	7,071E-01	3350	2,043E-01	4850	3,642E-02
440	8,817E-01	740	4,644E-04	1040	6,148E-04	1900	7,456E-01	3400	1,921E-01	4900	4,731E-02
450	8,959E-01	750	2,818E-04	1050	7,502E-04	1950	7,786E-01	3450	1,852E-01	4950	6,127E-02
460	9,080E-01	760	1,794E-04	1060	9,159E-04	2000	8,056E-01	3500	1,834E-01	5000	7,711E-02
470	9,150E-01	770	1,187E-04	1070	1,118E-03	2050	8,274E-01	3550	1,867E-01	5050	9,209E-02
480	9,214E-01	780	8,223E-05	1080	1,357E-03	2100	8,467E-01	3600	1,950E-01	5100	1,029E-01
490	9,303E-01	790	6,013E-05	1090	1,655E-03	2150	8,632E-01	3650	2,082E-01	5150	1,065E-01

Optical properties	
Reflection factor	
P _d = 0,914	
Spectral values guaranteed	
τ _i (405 nm)	≥ 0,85
τ _i (514 nm)	≥ 0,93
τ _i (633 nm)	≥ 0,1
τ _i (694 nm)	≤ 0,008
τ _i (1060 nm)	≤ 0,0015
Refractive indices	
n _F (486 nm)	= 1,544
n _e (546 nm)	= 1,54
n _d (587,6 nm)	= 1,538
Sellmeier coefficients	
valid from 340 nm to 1550 nm	
B ₁	1,3298
B ₂	0,0004
B ₃	2,5598
C ₁	9,241E-03 μm ²
C ₂	1,0918E-01 μm ²
C ₃	450,591 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,83 g/cm ³	
Knoop hardness	
HK[0.1/20] = 362	

Thermal properties	
Transformation temperature	
T _g = 411 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _(-30°C/+70°C) = 12,0	
α _(20°C/300°C) = 13,9	


Chemical properties	
Chemical resistance	
FR class = 1	
SR class = 52.2	
AR class = 3.2	
Resistance against humidity	

Colormetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,233	0,198	0,178
	y	0,315	0,300	0,287
	Y	64,1	50,6	42,0
	λ _d	489 nm	488 nm	488 nm
	P _e	0,300	0,442	0,525
Illuminant A	x	0,330	0,266	0,227
	y	0,435	0,436	0,429
	Y	55,7	40,8	32,2
	λ _d	499 nm	498 nm	496 nm
	P _e	0,270	0,421	0,514

Notes
Ionically colored glass
Bandpass filter / Shortpass filter
NIR cutoff filter
lambda_50%(d=0.3mm) = 633 nm
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

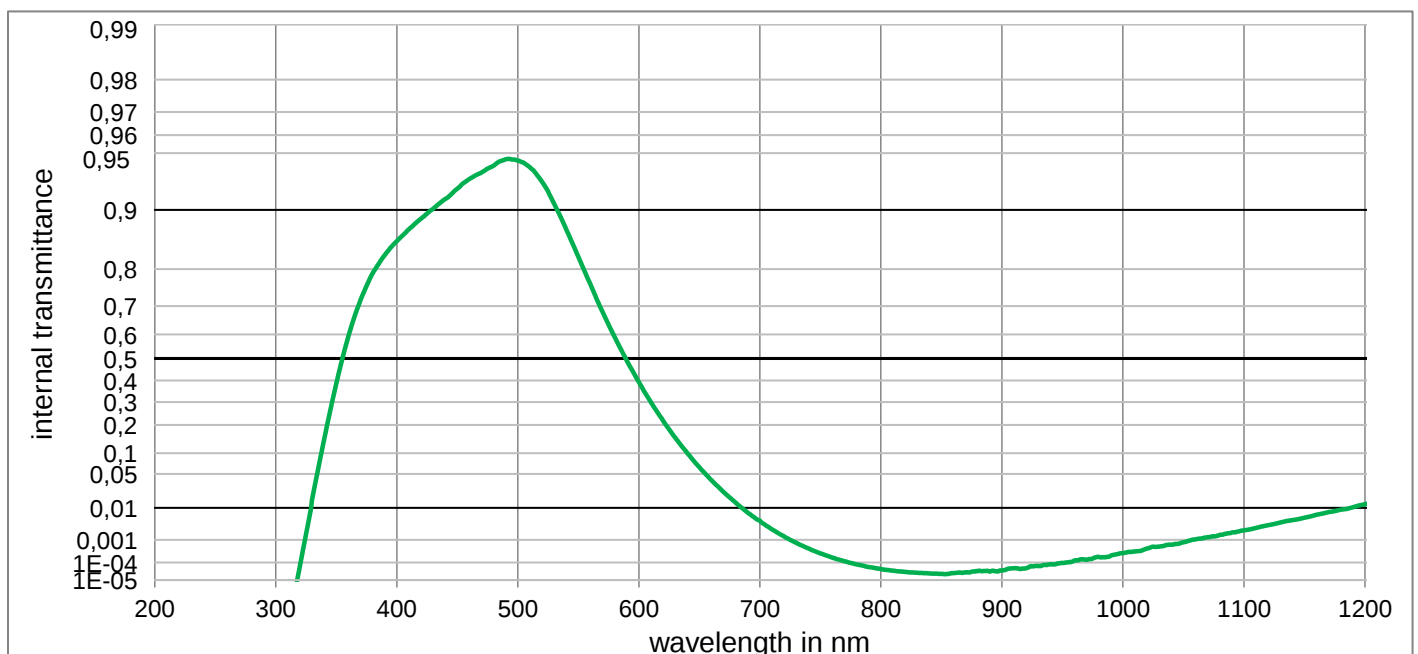

BG60HT

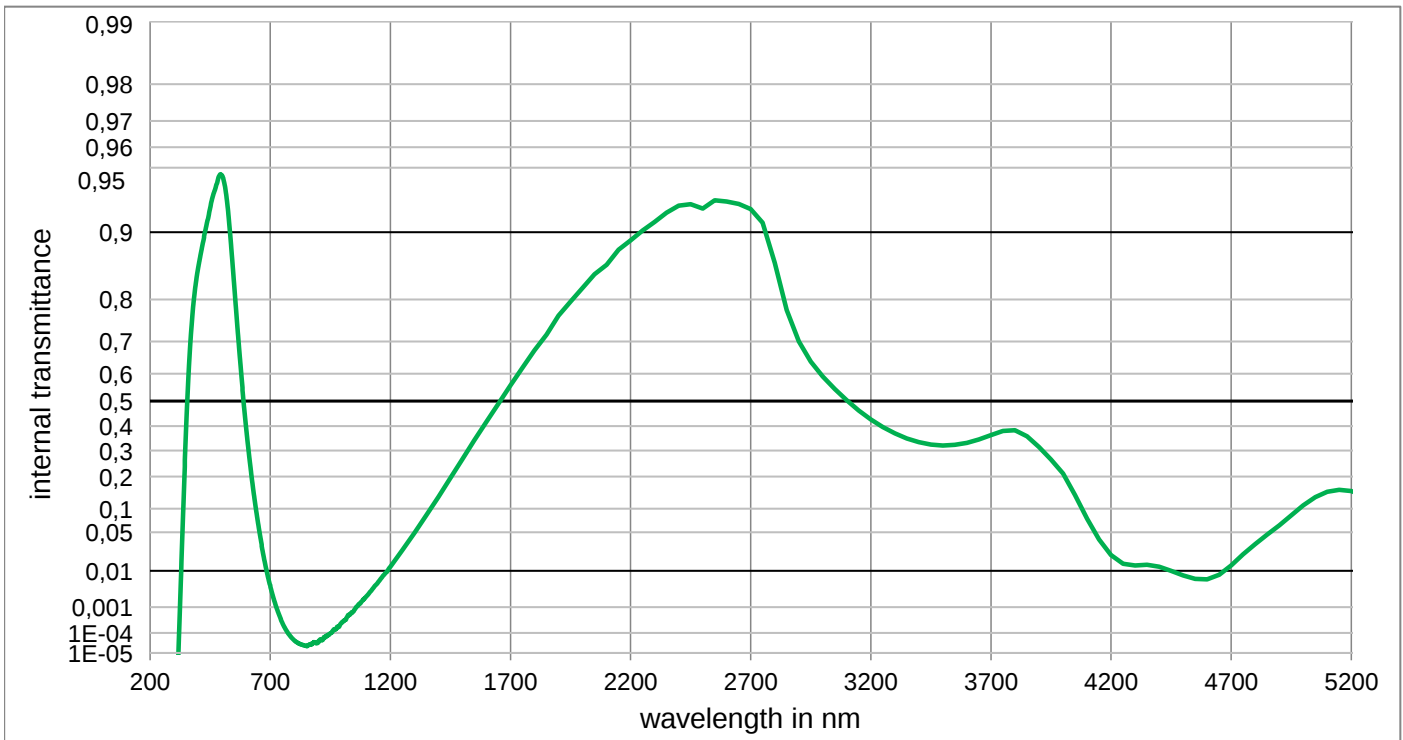Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,452E-01	800	4,502E-05	1100	2,177E-03	2200	8,909E-01	3700	3,635E-01
210	< 1,000E-05	510	9,404E-01	810	3,656E-05	1110	2,626E-03	2250	9,019E-01	3750	3,805E-01
220	< 1,000E-05	520	9,288E-01	820	3,119E-05	1120	3,188E-03	2300	9,103E-01	3800	3,826E-01
230	< 1,000E-05	530	9,073E-01	830	2,793E-05	1130	3,874E-03	2350	9,188E-01	3850	3,583E-01
240	< 1,000E-05	540	8,739E-01	840	2,564E-05	1140	4,603E-03	2400	9,246E-01	3900	3,143E-01
250	< 1,000E-05	550	8,260E-01	850	2,372E-05	1150	5,383E-03	2450	9,257E-01	3950	2,645E-01
260	< 1,000E-05	560	7,618E-01	860	2,639E-05	1160	6,519E-03	2500	9,222E-01	4000	2,114E-01
270	< 1,000E-05	570	6,817E-01	870	2,872E-05	1170	7,711E-03	2550	9,288E-01	4050	1,384E-01
280	< 1,000E-05	580	5,900E-01	880	3,410E-05	1180	8,976E-03	2600	9,279E-01	4100	7,617E-02
290	< 1,000E-05	590	4,908E-01	890	3,233E-05	1190	1,032E-02	2650	9,261E-01	4150	3,905E-02
300	< 1,000E-05	600	3,920E-01	900	3,719E-05	1200	1,224E-02	2700	9,218E-01	4200	2,110E-02
310	< 1,000E-05	610	2,994E-01	910	5,030E-05	1250	2,586E-02	2750	9,096E-01	4250	1,416E-02
320	7,415E-05	620	2,184E-01	920	4,952E-05	1300	4,890E-02	2800	8,624E-01	4300	1,306E-02
330	1,574E-02	630	1,509E-01	930	6,534E-05	1350	8,439E-02	2850	7,781E-01	4350	1,346E-02
340	1,447E-01	640	1,002E-01	940	8,100E-05	1400	1,324E-01	2900	7,003E-01	4400	1,236E-02
350	3,866E-01	650	6,391E-02	950	9,477E-05	1450	1,953E-01	2950	6,400E-01	4450	9,979E-03
360	5,939E-01	660	3,912E-02	960	1,248E-04	1500	2,655E-01	3000	5,905E-01	4500	7,775E-03
370	7,185E-01	670	2,310E-02	970	1,384E-04	1550	3,426E-01	3050	5,454E-01	4550	6,476E-03
380	7,901E-01	680	1,336E-02	980	1,873E-04	1600	4,175E-01	3100	5,027E-01	4600	6,340E-03
390	8,295E-01	690	7,552E-03	990	2,146E-04	1650	4,899E-01	3150	4,626E-01	4650	8,118E-03
400	8,554E-01	700	4,483E-03	1000	2,823E-04	1700	5,594E-01	3200	4,268E-01	4700	1,303E-02
410	8,740E-01	710	2,369E-03	1010	3,353E-04	1750	6,200E-01	3250	3,957E-01	4750	2,161E-02
420	8,890E-01	720	1,335E-03	1020	4,468E-04	1800	6,742E-01	3300	3,700E-01	4800	3,292E-02
430	9,016E-01	730	7,666E-04	1030	5,325E-04	1850	7,188E-01	3350	3,495E-01	4850	4,615E-02
440	9,125E-01	740	4,521E-04	1040	6,468E-04	1900	7,658E-01	3400	3,339E-01	4900	6,232E-02
450	9,226E-01	750	2,747E-04	1050	8,132E-04	1950	7,954E-01	3450	3,245E-01	4950	8,366E-02
460	9,312E-01	760	1,741E-04	1060	1,044E-03	2000	8,219E-01	3500	3,205E-01	5000	1,085E-01
470	9,365E-01	770	1,155E-04	1070	1,248E-03	2050	8,448E-01	3550	3,231E-01	5050	1,318E-01
480	9,417E-01	780	8,046E-05	1080	1,509E-03	2100	8,596E-01	3600	3,311E-01	5100	1,485E-01
490	9,460E-01	790	5,856E-05	1090	1,833E-03	2150	8,797E-01	3650	3,451E-01	5150	1,548E-01

Optical properties	
Reflection factor	
P _d = 0,915	
Spectral values guaranteed	
τ _i (405 nm)	≥ 0,84
τ _i (514 nm)	≥ 0,93
τ _i (633 nm)	≥ 0,18
τ _i (694 nm)	≤ 0,03
τ _i (1060 nm)	≤ 0,008
Refractive indices	
n _F (486 nm)	= 1,541
n _e (546 nm)	= 1,537
n _d (587,6 nm)	= 1,535
Sellmeier coefficients	
valid from 340 nm to 1550 nm	
B ₁	1,3212
B ₂	0,0004
B ₃	0,0589
C ₁	9,180E-03 μm ²
C ₂	1,1649E-01 μm ²
C ₃	12,101 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,81 g/cm ³	
Knoop hardness	
HK[0.1/20] = 363	

Thermal properties	
Transformation temperature	
T _g = 402 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _(-30°C/+70°C) = 11,9	
α _(20°C/300°C) = 13,9	


Chemical properties	
Chemical resistance	
FR class = 1	
SR class = 52.3	
AR class = 3.3	
Resistance against humidity	

Colorimetric properties				
	1 mm	2 mm	3 mm	
Illuminant D65	x	0,245	0,210	0,189
	y	0,319	0,307	0,296
	Y	68,0	55,2	46,7
	λ _d	490 nm	489 nm	488 nm
	P _e	0,254	0,391	0,476
Illuminant A	x	0,349	0,289	0,250
	y	0,432	0,438	0,435
	Y	60,4	45,7	36,9
	λ _d	499 nm	498 nm	497 nm
	P _e	0,225	0,365	0,458

Notes
Ionically colored glass
Bandpass filter / Shortpass filter
NIR cutoff filter
lambda_50%(d=0.3mm) = 648 nm
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

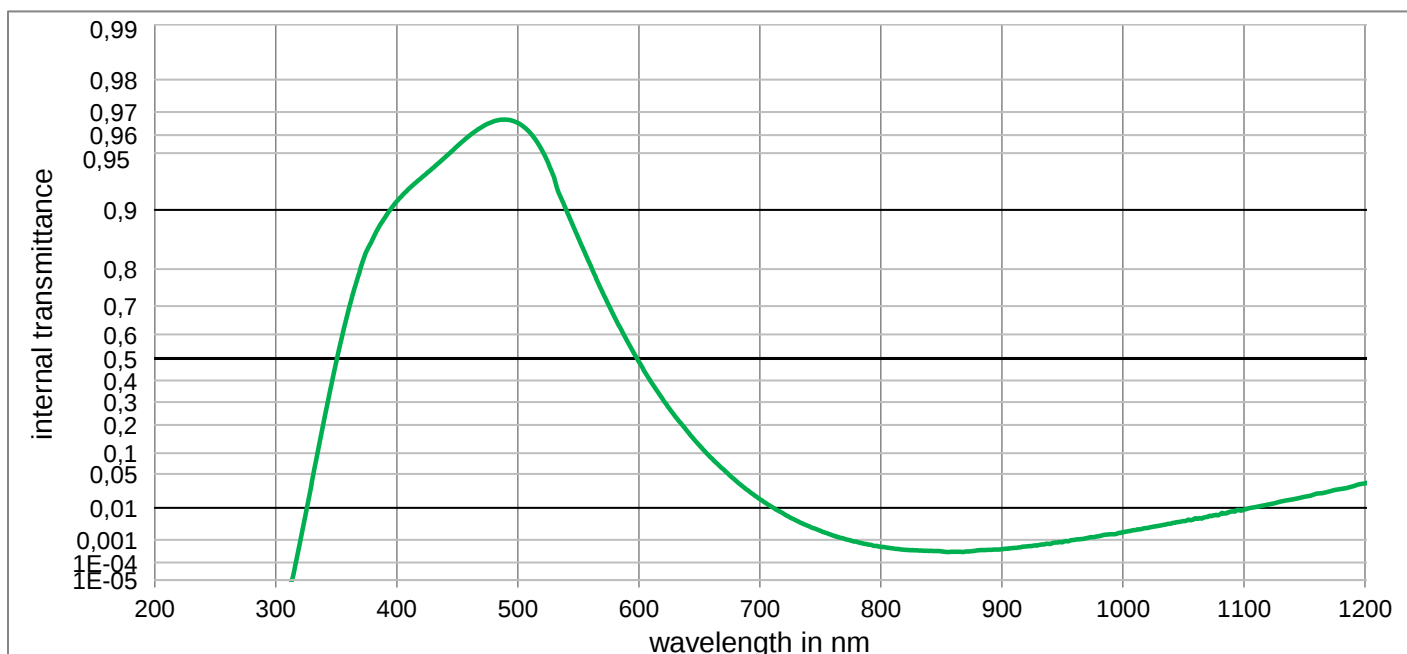

BG61

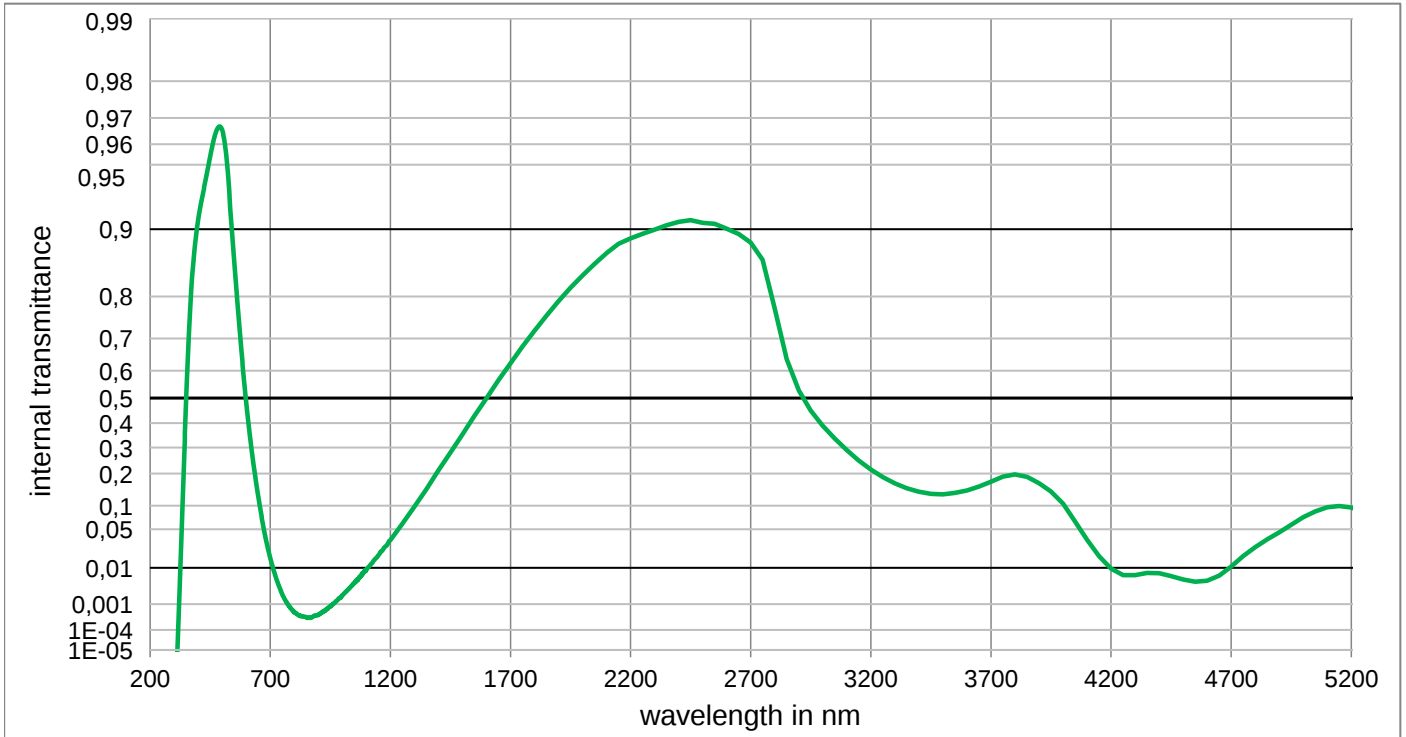Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,656E-01	800	5,193E-04	1100	9,044E-03	2200	8,897E-01	3700	1,718E-01
210	< 1,000E-05	510	9,612E-01	810	4,547E-04	1110	1,045E-02	2250	8,951E-01	3750	1,889E-01
220	< 1,000E-05	520	9,516E-01	820	3,958E-04	1120	1,210E-02	2300	8,995E-01	3800	1,973E-01
230	< 1,000E-05	530	9,326E-01	830	3,721E-04	1130	1,412E-02	2350	9,042E-01	3850	1,886E-01
240	< 1,000E-05	540	9,001E-01	840	3,530E-04	1140	1,599E-02	2400	9,076E-01	3900	1,668E-01
250	< 1,000E-05	550	8,602E-01	850	3,372E-04	1150	1,819E-02	2450	9,091E-01	3950	1,399E-01
260	< 1,000E-05	560	8,082E-01	860	3,277E-04	1160	2,144E-02	2500	9,064E-01	4000	1,051E-01
270	< 1,000E-05	570	7,417E-01	870	3,291E-04	1170	2,359E-02	2550	9,055E-01	4050	6,433E-02
280	< 1,000E-05	580	6,631E-01	880	3,728E-04	1180	2,664E-02	2600	9,005E-01	4100	3,430E-02
290	< 1,000E-05	590	5,767E-01	890	3,944E-04	1190	3,013E-02	2650	8,947E-01	4150	1,749E-02
300	< 1,000E-05	600	4,848E-01	900	4,116E-04	1200	3,407E-02	2700	8,849E-01	4200	9,654E-03
310	< 1,000E-05	610	3,949E-01	910	4,741E-04	1250	5,972E-02	2750	8,623E-01	4250	6,791E-03
320	8,279E-04	620	3,106E-01	920	5,553E-04	1300	9,768E-02	2800	7,744E-01	4300	6,709E-03
330	3,776E-02	630	2,359E-01	930	6,122E-04	1350	1,471E-01	2850	6,386E-01	4350	7,569E-03
340	2,218E-01	640	1,744E-01	940	6,917E-04	1400	2,110E-01	2900	5,289E-01	4400	7,518E-03
350	4,867E-01	650	1,247E-01	950	8,146E-04	1450	2,800E-01	2950	4,504E-01	4450	6,408E-03
360	6,867E-01	660	8,605E-02	960	9,997E-04	1500	3,528E-01	3000	3,893E-01	4500	5,234E-03
370	8,013E-01	670	5,862E-02	970	1,164E-03	1550	4,286E-01	3050	3,366E-01	4550	4,591E-03
380	8,579E-01	680	3,831E-02	980	1,375E-03	1600	4,994E-01	3100	2,896E-01	4600	4,923E-03
390	8,900E-01	690	2,506E-02	990	1,621E-03	1650	5,662E-01	3150	2,488E-01	4650	6,605E-03
400	9,099E-01	700	1,619E-02	1000	1,899E-03	1700	6,247E-01	3200	2,145E-01	4700	1,066E-02
410	9,225E-01	710	1,049E-02	1010	2,246E-03	1750	6,771E-01	3250	1,871E-01	4750	1,748E-02
420	9,320E-01	720	6,864E-03	1020	2,621E-03	1800	7,210E-01	3300	1,658E-01	4800	2,590E-02
430	9,401E-01	730	4,501E-03	1030	3,084E-03	1850	7,586E-01	3350	1,500E-01	4850	3,480E-02
440	9,475E-01	740	3,032E-03	1040	3,652E-03	1900	7,902E-01	3400	1,394E-01	4900	4,502E-02
450	9,542E-01	750	2,113E-03	1050	4,329E-03	1950	8,168E-01	3450	1,330E-01	4950	5,802E-02
460	9,597E-01	760	1,465E-03	1060	5,237E-03	2000	8,384E-01	3500	1,313E-01	5000	7,262E-02
470	9,638E-01	770	1,094E-03	1070	5,656E-03	2050	8,562E-01	3550	1,359E-01	5050	8,615E-02
480	9,663E-01	780	8,376E-04	1080	6,708E-03	2100	8,717E-01	3600	1,432E-01	5100	9,571E-02
490	9,670E-01	790	6,491E-04	1090	8,091E-03	2150	8,834E-01	3650	1,554E-01	5150	9,889E-02

Optical properties	
Reflection factor	
P _d = 0,915	
Spectral values guaranteed	
τ _i (405 nm)	≥ 0,73
τ _i (514 nm)	≥ 0,89
τ _i (633 nm)	≥ 0,08
τ _i (694 nm)	≤ 0,005
τ _i (1060 nm)	≤ 0,0005
Refractive indices	
n _F (486 nm)	= 1,546
n _e (546 nm)	= 1,542
n _d (587,6 nm)	= 1,54
Sellmeier coefficients	
valid from 340 nm to 1550 nm	
B ₁	1,2129
B ₂	0,1238
B ₃	0,0621
C ₁	6,667E-03 μm ²
C ₂	3,0034E-02 μm ²
C ₃	12,219 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,85 g/cm ³	
Knoop hardness	
HK[0.1/20] = 368	

Thermal properties	
Transformation temperature	
T _g = 410 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _(-30°C/+70°C) = 11,9	
α _(20°C/300°C) = 13,6	


Chemical properties	
Chemical resistance	
FR class = 1	
SR class = 52.3	
AR class = 3.3	
Resistance against humidity	

Colormetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,229	0,194	0,175
	y	0,320	0,311	0,305
	Y	60,0	45,1	35,8
	λ _d	490 nm	490 nm	489 nm
	P _e	0,312	0,446	0,520
Illuminant A	x	0,321	0,257	0,220
	y	0,441	0,447	0,445
	Y	51,6	36,0	27,2
	λ _d	499 nm	498 nm	498 nm
	P _e	0,290	0,438	0,524

Notes
Ionically colored glass
Bandpass filter / Shortpass filter
NIR cutoff filter
lambda_50%(d=0.21mm) = 644 nm
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

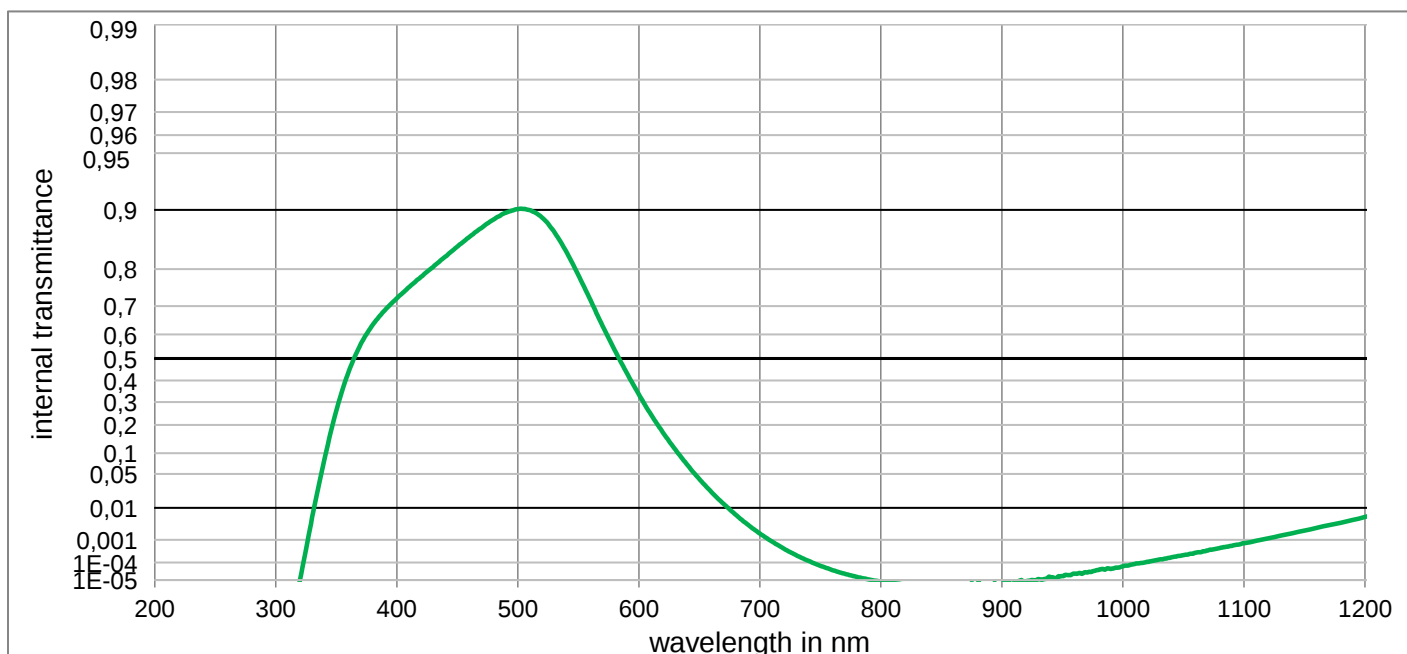


BG62

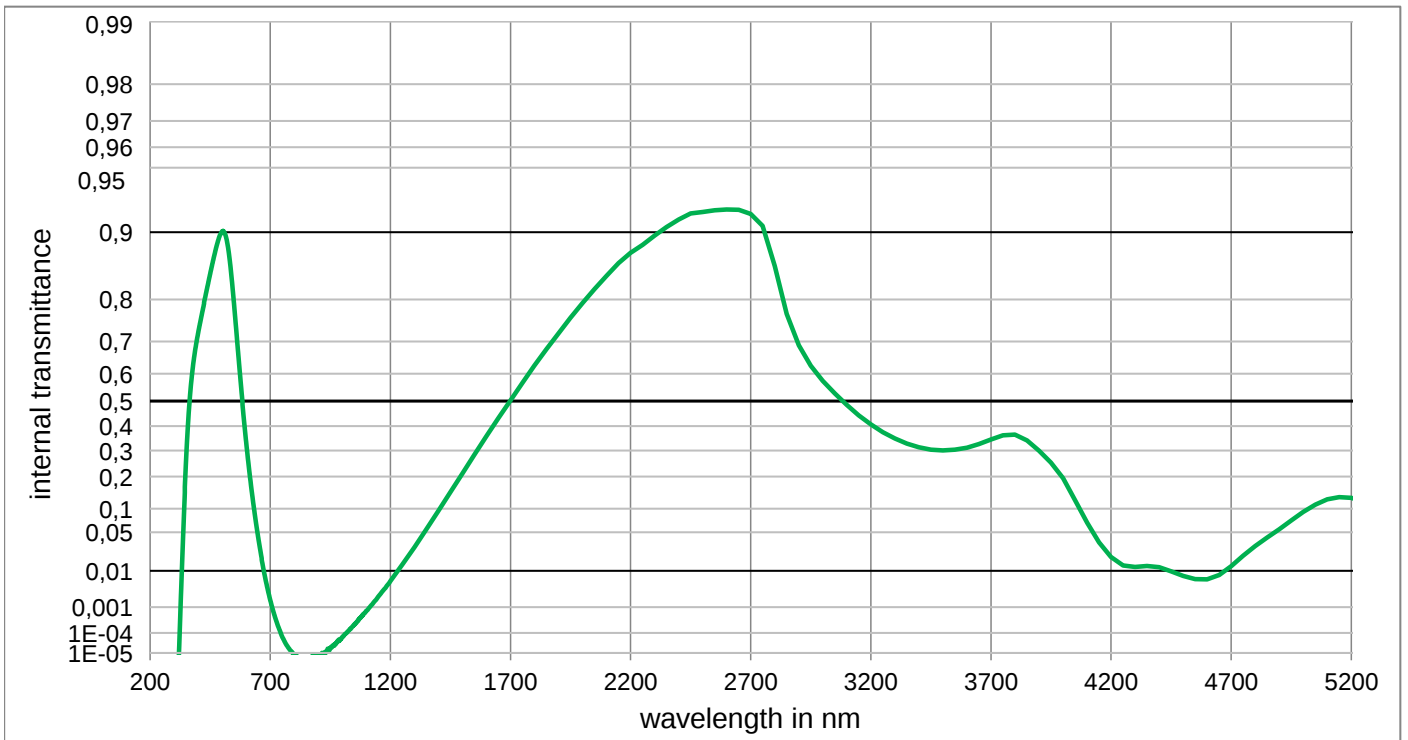Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,010E-01	800	< 1,000E-05	1100	7,390E-04	2200	8,757E-01	3700	3,448E-01
210	< 1,000E-05	510	8,996E-01	810	< 1,000E-05	1110	9,134E-04	2250	8,858E-01	3750	3,621E-01
220	< 1,000E-05	520	8,902E-01	820	< 1,000E-05	1120	1,135E-03	2300	8,963E-01	3800	3,647E-01
230	< 1,000E-05	530	8,704E-01	830	< 1,000E-05	1130	1,415E-03	2350	9,053E-01	3850	3,416E-01
240	< 1,000E-05	540	8,363E-01	840	< 1,000E-05	1140	1,732E-03	2400	9,126E-01	3900	2,998E-01
250	< 1,000E-05	550	7,859E-01	850	< 1,000E-05	1150	2,149E-03	2450	9,180E-01	3950	2,524E-01
260	< 1,000E-05	560	7,179E-01	860	< 1,000E-05	1160	2,620E-03	2500	9,193E-01	4000	1,940E-01
270	< 1,000E-05	570	6,330E-01	870	< 1,000E-05	1170	3,235E-03	2550	9,208E-01	4050	1,235E-01
280	< 1,000E-05	580	5,365E-01	880	< 1,000E-05	1180	3,803E-03	2600	9,215E-01	4100	6,781E-02
290	< 1,000E-05	590	4,347E-01	890	< 1,000E-05	1190	4,695E-03	2650	9,213E-01	4150	3,506E-02
300	< 1,000E-05	600	3,347E-01	900	< 1,000E-05	1200	5,724E-03	2700	9,177E-01	4200	1,926E-02
310	< 1,000E-05	610	2,446E-01	910	< 1,000E-05	1250	1,361E-02	2750	9,065E-01	4250	1,309E-02
320	1,091E-05	620	1,691E-01	920	< 1,000E-05	1300	2,886E-02	2800	8,575E-01	4300	1,218E-02
330	5,414E-03	630	1,115E-01	930	1,165E-05	1350	5,506E-02	2850	7,696E-01	4350	1,280E-02
340	7,963E-02	640	6,907E-02	940	1,541E-05	1400	9,391E-02	2900	6,891E-01	4400	1,197E-02
350	2,609E-01	650	4,086E-02	950	1,755E-05	1450	1,474E-01	2950	6,267E-01	4450	9,752E-03
360	4,385E-01	660	2,302E-02	960	2,479E-05	1500	2,108E-01	3000	5,754E-01	4500	7,643E-03
370	5,592E-01	670	1,251E-02	970	2,870E-05	1550	2,833E-01	3050	5,287E-01	4550	6,426E-03
380	6,359E-01	680	6,564E-03	980	4,020E-05	1600	3,593E-01	3100	4,846E-01	4600	6,306E-03
390	6,861E-01	690	3,364E-03	990	4,506E-05	1650	4,329E-01	3150	4,432E-01	4650	8,001E-03
400	7,241E-01	700	1,703E-03	1000	6,306E-05	1700	5,028E-01	3200	4,065E-01	4700	1,261E-02
410	7,548E-01	710	8,557E-04	1010	8,451E-05	1750	5,686E-01	3250	3,749E-01	4750	2,046E-02
420	7,817E-01	720	4,359E-04	1020	1,094E-04	1800	6,275E-01	3300	3,489E-01	4800	3,035E-02
430	8,047E-01	730	2,284E-04	1030	1,406E-04	1850	6,784E-01	3350	3,284E-01	4850	4,167E-02
440	8,263E-01	740	1,222E-04	1040	1,816E-04	1900	7,221E-01	3400	3,129E-01	4900	5,510E-02
450	8,455E-01	750	6,774E-05	1050	2,297E-04	1950	7,604E-01	3450	3,039E-01	4950	7,229E-02
460	8,620E-01	760	3,935E-05	1060	2,932E-04	2000	7,928E-01	3500	3,002E-01	5000	9,193E-02
470	8,761E-01	770	2,448E-05	1070	3,653E-04	2050	8,197E-01	3550	3,034E-01	5050	1,109E-01
480	8,878E-01	780	1,610E-05	1080	4,627E-04	2100	8,428E-01	3600	3,118E-01	5100	1,255E-01
490	8,965E-01	790	1,109E-05	1090	5,805E-04	2150	8,618E-01	3650	3,260E-01	5150	1,323E-01

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm		2 mm	3 mm	
P _d = 0,914		d = 1,00 mm		Illuminant D65	x	0,226	0,191	0,172
Spectral values guaranteed		Density			y	0,314	0,299	0,288
τ _i (405 nm)	≥ 0,8	ρ = 2,85 g/cm³			Y	60,8	46,6	37,7
τ _i (514 nm)	≥ 0,9	Knoop hardness			λ _d	489 nm	489 nm	488 nm
τ _i (633 nm)	≥ 0,08	HK[0.1/20] = 368			P _e	0,326	0,468	0,546
τ _i (694 nm)	≤ 0,004	Thermal properties		Illuminant A	x	0,317	0,252	0,215
τ _i (1060 nm)	≤ 0,0005	Transformation temperature			y	0,438	0,438	0,430
		Tg = 410 °C			Y	52,0	36,9	28,4
		Thermal expansion in 10 ⁻⁶ /K			λ _d	499 nm	497 nm	496 nm
		α _(-30°C/+70°C) = 11,8			P _e	0,299	0,452	0,542
Refractive indices		α _(20°C/300°C) = 13,7		Notes				
n _F (486 nm)	= 1,546			Ionically colored glass Bandpass filter / Shortpass filter NIR cutoff filter lambda_50%(d=0.21mm) = 644 nm ISO 23364:2021				
n _e (546 nm)	= 1,542							
n _d (587,6 nm)	= 1,54							
Sellmeier coefficients		Chemical properties		Disclaimer				
valid from 340 nm to 1550 nm		Chemical resistance		All data without tolerances are to be understood to be reference values.				
B ₁	1,2129	FR class = 1						
B ₂	0,1238	SR class = 52.3						
B ₃	0,0621	AR class = 3.3						
C ₁	6,667E-03 μm²	Resistance against humidity						
C ₂	3,0034E-02 μm²							
C ₃	12,219 μm²							
Internal quality								
Bubble class	2							

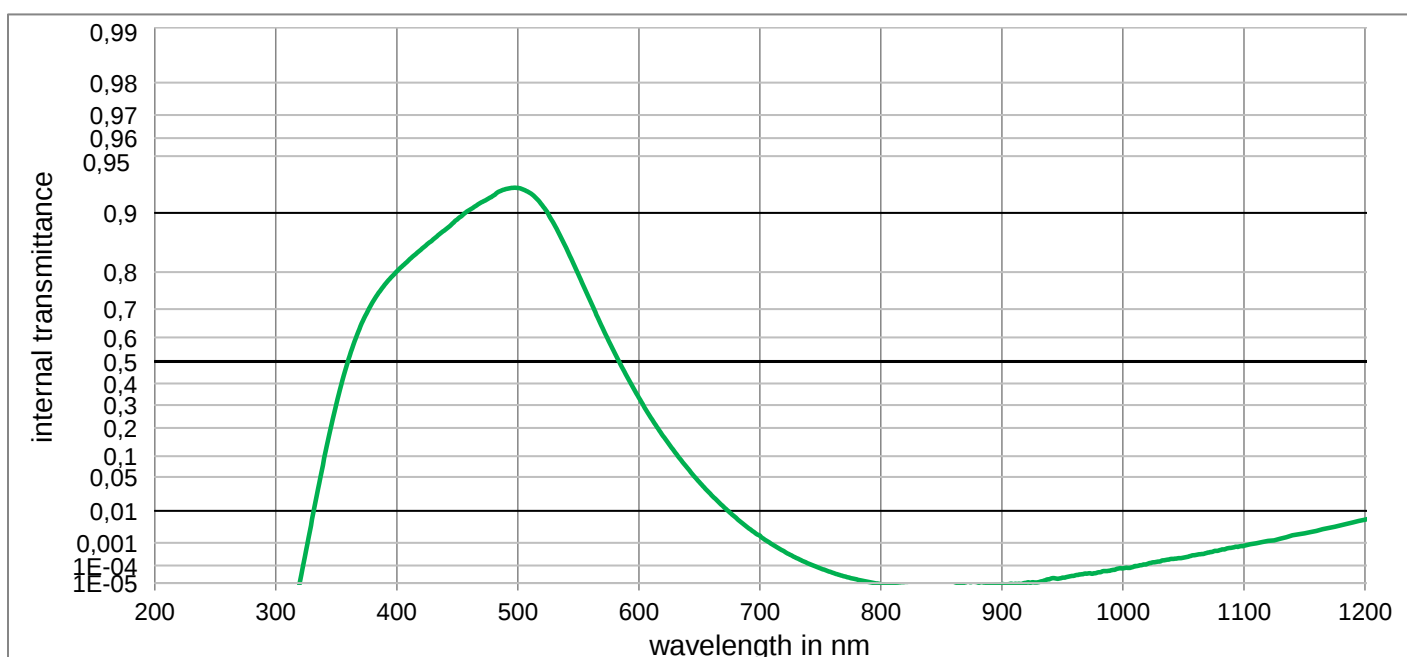


BG62HT

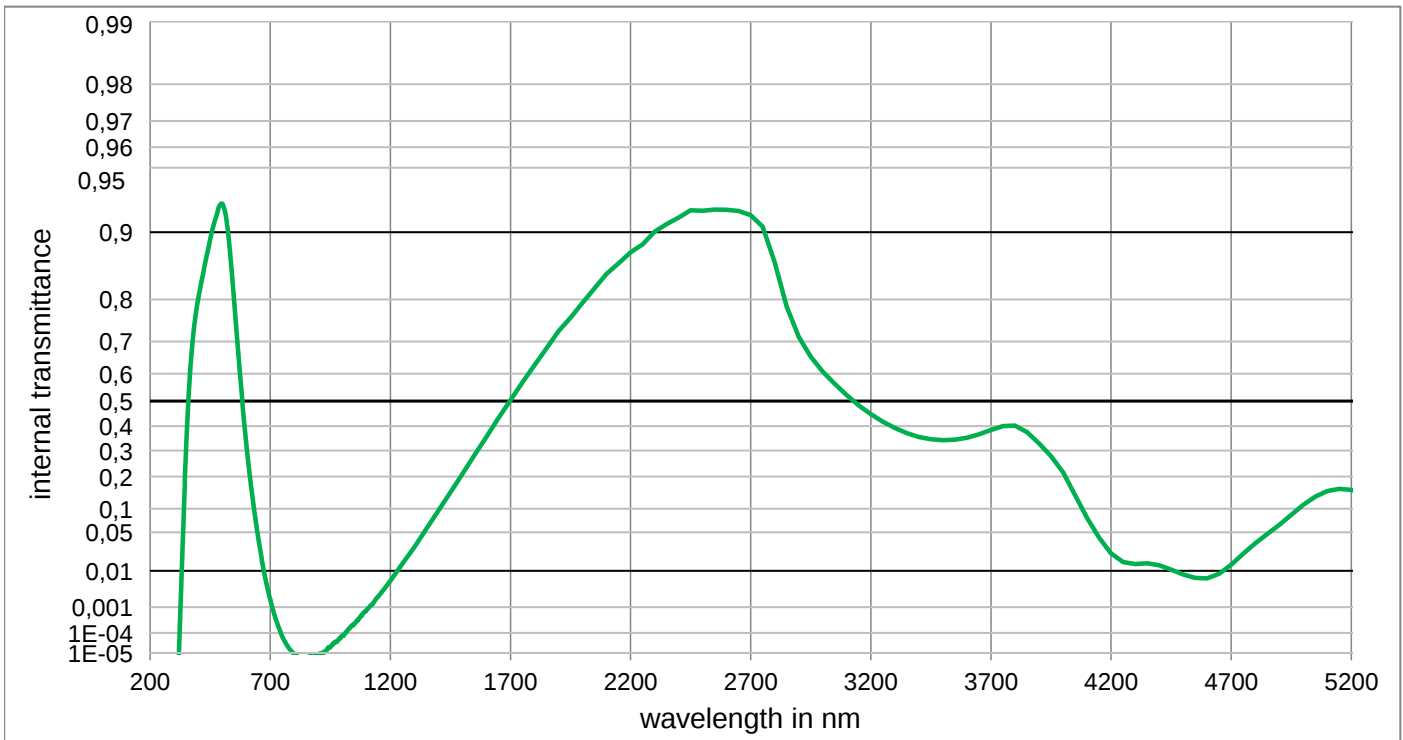Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,261E-01	800	< 1,000E-05	1100	7,708E-04	2200	8,764E-01	3700	3,841E-01
210	< 1,000E-05	510	9,214E-01	810	< 1,000E-05	1110	9,495E-04	2250	8,864E-01	3750	4,004E-01
220	< 1,000E-05	520	9,089E-01	820	< 1,000E-05	1120	1,194E-03	2300	9,006E-01	3800	4,015E-01
230	< 1,000E-05	530	8,856E-01	830	< 1,000E-05	1130	1,417E-03	2350	9,081E-01	3850	3,755E-01
240	< 1,000E-05	540	8,483E-01	840	< 1,000E-05	1140	1,889E-03	2400	9,143E-01	3900	3,297E-01
250	< 1,000E-05	550	7,945E-01	850	< 1,000E-05	1150	2,190E-03	2450	9,208E-01	3950	2,780E-01
260	< 1,000E-05	560	7,232E-01	860	< 1,000E-05	1160	2,656E-03	2500	9,204E-01	4000	2,153E-01
270	< 1,000E-05	570	6,361E-01	870	< 1,000E-05	1170	3,280E-03	2550	9,214E-01	4050	1,386E-01
280	< 1,000E-05	580	5,373E-01	880	< 1,000E-05	1180	3,977E-03	2600	9,213E-01	4100	7,754E-02
290	< 1,000E-05	590	4,338E-01	890	< 1,000E-05	1190	4,816E-03	2650	9,202E-01	4150	4,183E-02
300	< 1,000E-05	600	3,335E-01	900	< 1,000E-05	1200	5,792E-03	2700	9,166E-01	4200	2,268E-02
310	< 1,000E-05	610	2,433E-01	910	< 1,000E-05	1250	1,420E-02	2750	9,057E-01	4250	1,526E-02
320	1,339E-05	620	1,683E-01	920	1,017E-05	1300	2,938E-02	2800	8,625E-01	4300	1,405E-02
330	5,930E-03	630	1,110E-01	930	1,146E-05	1350	5,598E-02	2850	7,851E-01	4350	1,440E-02
340	9,512E-02	640	6,912E-02	940	1,861E-05	1400	9,470E-02	2900	7,123E-01	4400	1,317E-02
350	3,042E-01	650	4,089E-02	950	2,151E-05	1450	1,470E-01	2950	6,549E-01	4450	1,057E-02
360	5,087E-01	660	2,308E-02	960	2,868E-05	1500	2,097E-01	3000	6,073E-01	4500	8,216E-03
370	6,420E-01	670	1,259E-02	970	3,657E-05	1550	2,813E-01	3050	5,638E-01	4550	6,843E-03
380	7,214E-01	680	6,615E-03	980	4,364E-05	1600	3,563E-01	3100	5,224E-01	4600	6,690E-03
390	7,694E-01	690	3,406E-03	990	5,597E-05	1650	4,329E-01	3150	4,834E-01	4650	8,518E-03
400	8,016E-01	700	1,849E-03	1000	7,191E-05	1700	5,036E-01	3200	4,482E-01	4700	1,353E-02
410	8,257E-01	710	8,801E-04	1010	9,398E-05	1750	5,702E-01	3250	4,175E-01	4750	2,221E-02
420	8,456E-01	720	4,531E-04	1020	1,185E-04	1800	6,281E-01	3300	3,919E-01	4800	3,359E-02
430	8,627E-01	730	2,360E-04	1030	1,571E-04	1850	6,812E-01	3350	3,714E-01	4850	4,702E-02
440	8,779E-01	740	1,276E-04	1040	2,103E-04	1900	7,279E-01	3400	3,556E-01	4900	6,337E-02
450	8,919E-01	750	7,146E-05	1050	2,391E-04	1950	7,606E-01	3450	3,461E-01	4950	8,489E-02
460	9,036E-01	760	4,179E-05	1060	3,161E-04	2000	7,936E-01	3500	3,419E-01	5000	1,098E-01
470	9,121E-01	770	2,577E-05	1070	4,016E-04	2050	8,208E-01	3550	3,445E-01	5050	1,335E-01
480	9,190E-01	780	1,695E-05	1080	5,109E-04	2100	8,458E-01	3600	3,524E-01	5100	1,508E-01
490	9,251E-01	790	1,170E-05	1090	6,481E-04	2150	8,616E-01	3650	3,662E-01	5150	1,578E-01

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm 2 mm 3 mm				
P _d = 0,916		d = 1,00 mm		Illuminant D65	x	0,280	0,255	0,237
Spectral values guaranteed		Density			y	0,325	0,319	0,313
τ _i (405 nm)	≥ 0,95	ρ = 2,79 g/cm³			Y	80,9	73,0	67,0
τ _i (514 nm)	≥ 0,96	Knoop hardness			λ _d	490 nm	489 nm	489 nm
τ _i (633 nm)	≥ 0,5	HK[0.1/20] = 362			P _e	0,123	0,216	0,289
τ _i (694 nm)	≤ 0,25	Thermal properties		Illuminant A	x	0,403	0,366	0,336
τ _i (1060 nm)	≤ 0,16	Transformation temperature			y	0,420	0,428	0,432
		Tg = 416 °C			Y	76,5	66,2	58,6
		Thermal expansion in 10 ⁻⁶ /K			λ _d	500 nm	499 nm	499 nm
Refractive indices		α _(-30°C/+70°C) = 11,9			P _e	0,102	0,186	0,256
n _F (486 nm)	= 1,538	α _(20°C/300°C) = 13,9		Notes				
n _e (546 nm)	= 1,534			Ionically colored glass Bandpass filter / Shortpass filter NIR cutoff filter lambda_50%(d=1.5mm) = 614 nm ISO 23364:2021				
n _d (587,6 nm)	= 1,532							
Sellmeier coefficients		Chemical properties		Disclaimer				
valid from 365 nm to 2325 nm		Chemical resistance		All data without tolerances are to be understood to be reference values.				
B ₁	1,3115	FR class = 1						
B ₂	0,0046	SR class = 52.3						
B ₃	0,3087	AR class = 3.3						
Internal quality		Resistance against humidity						
C ₁	8,469E-03 μm²							
C ₂	5,7634E-02 μm²							
C ₃	46,721 μm²							
Bubble class	2							

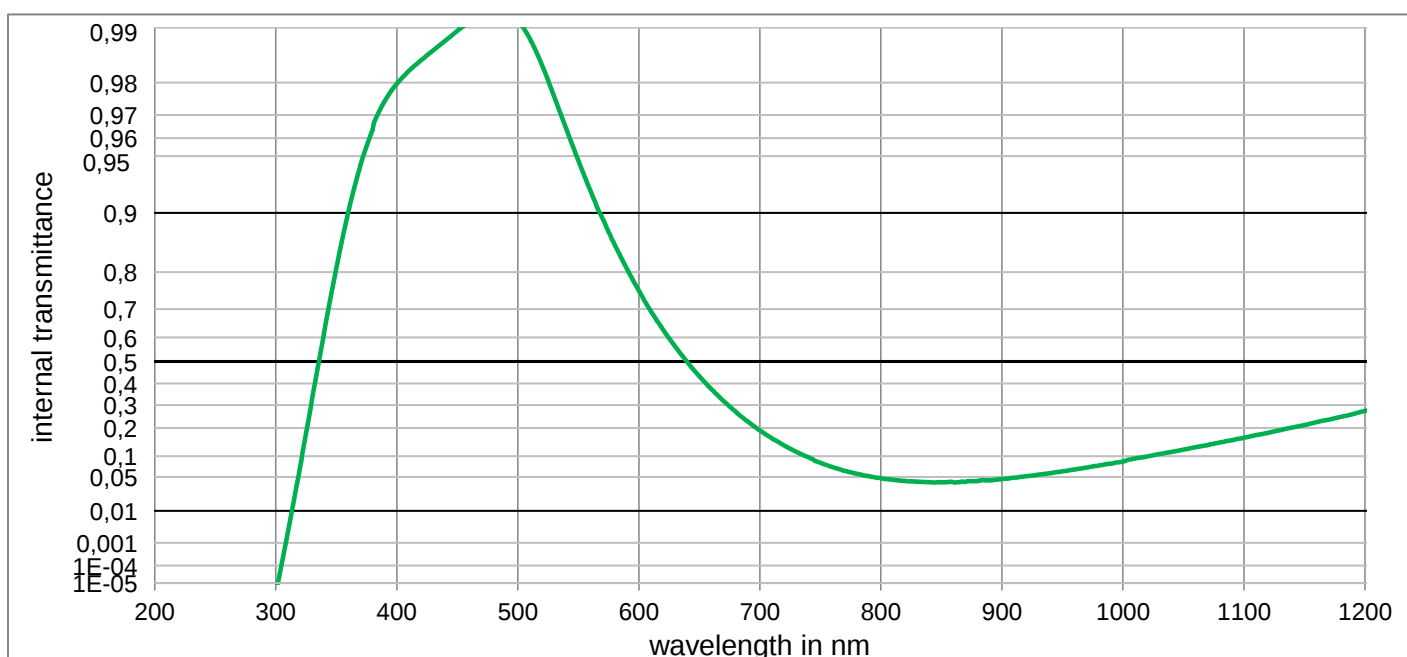

BG63

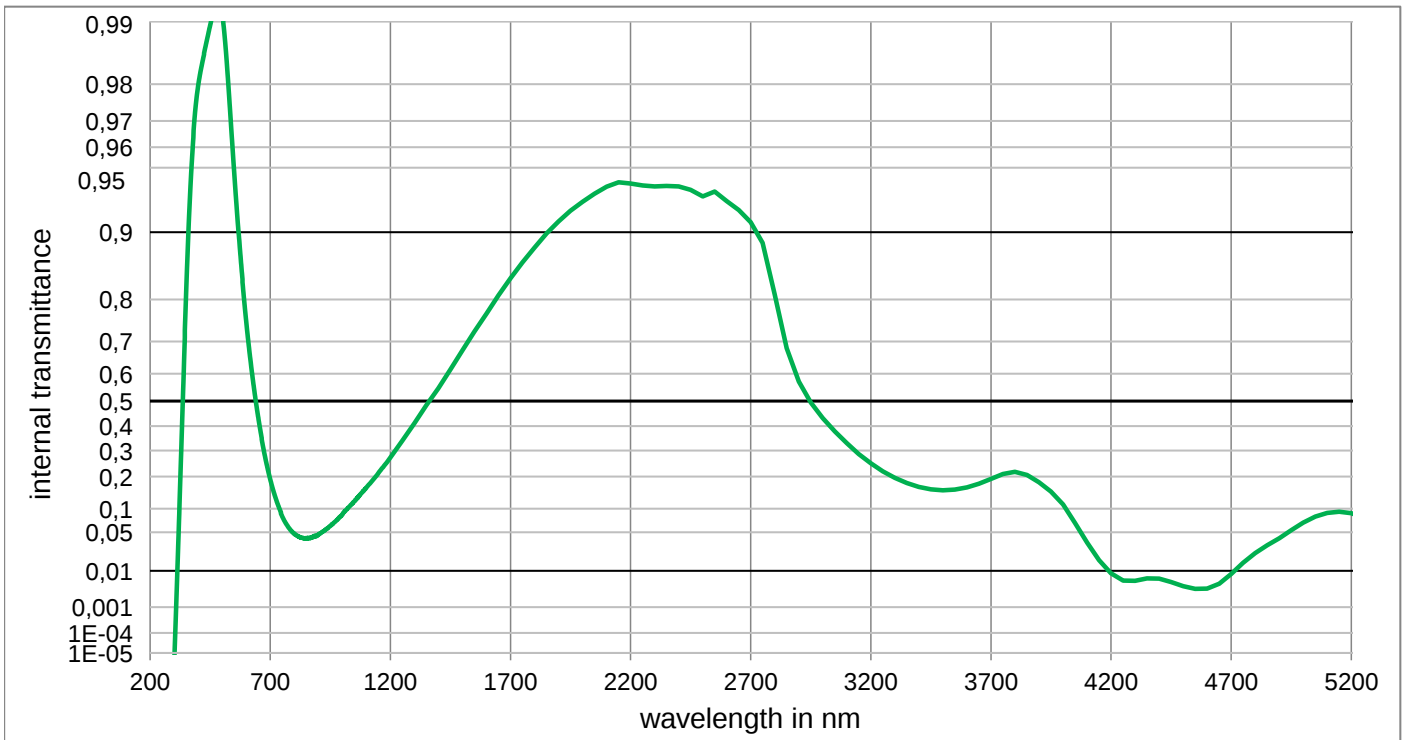Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,909E-01	800	4,771E-02	1100	1,621E-01	2200	9,406E-01	3700	1,921E-01
210	< 1,000E-05	510	9,885E-01	810	4,471E-02	1110	1,714E-01	2250	9,393E-01	3750	2,095E-01
220	< 1,000E-05	520	9,839E-01	820	4,271E-02	1120	1,806E-01	2300	9,388E-01	3800	2,171E-01
230	< 1,000E-05	530	9,763E-01	830	4,174E-02	1130	1,912E-01	2350	9,391E-01	3850	2,055E-01
240	< 1,000E-05	540	9,644E-01	840	4,061E-02	1140	2,015E-01	2400	9,387E-01	3900	1,796E-01
250	< 1,000E-05	550	9,471E-01	850	4,057E-02	1150	2,122E-01	2450	9,364E-01	3950	1,492E-01
260	< 1,000E-05	560	9,232E-01	860	4,065E-02	1160	2,240E-01	2500	9,317E-01	4000	1,114E-01
270	< 1,000E-05	570	8,935E-01	870	4,149E-02	1170	2,349E-01	2550	9,352E-01	4050	6,722E-02
280	< 1,000E-05	580	8,543E-01	880	4,238E-02	1180	2,467E-01	2600	9,284E-01	4100	3,475E-02
290	< 1,000E-05	590	8,076E-01	890	4,391E-02	1190	2,591E-01	2650	9,210E-01	4150	1,686E-02
300	< 1,000E-05	600	7,536E-01	900	4,619E-02	1200	2,726E-01	2700	9,101E-01	4200	8,809E-03
310	2,433E-03	610	6,937E-01	910	4,868E-02	1250	3,398E-01	2750	8,881E-01	4250	5,895E-03
320	7,008E-02	620	6,295E-01	920	5,153E-02	1300	4,115E-01	2800	8,095E-01	4300	5,826E-03
330	3,265E-01	630	5,632E-01	930	5,418E-02	1350	4,843E-01	2850	6,807E-01	4350	6,643E-03
340	6,188E-01	640	4,980E-01	940	5,756E-02	1400	5,477E-01	2900	5,725E-01	4400	6,550E-03
350	8,085E-01	650	4,343E-01	950	6,141E-02	1450	6,145E-01	2950	4,941E-01	4450	5,416E-03
360	9,020E-01	660	3,734E-01	960	6,548E-02	1500	6,746E-01	3000	4,325E-01	4500	4,256E-03
370	9,441E-01	670	3,185E-01	970	6,997E-02	1550	7,266E-01	3050	3,786E-01	4550	3,563E-03
380	9,639E-01	680	2,695E-01	980	7,511E-02	1600	7,697E-01	3100	3,298E-01	4600	3,622E-03
390	9,748E-01	690	2,267E-01	990	7,958E-02	1650	8,079E-01	3150	2,863E-01	4650	4,923E-03
400	9,797E-01	700	1,900E-01	1000	8,513E-02	1700	8,387E-01	3200	2,493E-01	4700	8,493E-03
410	9,827E-01	710	1,594E-01	1010	9,301E-02	1750	8,629E-01	3250	2,191E-01	4750	1,485E-02
420	9,849E-01	720	1,340E-01	1020	9,917E-02	1800	8,822E-01	3300	1,952E-01	4800	2,293E-02
430	9,867E-01	730	1,133E-01	1030	1,063E-01	1850	8,987E-01	3350	1,771E-01	4850	3,124E-02
440	9,882E-01	740	9,696E-02	1040	1,124E-01	1900	9,108E-01	3400	1,640E-01	4900	4,079E-02
450	9,896E-01	750	8,151E-02	1050	1,202E-01	1950	9,204E-01	3450	1,564E-01	4950	5,353E-02
460	9,907E-01	760	7,097E-02	1060	1,282E-01	2000	9,277E-01	3500	1,535E-01	5000	6,786E-02
470	9,915E-01	770	6,270E-02	1070	1,348E-01	2050	9,336E-01	3550	1,559E-01	5050	8,079E-02
480	9,919E-01	780	5,639E-02	1080	1,437E-01	2100	9,385E-01	3600	1,629E-01	5100	8,941E-02
490	9,919E-01	790	5,125E-02	1090	1,522E-01	2150	9,414E-01	3650	1,752E-01	5150	9,218E-02

Optical properties	
Reflection factor	
P _d = 0,916	
Spectral values guaranteed	
τ _i (405 nm)	≥ 0,99
τ _i (514 nm)	≥ 0,99
τ _i (633 nm)	≥ 0,72
τ _i (694 nm)	≤ 0,55
τ _i (1060 nm)	≤ 0,45
Refractive indices	
n _F (486 nm)	= 1,535
n _e (546 nm)	= 1,532
n _d (587,6 nm)	= 1,53
Sellmeier coefficients	
valid from 365 nm to 2325 nm	
B ₁	1,3031
B ₂	0,0067
B ₃	0,4940
C ₁	8,159E-03 μm ²
C ₂	5,5599E-02 μm ²
C ₃	69,869 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,78 g/cm ³	
Knoop hardness	
HK[0.1/20] = 371	

Thermal properties	
Transformation temperature	
Tg = 417 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _(-30°C/+70°C) = 12,0	
α _(20°C/300°C) = 13,8	


Chemical properties	
Chemical resistance	
FR class = 1	
SR class = 52.3	
AR class = 3.3	
Resistance against humidity	

Colorimetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,297	0,284	0,272
	y	0,327	0,325	0,323
	Y	86,6	82,4	78,6
	λ _d	490 nm	490 nm	490 nm
	P _e	0,058	0,109	0,154
Illuminant A	x	0,427	0,408	0,391
	y	0,414	0,419	0,423
	Y	84,4	78,4	73,3
	λ _d	500 nm	500 nm	500 nm
	P _e	0,047	0,089	0,129

Notes
Ionically colored glass
Bandpass filter / Shortpass filter
NIR cutoff filter
lambda_50%(d=3mm) = 619 nm
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

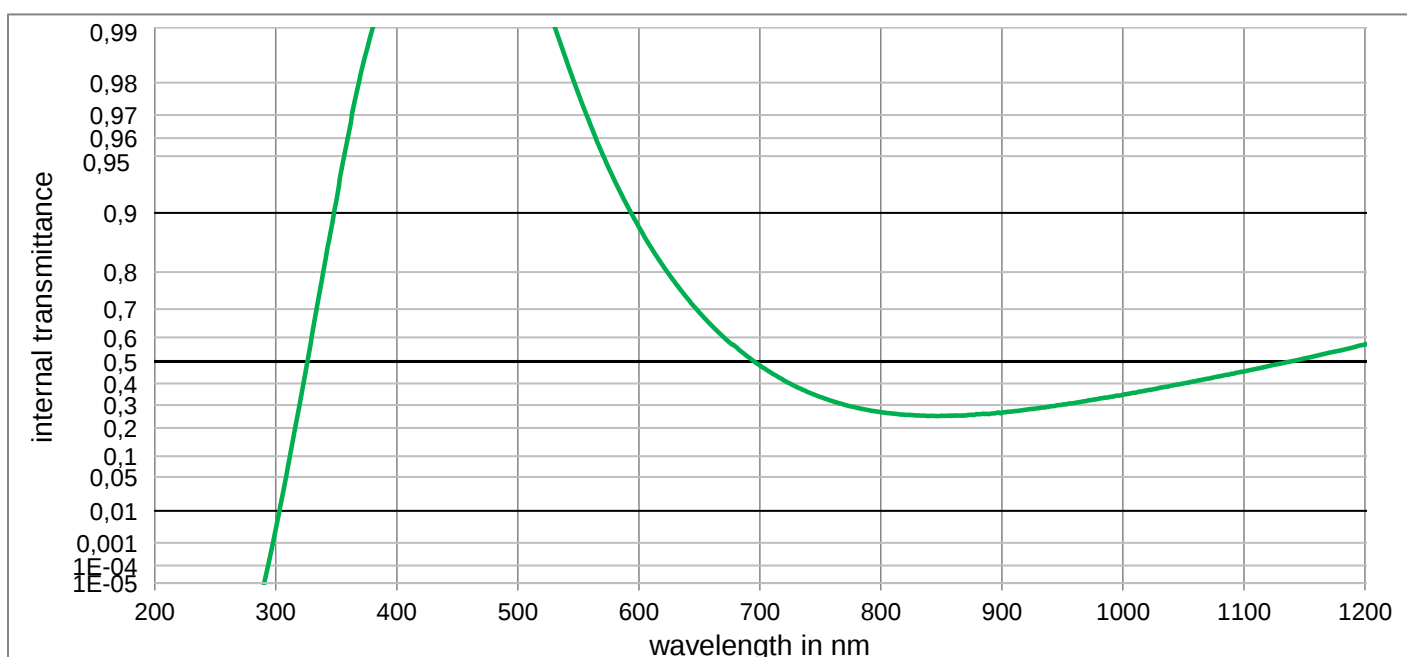

BG64

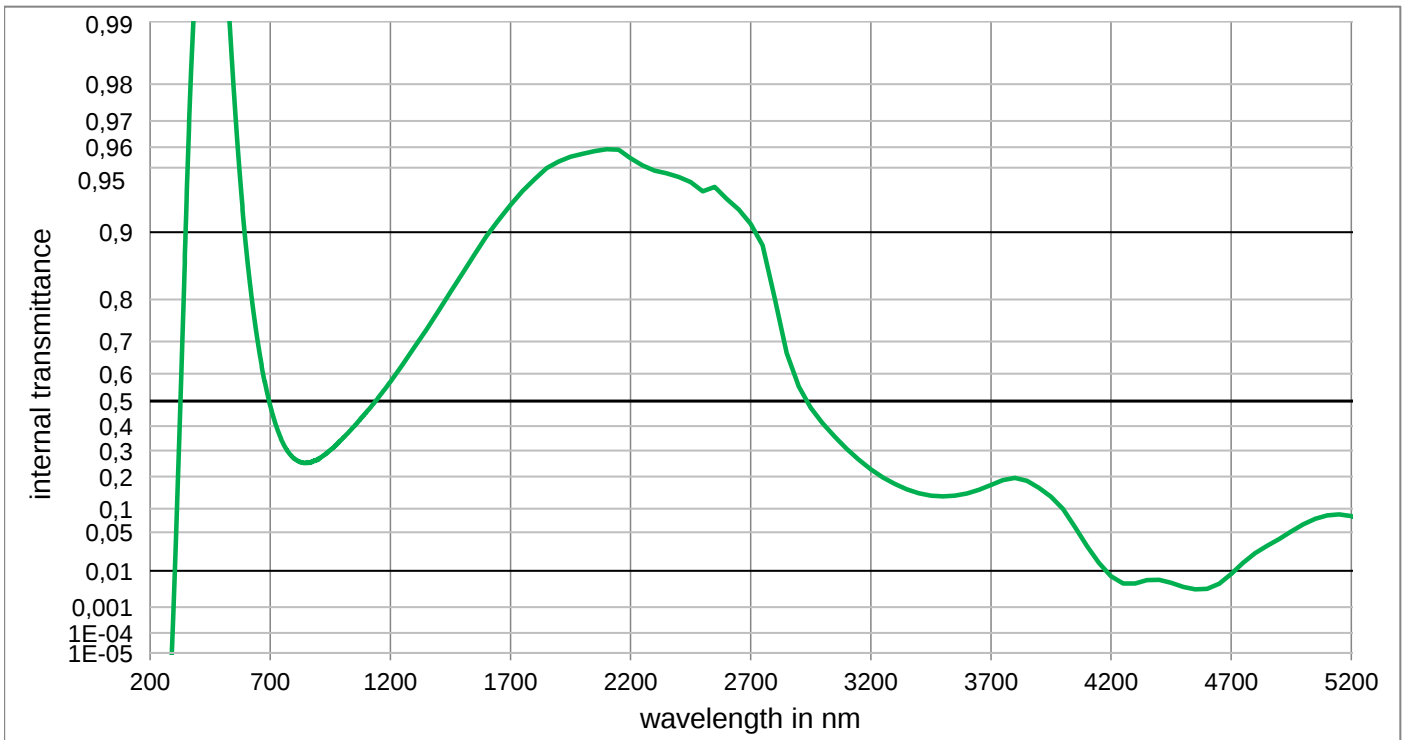Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,971E-01	800	2,682E-01	1100	4,553E-01	2200	9,549E-01	3700	1,706E-01
210	< 1,000E-05	510	9,959E-01	810	2,611E-01	1110	4,666E-01	2250	9,512E-01	3750	1,874E-01
220	< 1,000E-05	520	9,938E-01	820	2,558E-01	1120	4,786E-01	2300	9,484E-01	3800	1,951E-01
230	< 1,000E-05	530	9,903E-01	830	2,539E-01	1130	4,896E-01	2350	9,469E-01	3850	1,849E-01
240	< 1,000E-05	540	9,850E-01	840	2,511E-01	1140	5,017E-01	2400	9,447E-01	3900	1,614E-01
250	< 1,000E-05	550	9,770E-01	850	2,523E-01	1150	5,137E-01	2450	9,416E-01	3950	1,338E-01
260	< 1,000E-05	560	9,660E-01	860	2,522E-01	1160	5,248E-01	2500	9,354E-01	4000	9,910E-02
270	< 1,000E-05	570	9,513E-01	870	2,539E-01	1170	5,370E-01	2550	9,383E-01	4050	5,906E-02
280	< 1,000E-05	580	9,324E-01	880	2,592E-01	1180	5,479E-01	2600	9,299E-01	4100	3,025E-02
290	< 1,000E-05	590	9,093E-01	890	2,601E-01	1190	5,602E-01	2650	9,214E-01	4150	1,459E-02
300	2,982E-03	600	8,816E-01	900	2,661E-01	1200	5,719E-01	2700	9,084E-01	4200	7,556E-03
310	7,223E-02	610	8,496E-01	910	2,722E-01	1250	6,292E-01	2750	8,853E-01	4250	4,980E-03
320	3,138E-01	620	8,137E-01	920	2,787E-01	1300	6,842E-01	2800	8,020E-01	4300	4,985E-03
330	6,101E-01	630	7,745E-01	930	2,850E-01	1350	7,313E-01	2850	6,664E-01	4350	6,061E-03
340	8,116E-01	640	7,328E-01	940	2,938E-01	1400	7,753E-01	2900	5,540E-01	4400	6,099E-03
350	9,134E-01	650	6,894E-01	950	3,014E-01	1450	8,142E-01	2950	4,734E-01	4450	5,149E-03
360	9,618E-01	660	6,452E-01	960	3,100E-01	1500	8,461E-01	3000	4,106E-01	4500	4,072E-03
370	9,818E-01	670	6,013E-01	970	3,187E-01	1550	8,733E-01	3050	3,560E-01	4550	3,468E-03
380	9,899E-01	680	5,625E-01	980	3,291E-01	1600	8,959E-01	3100	3,067E-01	4600	3,580E-03
390	9,935E-01	690	5,212E-01	990	3,379E-01	1650	9,119E-01	3150	2,634E-01	4650	4,884E-03
400	9,950E-01	700	4,821E-01	1000	3,475E-01	1700	9,252E-01	3200	2,268E-01	4700	8,466E-03
410	9,959E-01	710	4,471E-01	1010	3,575E-01	1750	9,356E-01	3250	1,972E-01	4750	1,487E-02
420	9,962E-01	720	4,140E-01	1020	3,681E-01	1800	9,432E-01	3300	1,740E-01	4800	2,278E-02
430	9,966E-01	730	3,852E-01	1030	3,793E-01	1850	9,497E-01	3350	1,565E-01	4850	3,076E-02
440	9,970E-01	740	3,593E-01	1040	3,898E-01	1900	9,532E-01	3400	1,440E-01	4900	3,956E-02
450	9,973E-01	750	3,369E-01	1050	3,999E-01	1950	9,556E-01	3450	1,367E-01	4950	5,139E-02
460	9,976E-01	760	3,175E-01	1060	4,107E-01	2000	9,570E-01	3500	1,339E-01	5000	6,452E-02
470	9,977E-01	770	3,011E-01	1070	4,223E-01	2050	9,583E-01	3550	1,362E-01	5050	7,625E-02
480	9,977E-01	780	2,879E-01	1080	4,326E-01	2100	9,591E-01	3600	1,428E-01	5100	8,386E-02
490	9,977E-01	790	2,763E-01	1090	4,452E-01	2150	9,589E-01	3650	1,544E-01	5150	8,586E-02

Optical properties	
Reflection factor	
P _d = 0,914	
Spectral values guaranteed	
τ _i (430 nm)	≥ 0,815
τ _i (514 nm)	≥ 0,89
τ _i (565 nm)	≥ 0,615
τ _i (694 nm)	≤ 0,0015
τ _i (1060 nm)	≤ 0,0002
Refractive indices	
n _F (486 nm)	= 1,544
n _e (546 nm)	= 1,541
n _d (587,6 nm)	= 1,539
Sellmeier coefficients	
valid from 440 nm to 1550 nm	
B ₁	1,3353
B ₂	0,0004
B ₃	0,6203
C ₁	8,684E-03 μm ²
C ₂	2,0582E-02 μm ²
C ₃	100,000 μm ²
Internal quality	
Bubble class	0


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,85 g/cm ³	
Knoop hardness	
HK[0.1/20] = 373	

Thermal properties	
Transformation temperature	
T _g = 416 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _{-30°C/+70°C} = 11,8	
α _{20°C/300°C} = 13,7	


Chemical properties	
Chemical resistance	
FR class	
SR class = 52.3	
AR class = 3.3	
Resistance against humidity	

Colormetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,218	0,183	0,165
	y	0,313	0,297	0,286
	Y	57,0	42,1	33,1
	λ _d	489 nm	489 nm	488 nm
	P _e	0,356	0,497	0,571
Illuminant A	x	0,303	0,237	0,202
	y	0,440	0,438	0,429
	Y	48,0	32,8	24,5
	λ _d	499 nm	497 nm	496 nm
	P _e	0,332	0,487	0,574

Notes
Ionically colored glass
Bandpass filter / Shortpass filter
NIR cutoff filter
lambda_50%(d=0.21mm) @ 635 nm
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

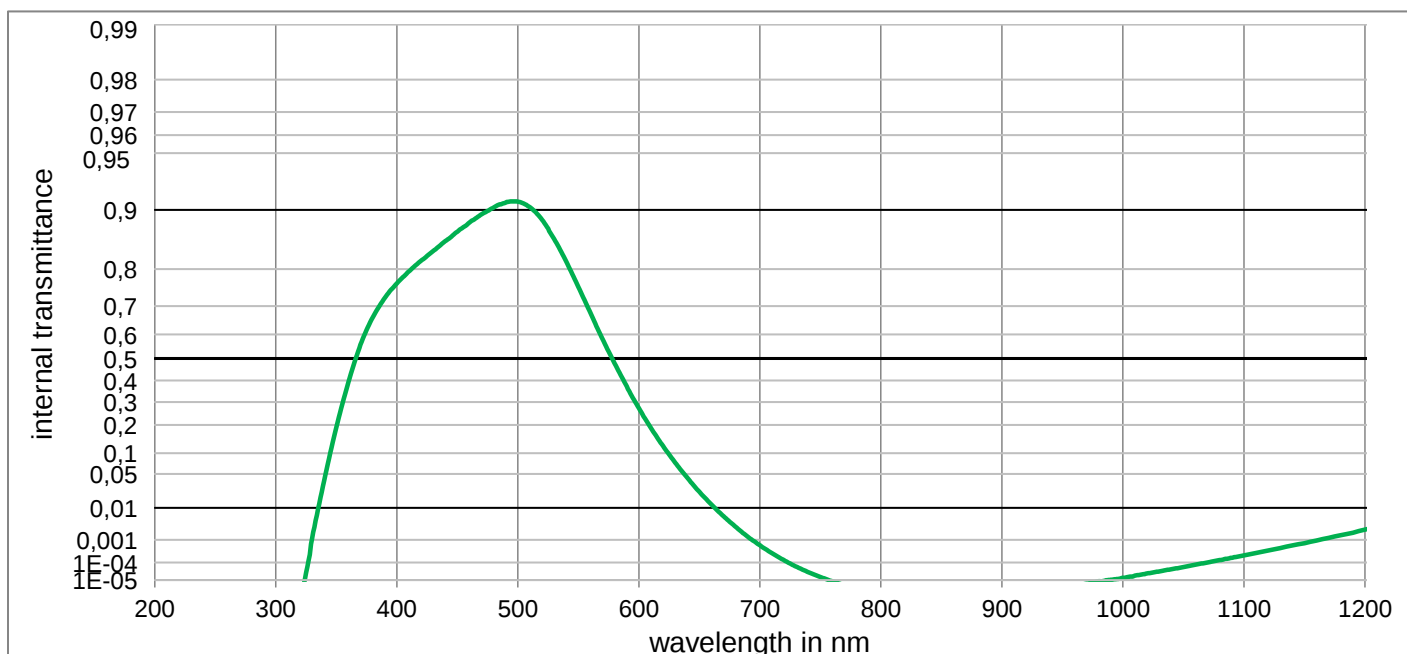

BG66

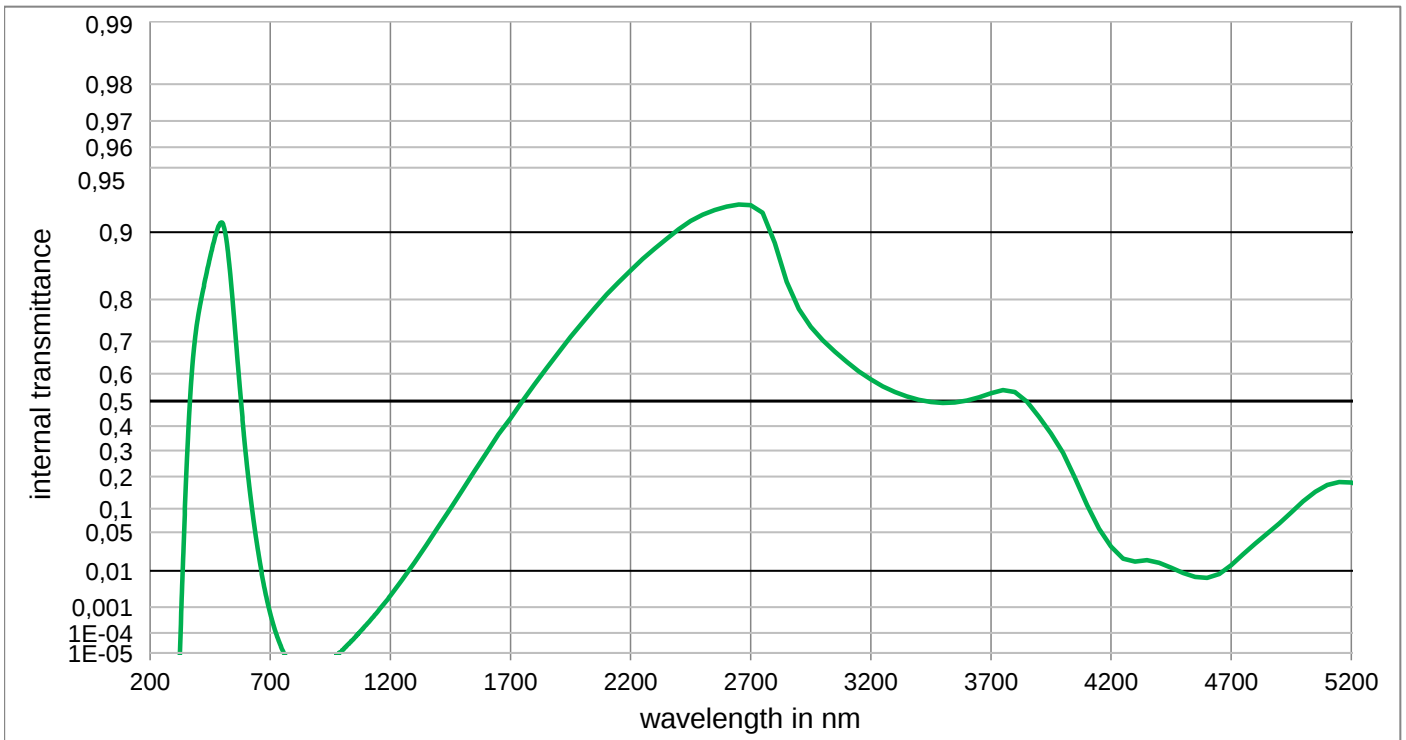Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,094E-01	800	< 1,000E-05	1100	2,196E-04	2200	8,507E-01	3700	5,296E-01
210	< 1,000E-05	510	9,031E-01	810	< 1,000E-05	1110	2,858E-04	2250	8,676E-01	3750	5,413E-01
220	< 1,000E-05	520	8,874E-01	820	< 1,000E-05	1120	3,654E-04	2300	8,810E-01	3800	5,348E-01
230	< 1,000E-05	530	8,590E-01	830	< 1,000E-05	1130	4,675E-04	2350	8,927E-01	3850	4,976E-01
240	< 1,000E-05	540	8,165E-01	840	< 1,000E-05	1140	5,998E-04	2400	9,031E-01	3900	4,373E-01
250	< 1,000E-05	550	7,560E-01	850	< 1,000E-05	1150	7,406E-04	2450	9,113E-01	3950	3,702E-01
260	< 1,000E-05	560	6,770E-01	860	< 1,000E-05	1160	9,407E-04	2500	9,170E-01	4000	2,907E-01
270	< 1,000E-05	570	5,822E-01	870	< 1,000E-05	1170	1,191E-03	2550	9,209E-01	4050	1,956E-01
280	< 1,000E-05	580	4,782E-01	880	< 1,000E-05	1180	1,473E-03	2600	9,239E-01	4100	1,091E-01
290	< 1,000E-05	590	3,726E-01	890	< 1,000E-05	1190	1,816E-03	2650	9,256E-01	4150	5,625E-02
300	< 1,000E-05	600	2,720E-01	900	< 1,000E-05	1200	2,301E-03	2700	9,250E-01	4200	2,989E-02
310	< 1,000E-05	610	1,883E-01	910	< 1,000E-05	1250	6,219E-03	2750	9,187E-01	4250	1,788E-02
320	< 1,000E-05	620	1,222E-01	920	< 1,000E-05	1300	1,501E-02	2800	8,882E-01	4300	1,572E-02
330	1,069E-03	630	7,459E-02	930	< 1,000E-05	1350	3,166E-02	2850	8,326E-01	4350	1,676E-02
340	3,817E-02	640	4,295E-02	940	< 1,000E-05	1400	5,986E-02	2900	7,804E-01	4400	1,484E-02
350	1,903E-01	650	2,347E-02	950	< 1,000E-05	1450	1,006E-01	2950	7,387E-01	4450	1,165E-02
360	3,932E-01	660	1,207E-02	960	< 1,000E-05	1500	1,543E-01	3000	7,035E-01	4500	8,858E-03
370	5,584E-01	670	5,939E-03	970	< 1,000E-05	1550	2,192E-01	3050	6,707E-01	4550	7,190E-03
380	6,617E-01	680	2,832E-03	980	< 1,000E-05	1600	2,908E-01	3100	6,389E-01	4600	6,838E-03
390	7,246E-01	690	1,320E-03	990	1,054E-05	1650	3,659E-01	3150	6,083E-01	4650	8,472E-03
400	7,656E-01	700	6,092E-04	1000	1,418E-05	1700	4,320E-01	3200	5,802E-01	4700	1,325E-02
410	7,944E-01	710	2,779E-04	1010	1,905E-05	1750	4,998E-01	3250	5,554E-01	4750	2,175E-02
420	8,179E-01	720	1,290E-04	1020	2,566E-05	1800	5,622E-01	3300	5,344E-01	4800	3,342E-02
430	8,373E-01	730	6,140E-05	1030	3,340E-05	1850	6,185E-01	3350	5,175E-01	4850	4,796E-02
440	8,553E-01	740	3,033E-05	1040	4,450E-05	1900	6,680E-01	3400	5,044E-01	4900	6,617E-02
450	8,702E-01	750	1,534E-05	1050	5,799E-05	1950	7,125E-01	3450	4,961E-01	4950	9,066E-02
460	8,835E-01	760	< 1,000E-05	1060	7,729E-05	2000	7,496E-01	3500	4,929E-01	5000	1,200E-01
470	8,947E-01	770	< 1,000E-05	1070	1,000E-04	2050	7,815E-01	3550	4,948E-01	5050	1,486E-01
480	9,029E-01	780	< 1,000E-05	1080	1,319E-04	2100	8,096E-01	3600	5,022E-01	5100	1,706E-01
490	9,085E-01	790	< 1,000E-05	1090	1,712E-04	2150	8,319E-01	3650	5,144E-01	5150	1,811E-01

Optical properties	
Reflection factor	
P _d = 0,913	
Spectral values guaranteed	
τ _i (405 nm)	≥ 0,71
τ _i (514 nm)	≥ 0,85
τ _i (633 nm)	≥ 0,04
τ _i (694 nm)	≤ 0,0025
τ _i (1060 nm)	≤ 0,0004
Refractive indices	
n _F (486 nm)	= 1,548
n _e (546 nm)	= 1,544
n _d (587,6 nm)	= 1,542
Sellmeier coefficients	
valid from 365 nm to 1550 nm	
B ₁	0,8063
B ₂	0,5354
B ₃	0,7669
C ₁	3,349E-03 μm ²
C ₂	1,7804E-02 μm ²
C ₃	131,310 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,87 g/cm ³	
Knoop hardness	
HK[0.1/20] = 385	

Thermal properties	
Transformation temperature	
T _g = 425 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _{-30°C/+70°C} = 11,5	
α _{20°C/300°C} = 13,3	


Chemical properties	
Chemical resistance	
FR class	
SR class = 52,3	
AR class	
Resistance against humidity	

Colorimetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,217	0,182	0,164
	y	0,313	0,298	0,288
	Y	56,0	40,9	31,9
	λ _d	489 nm	489 nm	488 nm
	P _e	0,362	0,502	0,576
Illuminant A	x	0,300	0,234	0,198
	y	0,440	0,438	0,430
	Y	47,0	31,7	23,5
	λ _d	499 nm	497 nm	496 nm
	P _e	0,338	0,495	0,581

Notes
Ionically colored glass
Bandpass filter / Shortpass filter
NIR cutoff filter
lambda_50%(d=0.21mm) = 634 nm
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

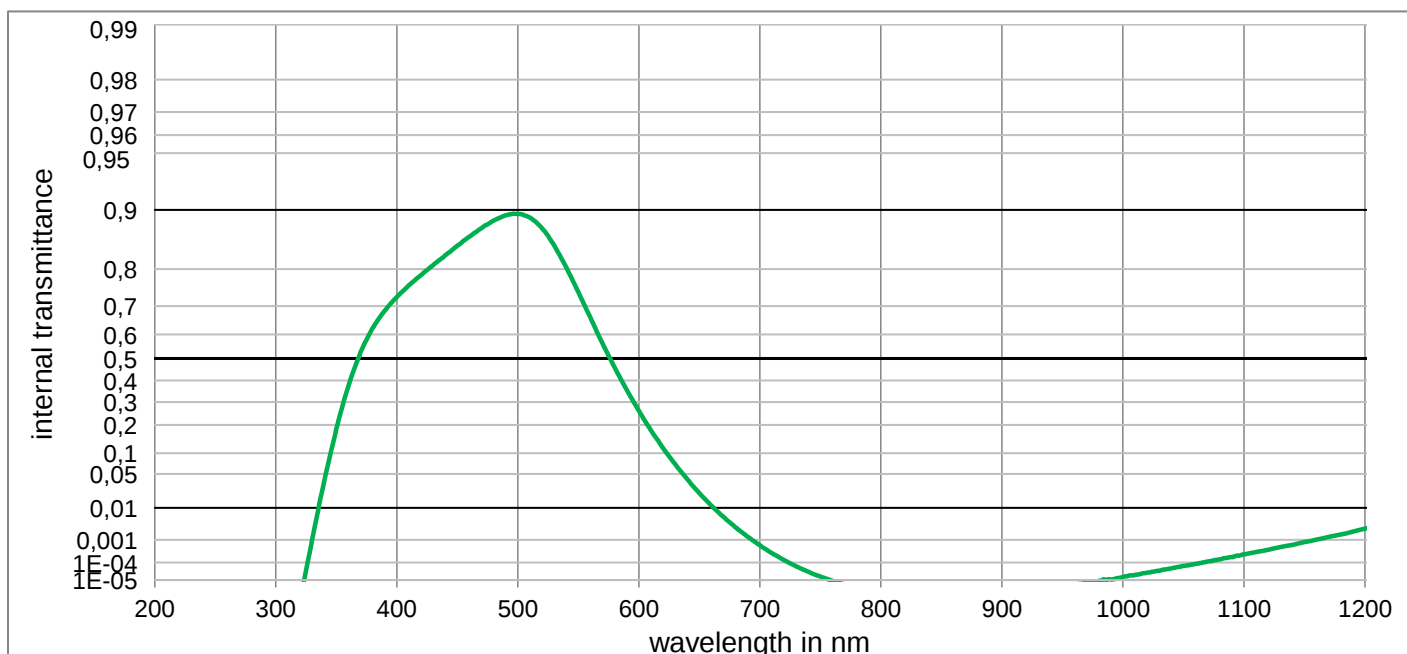


BG66HS

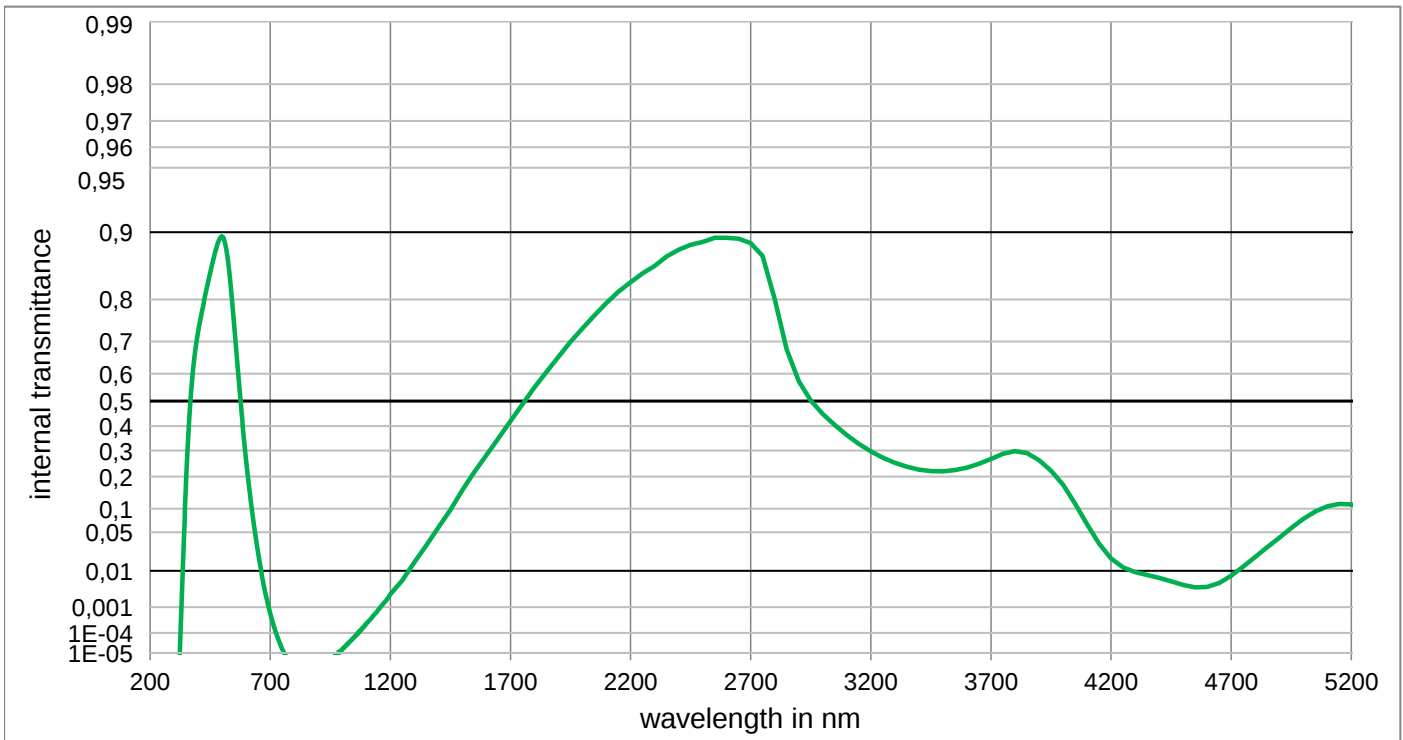Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	8,950E-01	800	< 1,000E-05	1100	2,451E-04	2200	8,318E-01	3700	2,668E-01
210	< 1,000E-05	510	8,901E-01	810	< 1,000E-05	1110	3,149E-04	2250	8,467E-01	3750	2,868E-01
220	< 1,000E-05	520	8,752E-01	820	< 1,000E-05	1120	3,900E-04	2300	8,577E-01	3800	2,981E-01
230	< 1,000E-05	530	8,479E-01	830	< 1,000E-05	1130	5,114E-04	2350	8,709E-01	3850	2,898E-01
240	< 1,000E-05	540	8,039E-01	840	< 1,000E-05	1140	6,304E-04	2400	8,798E-01	3900	2,617E-01
250	< 1,000E-05	550	7,414E-01	850	< 1,000E-05	1150	8,148E-04	2450	8,858E-01	3950	2,215E-01
260	< 1,000E-05	560	6,603E-01	860	< 1,000E-05	1160	1,017E-03	2500	8,891E-01	4000	1,714E-01
270	< 1,000E-05	570	5,644E-01	870	< 1,000E-05	1170	1,283E-03	2550	8,938E-01	4050	1,138E-01
280	< 1,000E-05	580	4,600E-01	880	< 1,000E-05	1180	1,561E-03	2600	8,939E-01	4100	6,435E-02
290	< 1,000E-05	590	3,557E-01	890	< 1,000E-05	1190	1,978E-03	2650	8,927E-01	4150	3,347E-02
300	< 1,000E-05	600	2,598E-01	900	< 1,000E-05	1200	2,514E-03	2700	8,877E-01	4200	1,817E-02
310	< 1,000E-05	610	1,786E-01	910	< 1,000E-05	1250	6,007E-03	2750	8,715E-01	4250	1,184E-02
320	< 1,000E-05	620	1,154E-01	920	< 1,000E-05	1300	1,525E-02	2800	8,004E-01	4300	9,431E-03
330	9,746E-04	630	7,064E-02	930	< 1,000E-05	1350	3,121E-02	2850	6,770E-01	4350	8,061E-03
340	3,686E-02	640	4,057E-02	940	< 1,000E-05	1400	5,831E-02	2900	5,736E-01	4400	6,827E-03
350	1,848E-01	650	2,192E-02	950	< 1,000E-05	1450	9,706E-02	2950	5,020E-01	4450	5,629E-03
360	3,750E-01	660	1,135E-02	960	< 1,000E-05	1500	1,543E-01	3000	4,490E-01	4500	4,562E-03
370	5,257E-01	670	5,713E-03	970	< 1,000E-05	1550	2,162E-01	3050	4,039E-01	4550	3,951E-03
380	6,234E-01	680	2,706E-03	980	< 1,000E-05	1600	2,816E-01	3100	3,635E-01	4600	4,022E-03
390	6,849E-01	690	1,310E-03	990	1,098E-05	1650	3,501E-01	3150	3,275E-01	4650	5,088E-03
400	7,276E-01	700	6,095E-04	1000	1,558E-05	1700	4,212E-01	3200	2,968E-01	4700	7,678E-03
410	7,600E-01	710	2,798E-04	1010	2,078E-05	1750	4,883E-01	3250	2,714E-01	4750	1,229E-02
420	7,860E-01	720	1,318E-04	1020	2,785E-05	1800	5,511E-01	3300	2,513E-01	4800	1,932E-02
430	8,087E-01	730	6,345E-05	1030	3,659E-05	1850	6,065E-01	3350	2,363E-01	4850	2,904E-02
440	8,292E-01	740	3,181E-05	1040	4,852E-05	1900	6,553E-01	3400	2,259E-01	4900	4,150E-02
450	8,471E-01	750	1,671E-05	1050	6,733E-05	1950	6,989E-01	3450	2,202E-01	4950	5,726E-02
460	8,626E-01	760	< 1,000E-05	1060	8,545E-05	2000	7,349E-01	3500	2,192E-01	5000	7,547E-02
470	8,758E-01	770	< 1,000E-05	1070	1,127E-04	2050	7,661E-01	3550	2,233E-01	5050	9,314E-02
480	8,864E-01	780	< 1,000E-05	1080	1,454E-04	2100	7,934E-01	3600	2,327E-01	5100	1,062E-01
490	8,933E-01	790	< 1,000E-05	1090	1,854E-04	2150	8,150E-01	3650	2,474E-01	5150	1,124E-01

Optical properties		Mechanical properties		Colormetric properties				
Reflection factor		Reference thickness		1 mm		2 mm	3 mm	
P _d = 0,913		d = 1,00 mm		Illuminant D65	x	0,209	0,176	0,159
Spectral values guaranteed		Density			y	0,321	0,317	0,318
τ _i (450 nm) ≥ 0,7		ρ = 2,85 g/cm³			Y	49,7	33,4	24,0
τ _i (500 nm) ≥ 0,8		Knoop hardness			λ _d	491 nm	490 nm	491 nm
τ _i (550 nm) ≥ 0,65		HK[0.1/20] = 364			P _e	0,383	0,508	0,569
τ _i (600 nm) ≤ 0,19		Thermal properties		Illuminant A	x	0,285	0,222	0,189
		Transformation temperature			y	0,450	0,456	0,457
		T _g = 390 °C			Y	40,9	25,4	17,5
		Thermal expansion in 10 ⁻⁶ /K			λ _d	499 nm	498 nm	498 nm
		α _{-30°C/+70°C} = 11,8			P _e	0,372	0,519	0,595
		α _{20°C/300°C} = 13,7						
Refractive indices		Notes						
n _F (486 nm) = 1,547								
n _e (546 nm) = 1,543								
n _d (587,6 nm) = 1,541								
Sellmeier coefficients		Ionically colored glass						
valid from 400 nm to 1550 nm		Bandpass filter / Shortpass filter						
B ₁ 0,7165		NIR cutoff filter						
B ₂ 0,6218		lambda_50%(d=0.145mm) @ 641 nm						
B ₃ 0,6042		ISO 23364:2021						
C ₁ 1,764E-09 μm²								
C ₂ 1,9422E-02 μm²								
C ₃ 100,000 μm²								
Internal quality		Disclaimer						
Bubble class 2		All data without tolerances are to be understood to be reference values.						

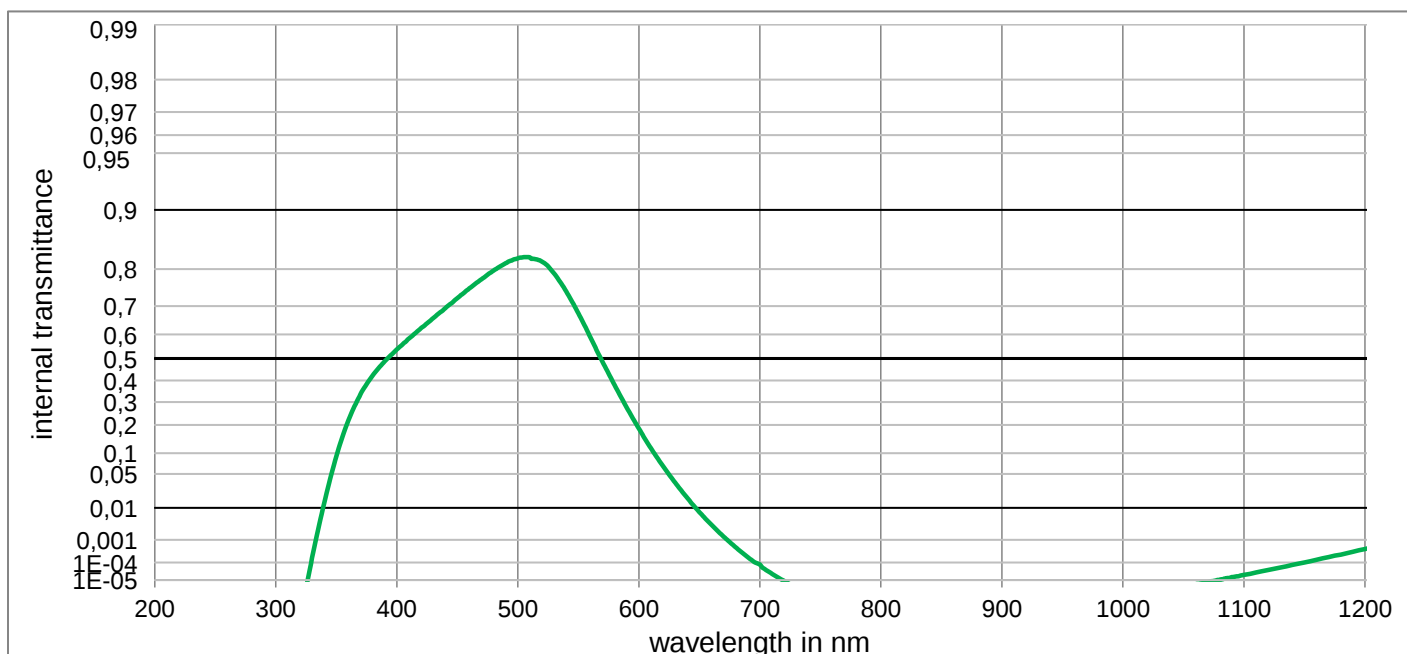

BG67

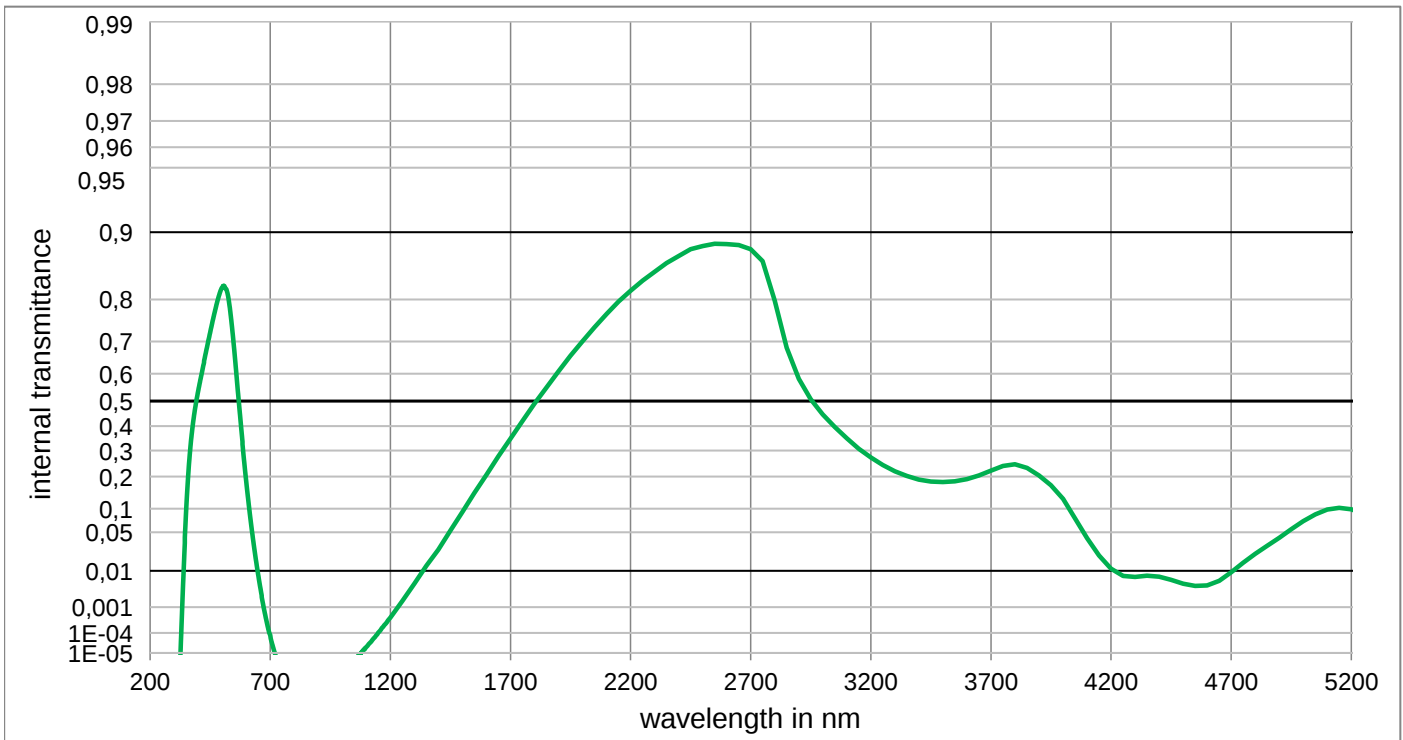Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	8,231E-01	800	< 1,000E-05	1100	2,071E-05	2200	8,164E-01	3700	2,218E-01
210	< 1,000E-05	510	8,251E-01	810	< 1,000E-05	1110	2,923E-05	2250	8,345E-01	3750	2,392E-01
220	< 1,000E-05	520	8,162E-01	820	< 1,000E-05	1120	3,952E-05	2300	8,488E-01	3800	2,455E-01
230	< 1,000E-05	530	7,899E-01	830	< 1,000E-05	1130	5,505E-05	2350	8,619E-01	3850	2,318E-01
240	< 1,000E-05	540	7,437E-01	840	< 1,000E-05	1140	7,511E-05	2400	8,717E-01	3900	2,036E-01
250	< 1,000E-05	550	6,764E-01	850	< 1,000E-05	1150	1,020E-04	2450	8,803E-01	3950	1,699E-01
260	< 1,000E-05	560	5,876E-01	860	< 1,000E-05	1160	1,362E-04	2500	8,844E-01	4000	1,268E-01
270	< 1,000E-05	570	4,859E-01	870	< 1,000E-05	1170	1,856E-04	2550	8,871E-01	4050	7,709E-02
280	< 1,000E-05	580	3,787E-01	880	< 1,000E-05	1180	2,399E-04	2600	8,867E-01	4100	4,066E-02
290	< 1,000E-05	590	2,747E-01	890	< 1,000E-05	1190	3,271E-04	2650	8,855E-01	4150	2,051E-02
300	< 1,000E-05	600	1,851E-01	900	< 1,000E-05	1200	4,258E-04	2700	8,805E-01	4200	1,109E-02
310	< 1,000E-05	610	1,152E-01	910	< 1,000E-05	1250	1,575E-03	2750	8,647E-01	4250	7,611E-03
320	< 1,000E-05	620	6,630E-02	920	< 1,000E-05	1300	4,935E-03	2800	7,974E-01	4300	7,207E-03
330	1,702E-04	630	3,513E-02	930	< 1,000E-05	1350	1,287E-02	2850	6,825E-01	4350	7,703E-03
340	1,300E-02	640	1,721E-02	940	< 1,000E-05	1400	2,625E-02	2900	5,817E-01	4400	7,300E-03
350	9,108E-02	650	7,798E-03	950	< 1,000E-05	1450	5,320E-02	2950	5,066E-01	4450	6,119E-03
360	2,195E-01	660	3,302E-03	960	< 1,000E-05	1500	9,161E-02	3000	4,476E-01	4500	4,921E-03
370	3,360E-01	670	1,321E-03	970	< 1,000E-05	1550	1,447E-01	3050	3,964E-01	4550	4,292E-03
380	4,226E-01	680	5,023E-04	980	< 1,000E-05	1600	2,069E-01	3100	3,497E-01	4600	4,391E-03
390	4,878E-01	690	1,842E-04	990	< 1,000E-05	1650	2,769E-01	3150	3,079E-01	4650	5,777E-03
400	5,392E-01	700	8,097E-05	1000	< 1,000E-05	1700	3,488E-01	3200	2,721E-01	4700	9,208E-03
410	5,833E-01	710	2,428E-05	1010	< 1,000E-05	1750	4,211E-01	3250	2,426E-01	4750	1,479E-02
420	6,234E-01	720	< 1,000E-05	1020	< 1,000E-05	1800	4,898E-01	3300	2,195E-01	4800	2,212E-02
430	6,594E-01	730	< 1,000E-05	1030	< 1,000E-05	1850	5,517E-01	3350	2,018E-01	4850	3,079E-02
440	6,935E-01	740	< 1,000E-05	1040	< 1,000E-05	1900	6,083E-01	3400	1,895E-01	4900	4,149E-02
450	7,239E-01	750	< 1,000E-05	1050	< 1,000E-05	1950	6,584E-01	3450	1,825E-01	4950	5,501E-02
460	7,523E-01	760	< 1,000E-05	1060	< 1,000E-05	2000	7,010E-01	3500	1,804E-01	5000	7,058E-02
470	7,760E-01	770	< 1,000E-05	1070	< 1,000E-05	2050	7,377E-01	3550	1,834E-01	5050	8,601E-02
480	7,970E-01	780	< 1,000E-05	1080	1,035E-05	2100	7,696E-01	3600	1,913E-01	5100	9,768E-02
490	8,128E-01	790	< 1,000E-05	1090	1,536E-05	2150	7,959E-01	3650	2,044E-01	5150	1,023E-01

Optical properties	
Reflection factor	
P_d	= 0,913
Spectral values guaranteed	
τ_i (450 nm)	≥ 0,75
τ_i (500 nm)	≥ 0,83
τ_i (550 nm)	≥ 0,65
τ_i (600 nm)	≤ 0,19
Refractive indices	
n_F (486 nm)	= 1,547
n_e (546 nm)	= 1,543
n_d (587,6 nm)	= 1,541
Sellmeier coefficients	
valid from 400 nm to 1550 nm	
B_1	0,7165
B_2	0,6218
B_3	0,6042
C_1	1,764E-09 μm^2
C_2	1,9422E-02 μm^2
C_3	100,000 μm^2
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d	= 1,00 mm
Density	
ρ	= 2,85 g/cm ³
Knoop hardness	
HK[0.1/20]	= 364

Thermal properties	
Transformation temperature	
T_g	= 390 °C
Thermal expansion in 10 ⁻⁶ /K	
α (-30°C/+70°C)	= 11,8
α (20°C/300°C)	= 13,7


Chemical properties	
Chemical resistance	
FR class	= 1
SR class	= 52.3
AR class	= 3.3
Resistance against humidity	

Colorimetric properties		1 mm	2 mm	3 mm
Illuminant D65	x	0,203	0,170	0,154
	y	0,312	0,300	0,294
	Y	49,0	33,2	24,1
	λ_d	490 nm	489 nm	489 nm
	P_e	0,413	0,543	0,607
Illuminant A	x	0,274	0,211	0,179
	y	0,445	0,441	0,434
	Y	39,9	24,9	17,2
	λ_d	499 nm	497 nm	496 nm
	P_e	0,398	0,549	0,625

Notes	
Ionically colored glass	
Bandpass filter / Shortpass filter	
NIR cutoff filter	
$\lambda_{50\%}(d=0.11\text{mm}) @ 634 \text{ nm}$	
ISO 23364:2021	
Disclaimer	
All data without tolerances are to be understood to be reference values.	

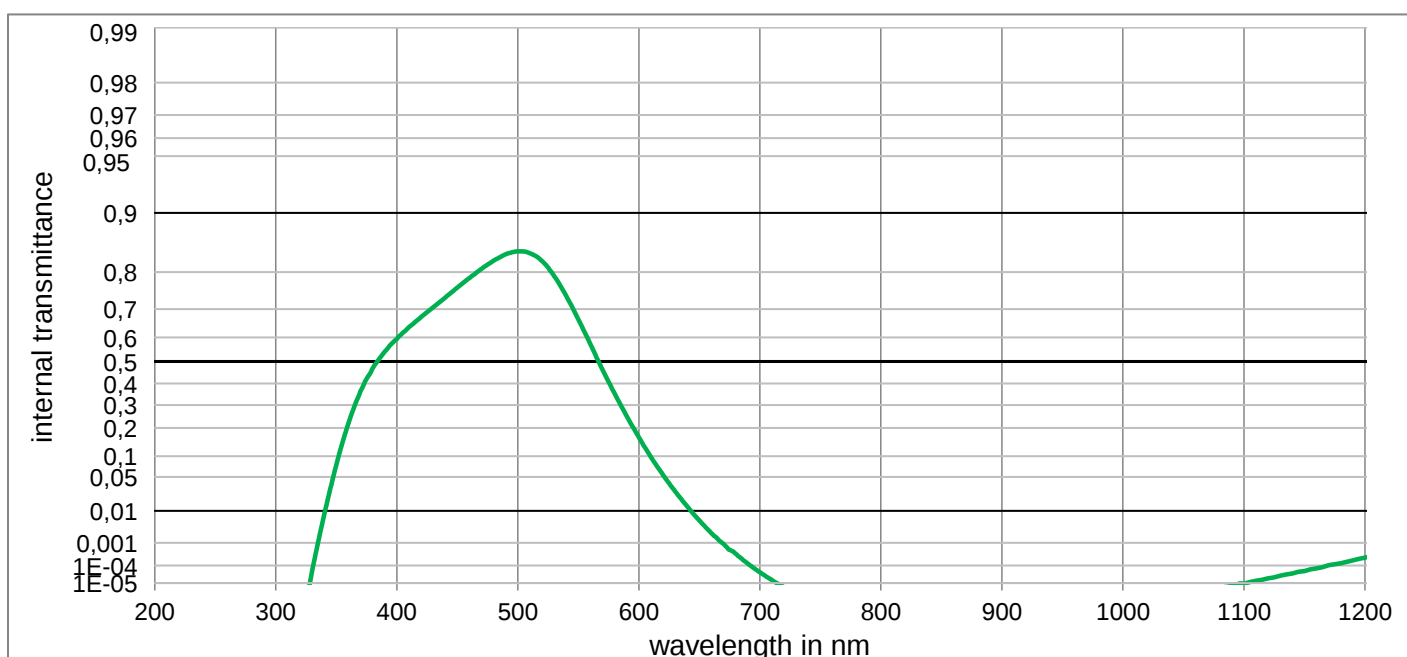

BG67HT

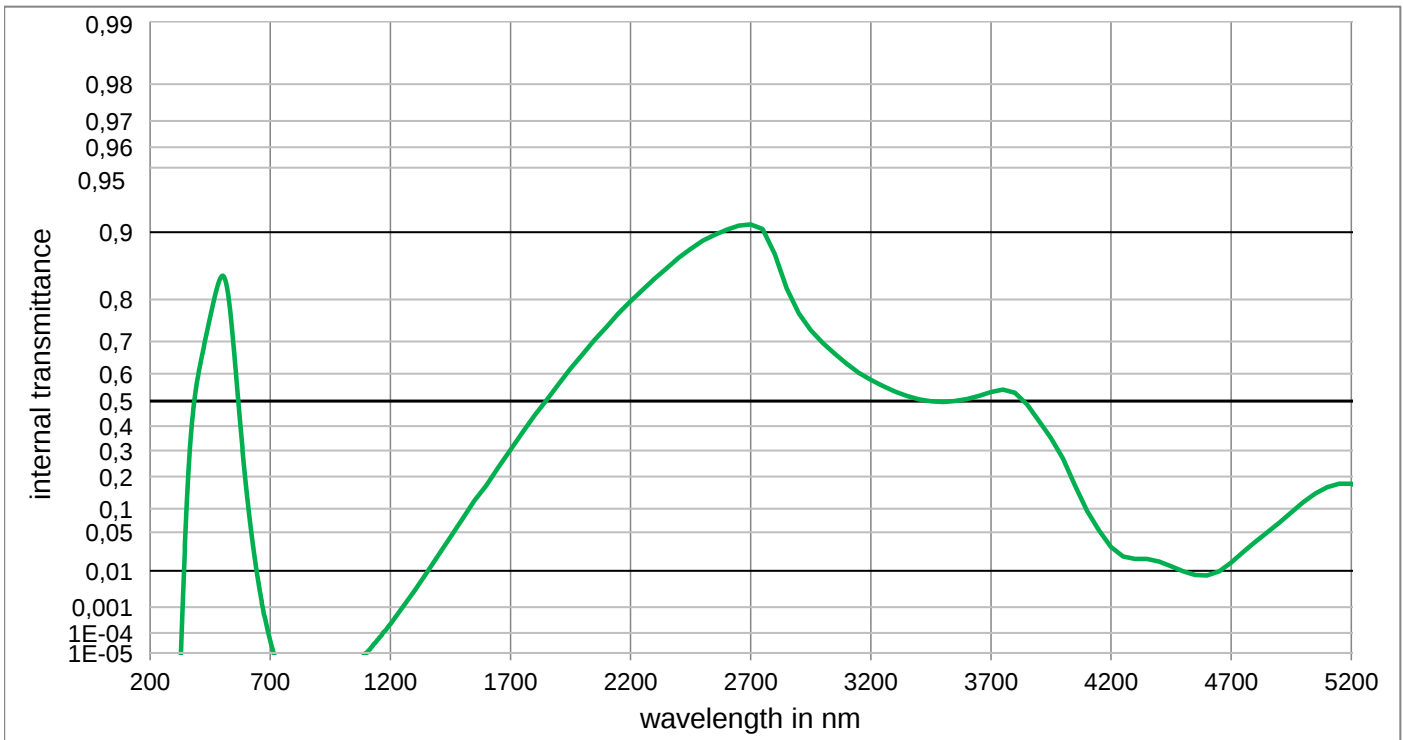Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	8,425E-01	800	< 1,000E-05	1100	< 1,000E-05	2200	7,964E-01	3700	5,342E-01
210	< 1,000E-05	510	8,389E-01	810	< 1,000E-05	1110	1,392E-05	2250	8,185E-01	3750	5,437E-01
220	< 1,000E-05	520	8,236E-01	820	< 1,000E-05	1120	1,999E-05	2300	8,379E-01	3800	5,316E-01
230	< 1,000E-05	530	7,914E-01	830	< 1,000E-05	1130	2,837E-05	2350	8,541E-01	3850	4,866E-01
240	< 1,000E-05	540	7,393E-01	840	< 1,000E-05	1140	3,755E-05	2400	8,694E-01	3900	4,207E-01
250	< 1,000E-05	550	6,655E-01	850	< 1,000E-05	1150	5,176E-05	2450	8,808E-01	3950	3,509E-01
260	< 1,000E-05	560	5,721E-01	860	< 1,000E-05	1160	7,067E-05	2500	8,905E-01	4000	2,676E-01
270	< 1,000E-05	570	4,641E-01	870	< 1,000E-05	1170	1,026E-04	2550	8,973E-01	4050	1,689E-01
280	< 1,000E-05	580	3,534E-01	880	< 1,000E-05	1180	1,293E-04	2600	9,027E-01	4100	9,411E-02
290	< 1,000E-05	590	2,493E-01	890	< 1,000E-05	1190	1,808E-04	2650	9,067E-01	4150	5,303E-02
300	< 1,000E-05	600	1,627E-01	900	< 1,000E-05	1200	2,372E-04	2700	9,079E-01	4200	2,924E-02
310	< 1,000E-05	610	9,760E-02	910	< 1,000E-05	1250	9,582E-04	2750	9,034E-01	4250	1,970E-02
320	< 1,000E-05	620	5,393E-02	920	< 1,000E-05	1300	3,153E-03	2800	8,741E-01	4300	1,772E-02
330	4,871E-05	630	2,735E-02	930	< 1,000E-05	1350	8,739E-03	2850	8,210E-01	4350	1,772E-02
340	7,922E-03	640	1,274E-02	940	< 1,000E-05	1400	2,078E-02	2900	7,707E-01	4400	1,571E-02
350	7,618E-02	650	5,556E-03	950	< 1,000E-05	1450	4,231E-02	2950	7,303E-01	4450	1,258E-02
360	2,203E-01	660	2,205E-03	960	< 1,000E-05	1500	7,563E-02	3000	6,961E-01	4500	9,730E-03
370	3,634E-01	670	8,986E-04	970	< 1,000E-05	1550	1,217E-01	3050	6,643E-01	4550	8,055E-03
380	4,698E-01	680	3,566E-04	980	< 1,000E-05	1600	1,704E-01	3100	6,331E-01	4600	7,823E-03
390	5,425E-01	690	1,258E-04	990	< 1,000E-05	1650	2,347E-01	3150	6,032E-01	4650	9,759E-03
400	5,941E-01	700	4,383E-05	1000	< 1,000E-05	1700	3,036E-01	3200	5,784E-01	4700	1,497E-02
410	6,380E-01	710	1,529E-05	1010	< 1,000E-05	1750	3,737E-01	3250	5,564E-01	4750	2,385E-02
420	6,736E-01	720	< 1,000E-05	1020	< 1,000E-05	1800	4,423E-01	3300	5,361E-01	4800	3,556E-02
430	7,056E-01	730	< 1,000E-05	1030	< 1,000E-05	1850	5,043E-01	3350	5,195E-01	4850	4,991E-02
440	7,350E-01	740	< 1,000E-05	1040	< 1,000E-05	1900	5,627E-01	3400	5,065E-01	4900	6,777E-02
450	7,620E-01	750	< 1,000E-05	1050	< 1,000E-05	1950	6,167E-01	3450	4,991E-01	4950	9,057E-02
460	7,861E-01	760	< 1,000E-05	1060	< 1,000E-05	2000	6,627E-01	3500	4,961E-01	5000	1,170E-01
470	8,074E-01	770	< 1,000E-05	1070	< 1,000E-05	2050	7,040E-01	3550	4,998E-01	5050	1,430E-01
480	8,244E-01	780	< 1,000E-05	1080	< 1,000E-05	2100	7,389E-01	3600	5,074E-01	5100	1,638E-01
490	8,370E-01	790	< 1,000E-05	1090	< 1,000E-05	2150	7,711E-01	3650	5,196E-01	5150	1,750E-01


S8022

Optical properties	
Reflection factor	
P _d = 0,910	
Values guaranteed	
The color of glass is within a circle of the CIE Yu'v'UCS(1976) defined by $(u' - 0,088)^2 + (v' - 0,543)^2 = (0,037)^2$ for any black body radiator 1500K to 3200K	
Black body radiator	Photopic Transmittance [%]
2100 K	13,5 ±1.5
1500 K	9 ±1.5
Refractive indices	
n _e (546 nm)	= 1,56
n _d (587,6 nm)	= 1,555 ± 0,005
Sellmeier coefficients	
valid from 440 nm to 1550 nm	
B ₁	1,0783
B ₂	0,3094
B ₃	36,9992
C ₁	5,301E-09 μm ²
C ₂	3,8950E-02 μm ²
C ₃	5395,591 μm ²
Internal quality	
Bubble class	1


Mechanical properties	
Reference thickness	
d	= 2 mm
Density	
ρ	= 2,77 g/cm ³
Knoop hardness	
HK[0.1/20]	
Thermal properties	
Transformation temperature	
T _g	= 453 °C
Thermal expansion in 10 ⁻⁶ /K	
α (-30°C/+70°C)	= 7,8
α (20°C/300°C)	= 8,9
α (20°C/200°C)	
Chemical properties	
Chemical resistance	
FR class	= 0
SR class	= 4
AR class	= 3
Resistance against humidity	
Delicate glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colormetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,196	0,169	0,154
	y	0,374	0,432	0,492
	Y	37,3	20,7	12,4
	λ_d	496,0	500,0	505,0
	P _e	0,400	0,470	0,510
Illuminant A	x	0,253	0,203	0,178
	y	0,498	0,549	0,593
	Y	29,6	15,5	9,0
	λ_d	503,0	505,0	508,0
	P _e	0,440	0,550	0,610

Notes
Ionically colored glass
Bandpass filter
NIR cutoff filter
NVIS-Green A - 2 mm bandpass filter according to MIL-STD-3009
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

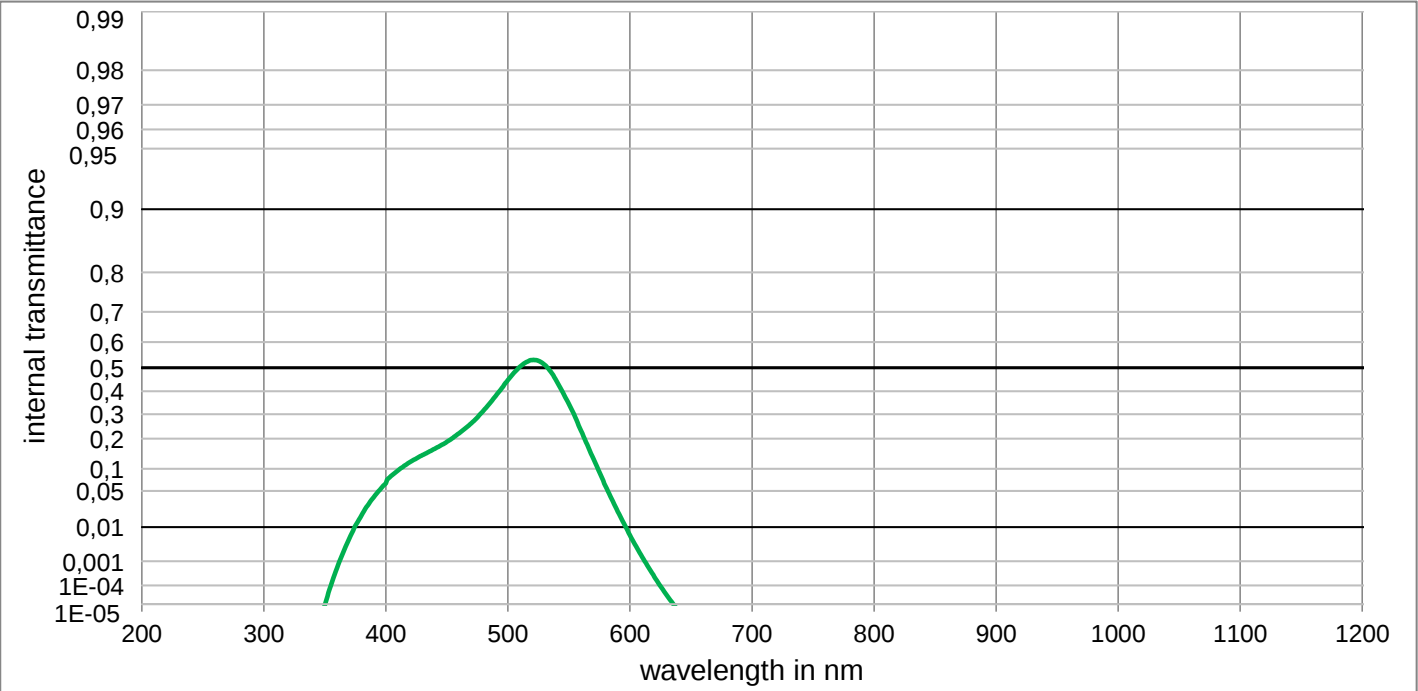


S8022

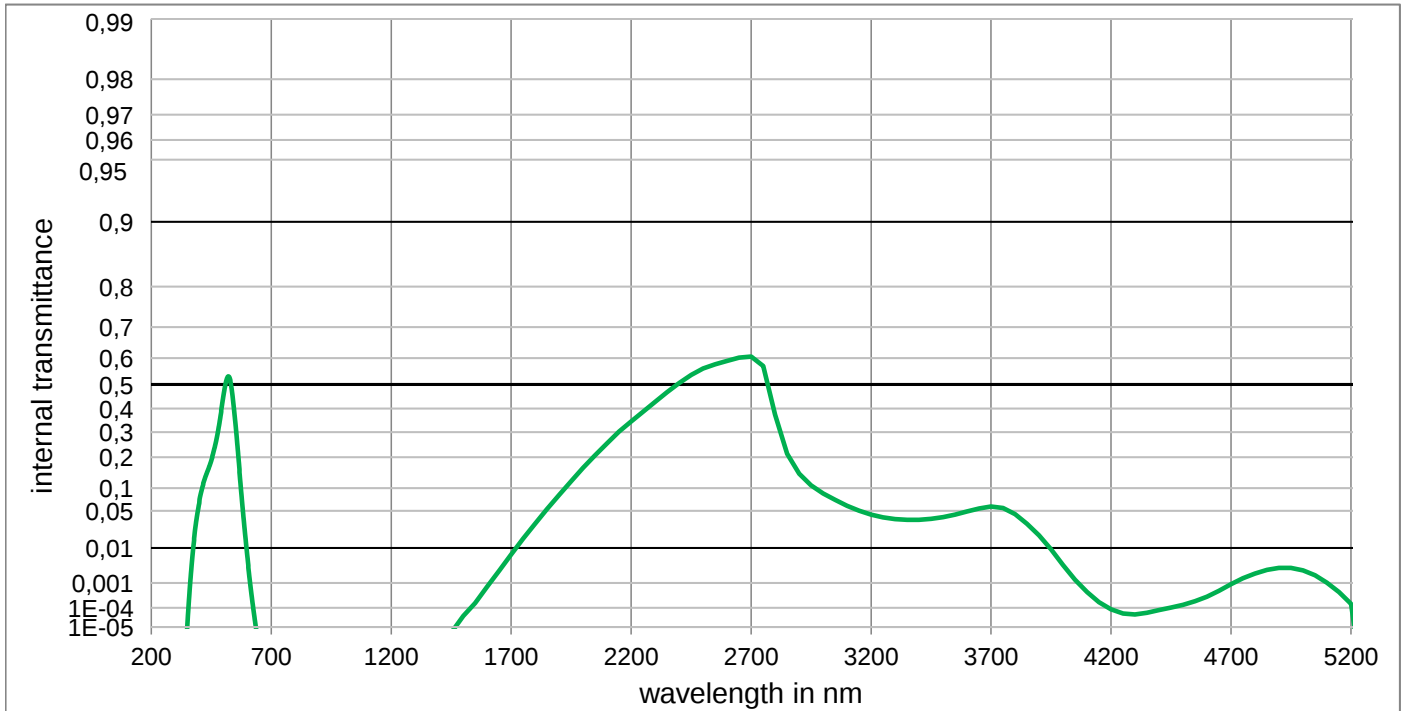Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	4,483E-01	800	< 1,000E-05	1100	< 1,000E-05	2200	3,453E-01	3700	5,800E-02
210	< 1,0E-05	510	5,049E-01	810	< 1,000E-05	1110	< 1,000E-05	2250	3,871E-01	3750	5,505E-02
220	< 1,0E-05	520	5,313E-01	820	< 1,000E-05	1120	< 1,000E-05	2300	4,287E-01	3800	4,448E-02
230	< 1,0E-05	530	5,123E-01	830	< 1,000E-05	1130	< 1,000E-05	2350	4,691E-01	3850	3,093E-02
240	< 1,0E-05	540	4,431E-01	840	< 1,000E-05	1140	< 1,000E-05	2400	5,060E-01	3900	1,879E-02
250	< 1,0E-05	550	3,430E-01	850	< 1,000E-05	1150	< 1,000E-05	2450	5,380E-01	3950	9,286E-03
260	< 1,0E-05	560	2,302E-01	860	< 1,000E-05	1160	< 1,000E-05	2500	5,617E-01	4000	3,658E-03
270	< 1,0E-05	570	1,295E-01	870	< 1,000E-05	1170	< 1,000E-05	2550	5,775E-01	4050	1,282E-03
280	< 1,0E-05	580	5,934E-02	880	< 1,000E-05	1180	< 1,000E-05	2600	5,903E-01	4100	4,598E-04
290	< 1,0E-05	590	2,168E-02	890	< 1,000E-05	1190	< 1,000E-05	2650	6,017E-01	4150	1,798E-04
300	< 1,0E-05	600	6,305E-03	900	< 1,000E-05	1200	< 1,000E-05	2700	6,055E-01	4200	8,400E-05
310	< 1,0E-05	610	1,407E-03	910	< 1,000E-05	1250	< 1,000E-05	2750	5,709E-01	4250	5,361E-05
320	< 1,000E-05	620	2,455E-04	920	< 1,000E-05	1300	< 1,000E-05	2800	3,741E-01	4300	4,785E-05
330	< 1,000E-05	630	3,322E-05	930	< 1,000E-05	1350	< 1,000E-05	2850	2,130E-01	4350	5,774E-05
340	< 1,000E-05	640	< 1,000E-05	940	< 1,000E-05	1400	< 1,000E-05	2900	1,425E-01	4400	7,778E-05
350	< 1,000E-05	650	< 1,000E-05	950	< 1,000E-05	1450	< 1,000E-05	2950	1,074E-01	4450	1,016E-04
360	5,717E-04	660	< 1,000E-05	960	< 1,000E-05	1500	3,995E-05	3000	8,629E-02	4500	1,365E-04
370	5,212E-03	670	< 1,000E-05	970	< 1,000E-05	1550	1,610E-04	3050	7,123E-02	4550	1,958E-04
380	1,815E-02	680	< 1,000E-05	980	< 1,000E-05	1600	7,352E-04	3100	5,950E-02	4600	3,023E-04
390	3,992E-02	690	< 1,000E-05	990	< 1,000E-05	1650	2,520E-03	3150	5,038E-02	4650	5,195E-04
400	6,468E-02	700	< 1,000E-05	1000	< 1,000E-05	1700	6,915E-03	3200	4,380E-02	4700	9,015E-04
410	9,600E-02	710	< 1,000E-05	1010	< 1,000E-05	1750	1,600E-02	3250	3,942E-02	4750	1,433E-03
420	1,198E-01	720	< 1,000E-05	1020	< 1,000E-05	1800	3,121E-02	3300	3,689E-02	4800	2,044E-03
430	1,414E-01	730	< 1,000E-05	1030	< 1,000E-05	1850	5,323E-02	3350	3,594E-02	4850	2,635E-03
440	1,629E-01	740	< 1,000E-05	1040	< 1,000E-05	1900	8,298E-02	3400	3,609E-02	4900	3,028E-03
450	1,883E-01	750	< 1,000E-05	1050	< 1,000E-05	1950	1,197E-01	3450	3,746E-02	4950	3,019E-03
460	2,211E-01	760	< 1,000E-05	1060	< 1,000E-05	2000	1,616E-01	3500	4,005E-02	5000	2,545E-03
470	2,620E-01	770	< 1,000E-05	1070	< 1,000E-05	2050	2,074E-01	3550	4,379E-02	5050	1,799E-03
480	3,155E-01	780	< 1,000E-05	1080	< 1,000E-05	2100	2,550E-01	3600	4,878E-02	5100	1,030E-03
490	3,799E-01	790	< 1,000E-05	1090	< 1,000E-05	2150	3,025E-01	3650	5,436E-02	5150	4,597E-04

Chromaticity dependence on Incandescent Color Temperature

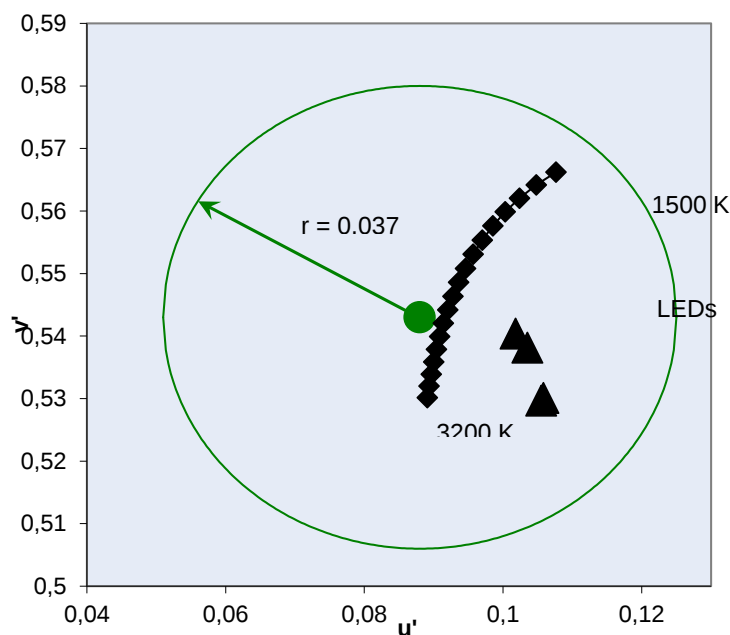

Chromaticity and NVIS Radiance at reference thickness 2 mm

Planck [K]	u'	v'	x	y	Y	NR_A
1500	0,108	0,566	0,270	0,631	9,5	6,1E-11
1600	0,105	0,564	0,262	0,627	10,4	5,8E-11
1700	0,102	0,562	0,254	0,621	11,2	5,6E-11
1800	0,100	0,560	0,248	0,615	11,9	5,4E-11
1900	0,099	0,558	0,242	0,608	12,6	5,2E-11
2000	0,097	0,555	0,236	0,601	13,3	5,1E-11
2100	0,096	0,553	0,231	0,594	13,9	5,0E-11
2200	0,095	0,551	0,227	0,587	14,5	4,9E-11
2300	0,094	0,549	0,223	0,580	15,0	4,8E-11
2400	0,093	0,546	0,219	0,573	15,5	4,7E-11
2500	0,092	0,544	0,215	0,566	15,9	4,7E-11
2600	0,091	0,542	0,212	0,559	16,3	4,6E-11
2700	0,091	0,540	0,209	0,553	16,7	4,6E-11
2800	0,090	0,538	0,207	0,547	17,1	4,5E-11
2900	0,090	0,536	0,204	0,540	17,4	4,5E-11
3000	0,090	0,534	0,202	0,535	17,8	4,4E-11
3100	0,089	0,532	0,200	0,529	18,1	4,4E-11
3200	0,089	0,530	0,198	0,523	18,4	4,4E-11

NVIS Green A

NVIS Green A Chromaticity coordinates
(as defined by MIL-STD-3009) $u' = 0.088$ $v' = 0.543$ with radius of tolerance $r = 0.037$


LED	u'	v'	x	y	Y	NR_A
LUXEON rebel A2-RM-G	0,102	0,540	0,231	0,545	21,1	4,2E-11
LUXEON rebel T2-SO-L	0,106	0,530	0,229	0,511	20,9	4,2E-11
LUXEON rebel B5-R0-G	0,106	0,530	0,228	0,510	20,7	4,3E-11
LUXEON rebel Q1-RM-K	0,104	0,538	0,232	0,537	20,7	4,3E-11

other sources of illumination


A service for calculating chromaticity or NVIS radiance can be provided

S8023

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		Illuminant D65		1 mm	2 mm	3 mm
P _d = 0,913		d = 3 mm			x	0,206	0,176	0,160
Values guaranteed		Density			y	0,328	0,334	0,346
The color of the glass is within a circle of the CIE Y u' v' UCS(1976) defined by (u' - 0,088) ² + (v' - 0,543) ² = (0,037) ² for any black body radiator 1500K to 3200K		ρ = 2,75 g/cm ³			Y	50,5	35,3	26,4
		Knoop hardness			λ _d	491,5	492,0	492,9
		HK[0.1/20]		P _e	0,388	0,496	0,544	
Black body radiator		Photopic Transmittance [%]		Illuminant A	x	0,277	0,218	0,189
2100 K	15 ±1.5				y	0,459	0,474	0,486
1500 K	10 ±1.5				Y	41,3	26,9	19,3
					λ _d	500,1	499,8	500,1
					P _e	0,388	0,522	0,588
Refractive indices				Notes				
n _e (546 nm) = 1,54				Ionically colored glass Bandpass filter NIR cutoff filter NVIS-Green A - 3 mm bandpass filter according to MIL-STD-3009 ISO 23364:2021				
n _d (587,6 nm) = 1,541 ± 0,005								
Sellmeier coefficients				Disclaimer				
valid from 440 nm to 1550 nm				All data without tolerances are to be understood to be reference values.				
B ₁	0,0304	Chemical properties						
		Chemical resistance						
B ₂	1,3342	FR class = 0						
B ₃	381,6503	SR class = 4						
C ₁	1,246E-01 μm ²	AR class = 3						
		Resistance against humidity						
C ₃	32646,623 μm ²	Delicate glass						
Internal quality		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5						
Bubble class	1							

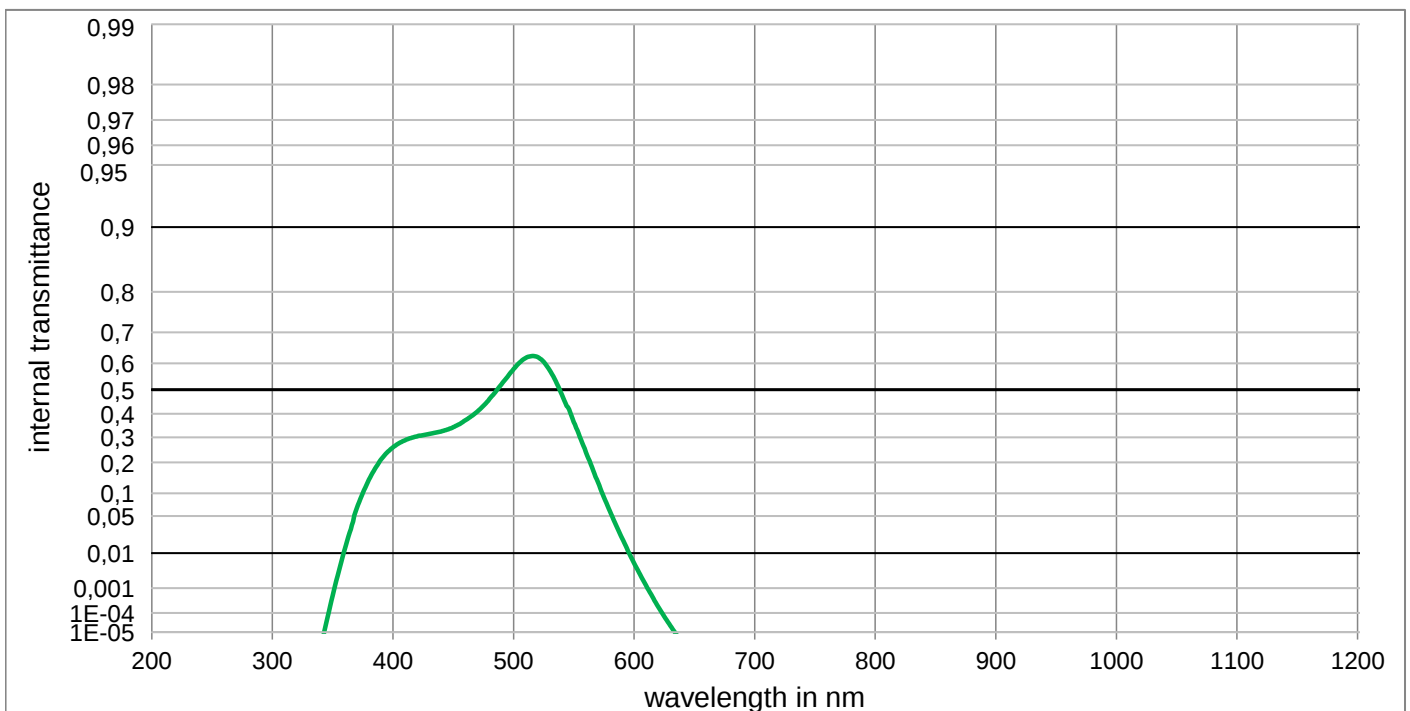


S8023

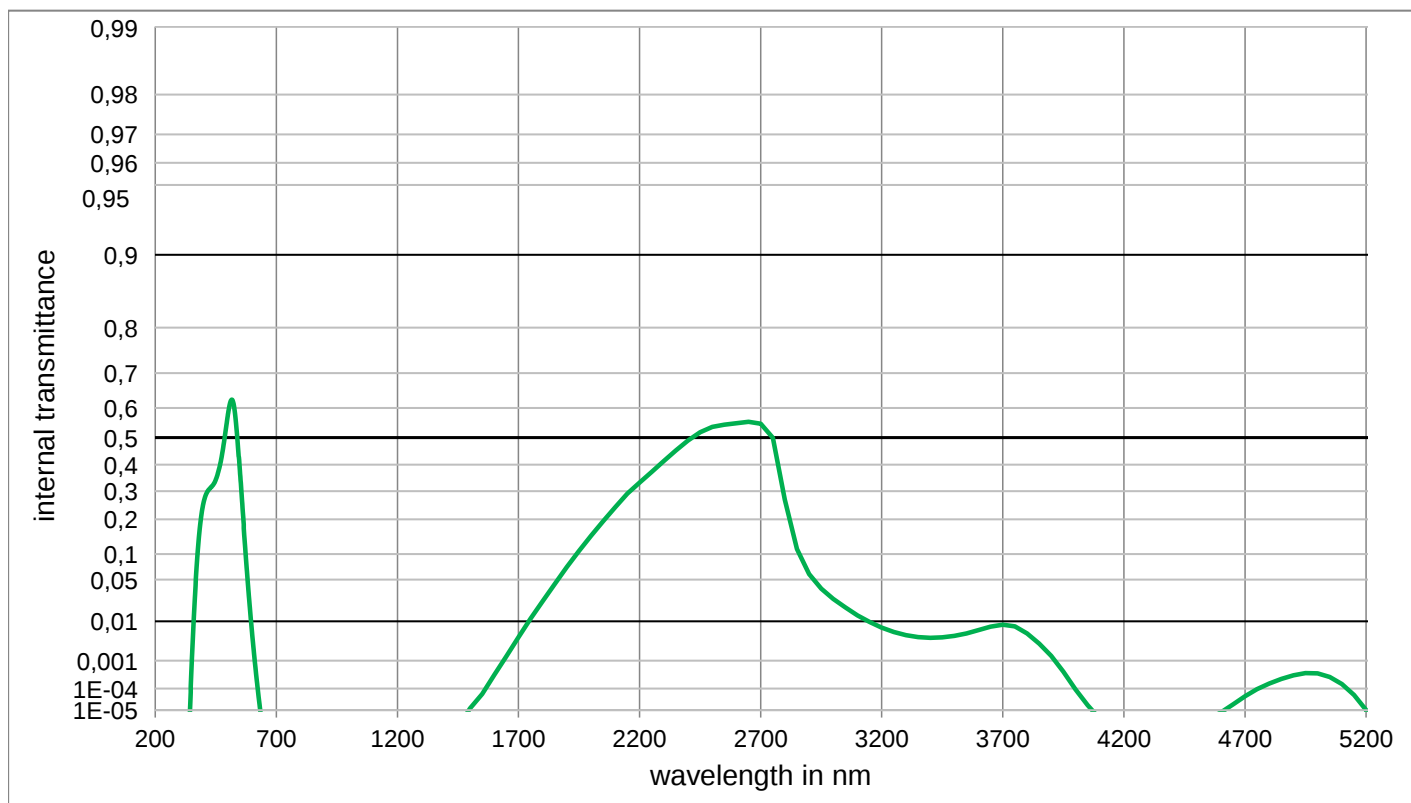Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	5,796E-01	800	< 1,000E-05	1100	< 1,000E-05	2200	3,323E-01	3700	8,548E-03
210	< 1,0E-05	510	6,186E-01	810	< 1,000E-05	1110	< 1,000E-05	2250	3,728E-01	3750	7,773E-03
220	< 1,0E-05	520	6,216E-01	820	< 1,000E-05	1120	< 1,000E-05	2300	4,136E-01	3800	5,431E-03
230	< 1,0E-05	530	5,754E-01	830	< 1,000E-05	1130	< 1,000E-05	2350	4,531E-01	3850	3,027E-03
240	< 1,0E-05	540	4,804E-01	840	< 1,000E-05	1140	< 1,000E-05	2400	4,891E-01	3900	1,397E-03
250	< 1,0E-05	550	3,646E-01	850	< 1,000E-05	1150	< 1,000E-05	2450	5,187E-01	3950	4,345E-04
260	< 1,0E-05	560	2,394E-01	860	< 1,000E-05	1160	< 1,000E-05	2500	5,374E-01	4000	9,178E-05
270	< 1,0E-05	570	1,317E-01	870	< 1,000E-05	1170	< 1,000E-05	2550	5,451E-01	4050	1,790E-05
280	< 1,0E-05	580	5,863E-02	880	< 1,000E-05	1180	< 1,000E-05	2600	5,502E-01	4100	< 1,000E-05
290	< 1,0E-05	590	2,067E-02	890	< 1,000E-05	1190	< 1,000E-05	2650	5,547E-01	4150	< 1,000E-05
300	< 1,0E-05	600	5,710E-03	900	< 1,000E-05	1200	< 1,000E-05	2700	5,481E-01	4200	< 1,000E-05
310	< 1,0E-05	610	1,196E-03	910	< 1,000E-05	1250	< 1,000E-05	2750	4,994E-01	4250	< 1,000E-05
320	< 1,000E-05	620	1,920E-04	920	< 1,000E-05	1300	< 1,000E-05	2800	2,689E-01	4300	< 1,000E-05
330	< 1,000E-05	630	2,354E-05	930	< 1,000E-05	1350	< 1,000E-05	2850	1,121E-01	4350	< 1,000E-05
340	< 1,000E-05	640	< 1,000E-05	940	< 1,000E-05	1400	< 1,000E-05	2900	5,898E-02	4400	< 1,000E-05
350	5,305E-04	650	< 1,000E-05	950	< 1,000E-05	1450	< 1,000E-05	2950	3,724E-02	4450	< 1,000E-05
360	1,243E-02	660	< 1,000E-05	960	< 1,000E-05	1500	1,239E-05	3000	2,578E-02	4500	< 1,000E-05
370	6,439E-02	670	< 1,000E-05	970	< 1,000E-05	1550	5,810E-05	3050	1,840E-02	4550	< 1,000E-05
380	1,397E-01	680	< 1,000E-05	980	< 1,000E-05	1600	3,349E-04	3100	1,314E-02	4600	< 1,000E-05
390	2,098E-01	690	< 1,000E-05	990	< 1,000E-05	1650	1,381E-03	3150	9,636E-03	4650	1,919E-05
400	2,590E-01	700	< 1,000E-05	1000	< 1,000E-05	1700	4,363E-03	3200	7,306E-03	4700	4,704E-05
410	2,881E-01	710	< 1,000E-05	1010	< 1,000E-05	1750	1,129E-02	3250	5,847E-03	4750	9,473E-05
420	3,042E-01	720	< 1,000E-05	1020	< 1,000E-05	1800	2,387E-02	3300	4,945E-03	4800	1,584E-04
430	3,144E-01	730	< 1,000E-05	1030	< 1,000E-05	1850	4,389E-02	3350	4,463E-03	4850	2,376E-04
440	3,249E-01	740	< 1,000E-05	1040	< 1,000E-05	1900	7,212E-02	3400	4,260E-03	4900	3,262E-04
450	3,430E-01	750	< 1,000E-05	1050	< 1,000E-05	1950	1,074E-01	3450	4,380E-03	4950	3,896E-04
460	3,719E-01	760	< 1,000E-05	1060	< 1,000E-05	2000	1,488E-01	3500	4,740E-03	5000	3,832E-04
470	4,097E-01	770	< 1,000E-05	1070	< 1,000E-05	2050	1,947E-01	3550	5,450E-03	5050	2,843E-04
480	4,614E-01	780	< 1,000E-05	1080	< 1,000E-05	2100	2,428E-01	3600	6,450E-03	5100	1,509E-04
490	5,213E-01	790	< 1,000E-05	1090	< 1,000E-05	2150	2,908E-01	3650	7,713E-03	5150	5,275E-05

Chromaticity dependence on Incandescent Color Temperature

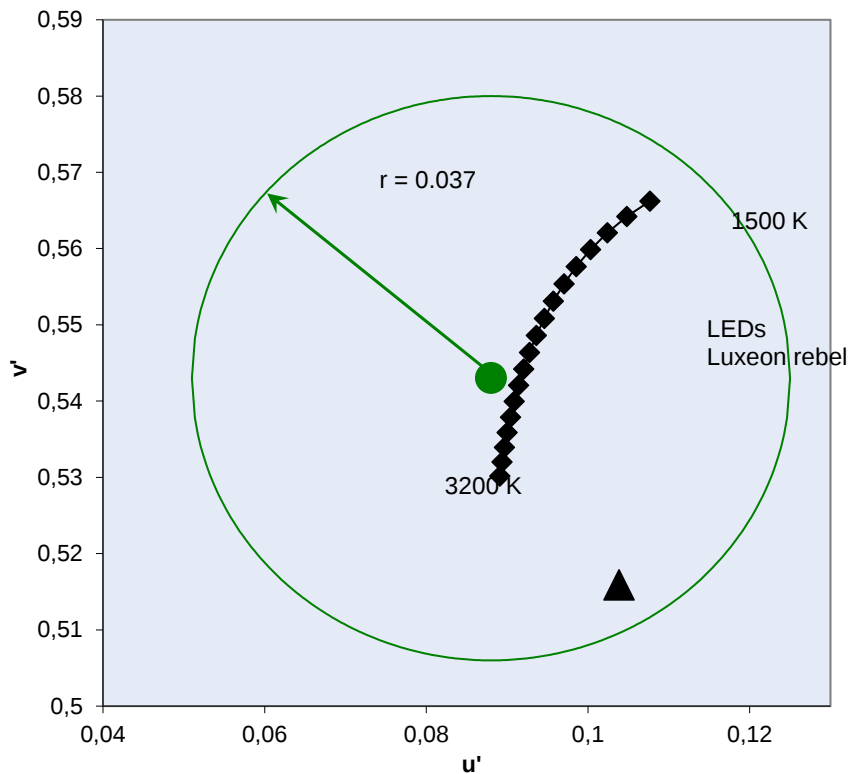

Chromaticity and NVIS Radiance at reference thickness 3 mm						
Planck [K]	u'	v'	x	y	Y	NR _A
1500	0,103	0,561	0,254	0,616	10,2	5,5E-11
1600	0,100	0,558	0,245	0,607	11,2	5,3E-11
1700	0,098	0,555	0,237	0,598	12,2	5,1E-11
1800	0,096	0,551	0,231	0,587	13,0	4,9E-11
1900	0,095	0,548	0,224	0,577	13,8	4,8E-11
2000	0,094	0,545	0,219	0,566	14,6	4,7E-11
2100	0,093	0,541	0,214	0,556	15,3	4,6E-11
2200	0,092	0,538	0,209	0,546	15,9	4,6E-11
2300	0,091	0,535	0,205	0,536	16,6	4,5E-11
2400	0,091	0,531	0,202	0,526	17,1	4,4E-11
2500	0,090	0,528	0,198	0,516	17,7	4,4E-11
2600	0,090	0,525	0,196	0,507	18,2	4,3E-11
2700	0,090	0,522	0,193	0,499	18,6	4,3E-11
2800	0,090	0,519	0,190	0,490	19,1	4,3E-11
2900	0,089	0,516	0,188	0,482	19,5	4,2E-11
3000	0,089	0,513	0,186	0,475	19,9	4,2E-11
3100	0,089	0,510	0,184	0,467	20,2	4,2E-11
3200	0,089	0,508	0,182	0,460	20,6	4,2E-11
LED	u'	v'	x	y	Y	NR _A
LUXEON rebel A2-RM-G	0,104	0,516	0,214	0,472	23,0	4,0E-11
other sources of illumination	A service for calculating chromaticity or NVIS radiance can be provided					

NVIS Green A

NVIS Green A Chromaticity coordinates
(as defined by MIL-STD-3009)

u' = 0.088
v' = 0.543

with radius of tolerance r = 0.037

S8612

Optical properties	
Reflection factor	
P_d	= 0,913
Spectral values guaranteed	
τ_i (500 nm)	≥ 0,96
τ_i (600 nm)	≥ 0,48
τ_i (700 nm)	< 0,02
λ ($\tau_{i, \max}$) [nm]	= 500 ± 5
Refractive indices	
n_F (486 nm)	= 1,55
n_e (546 nm)	= 1,54
n_d (587,6 nm)	= 1,54
Sellmeier coefficients	
valid from 400 nm to 1550 nm	
B_1	0,9589
B_2	0,3811
B_3	1,1938
C_1	8,342E-03 μm^2
C_2	1,0187E-02 μm^2
C_3	134,146 μm^2
Internal quality	
Bubble class	1


Mechanical properties	
Reference thickness	
d	= 1,00 mm
Density	
ρ	= 2,66 g/cm ³
Knoop hardness	
HK[0.1/20]	= 470

Thermal properties	
Transformation temperature	
T_g	= 391 °C
Thermal expansion in 10 ⁻⁶ /K	
α (20°C/300°C)	= 9,5


Chemical properties	
Chemical resistance	
FR class	= 0
SR class	= 3
AR class	= 3
Resistance against humidity	
Delicate glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colorimetric properties		1 mm	2 mm	3 mm
Illuminant D65	x	0,251	0,218	0,198
	y	0,321	0,311	0,302
	Y	72,1	61,5	54,4
	λ_d	490 nm	489 nm	489 nm
	P_e	0,232	0,358	0,438
Illuminant A	x	0,356	0,301	0,265
	y	0,433	0,440	0,440
	Y	64,6	51,8	43,9
	λ_d	500 nm	499 nm	498 nm
	P_e	0,208	0,335	0,421

Notes	
Ionically colored glass	
Bandpass filter / Shortpass filter	
NIR cutoff filter	
ISO 23364:2021	
Disclaimer	
All data without tolerances are to be understood to be reference values.	

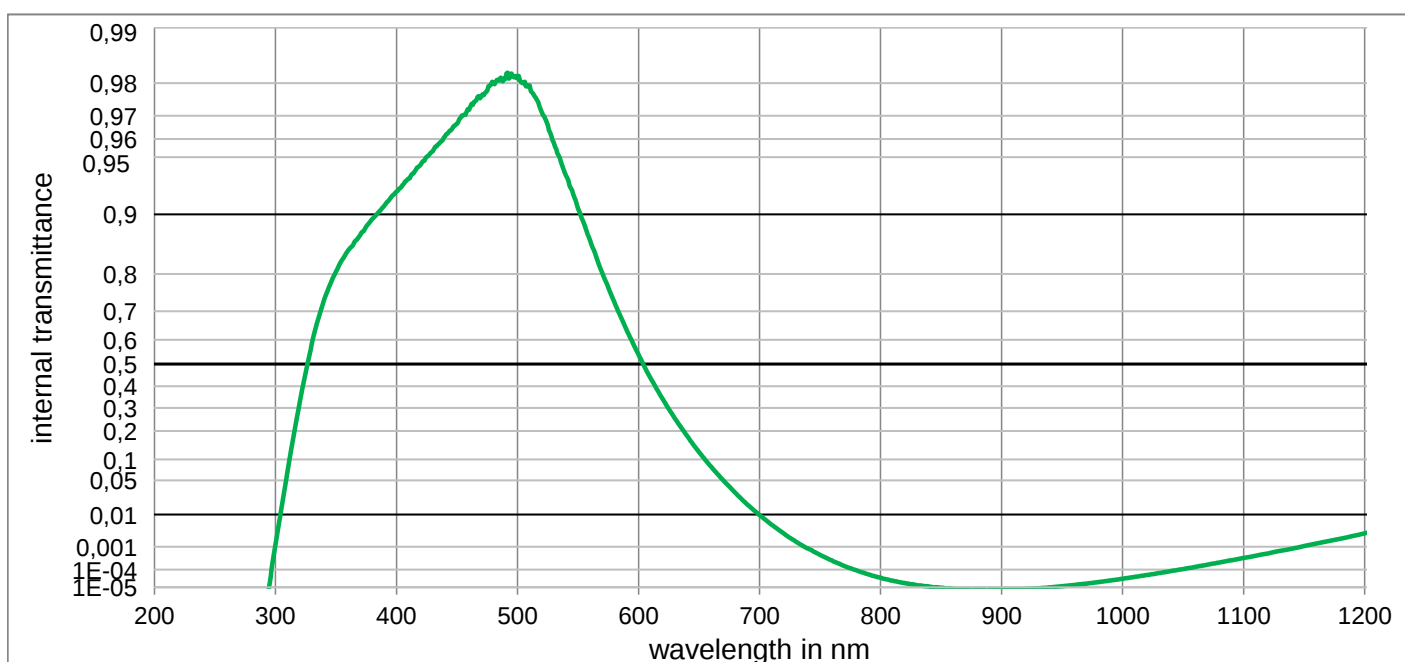

S8612

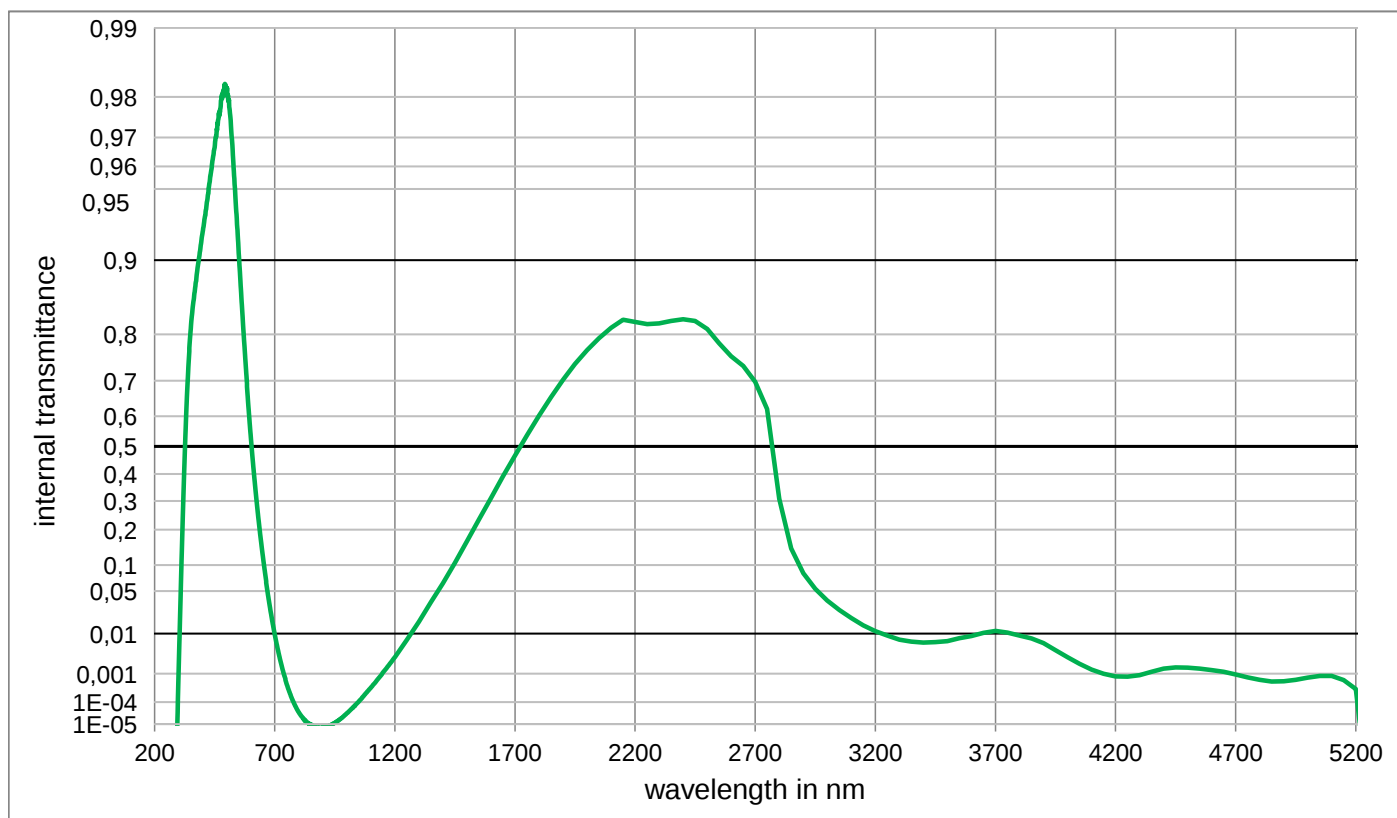Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,812E-01	800	3,721E-05	1100	3,490E-04	2200	8,214E-01	3700	1,127E-02
210	< 1,0E-05	510	9,794E-01	810	2,547E-05	1110	4,398E-04	2250	8,176E-01	3750	1,048E-02
220	< 1,0E-05	520	9,712E-01	820	1,846E-05	1120	5,462E-04	2300	8,190E-01	3800	9,124E-03
230	< 1,0E-05	530	9,581E-01	830	1,353E-05	1130	6,882E-04	2350	8,230E-01	3850	7,921E-03
240	< 1,0E-05	540	9,376E-01	840	1,144E-05	1140	8,525E-04	2400	8,257E-01	3900	6,253E-03
250	< 1,0E-05	550	9,064E-01	850	< 1,000E-05	1150	1,056E-03	2450	8,228E-01	3950	4,323E-03
260	< 1,0E-05	560	8,634E-01	860	< 1,000E-05	1160	1,303E-03	2500	8,093E-01	4000	2,878E-03
270	< 1,0E-05	570	8,031E-01	870	< 1,000E-05	1170	1,600E-03	2550	7,833E-01	4050	1,922E-03
280	< 1,0E-05	580	7,281E-01	880	< 1,000E-05	1180	1,949E-03	2600	7,570E-01	4100	1,324E-03
290	< 1,0E-05	590	6,380E-01	890	< 1,000E-05	1190	2,376E-03	2650	7,355E-01	4150	9,941E-04
300	1,2E-03	600	5,394E-01	900	< 1,000E-05	1200	2,905E-03	2700	6,974E-01	4200	8,230E-04
310	7,0E-02	610	4,375E-01	910	< 1,000E-05	1250	7,369E-03	2750	6,221E-01	4250	8,062E-04
320	3,262E-01	620	3,402E-01	920	< 1,000E-05	1300	1,688E-02	2800	3,075E-01	4300	8,948E-04
330	5,836E-01	630	2,532E-01	930	< 1,000E-05	1350	3,500E-02	2850	1,427E-01	4350	1,139E-03
340	7,324E-01	640	1,806E-01	940	< 1,000E-05	1400	6,250E-02	2900	8,200E-02	4400	1,405E-03
350	8,052E-01	650	1,227E-01	950	1,169E-05	1450	1,056E-01	2950	5,346E-02	4450	1,517E-03
360	8,471E-01	660	8,015E-02	960	1,407E-05	1500	1,633E-01	3000	3,712E-02	4500	1,498E-03
370	8,719E-01	670	5,011E-02	970	1,696E-05	1550	2,331E-01	3050	2,668E-02	4550	1,412E-03
380	8,942E-01	680	3,002E-02	980	2,080E-05	1600	3,106E-01	3100	1,947E-02	4600	1,288E-03
390	9,098E-01	690	1,724E-02	990	2,577E-05	1650	3,906E-01	3150	1,445E-02	4650	1,134E-03
400	9,241E-01	700	9,713E-03	1000	3,264E-05	1700	4,675E-01	3200	1,116E-02	4700	9,531E-04
410	9,351E-01	710	5,318E-03	1010	4,113E-05	1750	5,384E-01	3250	9,156E-03	4750	7,737E-04
420	9,452E-01	720	2,878E-03	1020	5,209E-05	1800	6,014E-01	3300	7,488E-03	4800	6,368E-04
430	9,536E-01	730	1,550E-03	1030	6,608E-05	1850	6,560E-01	3350	6,807E-03	4850	5,693E-04
440	9,614E-01	740	8,691E-04	1040	8,476E-05	1900	7,019E-01	3400	6,426E-03	4900	5,713E-04
450	9,668E-01	750	4,709E-04	1050	1,072E-04	1950	7,397E-01	3450	6,601E-03	4950	6,405E-04
460	9,722E-01	760	2,680E-04	1060	1,355E-04	2000	7,696E-01	3500	6,905E-03	5000	7,477E-04
470	9,764E-01	770	1,513E-04	1070	1,735E-04	2050	7,930E-01	3550	7,981E-03	5050	8,493E-04
480	9,801E-01	780	9,133E-05	1080	2,205E-04	2100	8,115E-01	3600	8,930E-03	5100	8,478E-04
490	9,810E-01	790	5,627E-05	1090	2,782E-04	2150	8,248E-01	3650	1,037E-02	5150	6,335E-04

Optical properties	
Reflection factor	
P _d = 0,911	
Spectral values guaranteed	
τ _i (450 nm)	≤ 0,21
τ _i (514 nm)	≥ 0,67
τ _i (633 nm)	≤ 0,15
τ _i (725 nm)	≤ 0,07
τ _i (1060 nm)	≤ 0,18
Refractive indices	
n _F (486 nm)	= 1,558
n _e (546 nm)	= 1,552
n _d (587,6 nm)	= 1,549
Sellmeier coefficients	
valid from 440 nm to 1550 nm	
B ₁	0,3483
B ₂	1,0034
B ₃	34,8247
C ₁	1,326E-02 μm ²
C ₂	1,2265E-02 μm ²
C ₃	5797,735 μm ²
Internal quality	
Bubble class	1


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,87 g/cm ³	
Knoop hardness	
HK[0.1/20] = 449	


Thermal properties	
Transformation temperature	
T _g = 451 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _{-30°C/+70°C} = 9,2	
α _{20°C/300°C} = 10,6	

Chemical properties	
Chemical resistance	
FR class = 0	
SR class = 1	
AR class = 1	
Resistance against humidity	
Robust glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colorimetric properties				
	1 mm	2 mm	3 mm	
Illuminant D65	x	0,284	0,246	0,220
	y	0,493	0,582	0,637
	Y	44,8	25,2	15,2
	λ _d	541 nm	535 nm	532 nm
	P _e	0,392	0,561	0,660
Illuminant A	x	0,370	0,306	0,265
	y	0,522	0,596	0,645
	Y	39,7	20,9	12,1
	λ _d	535 nm	529 nm	527 nm
	P _e	0,307	0,468	0,576

Notes
Ionically colored glass
Bandpass filter
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

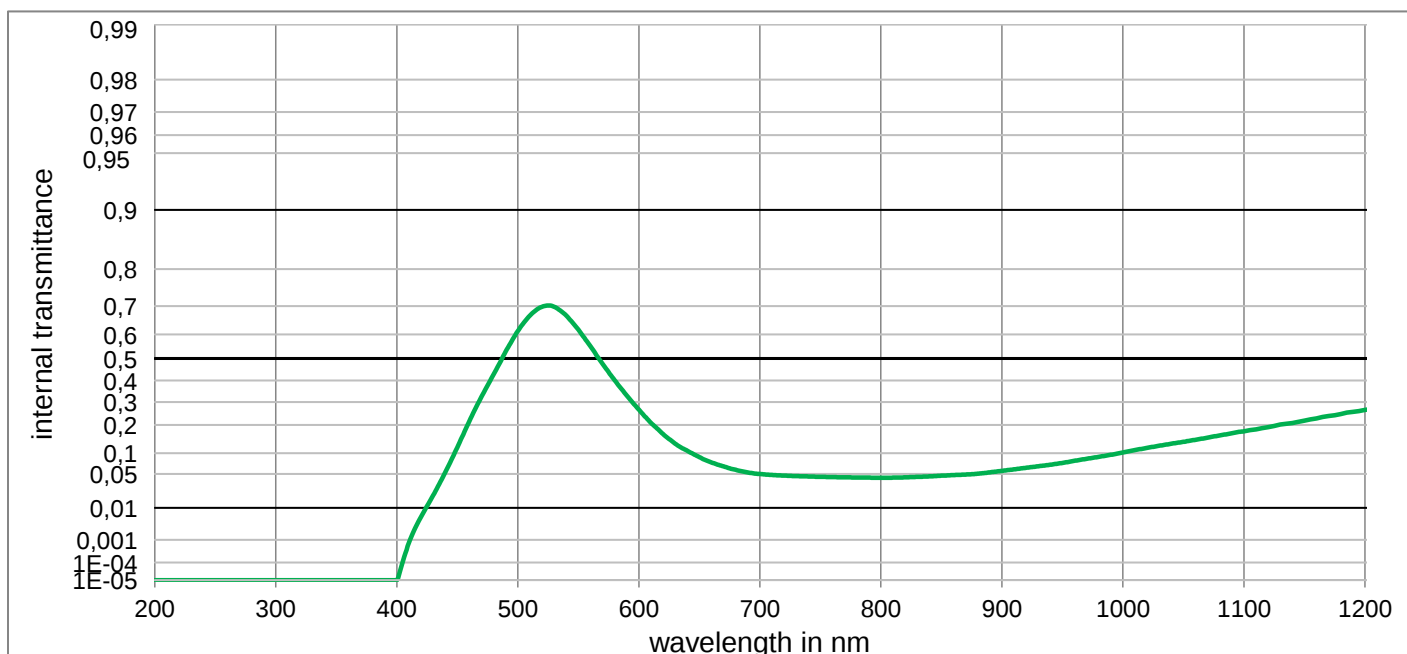

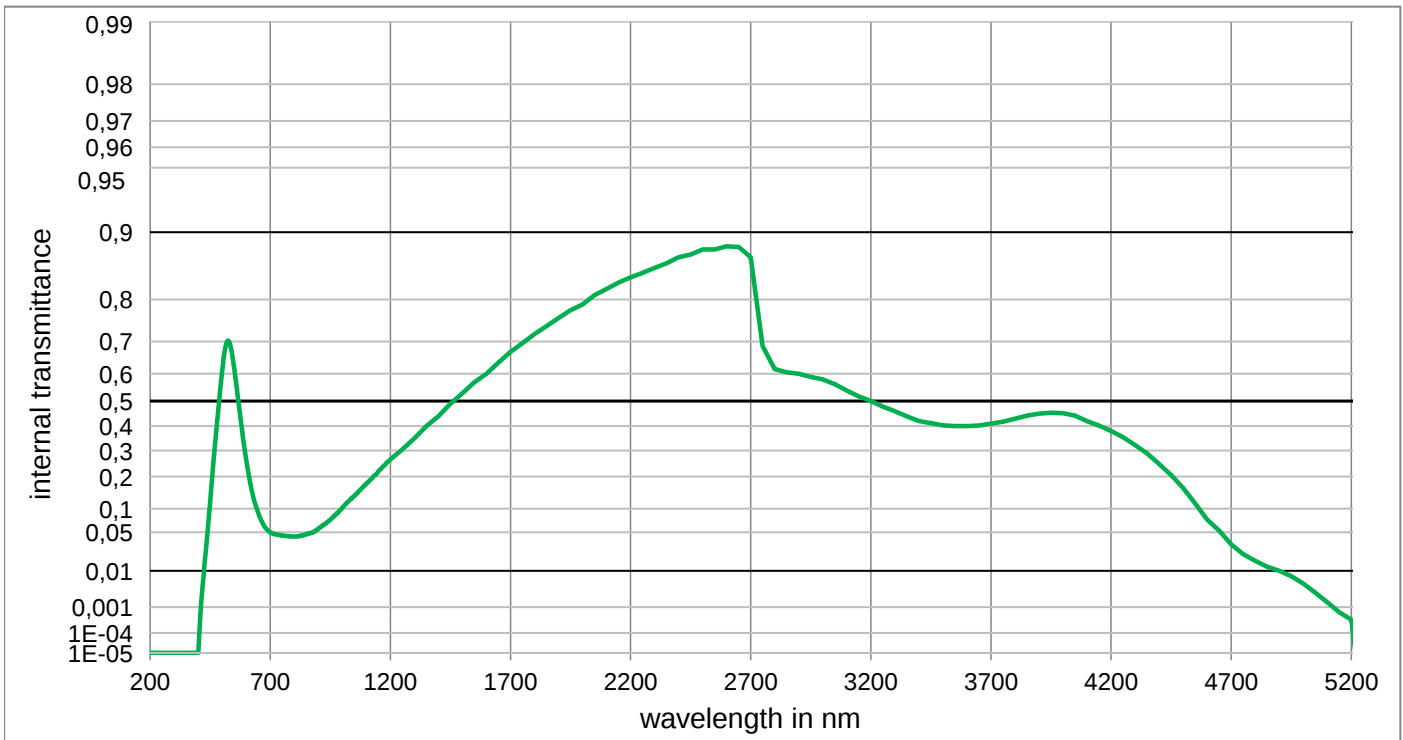Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	6,130E-01	800	4,315E-02	1100	1,745E-01	2200	8,400E-01	3700	4,100E-01
210	< 1,000E-05	510	6,690E-01	810	4,327E-02	1110	1,824E-01	2250	8,472E-01	3750	4,175E-01
220	< 1,000E-05	520	6,980E-01	820	4,381E-02	1120	1,907E-01	2300	8,548E-01	3800	4,300E-01
230	< 1,000E-05	530	6,980E-01	830	4,462E-02	1130	2,013E-01	2350	8,614E-01	3850	4,420E-01
240	< 1,000E-05	540	6,690E-01	840	4,547E-02	1140	2,079E-01	2400	8,700E-01	3900	4,500E-01
250	< 1,000E-05	550	6,180E-01	850	4,674E-02	1150	2,184E-01	2450	8,736E-01	3950	4,542E-01
260	< 1,000E-05	560	5,520E-01	860	4,781E-02	1160	2,273E-01	2500	8,800E-01	4000	4,524E-01
270	< 1,000E-05	570	4,770E-01	870	4,890E-02	1170	2,372E-01	2550	8,800E-01	4050	4,429E-01
280	< 1,000E-05	580	4,010E-01	880	5,036E-02	1180	2,460E-01	2600	8,840E-01	4100	4,200E-01
290	< 1,000E-05	590	3,300E-01	890	5,300E-02	1190	2,562E-01	2650	8,830E-01	4150	4,015E-01
300	< 1,000E-05	600	2,650E-01	900	5,608E-02	1200	2,644E-01	2700	8,700E-01	4200	3,800E-01
310	< 1,000E-05	610	2,090E-01	910	5,926E-02	1250	3,044E-01	2750	6,870E-01	4250	3,543E-01
320	< 1,000E-05	620	1,640E-01	920	6,255E-02	1300	3,500E-01	2800	6,154E-01	4300	3,223E-01
330	< 1,000E-05	630	1,300E-01	930	6,600E-02	1350	4,000E-01	2850	6,050E-01	4350	2,884E-01
340	< 1,000E-05	640	1,070E-01	940	6,967E-02	1400	4,400E-01	2900	6,000E-01	4400	2,469E-01
350	< 1,000E-05	650	8,900E-02	950	7,392E-02	1450	4,901E-01	2950	5,890E-01	4450	2,054E-01
360	< 1,000E-05	660	7,500E-02	960	7,900E-02	1500	5,300E-01	3000	5,800E-01	4500	1,600E-01
370	< 1,000E-05	670	6,558E-02	970	8,434E-02	1550	5,702E-01	3050	5,626E-01	4550	1,140E-01
380	< 1,000E-05	680	5,811E-02	980	8,972E-02	1600	6,000E-01	3100	5,400E-01	4600	7,450E-02
390	< 1,000E-05	690	5,297E-02	990	9,538E-02	1650	6,371E-01	3150	5,183E-01	4650	5,248E-02
400	< 1,000E-05	700	4,985E-02	1000	1,020E-01	1700	6,700E-01	3200	5,000E-01	4700	3,251E-02
410	7,621E-04	710	4,816E-02	1010	1,091E-01	1750	6,955E-01	3250	4,787E-01	4750	2,203E-02
420	5,715E-03	720	4,695E-02	1020	1,162E-01	1800	7,200E-01	3300	4,600E-01	4800	1,614E-02
430	1,963E-02	730	4,597E-02	1030	1,230E-01	1850	7,407E-01	3350	4,392E-01	4850	1,230E-02
440	5,343E-02	740	4,533E-02	1040	1,295E-01	1900	7,600E-01	3400	4,213E-01	4900	1,000E-02
450	1,170E-01	750	4,479E-02	1050	1,360E-01	1950	7,775E-01	3450	4,118E-01	4950	7,534E-03
460	2,160E-01	760	4,422E-02	1060	1,430E-01	2000	7,900E-01	3500	4,034E-01	5000	5,000E-03
470	3,250E-01	770	4,387E-02	1070	1,510E-01	2050	8,086E-01	3550	4,000E-01	5050	2,773E-03
480	4,290E-01	780	4,354E-02	1080	1,590E-01	2100	8,200E-01	3600	4,000E-01	5100	1,455E-03
490	5,300E-01	790	4,328E-02	1090	1,670E-01	2150	8,312E-01	3650	4,024E-01	5150	6,637E-04

Optical properties	
Reflection factor	
P _d = 0,913	
Spectral values guaranteed	
τ _i (450 nm)	≥ 0,75
τ _i (500 nm)	≥ 0,83
τ _i (550 nm)	≥ 0,65
τ _i (600 nm)	≤ 0,19
Refractive indices	
n _F (486 nm)	= 1,547
n _e (546 nm)	= 1,543
n _d (587,6 nm)	= 1,541
Sellmeier coefficients	
valid from 400 nm to 1550 nm	
B ₁	0,7165
B ₂	0,6218
B ₃	0,6042
C ₁	1,764E-09 μm ²
C ₂	1,9422E-02 μm ²
C ₃	100,000 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,85 g/cm ³	
Knoop hardness	
HK[0.1/20] = 364	

Thermal properties	
Transformation temperature	
T _g = 390 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _{-30°C/+70°C} = 11,8	
α _{20°C/300°C} = 13,7	


Chemical properties	
Chemical resistance	
FR class = 1	
SR class = 52.3	
AR class = 3.3	
Resistance against humidity	
Robust glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colorimetric properties				
	1 mm	2 mm	3 mm	
Illuminant D65	x	0,203	0,170	0,154
	y	0,312	0,300	0,294
	Y	49,0	33,2	24,1
	λ _d	490 nm	489 nm	489 nm
	P _e	0,413	0,543	0,607
Illuminant A	x	0,274	0,211	0,179
	y	0,445	0,441	0,434
	Y	39,9	24,9	17,2
	λ _d	499 nm	497 nm	496 nm
	P _e	0,398	0,549	0,625

Notes
Ionically colored glass
Bandpass filter
NIR cutoff filter
lambda_50%(d=0.3mm) @ 604 nm
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

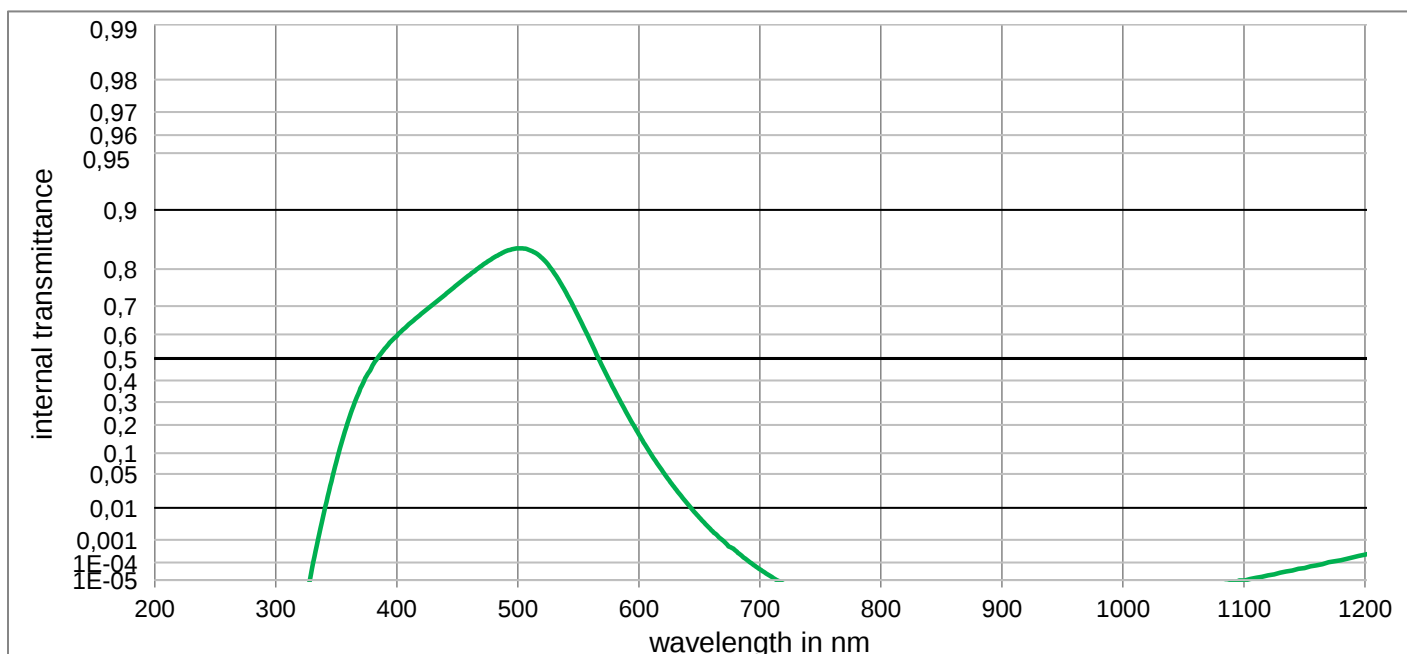


VG20

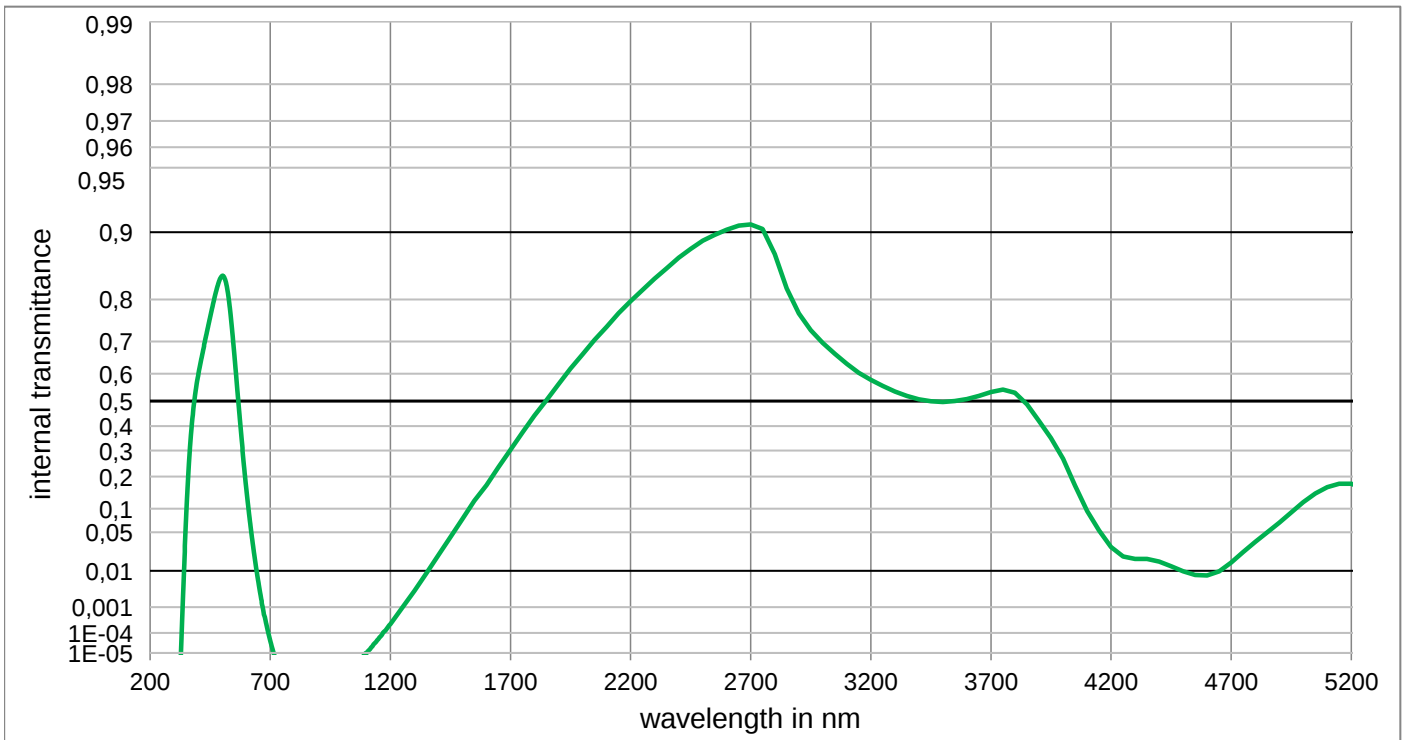Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	8,425E-01	800	< 1,000E-05	1100	< 1,000E-05	2200	7,964E-01	3700	5,342E-01
210	< 1,000E-05	510	8,389E-01	810	< 1,000E-05	1110	1,392E-05	2250	8,185E-01	3750	5,437E-01
220	< 1,000E-05	520	8,236E-01	820	< 1,000E-05	1120	1,999E-05	2300	8,379E-01	3800	5,316E-01
230	< 1,000E-05	530	7,914E-01	830	< 1,000E-05	1130	2,837E-05	2350	8,541E-01	3850	4,866E-01
240	< 1,000E-05	540	7,393E-01	840	< 1,000E-05	1140	3,755E-05	2400	8,694E-01	3900	4,207E-01
250	< 1,000E-05	550	6,655E-01	850	< 1,000E-05	1150	5,176E-05	2450	8,808E-01	3950	3,509E-01
260	< 1,000E-05	560	5,721E-01	860	< 1,000E-05	1160	7,067E-05	2500	8,905E-01	4000	2,676E-01
270	< 1,000E-05	570	4,641E-01	870	< 1,000E-05	1170	1,026E-04	2550	8,973E-01	4050	1,689E-01
280	< 1,000E-05	580	3,534E-01	880	< 1,000E-05	1180	1,293E-04	2600	9,027E-01	4100	9,411E-02
290	< 1,000E-05	590	2,493E-01	890	< 1,000E-05	1190	1,808E-04	2650	9,067E-01	4150	5,303E-02
300	< 1,000E-05	600	1,627E-01	900	< 1,000E-05	1200	2,372E-04	2700	9,079E-01	4200	2,924E-02
310	< 1,000E-05	610	9,760E-02	910	< 1,000E-05	1250	9,582E-04	2750	9,034E-01	4250	1,970E-02
320	< 1,000E-05	620	5,393E-02	920	< 1,000E-05	1300	3,153E-03	2800	8,741E-01	4300	1,772E-02
330	4,871E-05	630	2,735E-02	930	< 1,000E-05	1350	8,739E-03	2850	8,210E-01	4350	1,772E-02
340	7,922E-03	640	1,274E-02	940	< 1,000E-05	1400	2,078E-02	2900	7,707E-01	4400	1,571E-02
350	7,618E-02	650	5,556E-03	950	< 1,000E-05	1450	4,231E-02	2950	7,303E-01	4450	1,258E-02
360	2,203E-01	660	2,205E-03	960	< 1,000E-05	1500	7,563E-02	3000	6,961E-01	4500	9,730E-03
370	3,634E-01	670	8,986E-04	970	< 1,000E-05	1550	1,217E-01	3050	6,643E-01	4550	8,055E-03
380	4,698E-01	680	3,566E-04	980	< 1,000E-05	1600	1,704E-01	3100	6,331E-01	4600	7,823E-03
390	5,425E-01	690	1,258E-04	990	< 1,000E-05	1650	2,347E-01	3150	6,032E-01	4650	9,759E-03
400	5,941E-01	700	4,383E-05	1000	< 1,000E-05	1700	3,036E-01	3200	5,784E-01	4700	1,497E-02
410	6,380E-01	710	1,529E-05	1010	< 1,000E-05	1750	3,737E-01	3250	5,564E-01	4750	2,385E-02
420	6,736E-01	720	< 1,000E-05	1020	< 1,000E-05	1800	4,423E-01	3300	5,361E-01	4800	3,556E-02
430	7,056E-01	730	< 1,000E-05	1030	< 1,000E-05	1850	5,043E-01	3350	5,195E-01	4850	4,991E-02
440	7,350E-01	740	< 1,000E-05	1040	< 1,000E-05	1900	5,627E-01	3400	5,065E-01	4900	6,777E-02
450	7,620E-01	750	< 1,000E-05	1050	< 1,000E-05	1950	6,167E-01	3450	4,991E-01	4950	9,057E-02
460	7,861E-01	760	< 1,000E-05	1060	< 1,000E-05	2000	6,627E-01	3500	4,961E-01	5000	1,170E-01
470	8,074E-01	770	< 1,000E-05	1070	< 1,000E-05	2050	7,040E-01	3550	4,998E-01	5050	1,430E-01
480	8,244E-01	780	< 1,000E-05	1080	< 1,000E-05	2100	7,389E-01	3600	5,074E-01	5100	1,638E-01
490	8,370E-01	790	< 1,000E-05	1090	< 1,000E-05	2150	7,711E-01	3650	5,196E-01	5150	1,750E-01

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,913$	$d = 1,00 \text{ mm}$	
Spectral values guaranteed	Density	Illuminant D65
$\tau_i (365 \text{ nm}) \geq 0,8$	$\rho = 2,77 \text{ g/cm}^3$	x
$\tau_i (405 \text{ nm}) \leq 0,1$	Knoop hardness	y
$\tau_i (694 \text{ nm}) \leq 0,06$	$HK[0.1/20] = 482$	Y
$\tau_i (750 \text{ nm}) \leq 0,53$		λ_d
		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	Notes
$n_F (486 \text{ nm}) = 1,548$	Transformation temperature	UV
$n_e (546 \text{ nm}) = 1,543$	$T_g = 575 \text{ }^\circ\text{C}$	Transmission changes are possible under the action of intense ultraviolet radiation.
$n_d (587,6 \text{ nm}) = 1,541$	Thermal expansion in $10^{-6}/\text{K}$	Ionically colored glass
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,9$	Bandpass filter
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 8,9$	
Sellmeier coefficients	Chemical properties	
valid from 400 nm to 1550 nm	Chemical resistance	
$B_1 = 0,9475$	FR class = 0	
$B_2 = 0,3895$	SR class = 1	
$B_3 = 1,1076$	AR class = 1	ISO 23364:2021
$C_1 = 9,783\text{E-}03 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,1182\text{E-}02 \text{ } \mu\text{m}^2$	Sensitive glass	Disclaimer
$C_3 = 147,627 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	All data without tolerances are to be understood to be reference values.
Internal quality		
Bubble class 1		

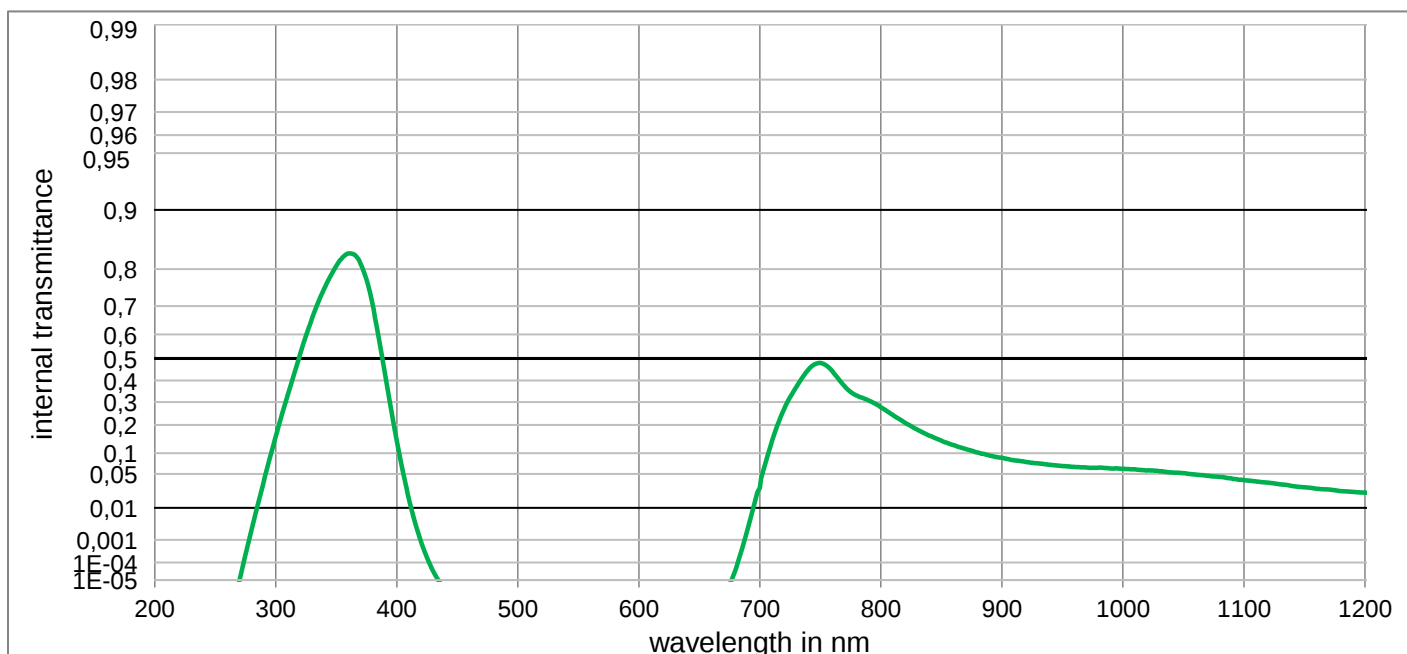

UG1

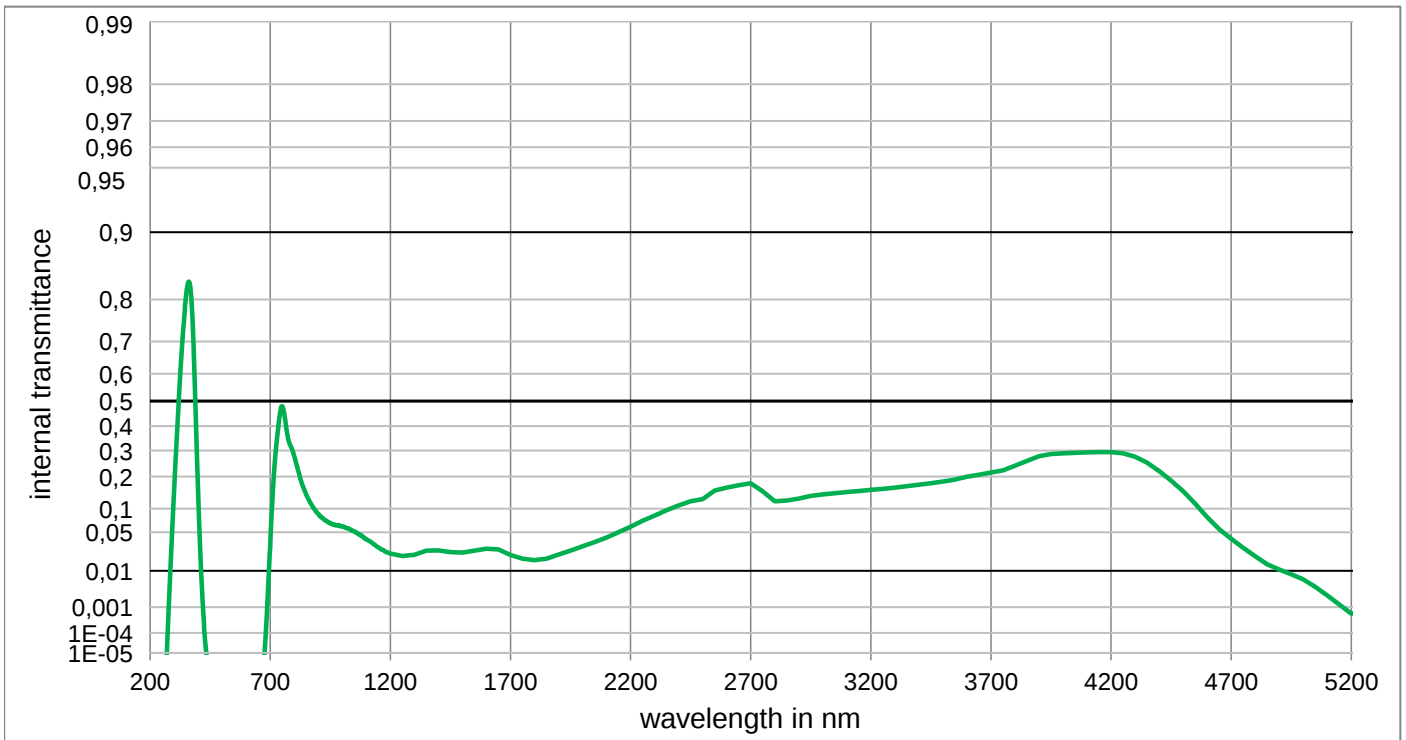Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	< 1,000E-05	800	2,769E-01	1100	3,919E-02	2200	5,979E-02	3700	2,146E-01
210	< 1,000E-05	510	< 1,000E-05	810	2,416E-01	1110	3,721E-02	2250	7,156E-02	3750	2,230E-01
220	< 1,000E-05	520	< 1,000E-05	820	2,091E-01	1120	3,533E-02	2300	8,324E-02	3800	2,400E-01
230	< 1,000E-05	530	< 1,000E-05	830	1,812E-01	1130	3,286E-02	2350	9,590E-02	3850	2,592E-01
240	< 1,000E-05	540	< 1,000E-05	840	1,584E-01	1140	3,046E-02	2400	1,083E-01	3900	2,774E-01
250	< 1,000E-05	550	< 1,000E-05	850	1,402E-01	1150	2,892E-02	2450	1,199E-01	3950	2,859E-01
260	< 1,000E-05	560	< 1,000E-05	860	1,250E-01	1160	2,682E-02	2500	1,262E-01	4000	2,887E-01
270	< 1,000E-05	570	< 1,000E-05	870	1,123E-01	1170	2,601E-02	2550	1,524E-01	4050	2,906E-01
280	2,377E-03	580	< 1,000E-05	880	1,019E-01	1180	2,411E-02	2600	1,615E-01	4100	2,925E-01
290	3,691E-02	590	< 1,000E-05	890	9,311E-02	1190	2,337E-02	2650	1,700E-01	4150	2,934E-01
300	1,551E-01	600	< 1,000E-05	900	8,686E-02	1200	2,243E-02	2700	1,762E-01	4200	2,934E-01
310	3,350E-01	610	< 1,000E-05	910	8,073E-02	1250	2,020E-02	2750	1,498E-01	4250	2,893E-01
320	5,189E-01	620	< 1,000E-05	920	7,633E-02	1300	2,134E-02	2800	1,200E-01	4300	2,755E-01
330	6,591E-01	630	< 1,000E-05	930	7,269E-02	1350	2,534E-02	2850	1,219E-01	4350	2,523E-01
340	7,508E-01	640	< 1,000E-05	940	6,916E-02	1400	2,552E-02	2900	1,279E-01	4400	2,200E-01
350	8,072E-01	650	< 1,000E-05	950	6,633E-02	1450	2,378E-02	2950	1,354E-01	4450	1,860E-01
360	8,327E-01	660	< 1,000E-05	960	6,451E-02	1500	2,337E-02	3000	1,400E-01	4500	1,500E-01
370	8,124E-01	670	< 1,000E-05	970	6,314E-02	1550	2,540E-02	3050	1,439E-01	4550	1,131E-01
380	7,060E-01	680	4,430E-05	980	6,293E-02	1600	2,746E-02	3100	1,476E-01	4600	8,000E-02
390	4,380E-01	690	2,460E-03	990	6,107E-02	1650	2,657E-02	3150	1,508E-01	4650	5,508E-02
400	1,376E-01	700	2,820E-02	1000	6,046E-02	1700	2,106E-02	3200	1,546E-01	4700	4,000E-02
410	1,650E-02	710	1,395E-01	1010	5,929E-02	1750	1,786E-02	3250	1,580E-01	4750	2,838E-02
420	8,618E-04	720	2,686E-01	1020	5,705E-02	1800	1,677E-02	3300	1,621E-01	4800	2,000E-02
430	3,463E-05	730	3,682E-01	1030	5,553E-02	1850	1,793E-02	3350	1,668E-01	4850	1,380E-02
440	< 1,000E-05	740	4,499E-01	1040	5,300E-02	1900	2,145E-02	3400	1,718E-01	4900	1,057E-02
450	< 1,000E-05	750	4,798E-01	1050	5,141E-02	1950	2,515E-02	3450	1,769E-01	4950	8,356E-03
460	< 1,000E-05	760	4,419E-01	1060	4,881E-02	2000	3,012E-02	3500	1,825E-01	5000	6,281E-03
470	< 1,000E-05	770	3,736E-01	1070	4,668E-02	2050	3,544E-02	3550	1,891E-01	5050	4,055E-03
480	< 1,000E-05	780	3,298E-01	1080	4,456E-02	2100	4,160E-02	3600	1,995E-01	5100	2,328E-03
490	< 1,000E-05	790	3,068E-01	1090	4,168E-02	2150	5,012E-02	3650	2,070E-01	5150	1,230E-03

Optical properties	
Reflection factor	
P _d = 0,918	
Spectral values guaranteed	
τ _i (303 nm)	≤ 0,07
τ _i (365 nm)	≥ 0,81
τ _i (405 nm)	≤ 0,1
τ _i (694 nm)	≤ 0,04
τ _i (750 nm)	≤ 0,52
Refractive indices	
n _F (486 nm)	= 1,529
n _e (546 nm)	= 1,525
n _d (587,6 nm)	= 1,523
Sellmeier coefficients	
valid from 295 nm to 1600 nm	
B ₁	0,8819
B ₂	0,4027
B ₃	1,2925
C ₁	4,435E-03 μm ²
C ₂	2,0863E-02 μm ²
C ₃	169,418 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 3,00 mm	
Density	
ρ = 2,60 g/cm ³	
Knoop hardness	
HK[0.1/20]	

Thermal properties	
Transformation temperature	
T _g = 484 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _{-30°C/+70°C} = 8,7	
α _{20°C/300°C} = 9,9	


Chemical properties	
Chemical resistance	
FR class	
SR class = 1.0	
AR class = 1.3	
Resistance against humidity	
Sensitive glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colorimetric properties			
	1 mm	2 mm	3 mm
Illuminant D65	x		
	y		
	Y		
	λ _d		
	P _e		
Illuminant A	x		
	y		
	Y		
	λ _d		
	P _e		

Notes
UV
Transmission changes are possible under the action of intense ultraviolet radiation.
Ionically colored glass
Bandpass filter
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

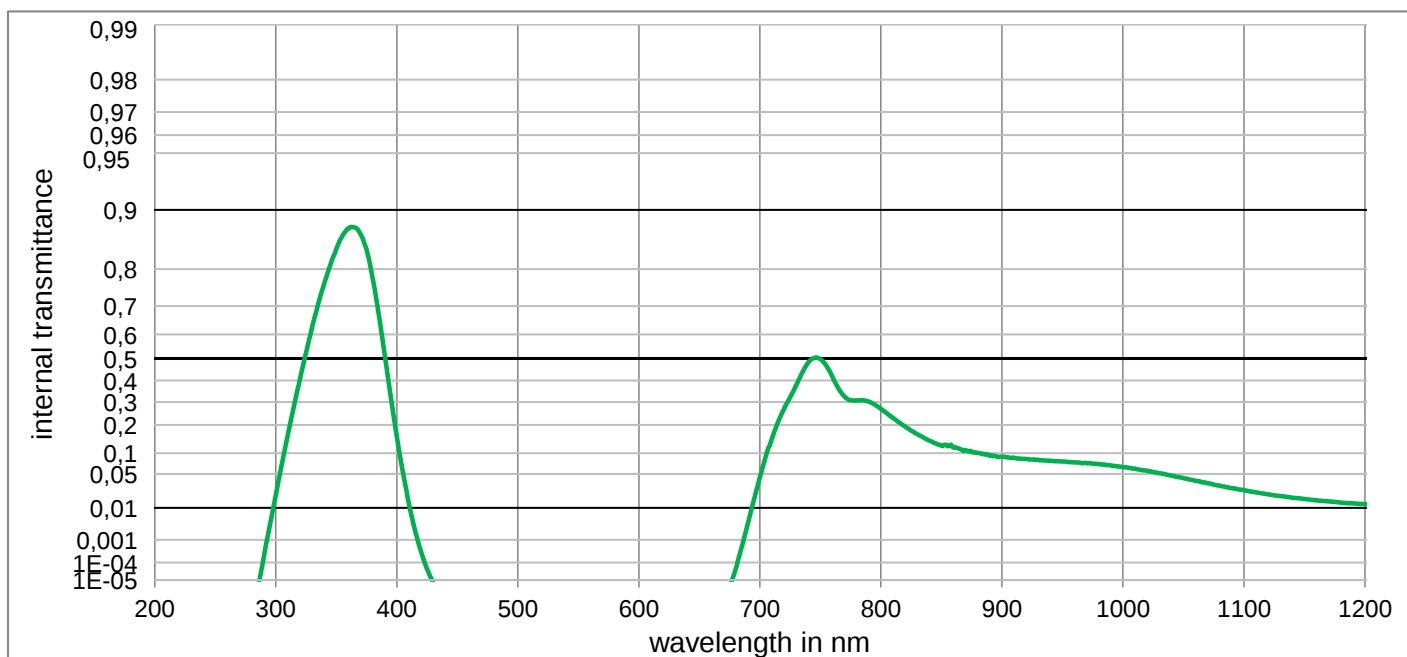


UG2A

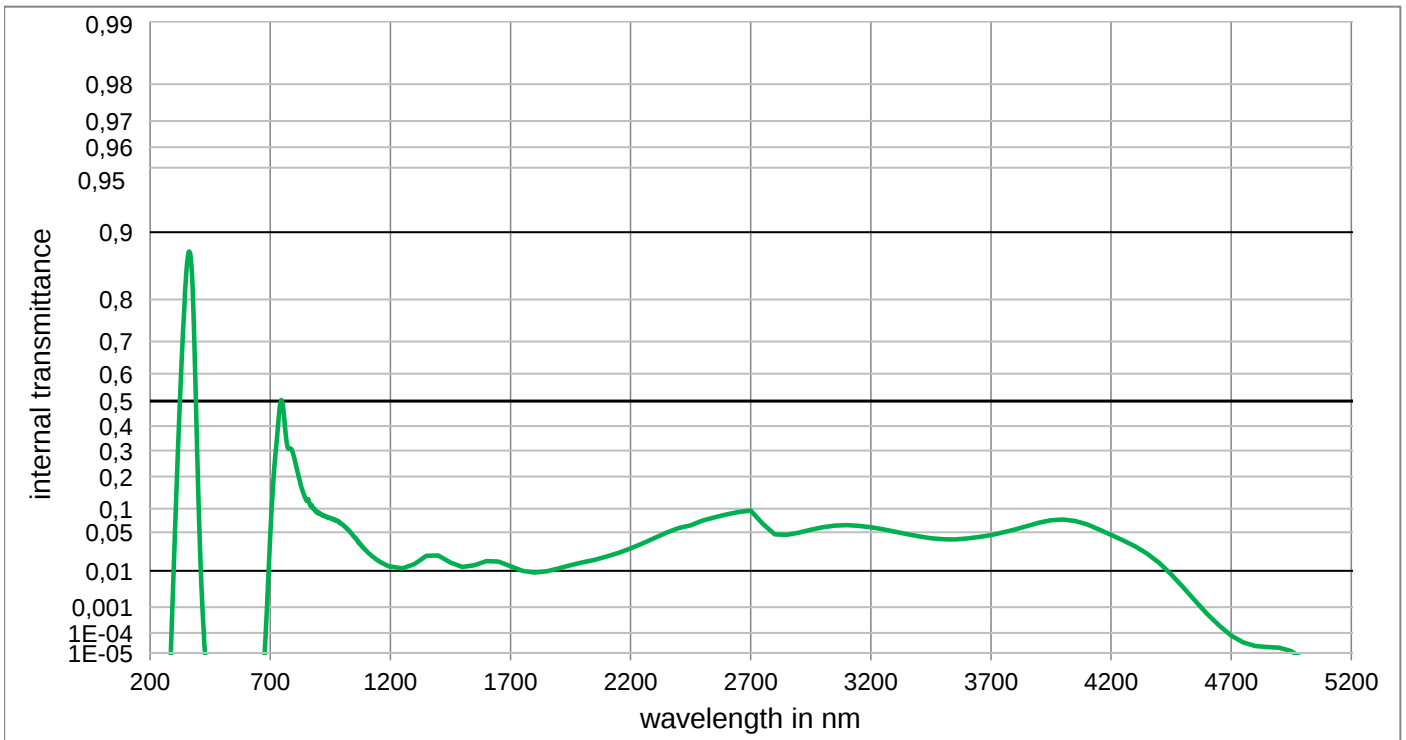Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	< 1,000E-05	800	2,694E-01	1100	2,523E-02	2200	2,753E-02	3700	4,550E-02
210	< 1,000E-05	510	< 1,000E-05	810	2,291E-01	1110	2,269E-02	2250	3,365E-02	3750	4,960E-02
220	< 1,000E-05	520	< 1,000E-05	820	1,934E-01	1120	2,075E-02	2300	4,119E-02	3800	5,487E-02
230	< 1,000E-05	530	< 1,000E-05	830	1,638E-01	1130	1,906E-02	2350	4,948E-02	3850	6,125E-02
240	< 1,000E-05	540	< 1,000E-05	840	1,408E-01	1140	1,742E-02	2400	5,747E-02	3900	6,769E-02
250	< 1,000E-05	550	< 1,000E-05	850	1,232E-01	1150	1,630E-02	2450	6,255E-02	3950	7,273E-02
260	< 1,000E-05	560	< 1,000E-05	860	1,173E-01	1160	1,523E-02	2500	7,233E-02	4000	7,429E-02
270	< 1,000E-05	570	< 1,000E-05	870	1,091E-01	1170	1,438E-02	2550	7,920E-02	4050	7,123E-02
280	< 1,000E-05	580	< 1,000E-05	880	1,008E-01	1180	1,343E-02	2600	8,580E-02	4100	6,414E-02
290	1,820E-04	590	< 1,000E-05	890	9,226E-02	1190	1,285E-02	2650	9,190E-02	4150	5,492E-02
300	1,967E-02	600	< 1,000E-05	900	8,992E-02	1200	1,239E-02	2700	9,526E-02	4200	4,586E-02
310	1,622E-01	610	< 1,000E-05	910	8,713E-02	1250	1,130E-02	2750	6,593E-02	4250	3,757E-02
320	4,089E-01	620	< 1,000E-05	920	8,362E-02	1300	1,398E-02	2800	4,651E-02	4300	3,000E-02
330	6,267E-01	630	< 1,000E-05	930	8,186E-02	1350	2,031E-02	2850	4,580E-02	4350	2,243E-02
340	7,641E-01	640	< 1,000E-05	940	7,948E-02	1400	2,052E-02	2900	4,947E-02	4400	1,481E-02
350	8,415E-01	650	< 1,000E-05	950	7,743E-02	1450	1,494E-02	2950	5,439E-02	4450	8,338E-03
360	8,747E-01	660	< 1,000E-05	960	7,516E-02	1500	1,214E-02	3000	5,885E-02	4500	3,947E-03
370	8,670E-01	670	< 1,000E-05	970	7,294E-02	1550	1,314E-02	3050	6,181E-02	4550	1,607E-03
380	7,794E-01	680	4,743E-05	980	7,087E-02	1600	1,595E-02	3100	6,279E-02	4600	5,872E-04
390	5,154E-01	690	3,525E-03	990	6,786E-02	1650	1,574E-02	3150	6,159E-02	4650	2,055E-04
400	1,524E-01	700	4,381E-02	1000	6,441E-02	1700	1,264E-02	3200	5,873E-02	4700	7,701E-05
410	1,277E-02	710	1,482E-01	1010	6,074E-02	1750	1,000E-02	3250	5,510E-02	4750	3,602E-05
420	3,343E-04	720	2,701E-01	1020	5,634E-02	1800	9,086E-03	3300	5,112E-02	4800	2,360E-05
430	< 1,000E-05	730	3,772E-01	1030	5,164E-02	1850	9,759E-03	3350	4,711E-02	4850	2,090E-05
440	< 1,000E-05	740	4,822E-01	1040	4,693E-02	1900	1,129E-02	3400	4,352E-02	4900	1,931E-05
450	< 1,000E-05	750	4,969E-01	1050	4,254E-02	1950	1,318E-02	3450	4,076E-02	4950	1,251E-05
460	< 1,000E-05	760	4,160E-01	1060	3,842E-02	2000	1,507E-02	3500	3,919E-02	5000	< 1,000E-05
470	< 1,000E-05	770	3,251E-01	1070	3,455E-02	2050	1,693E-02	3550	3,909E-02	5050	< 1,000E-05
480	< 1,000E-05	780	3,076E-01	1080	3,079E-02	2100	1,983E-02	3600	4,021E-02	5100	< 1,000E-05
490	< 1,000E-05	790	3,020E-01	1090	2,776E-02	2150	2,320E-02	3650	4,237E-02	5150	< 1,000E-05

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,914$	$d = 1,00 \text{ mm}$	
Spectral values guaranteed	Density	Illuminant D65
$\tau_i (254 \text{ nm}) \geq 0,8$	$\rho = 2,84 \text{ g/cm}^3$	x
$\tau_i (308 \text{ nm}) \geq 0,94$	Knoop hardness	y
$\tau_i (405 \text{ nm}) \leq 0,5$	$HK[0.1/20] = 407$	Y
$\tau_i (546 \text{ nm}) \leq 0,05$		λ_d
$\tau_i (633 \text{ nm}) \leq 0,05$		P_e
$\tau_i (725 \text{ nm}) \leq 0,85$		
	Thermal properties	Illuminant A
	Transformation temperature	x
	$T_g = 462 \text{ }^\circ\text{C}$	y
	Thermal expansion in $10^{-6}/\text{K}$	Y
Refractive indices	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,1$	λ_d
$n_F (486 \text{ nm}) = 1,548$	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,3$	P_e
$n_e (546 \text{ nm}) = 1,545$		
$n_d (587,6 \text{ nm}) = 1,543$		
Sellmeier coefficients	Chemical properties	Notes
valid from 250 nm to 1550 nm	Chemical resistance	UV
$B_1 = 0,8861$	FR class = 0	Transmission changes are possible under the action of intense ultraviolet radiation.
$B_2 = 0,4613$	SR class = 3	Ionically colored glass
$B_3 = 29,7610$	AR class = 2	Bandpass filter
$C_1 = 9,024\text{E-}03 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 8,3379\text{E-}03 \text{ } \mu\text{m}^2$	Sensitive glass	
$C_3 = 3197,045 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	ISO 23364:2021
Internal quality		
Bubble class 2		Disclaimer
		All data without tolerances are to be understood to be reference values.

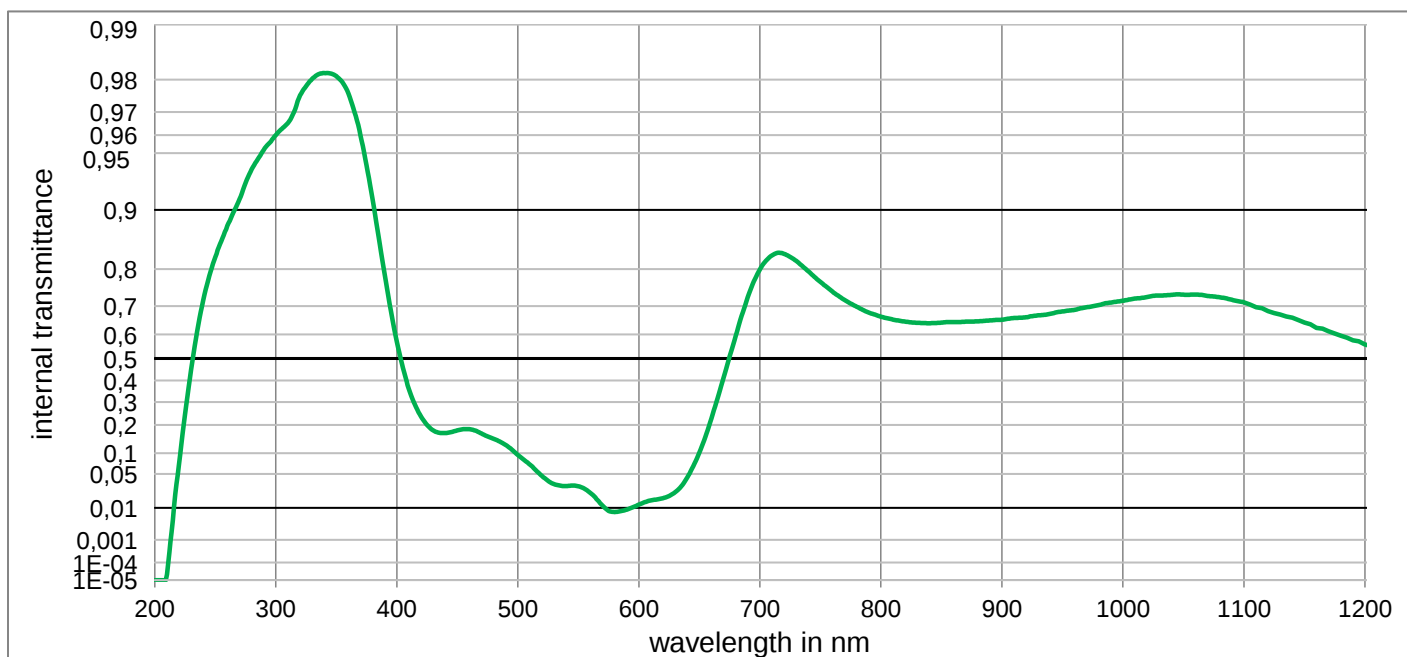

UG5

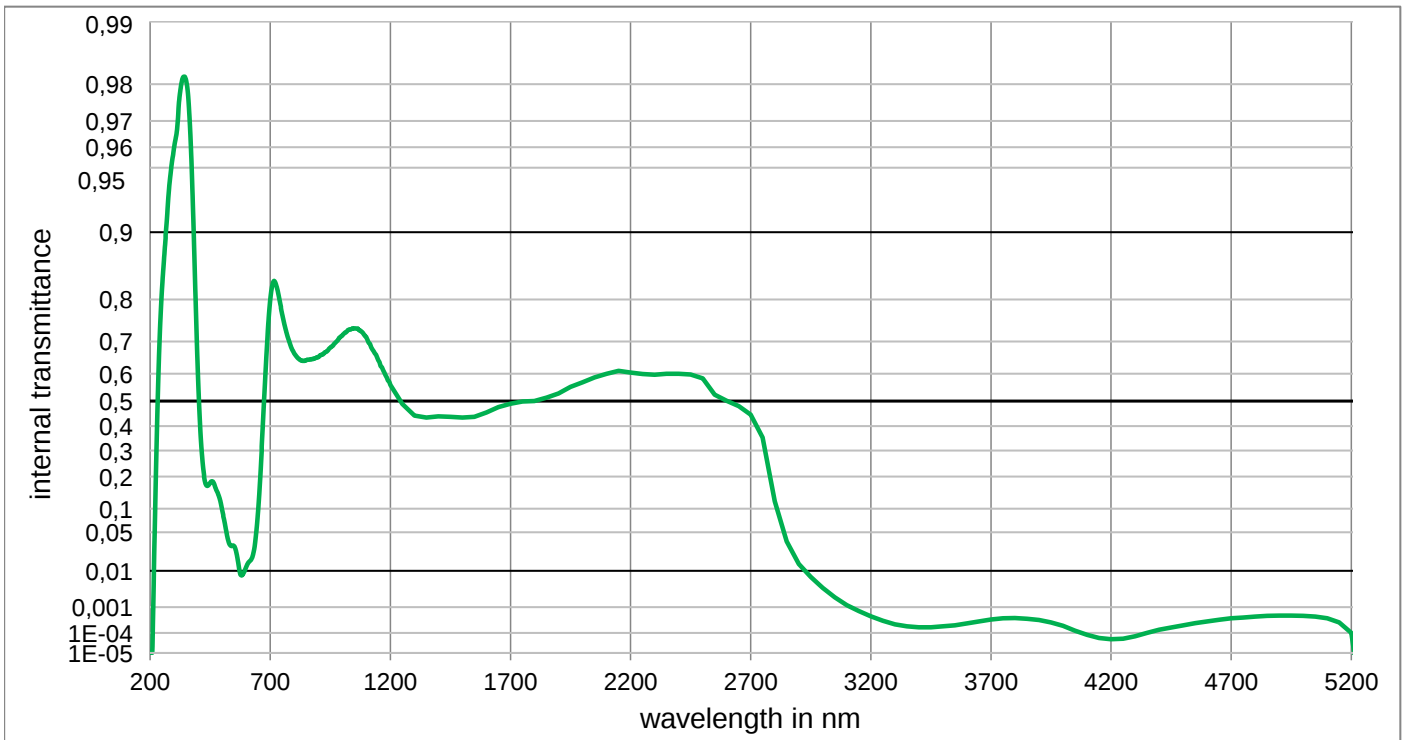Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,00E-05	500	9,500E-02	800	6,650E-01	1100	7,118E-01	2200	6,039E-01	3700	3,581E-04
210	2,234E-05	510	7,000E-02	810	6,550E-01	1110	6,962E-01	2250	5,992E-01	3750	4,036E-04
220	6,900E-02	520	4,600E-02	820	6,476E-01	1120	6,834E-01	2300	5,961E-01	3800	4,130E-04
230	4,500E-01	530	3,300E-02	830	6,436E-01	1130	6,725E-01	2350	6,000E-01	3850	3,873E-04
240	7,180E-01	540	3,041E-02	840	6,420E-01	1140	6,615E-01	2400	6,000E-01	3900	3,451E-04
250	8,260E-01	550	3,015E-02	850	6,443E-01	1150	6,444E-01	2450	5,969E-01	3950	2,780E-04
260	8,790E-01	560	2,200E-02	860	6,463E-01	1160	6,248E-01	2500	5,835E-01	4000	2,000E-04
270	9,120E-01	570	1,136E-02	870	6,476E-01	1170	6,122E-01	2550	5,246E-01	4050	1,271E-04
280	9,390E-01	580	7,810E-03	880	6,487E-01	1180	5,947E-01	2600	5,010E-01	4100	8,166E-05
290	9,520E-01	590	9,020E-03	890	6,518E-01	1190	5,762E-01	2650	4,806E-01	4150	5,902E-05
300	9,600E-01	600	1,203E-02	900	6,543E-01	1200	5,600E-01	2700	4,461E-01	4200	5,093E-05
310	9,656E-01	610	1,514E-02	910	6,606E-01	1250	4,893E-01	2750	3,534E-01	4250	5,433E-05
320	9,757E-01	620	1,703E-02	920	6,628E-01	1300	4,429E-01	2800	1,200E-01	4300	7,000E-05
330	9,802E-01	630	2,304E-02	930	6,694E-01	1350	4,351E-01	2850	3,622E-02	4350	1,009E-04
340	9,816E-01	640	4,400E-02	940	6,745E-01	1400	4,400E-01	2900	1,396E-02	4400	1,371E-04
350	9,809E-01	650	1,010E-01	950	6,826E-01	1450	4,374E-01	2950	7,228E-03	4450	1,726E-04
360	9,761E-01	660	2,270E-01	960	6,876E-01	1500	4,343E-01	3000	3,784E-03	4500	2,113E-04
370	9,600E-01	670	4,140E-01	970	6,962E-01	1550	4,374E-01	3050	2,037E-03	4550	2,570E-04
380	9,120E-01	680	5,950E-01	980	7,030E-01	1600	4,555E-01	3100	1,169E-03	4600	3,000E-04
390	7,870E-01	690	7,270E-01	990	7,112E-01	1650	4,767E-01	3150	7,430E-04	4650	3,516E-04
400	5,700E-01	700	7,990E-01	1000	7,164E-01	1700	4,900E-01	3200	4,775E-04	4700	4,000E-04
410	3,600E-01	710	8,290E-01	1010	7,232E-01	1750	4,979E-01	3250	3,236E-04	4750	4,315E-04
420	2,360E-01	720	8,320E-01	1020	7,278E-01	1800	5,000E-01	3300	2,296E-04	4800	4,688E-04
430	1,780E-01	730	8,180E-01	1030	7,317E-01	1850	5,128E-01	3350	1,910E-04	4850	4,909E-04
440	1,680E-01	740	7,950E-01	1040	7,338E-01	1900	5,293E-01	3400	1,758E-04	4900	5,000E-04
450	1,780E-01	750	7,690E-01	1050	7,344E-01	1950	5,529E-01	3450	1,758E-04	4950	5,000E-04
460	1,830E-01	760	7,430E-01	1060	7,347E-01	2000	5,700E-01	3500	1,910E-04	5000	4,955E-04
470	1,660E-01	770	7,190E-01	1070	7,305E-01	2050	5,874E-01	3550	2,133E-04	5050	4,645E-04
480	1,470E-01	780	6,980E-01	1080	7,267E-01	2100	6,000E-01	3600	2,547E-04	5100	4,000E-04
490	1,260E-01	790	6,789E-01	1090	7,194E-01	2150	6,094E-01	3650	3,000E-04	5150	2,742E-04

Optical properties	
Reflection factor	
P _d = 0,908	
Spectral values guaranteed	
τ _i (254 nm)	≥ 0,06
τ _i (334 nm)	≥ 0,9
τ _i (405 nm)	≤ 0,001
τ _i (694 nm)	≤ 0,26
τ _i (725 nm)	≤ 0,32
Refractive indices	
n _F (486 nm)	= 1,569
n _e (546 nm)	= 1,565
n _d (587,6 nm)	= 1,563
Sellmeier coefficients	
valid from 270 nm to 600 nm	
B ₁	1,3960
B ₂	0,0097
B ₃	0,5658
C ₁	9,230E-03 μm ²
C ₂	4,4000E-02 μm ²
C ₃	96,000 μm ²
Internal quality	
Bubble class	2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,92 g/cm ³	
Knoop hardness	
HK[0.1/20] = 440	

Thermal properties	
Transformation temperature	
T _g = 545 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _{-30°C/+70°C} = 7,8	
α _{20°C/300°C} = 9,0	


Chemical properties	
Chemical resistance	
FR class = 0	
SR class = 3	
AR class = 2.2	
Resistance against humidity	
Sensitive glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colorimetric properties			
	1 mm	2 mm	3 mm
Illuminant D65	x		
	y		
	Y		
	λ _d		
	P _e		
Illuminant A	x		
	y		
	Y		
	λ _d		
	P _e		

Notes
UV
Transmission changes are possible under the action of intense ultraviolet radiation.
Ionically colored glass
Bandpass filter
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

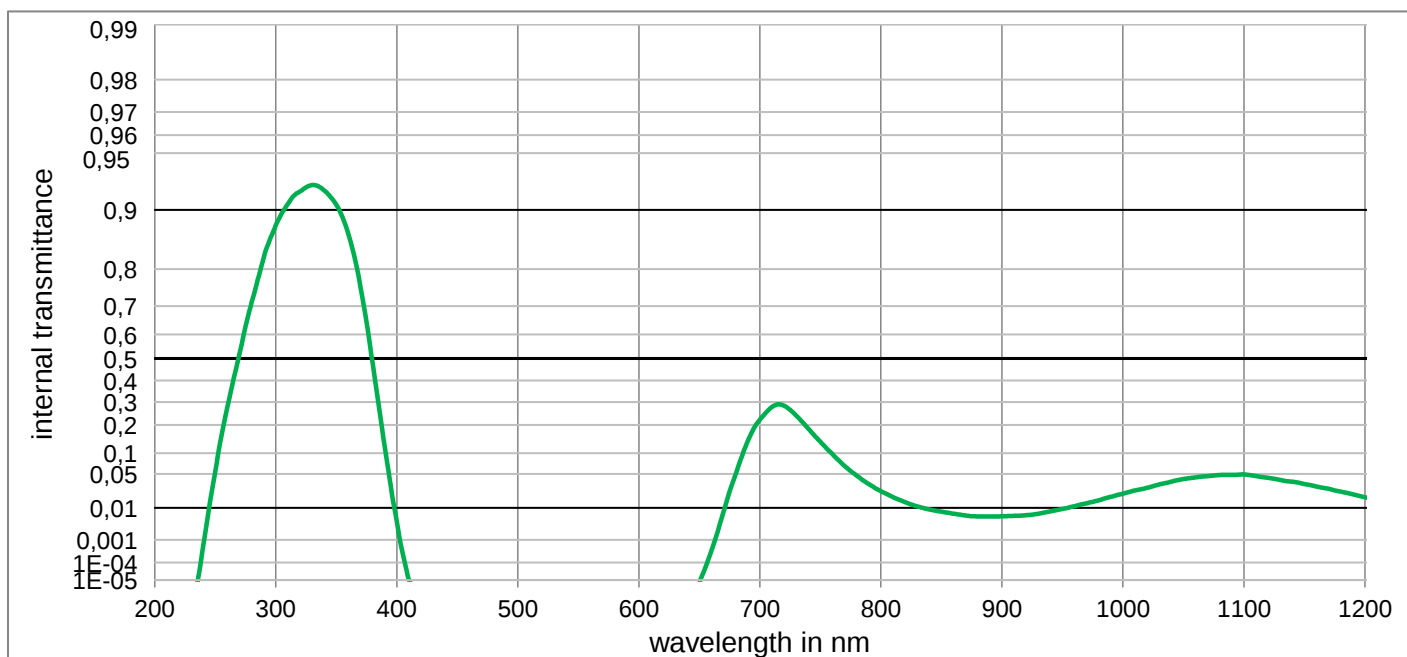


UG11

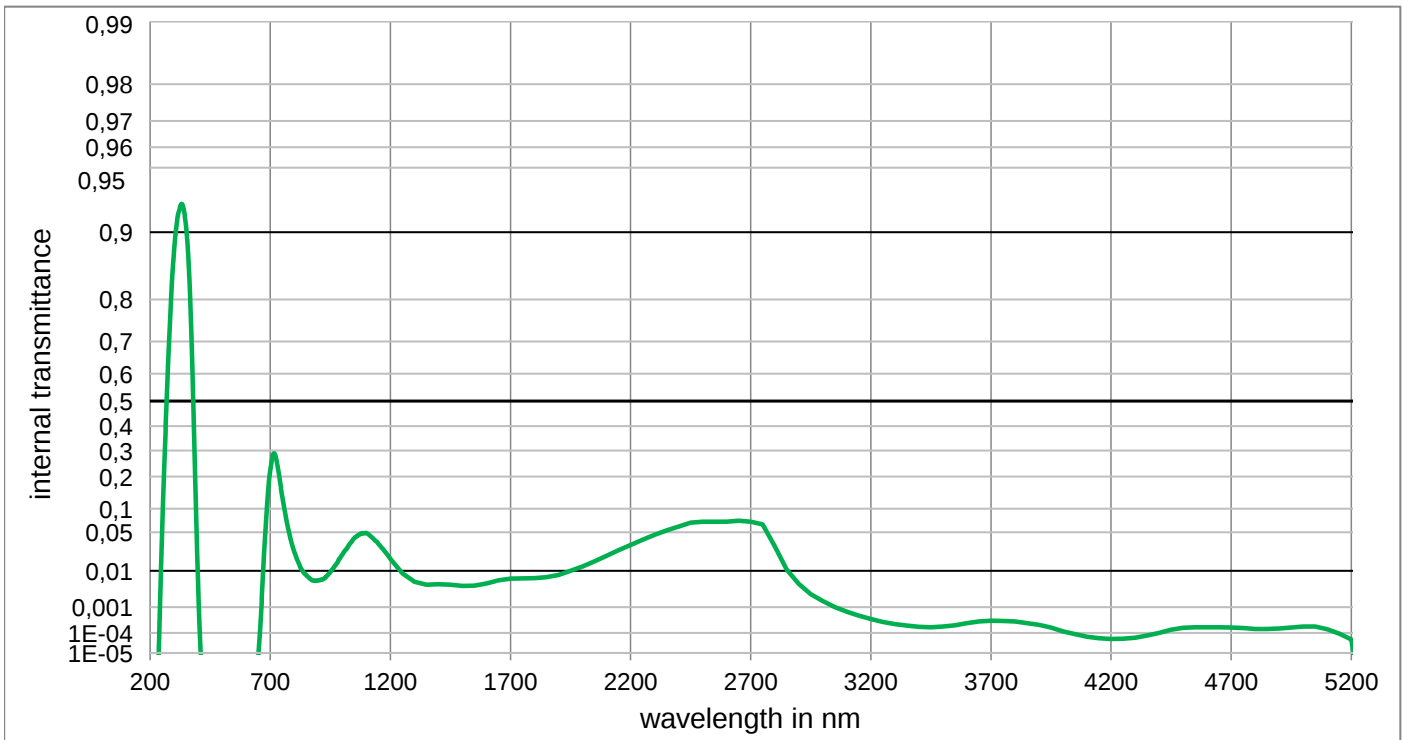Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	< 1,000E-05	800	2,400E-02	1100	4,897E-02	2200	3,160E-02	3700	3,206E-04
210	< 1,000E-05	510	< 1,000E-05	810	1,800E-02	1110	4,608E-02	2250	3,845E-02	3750	3,177E-04
220	< 1,000E-05	520	< 1,000E-05	820	1,382E-02	1120	4,300E-02	2300	4,600E-02	3800	3,000E-04
230	< 1,000E-05	530	< 1,000E-05	830	1,088E-02	1130	3,948E-02	2350	5,309E-02	3850	2,594E-04
240	6,067E-04	540	< 1,000E-05	840	9,121E-03	1140	3,666E-02	2400	6,000E-02	3900	2,213E-04
250	5,610E-02	550	< 1,000E-05	850	7,965E-03	1150	3,325E-02	2450	6,776E-02	3950	1,710E-04
260	2,760E-01	560	< 1,000E-05	860	7,014E-03	1160	2,970E-02	2500	7,000E-02	4000	1,180E-04
270	5,210E-01	570	< 1,000E-05	870	6,255E-03	1170	2,691E-02	2550	7,000E-02	4050	8,954E-05
280	7,120E-01	580	< 1,000E-05	880	5,892E-03	1180	2,354E-02	2600	7,000E-02	4100	6,653E-05
290	8,250E-01	590	< 1,000E-05	890	5,834E-03	1190	2,064E-02	2650	7,161E-02	4150	5,741E-05
300	8,800E-01	600	< 1,000E-05	900	5,948E-03	1200	1,775E-02	2700	7,000E-02	4200	5,236E-05
310	9,070E-01	610	< 1,000E-05	910	6,114E-03	1250	8,800E-03	2750	6,427E-02	4250	5,383E-05
320	9,200E-01	620	< 1,000E-05	920	6,368E-03	1300	5,470E-03	2800	3,000E-02	4300	6,067E-05
330	9,260E-01	630	< 1,000E-05	930	7,000E-03	1350	4,590E-03	2850	1,057E-02	4350	7,621E-05
340	9,210E-01	640	< 1,000E-05	940	8,090E-03	1400	4,770E-03	2900	4,819E-03	4400	1,000E-04
350	9,060E-01	650	< 1,000E-05	950	9,390E-03	1450	4,650E-03	2950	2,547E-03	4450	1,384E-04
360	8,660E-01	660	3,631E-04	960	1,100E-02	1500	4,270E-03	3000	1,589E-03	4500	1,663E-04
370	7,560E-01	670	8,128E-03	970	1,300E-02	1550	4,340E-03	3050	1,000E-03	4550	1,742E-04
380	4,820E-01	680	5,000E-02	980	1,520E-02	1600	5,000E-03	3100	6,966E-04	4600	1,766E-04
390	1,200E-01	690	1,380E-01	990	1,825E-02	1650	5,970E-03	3150	5,000E-04	4650	1,750E-04
400	3,999E-03	700	2,220E-01	1000	2,132E-02	1700	6,600E-03	3200	3,750E-04	4700	1,710E-04
410	1,047E-05	710	2,780E-01	1010	2,498E-02	1750	6,660E-03	3250	2,897E-04	4750	1,633E-04
420	< 1,000E-05	720	2,830E-01	1020	2,809E-02	1800	6,790E-03	3300	2,360E-04	4800	1,503E-04
430	< 1,000E-05	730	2,400E-01	1030	3,263E-02	1850	7,160E-03	3350	2,075E-04	4850	1,496E-04
440	< 1,000E-05	740	1,850E-01	1040	3,673E-02	1900	8,040E-03	3400	1,824E-04	4900	1,560E-04
450	< 1,000E-05	750	1,360E-01	1050	4,100E-02	1950	1,000E-02	3450	1,758E-04	4950	1,726E-04
460	< 1,000E-05	760	9,700E-02	1060	4,375E-02	2000	1,238E-02	3500	1,875E-04	5000	1,866E-04
470	< 1,000E-05	770	6,700E-02	1070	4,599E-02	2050	1,577E-02	3550	2,133E-04	5050	1,875E-04
480	< 1,000E-05	780	4,700E-02	1080	4,800E-02	2100	2,029E-02	3600	2,594E-04	5100	1,435E-04
490	< 1,000E-05	790	3,300E-02	1090	4,828E-02	2150	2,582E-02	3650	3,000E-04	5150	9,376E-05

Optical properties		Mechanical properties		Colorimetric properties									
Reflection factor		Reference thickness		1 mm 2 mm 3 mm									
P _d = 0,877		d = 1,00 mm		Illuminant D65	x	0,344	0,395	0,429					
Spectral values guaranteed		Density			y	0,327	0,356	0,370					
τ _i (405 nm) ≥ 0,9		ρ = 3,59 g/cm³			Y	39,5	29,0	23,5					
τ _i (450 nm) ≤ 0,42		Knoop hardness			λ _d	622 nm	591 nm	590 nm					
τ _i (650 nm) ≥ 0,9		HK[0.1/20] = 701			P _e	0,082	0,305	0,437					
τ _i (800 nm) ≤ 0,01		Thermal properties		Illuminant A	x	0,495	0,534	0,557					
		Transformation temperature			y	0,387	0,390	0,389					
		T _g = 657 °C			Y	41,4	32,2	26,9					
		Thermal expansion in 10 ⁻⁶ /K			λ _d	628 nm	600 nm	599 nm					
		α _[-30°C/+70°C] = 6,1			P _e	0,185	0,478	0,628					
		α _[20°C/300°C] = 7,2		Notes									
				Ionically colored glass									
Refractive indices									Multi bandpass filter				
n _d (587,6 nm) = 1,69				ISO 23364:2021									
Sellmeier coefficients		Chemical properties		Disclaimer									
on request		Chemical resistance							All data without tolerances are to be understood to be reference values.				
		FR class = 1											
		SR class = 52.2											
		AR class = 1.2											
		Resistance against humidity											
		Resistant glass											
Internal quality		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5											
Bubble class	3												

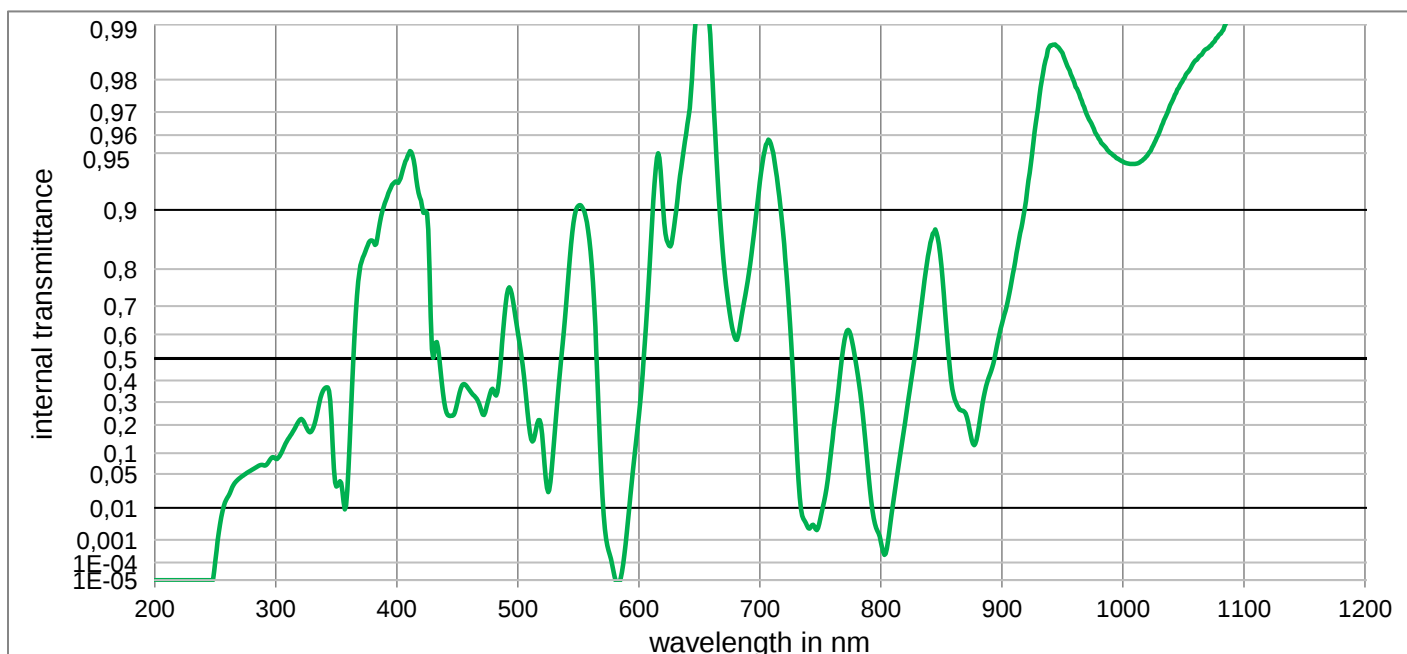

BG36

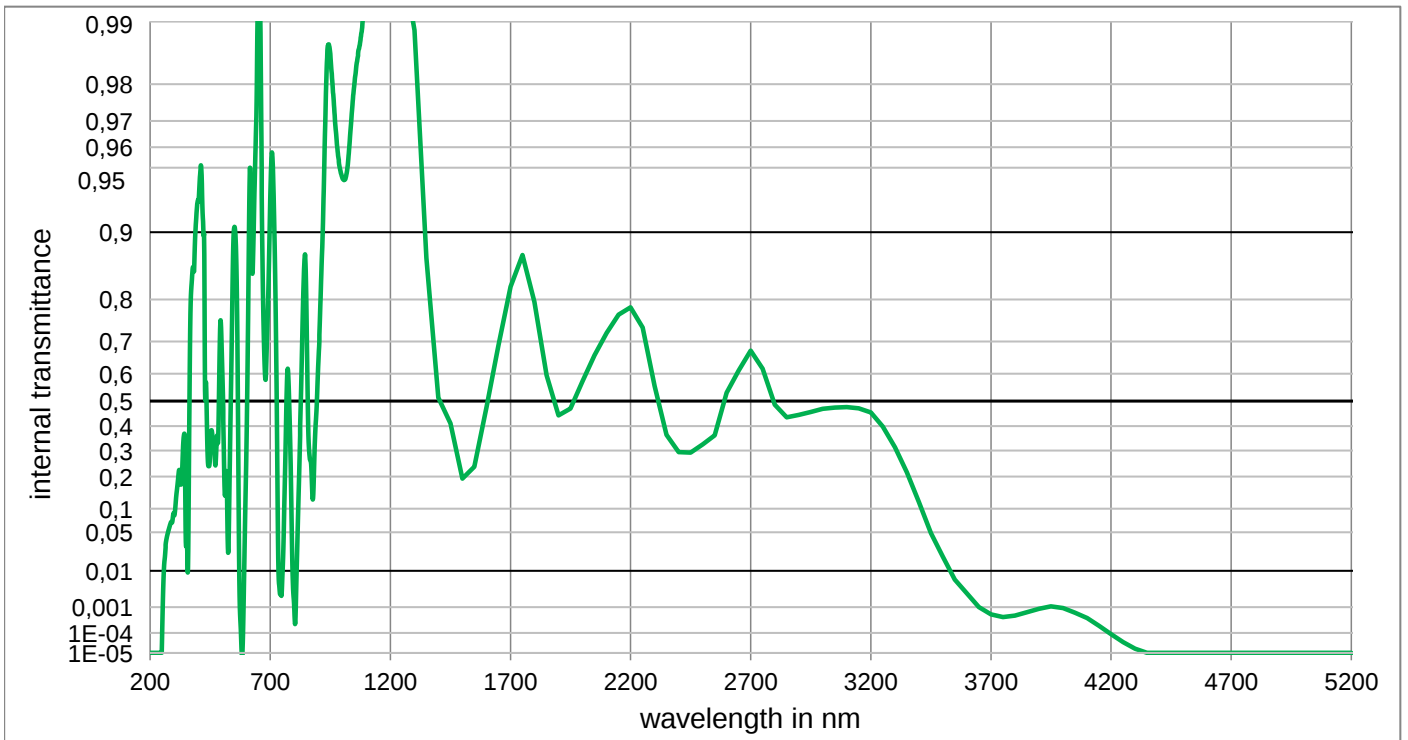Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	6,084E-01	800	8,615E-04	1100	9,947E-01	2200	7,840E-01	3700	5,636E-04
210	< 1,000E-05	510	1,685E-01	810	1,212E-02	1110	9,956E-01	2250	7,370E-01	3750	4,498E-04
220	< 1,000E-05	520	1,625E-01	820	2,111E-01	1120	9,965E-01	2300	5,570E-01	3800	5,035E-04
230	< 1,000E-05	530	1,386E-01	830	5,842E-01	1130	9,973E-01	2350	3,641E-01	3850	6,764E-04
240	< 1,000E-05	540	7,084E-01	840	8,398E-01	1140	9,979E-01	2400	2,940E-01	3900	8,872E-04
250	1,297E-04	550	9,047E-01	850	8,090E-01	1150	9,981E-01	2450	2,914E-01	3950	1,054E-03
260	1,734E-02	560	8,367E-01	860	3,330E-01	1160	9,979E-01	2500	3,250E-01	4000	9,311E-04
270	4,220E-02	570	1,873E-02	870	2,481E-01	1170	9,974E-01	2550	3,616E-01	4050	6,485E-04
280	5,797E-02	580	1,610E-05	880	1,625E-01	1180	9,966E-01	2600	5,320E-01	4100	4,112E-04
290	6,801E-02	590	1,816E-03	890	4,256E-01	1190	9,956E-01	2650	6,110E-01	4150	2,000E-04
300	8,428E-02	600	2,413E-01	900	6,394E-01	1200	9,946E-01	2700	6,740E-01	4200	8,913E-05
310	1,446E-01	610	8,512E-01	910	8,023E-01	1250	9,950E-01	2750	6,170E-01	4250	3,746E-05
320	2,223E-01	620	9,037E-01	920	9,102E-01	1300	9,890E-01	2800	4,856E-01	4300	1,710E-05
330	1,781E-01	630	8,899E-01	930	9,718E-01	1350	8,689E-01	2850	4,360E-01	4350	< 1,000E-05
340	3,601E-01	640	9,649E-01	940	9,870E-01	1400	5,130E-01	2900	4,455E-01	4400	< 1,000E-05
350	2,978E-02	650	9,962E-01	950	9,857E-01	1450	4,112E-01	2950	4,570E-01	4450	< 1,000E-05
360	6,104E-02	660	9,844E-01	960	9,792E-01	1500	1,930E-01	3000	4,695E-01	4500	< 1,000E-05
370	8,080E-01	670	8,158E-01	970	9,692E-01	1550	2,365E-01	3050	4,748E-01	4550	< 1,000E-05
380	8,558E-01	680	5,792E-01	980	9,582E-01	1600	4,754E-01	3100	4,767E-01	4600	< 1,000E-05
390	9,077E-01	690	7,712E-01	990	9,499E-01	1650	6,889E-01	3150	4,720E-01	4650	< 1,000E-05
400	9,286E-01	700	9,289E-01	1000	9,445E-01	1700	8,240E-01	3200	4,547E-01	4700	< 1,000E-05
410	9,496E-01	710	9,529E-01	1010	9,429E-01	1750	8,730E-01	3250	3,980E-01	4750	< 1,000E-05
420	9,107E-01	720	8,502E-01	1020	9,484E-01	1800	7,951E-01	3300	3,137E-01	4800	< 1,000E-05
430	5,033E-01	730	1,533E-01	1030	9,614E-01	1850	5,949E-01	3350	2,154E-01	4850	< 1,000E-05
440	2,722E-01	740	2,600E-03	1040	9,731E-01	1900	4,433E-01	3400	1,186E-01	4900	< 1,000E-05
450	2,957E-01	750	5,260E-03	1050	9,801E-01	1950	4,709E-01	3450	4,861E-02	4950	< 1,000E-05
460	3,560E-01	760	1,460E-01	1060	9,843E-01	2000	5,741E-01	3500	1,952E-02	5000	< 1,000E-05
470	2,574E-01	770	5,782E-01	1070	9,865E-01	2050	6,600E-01	3550	6,251E-03	5050	< 1,000E-05
480	3,513E-01	780	4,586E-01	1080	9,887E-01	2100	7,230E-01	3600	2,675E-03	5100	< 1,000E-05
490	7,056E-01	790	4,187E-02	1090	9,918E-01	2150	7,680E-01	3650	1,009E-03	5150	< 1,000E-05

Optical properties		
Reflection factor		
$P_d = 0,908$		
Spectral values guaranteed		
τ_i (360 nm)	=	0,414 ± 0,12
Refractive indices		
n_d (587,6 nm)	=	1,562
Sellmeier coefficients		
on request		
Internal quality		
Bubble class	-	


Mechanical properties
Reference thickness
$d = 2,00 \text{ mm}$
Density
$\rho = 2,88 \text{ g/cm}^3$
Knoop hardness
$HK[0.1/20] = 529$

Thermal properties	
Transformation temperature	
$T_g = 452\text{ }^{\circ}\text{C}$	
Thermal expansion in	$10^{-6}/\text{K}$
$\alpha_{(20^{\circ}\text{C}/300^{\circ}\text{C})} =$	11,5


Chemical properties
Chemical resistance
FR class = 1
SR class = 1.2
AR class = 1.0
Resistance against humidity
Resistant glass
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5

Colorimetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,314	0,316	0,317
	y	0,331	0,333	0,335
	Y	90,6	90,4	90,2
	λ_d	572,1	572,1	572,2
	P _e	0,010	0,020	0,030
Illuminant A	x	0,449	0,450	0,451
	y	0,408	0,409	0,410
	Y	90,7	90,6	90,4
	λ_d	581,8	581,8	581,9
	P _e	0,014	0,028	0,042

Notes
Ionically colored glass
Samarium doped
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

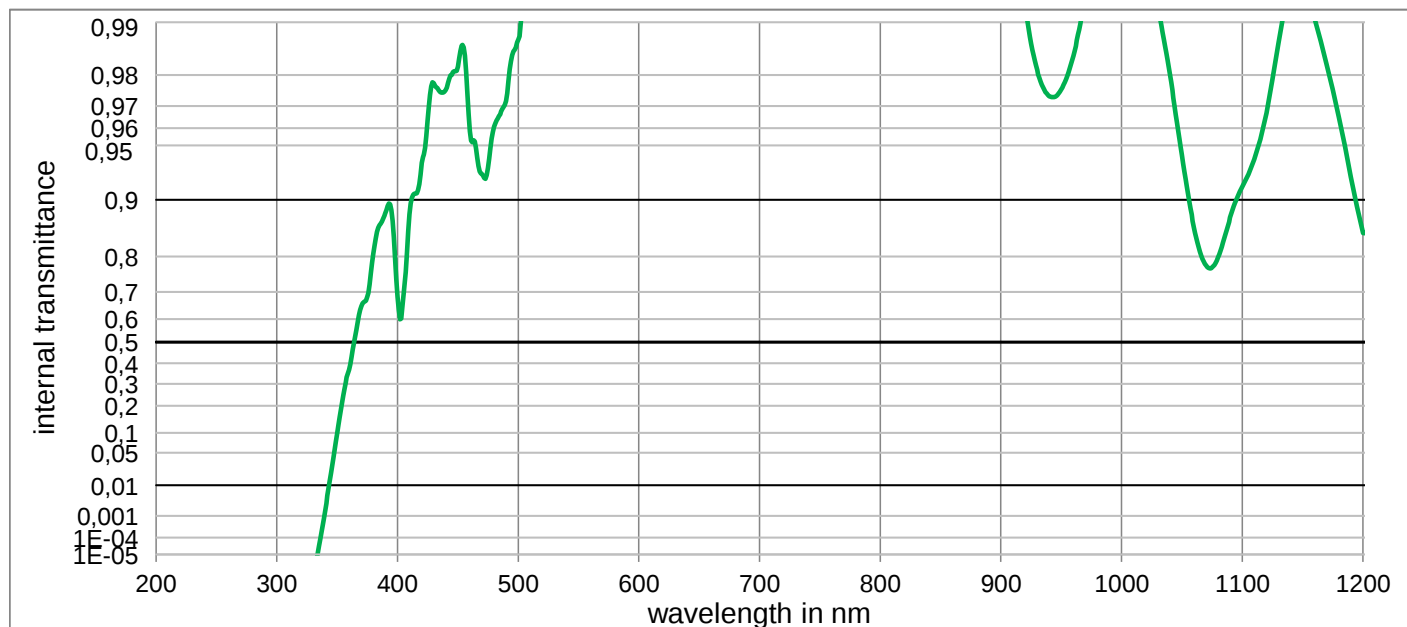

S7005

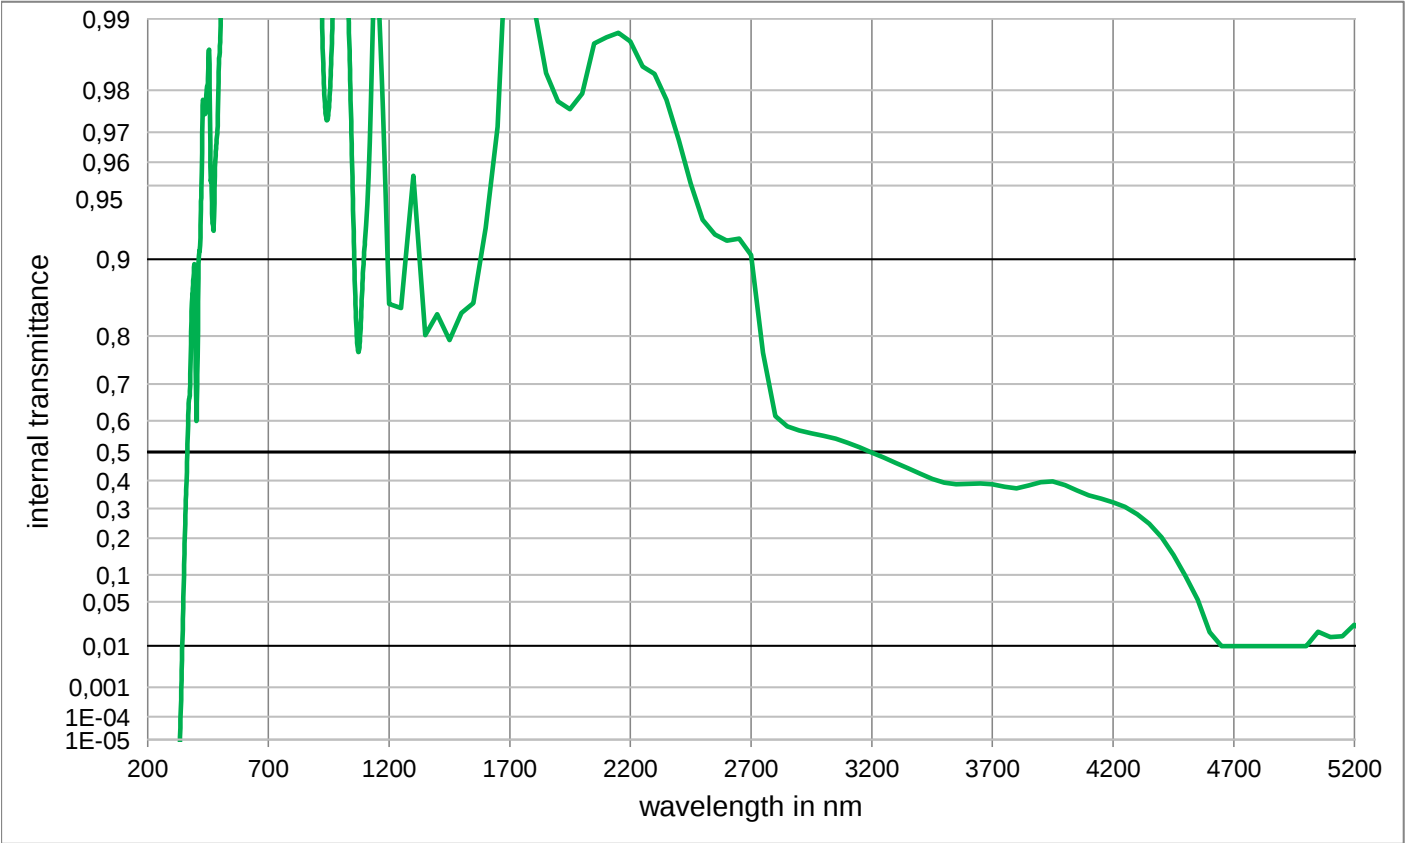

Internal transmittance τ_i at reference thickness									
The internal transmittance values, tabulated and graphically represented, are reference values only									
λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,874E-01	800	9,984E-01	1100	9,151E-01	2200	9,875E-01
210	< 1,0E-05	510	9,967E-01	810	9,987E-01	1110	9,401E-01	2250	9,841E-01
220	< 1,0E-05	520	9,980E-01	820	9,989E-01	1120	9,671E-01	2300	9,829E-01
230	< 1,0E-05	530	9,963E-01	830	9,989E-01	1130	9,868E-01	2350	9,781E-01
240	< 1,0E-05	540	9,981E-01	840	9,981E-01	1140	9,942E-01	2400	9,677E-01
250	< 1,0E-05	550	9,975E-01	850	9,983E-01	1150	9,941E-01	2450	9,510E-01
260	< 1,0E-05	560	9,963E-01	860	9,985E-01	1160	9,905E-01	2500	9,310E-01
270	< 1,0E-05	570	9,980E-01	870	9,989E-01	1170	9,826E-01	2550	9,205E-01
280	< 1,0E-05	580	9,999E-01	880	9,993E-01	1180	9,653E-01	2600	9,157E-01
290	< 1,0E-05	590	9,968E-01	890	9,985E-01	1190	9,252E-01	2650	9,175E-01
300	< 1,0E-05	600	9,969E-01	900	9,977E-01	1200	8,493E-01	2700	9,039E-01
310	< 1,0E-05	610	9,970E-01	910	9,981E-01	1250	8,438E-01	2750	7,688E-01
320	< 1,000E-05	620	9,971E-01	920	9,920E-01	1300	9,545E-01	2800	6,136E-01
330	< 1,000E-05	630	9,973E-01	930	9,813E-01	1350	8,013E-01	2850	5,831E-01
340	1,598E-03	640	9,973E-01	940	9,737E-01	1400	8,351E-01	2900	5,707E-01
350	9,824E-02	650	9,975E-01	950	9,758E-01	1450	7,926E-01	2950	5,612E-01
360	3,675E-01	660	9,979E-01	960	9,844E-01	1500	8,367E-01	3000	5,532E-01
370	6,496E-01	670	9,975E-01	970	9,930E-01	1550	8,509E-01	3050	5,439E-01
380	8,064E-01	680	9,978E-01	980	9,984E-01	1600	9,254E-01	3100	5,313E-01
390	8,817E-01	690	9,982E-01	990	9,973E-01	1650	9,715E-01	3150	5,159E-01
400	6,832E-01	700	9,983E-01	1000	9,974E-01	1700	9,979E-01	3200	4,984E-01
410	8,806E-01	710	9,982E-01	1010	9,994E-01	1750	9,968E-01	3250	4,804E-01
420	9,374E-01	720	9,985E-01	1020	9,969E-01	1800	9,912E-01	3300	4,624E-01
430	9,777E-01	730	9,986E-01	1030	9,921E-01	1850	9,831E-01	3350	4,439E-01
440	9,756E-01	740	9,982E-01	1040	9,801E-01	1900	9,778E-01	3400	4,247E-01
450	9,821E-01	750	9,987E-01	1050	9,434E-01	1950	9,760E-01	3450	4,063E-01
460	9,584E-01	760	9,978E-01	1060	8,591E-01	2000	9,794E-01	3500	3,930E-01
470	9,279E-01	770	9,989E-01	1070	7,772E-01	2050	9,873E-01	3550	3,874E-01
480	9,607E-01	780	9,988E-01	1080	7,978E-01	2100	9,880E-01	3600	3,887E-01
490	9,718E-01	790	9,983E-01	1090	8,752E-01	2150	9,885E-01	3650	3,896E-01
								3700	3,872E-01
								3750	3,775E-01
								3800	3,725E-01
								3850	3,825E-01
								3900	3,944E-01
								3950	3,970E-01
								4000	3,839E-01
								4050	3,641E-01
								4100	3,467E-01
								4150	3,344E-01
								4200	3,220E-01
								4250	3,065E-01
								4300	2,805E-01
								4350	2,469E-01
								4400	2,034E-01
								4450	1,508E-01
								4500	9,816E-02
								4550	5,334E-02
								4600	1,783E-02
								4650	9,925E-03
								4700	9,925E-03
								4750	9,925E-03
								4800	9,925E-03
								4850	9,925E-03
								4900	9,925E-03
								4950	9,925E-03
								5000	9,925E-03
								5050	1,806E-02
								5100	1,447E-02
								5150	1,512E-02

Optical properties	
Reflection factor	
P _d = 0,908	
Spectral values guaranteed	
τ _i (364 nm)	= 0,414
τ _i (500 nm)	≥ 0,85
Refractive indices	
n _F (486 nm)	= 1,567
n _e (546 nm)	= 1,562
n _d (587,6 nm)	= 1,560
Sellmeier coefficients	
valid from 440 nm to 1550 nm	
B ₁	1,3895
B ₂	0,0016
B ₃	0,7429
C ₁	1,066E-02 μm ²
C ₂	4,5581E-03 μm ²
C ₃	100,000 μm ²
Internal quality	
Bubble class	1


Mechanical properties	
Reference thickness	
d = 2,00 mm	
Density	
ρ = 2,88 g/cm ³	
Knoop hardness	
HK[0.1/20] = 536	

Thermal properties	
Transformation temperature	
T _g = 452 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _(-30°C/+70°C) = 9,2	
α _(20°C/300°C) = 11,5	


Chemical properties	
Chemical resistance	
FR class = 1	
SR class = 1.2	
AR class = 1.0	
Resistance against humidity	

Colorimetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,316	0,319	0,322
	y	0,334	0,338	0,343
	Y	90,3	89,9	89,4
	λ _d	572 nm	572 nm	573 nm
	P _e	0,023	0,044	0,065
Illuminant A	x	0,450	0,452	0,455
	y	0,410	0,412	0,414
	Y	90,5	90,3	90,0
	λ _d	582 nm	582 nm	582 nm
	P _e	0,033	0,063	0,092

Notes
Ionically colored glass
Samarium doped
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

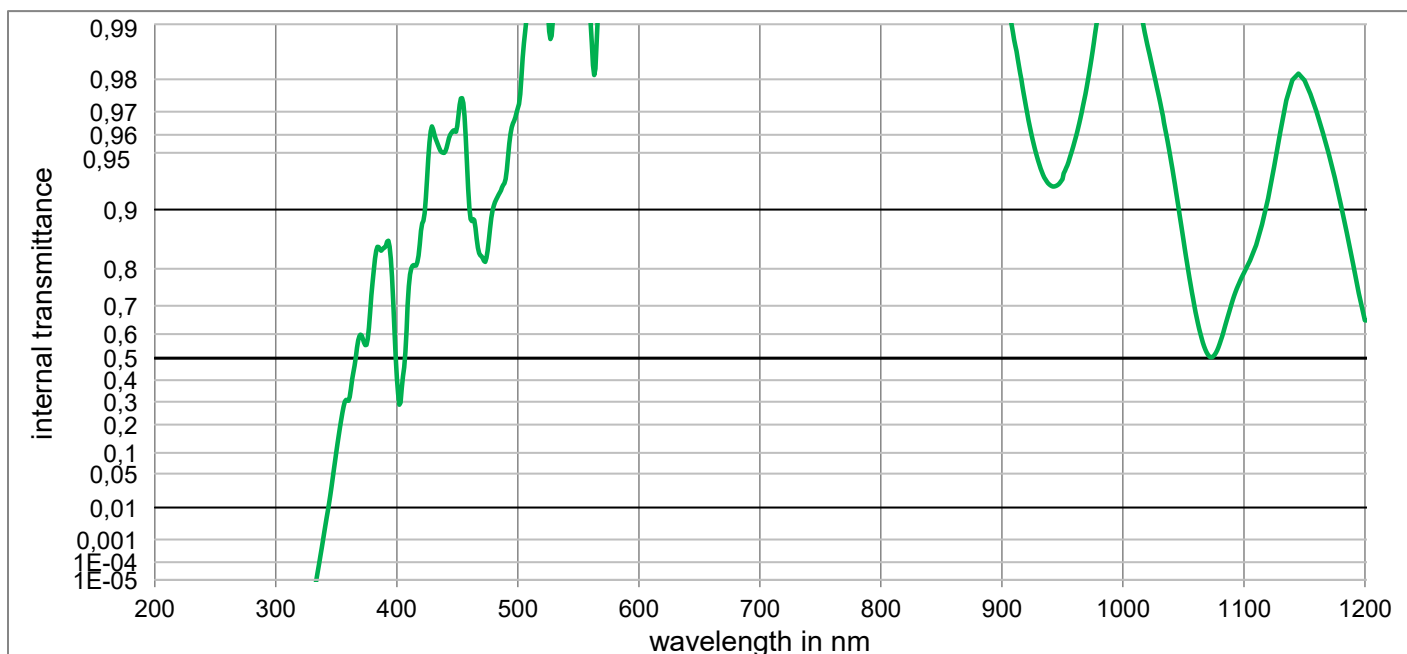

S7010N

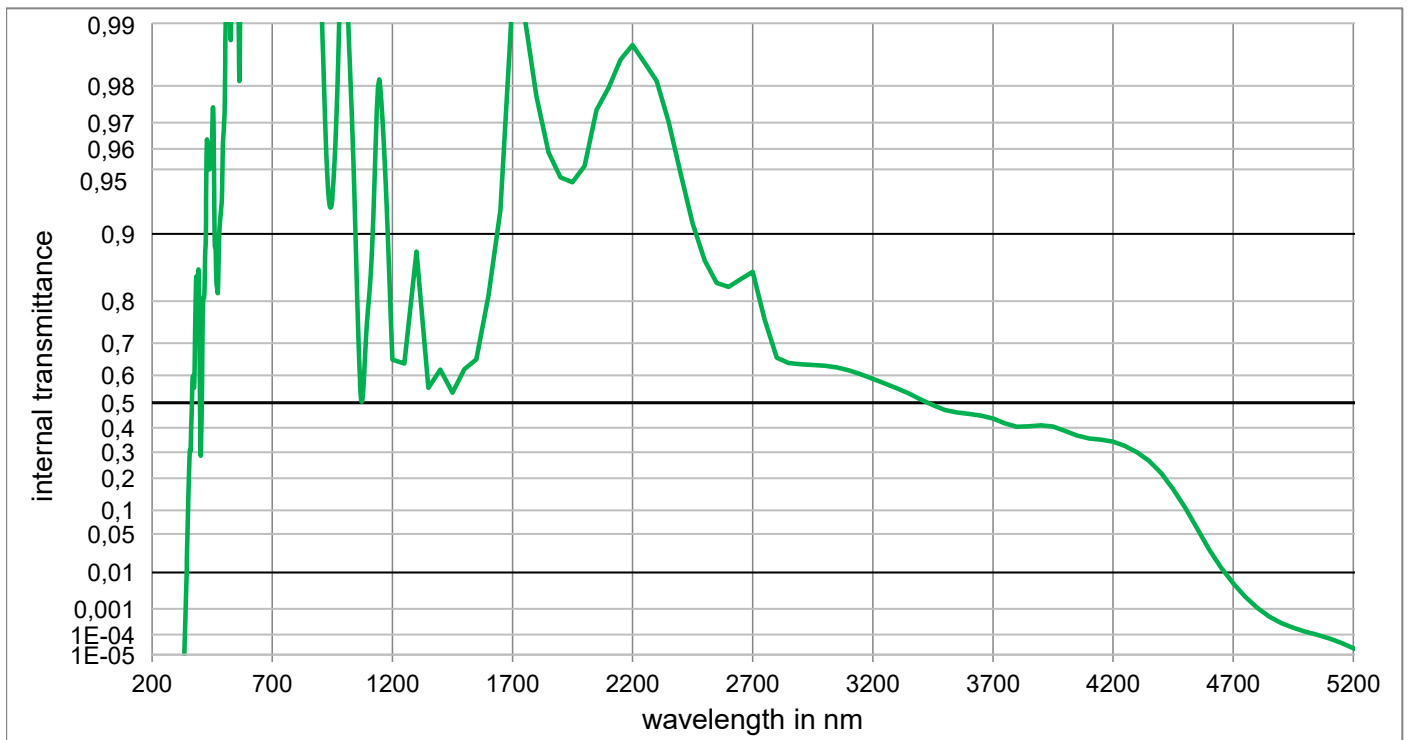
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,713E-01	800	9,992E-01	1100	7,904E-01	2200	9,873E-01	3700	4,375E-01
210	< 1,000E-05	510	9,947E-01	810	9,995E-01	1110	8,478E-01	2250	9,845E-01	3750	4,176E-01
220	< 1,000E-05	520	9,973E-01	820	9,991E-01	1120	9,123E-01	2300	9,811E-01	3800	4,038E-01
230	< 1,000E-05	530	9,927E-01	830	9,993E-01	1130	9,613E-01	2350	9,704E-01	3850	4,062E-01
240	< 1,000E-05	540	9,965E-01	840	9,989E-01	1140	9,799E-01	2400	9,475E-01	3900	4,102E-01
250	< 1,000E-05	550	9,949E-01	850	9,986E-01	1150	9,797E-01	2450	9,106E-01	3950	4,048E-01
260	< 1,000E-05	560	9,903E-01	860	9,977E-01	1160	9,701E-01	2500	8,676E-01	4000	3,874E-01
270	< 1,000E-05	570	9,952E-01	870	9,993E-01	1170	9,496E-01	2550	8,334E-01	4050	3,685E-01
280	< 1,000E-05	580	9,995E-01	880	9,989E-01	1180	9,061E-01	2600	8,267E-01	4100	3,564E-01
290	< 1,000E-05	590	9,999E-01	890	9,976E-01	1190	8,117E-01	2650	8,399E-01	4150	3,516E-01
300	< 1,000E-05	600	9,970E-01	900	9,949E-01	1200	6,513E-01	2700	8,516E-01	4200	3,436E-01
310	< 1,000E-05	610	9,974E-01	910	9,879E-01	1250	6,393E-01	2750	7,606E-01	4250	3,254E-01
320	< 1,000E-05	620	9,975E-01	920	9,718E-01	1300	8,795E-01	2800	6,575E-01	4300	2,994E-01
330	< 1,000E-05	630	9,977E-01	930	9,450E-01	1350	5,560E-01	2850	6,406E-01	4350	2,655E-01
340	1,751E-03	640	9,979E-01	940	9,254E-01	1400	6,197E-01	2900	6,365E-01	4400	2,188E-01
350	1,027E-01	650	9,981E-01	950	9,309E-01	1450	5,378E-01	2950	6,345E-01	4450	1,625E-01
360	3,035E-01	660	9,982E-01	960	9,561E-01	1500	6,209E-01	3000	6,321E-01	4500	1,064E-01
370	5,979E-01	670	9,979E-01	970	9,777E-01	1550	6,524E-01	3050	6,265E-01	4550	5,990E-02
380	7,672E-01	680	9,984E-01	980	9,918E-01	1600	8,107E-01	3100	6,167E-01	4600	2,838E-02
390	8,431E-01	690	9,988E-01	990	9,972E-01	1650	9,225E-01	3150	6,036E-01	4650	1,261E-02
400	4,080E-01	700	9,989E-01	1000	9,973E-01	1700	9,925E-01	3200	5,884E-01	4700	5,539E-03
410	7,567E-01	710	9,988E-01	1010	9,941E-01	1750	9,908E-01	3250	5,718E-01	4750	2,426E-03
420	8,714E-01	720	9,989E-01	1020	9,872E-01	1800	9,775E-01	3300	5,542E-01	4800	1,089E-03
430	9,625E-01	730	9,990E-01	1030	9,746E-01	1850	9,583E-01	3350	5,352E-01	4850	5,416E-04
440	9,508E-01	740	9,987E-01	1040	9,440E-01	1900	9,454E-01	3400	5,126E-01	4900	3,059E-04
450	9,640E-01	750	9,992E-01	1050	8,572E-01	1950	9,425E-01	3450	4,911E-01	4950	1,974E-04
460	9,014E-01	760	9,983E-01	1060	6,792E-01	2000	9,518E-01	3500	4,720E-01	5000	1,355E-04
470	8,266E-01	770	9,990E-01	1070	5,165E-01	2050	9,739E-01	3550	4,617E-01	5050	9,711E-05
480	9,043E-01	780	9,990E-01	1080	5,608E-01	2100	9,796E-01	3600	4,564E-01	5100	6,627E-05
490	9,311E-01	790	9,990E-01	1090	7,086E-01	2150	9,850E-01	3650	4,492E-01	5150	4,091E-05

S8008G

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,912$	$d = 1,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed	Density	x
	$\rho = 2,78 \text{ g/cm}^3$	y
	Knoop hardness	Y
	$HK[0.1/20] = 569$	λ_d
		P_e
	Thermal properties	Illuminant A
	Transformation temperature	x
	$T_g = 480 \text{ }^\circ\text{C}$	y
	Thermal expansion in $10^{-6}/\text{K}$	Y
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,6$	λ_d
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,0$	P_e
Refractive indices	Chemical properties	Notes
$n_h (404,7 \text{ nm}) = 1,566$	Chemical resistance	
$n_e (546 \text{ nm}) = 1,551$	FR class	Ionically colored glass
$n_d (587,6 \text{ nm}) = 1,548$	SR class = 1	Contrast enhancement filter
	AR class = 1	
Sellmeier coefficients	Resistance against humidity	ISO 23364:2021
valid from 440 nm to 1550 nm	Resistant glass	
$B_1 = 0,8874$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	Disclaimer
$B_2 = 0,4659$		All data without tolerances are to be understood to be reference values.
$B_3 = 21,3145$		
$C_1 = 1,137\text{E-}02 \text{ } \mu\text{m}^2$		
$C_2 = 1,1165\text{E-}02 \text{ } \mu\text{m}^2$		
$C_3 = 3495,165 \text{ } \mu\text{m}^2$		
Internal quality		
Bubble class 0		

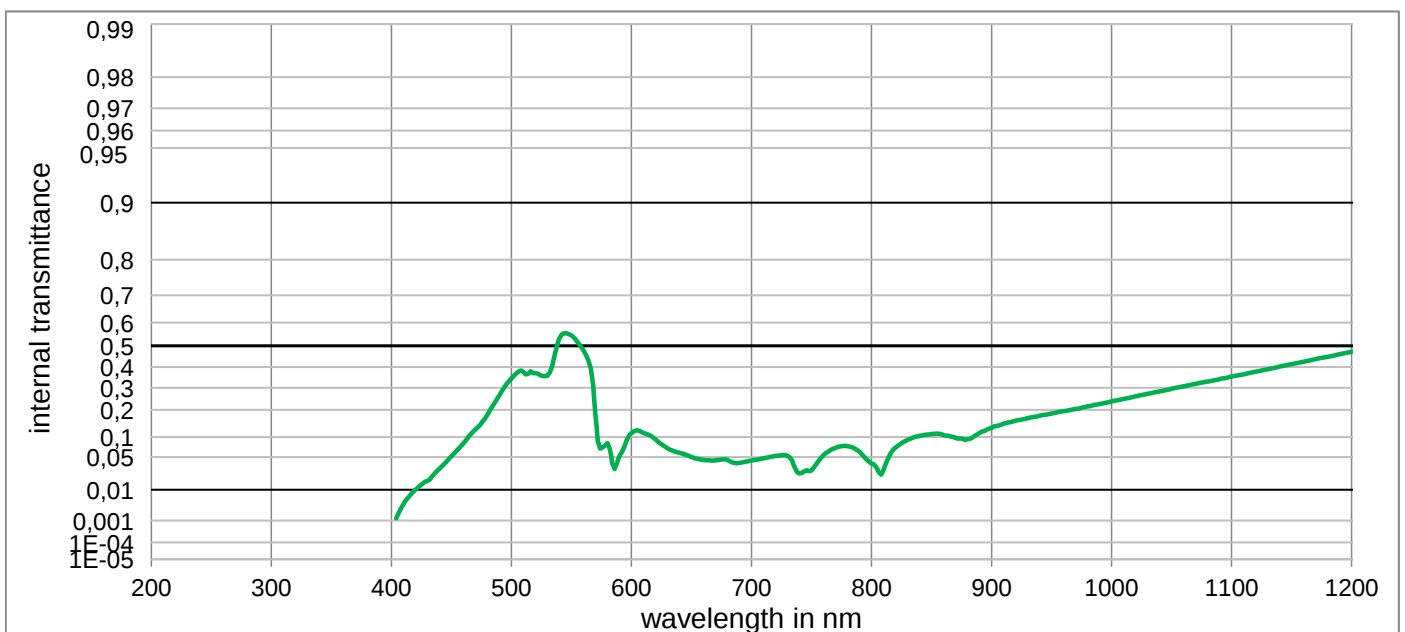


S8008G

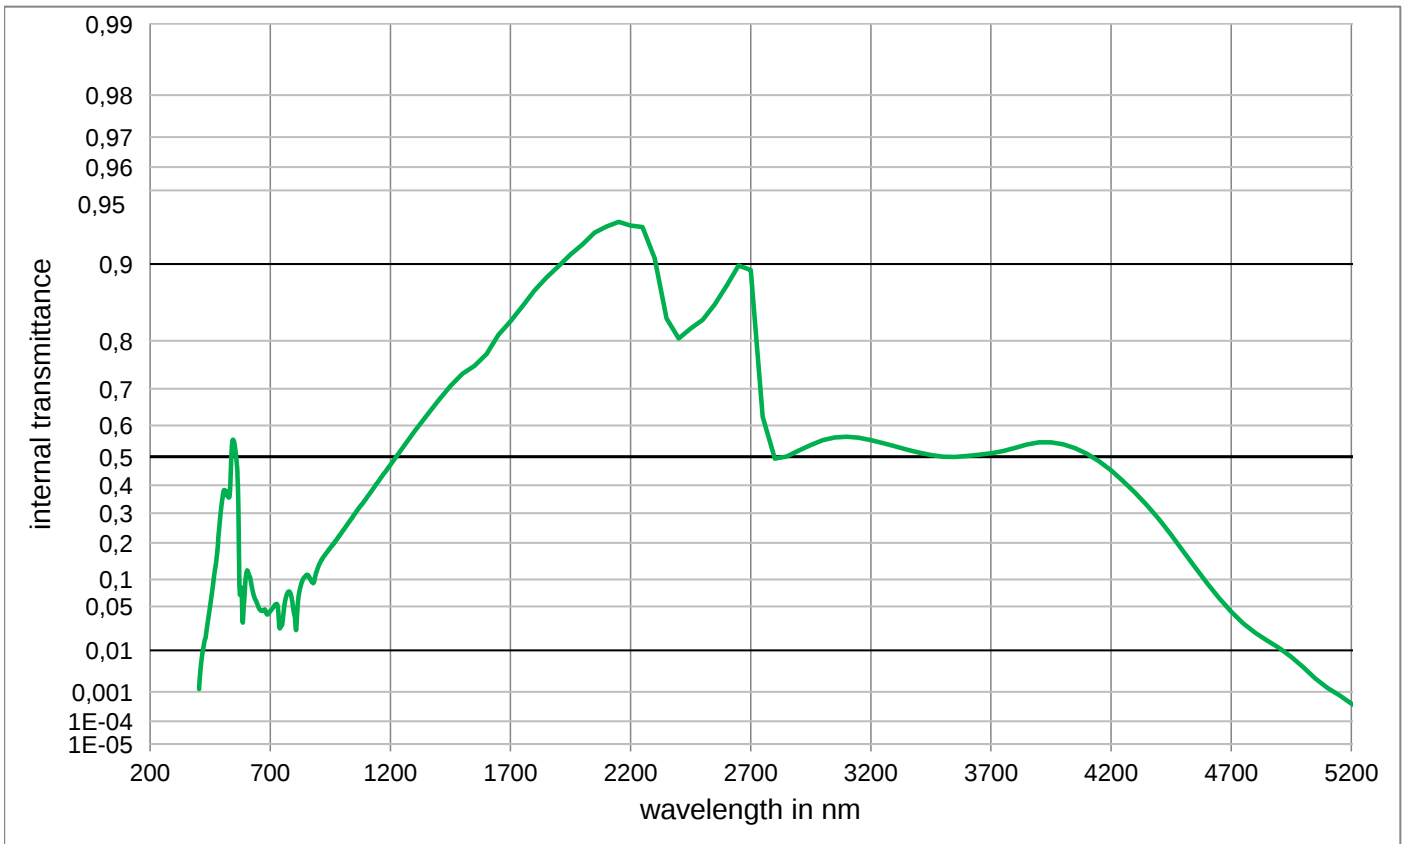Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	3,449E-01	800	3,835E-02	1100	3,535E-01	2200	9,303E-01	3700	5,118E-01
210	< 1,0E-05	510	3,761E-01	810	2,828E-02	1110	3,650E-01	2250	9,292E-01	3750	5,188E-01
220	< 1,0E-05	520	3,701E-01	820	7,119E-02	1120	3,779E-01	2300	9,054E-01	3800	5,291E-01
230	< 1,0E-05	530	3,578E-01	830	9,166E-02	1130	3,891E-01	2350	8,359E-01	3850	5,408E-01
240	< 1,0E-05	540	5,335E-01	840	1,038E-01	1140	4,021E-01	2400	8,040E-01	3900	5,474E-01
250	< 1,0E-05	550	5,462E-01	850	1,097E-01	1150	4,136E-01	2450	8,206E-01	3950	5,475E-01
260	< 1,0E-05	560	4,795E-01	860	1,057E-01	1160	4,259E-01	2500	8,337E-01	4000	5,411E-01
270	< 1,0E-05	570	1,834E-01	870	9,770E-02	1170	4,384E-01	2550	8,554E-01	4050	5,286E-01
280	< 1,0E-05	580	8,299E-02	880	9,302E-02	1180	4,488E-01	2600	8,778E-01	4100	5,098E-01
290	< 1,0E-05	590	5,203E-02	890	1,124E-01	1190	4,617E-01	2650	8,986E-01	4150	4,845E-01
300	< 1,0E-05	600	1,122E-01	900	1,301E-01	1200	4,725E-01	2700	8,943E-01	4200	4,530E-01
310	< 1,0E-05	610	1,127E-01	910	1,449E-01	1250	5,288E-01	2750	6,253E-01	4250	4,152E-01
320	< 1,000E-05	620	9,318E-02	920	1,560E-01	1300	5,811E-01	2800	4,937E-01	4300	3,734E-01
330	< 1,000E-05	630	6,941E-02	930	1,658E-01	1350	6,280E-01	2850	5,009E-01	4350	3,278E-01
340	< 1,000E-05	640	5,888E-02	940	1,757E-01	1400	6,701E-01	2900	5,203E-01	4400	2,778E-01
350	< 1,000E-05	650	5,005E-02	950	1,848E-01	1450	7,065E-01	2950	5,390E-01	4450	2,258E-01
360	< 1,000E-05	660	4,456E-02	960	1,948E-01	1500	7,348E-01	3000	5,543E-01	4500	1,749E-01
370	< 1,000E-05	670	4,374E-02	970	2,037E-01	1550	7,519E-01	3050	5,634E-01	4550	1,294E-01
380	< 1,000E-05	680	4,445E-02	980	2,149E-01	1600	7,756E-01	3100	5,656E-01	4600	9,202E-02
390	< 1,000E-05	690	3,929E-02	990	2,249E-01	1650	8,104E-01	3150	5,620E-01	4650	6,337E-02
400	< 1,000E-05	700	4,328E-02	1000	2,371E-01	1700	8,315E-01	3200	5,546E-01	4700	4,275E-02
410	3,762E-03	710	4,748E-02	1010	2,480E-01	1750	8,530E-01	3250	5,450E-01	4750	2,920E-02
420	9,953E-03	720	5,215E-02	1020	2,598E-01	1800	8,725E-01	3300	5,346E-01	4800	2,065E-02
430	1,650E-02	730	5,249E-02	1030	2,716E-01	1850	8,867E-01	3350	5,240E-01	4850	1,526E-02
440	3,046E-02	740	2,429E-02	1040	2,827E-01	1900	8,979E-01	3400	5,139E-01	4900	1,114E-02
450	5,121E-02	750	2,797E-02	1050	2,950E-01	1950	9,084E-01	3450	5,054E-01	4950	7,390E-03
460	8,230E-02	760	5,401E-02	1060	3,073E-01	2000	9,168E-01	3500	5,000E-01	5000	4,413E-03
470	1,248E-01	770	7,056E-02	1070	3,189E-01	2050	9,254E-01	3550	4,990E-01	5050	2,345E-03
480	1,794E-01	780	7,483E-02	1080	3,307E-01	2100	9,295E-01	3600	5,022E-01	5100	1,315E-03
490	2,659E-01	790	6,097E-02	1090	3,420E-01	2150	9,326E-01	3650	5,062E-01	5150	7,920E-04

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm2 mm3 mm
$P_d = 0,915$	$d = 3,50 \text{ mm}$	
Spectral values guaranteed	Density	Illuminant D65
$\tau_i (445 \text{ nm}) = 0,15 \pm 0,025$	$\rho = 2,70 \text{ g/cm}^3$	x
$\tau_i (555 \text{ nm}) = 0,305 \pm 0,035$	Knoop hardness	y
$\tau_i (630 \text{ nm}) = 0,275 \pm 0,035$	HK[0.1/20]	Y
		λ_d
		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	
	Transformation temperature	
	$T_g = 510 \text{ }^\circ\text{C}$	
	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha (20^\circ\text{C}/300^\circ\text{C}) = 10,8$	
Sellmeier coefficients	Chemical properties	
on request	Chemical resistance	
	FR class = 0	Ionically colored glass
	SR class = 1.0	Contrast enhancement filter
	AR class = 1.0	
	Resistance against humidity	ISO 23364:2021
	Resistant glass	
	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
Internal quality		Disclaimer
Bubble class 0		All data without tolerances are to be understood to be reference values.

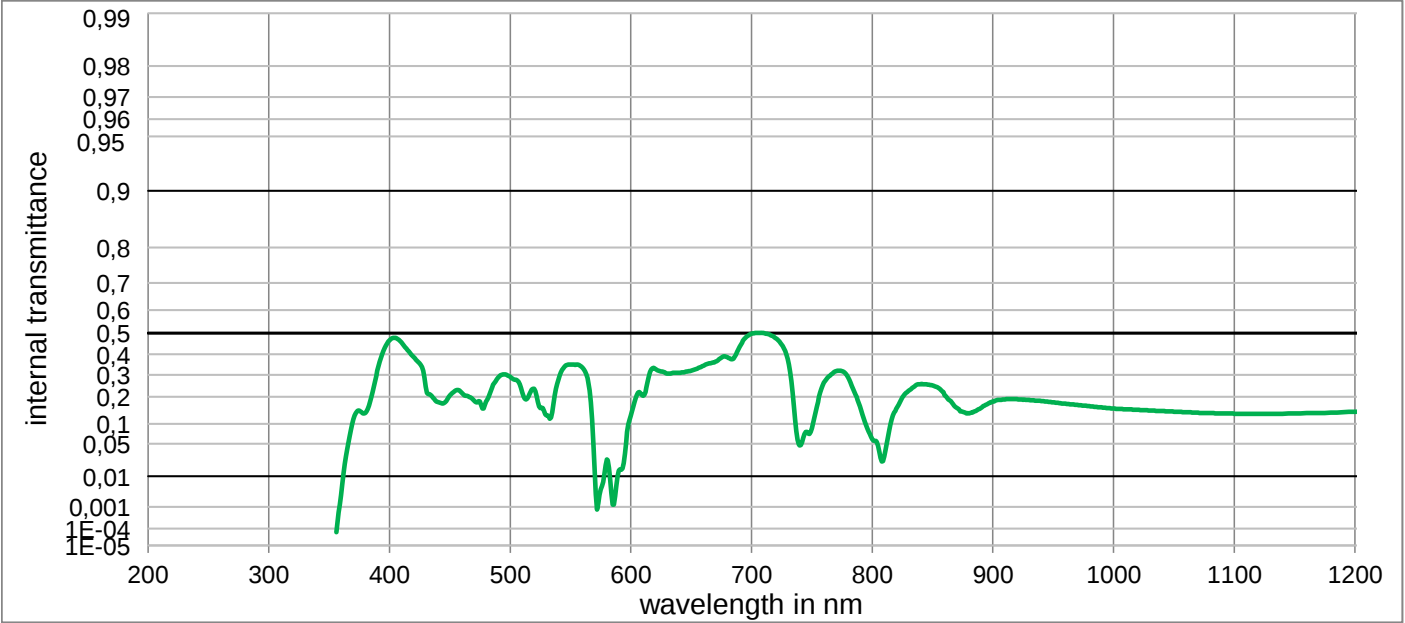


S8802

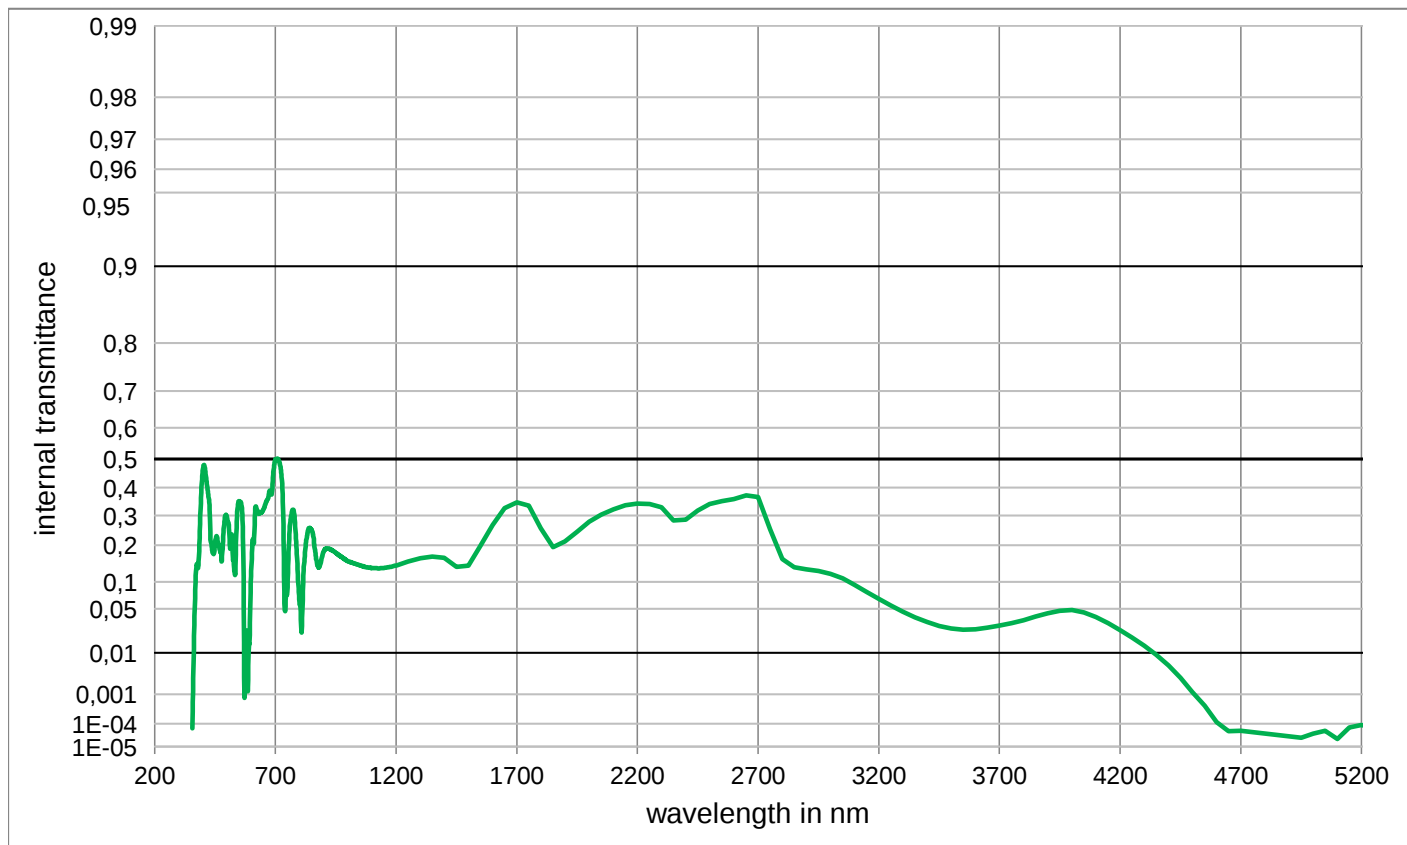Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	2,896E-01	800	5,938E-02	1100	1,335E-01	2200	3,427E-01	3700	2,912E-02
210	< 1,0E-05	510	2,193E-01	810	2,875E-02	1110	1,334E-01	2250	3,415E-01	3750	3,168E-02
220	< 1,0E-05	520	2,346E-01	820	1,510E-01	1120	1,331E-01	2300	3,298E-01	3800	3,501E-02
230	< 1,0E-05	530	1,277E-01	830	2,257E-01	1130	1,331E-01	2350	2,833E-01	3850	3,929E-02
240	< 1,0E-05	540	2,777E-01	840	2,563E-01	1140	1,334E-01	2400	2,858E-01	3900	4,375E-02
250	< 1,0E-05	550	3,506E-01	850	2,499E-01	1150	1,341E-01	2450	3,180E-01	3950	4,716E-02
260	< 1,0E-05	560	3,339E-01	860	2,056E-01	1160	1,353E-01	2500	3,404E-01	4000	4,799E-02
270	< 1,0E-05	570	1,558E-02	870	1,562E-01	1170	1,361E-01	2550	3,510E-01	4050	4,507E-02
280	< 1,0E-05	580	2,479E-02	880	1,342E-01	1180	1,373E-01	2600	3,584E-01	4100	3,911E-02
290	< 1,0E-05	590	1,384E-02	890	1,547E-01	1190	1,387E-01	2650	3,715E-01	4150	3,192E-02
300	< 1,0E-05	600	1,262E-01	900	1,799E-01	1200	1,407E-01	2700	3,654E-01	4200	2,508E-02
310	< 1,0E-05	610	2,039E-01	910	1,893E-01	1250	1,512E-01	2750	2,525E-01	4250	1,899E-02
320	< 1,000E-05	620	3,306E-01	920	1,902E-01	1300	1,606E-01	2800	1,581E-01	4300	1,370E-02
330	< 1,000E-05	630	3,067E-01	930	1,869E-01	1350	1,656E-01	2850	1,361E-01	4350	9,150E-03
340	< 1,000E-05	640	3,100E-01	940	1,825E-01	1400	1,623E-01	2900	1,305E-01	4400	5,447E-03
350	< 1,000E-05	650	3,202E-01	950	1,769E-01	1450	1,367E-01	2950	1,264E-01	4450	2,797E-03
360	2,721E-03	660	3,436E-01	960	1,712E-01	1500	1,402E-01	3000	1,191E-01	4500	1,146E-03
370	1,147E-01	670	3,631E-01	970	1,663E-01	1550	1,984E-01	3050	1,076E-01	4550	4,483E-04
380	1,358E-01	680	3,854E-01	980	1,615E-01	1600	2,675E-01	3100	9,357E-02	4600	1,161E-04
390	3,197E-01	690	4,354E-01	990	1,568E-01	1650	3,258E-01	3150	7,907E-02	4650	4,912E-05
400	4,675E-01	700	4,973E-01	1000	1,526E-01	1700	3,471E-01	3200	6,593E-02	4700	5,289E-05
410	4,563E-01	710	5,003E-01	1010	1,501E-01	1750	3,352E-01	3250	5,475E-02	4750	-
420	3,863E-01	720	4,765E-01	1020	1,477E-01	1800	2,551E-01	3300	4,581E-02	4800	-
430	2,438E-01	730	3,768E-01	1030	1,454E-01	1850	1,944E-01	3350	3,869E-02	4850	-
440	1,778E-01	740	4,625E-02	1040	1,433E-01	1900	2,119E-01	3400	3,324E-02	4900	-
450	2,059E-01	750	8,774E-02	1050	1,411E-01	1950	2,430E-01	3450	2,897E-02	4950	2,537E-05
460	2,162E-01	760	2,625E-01	1060	1,392E-01	2000	2,785E-01	3500	2,641E-02	5000	3,913E-05
470	1,852E-01	770	3,179E-01	1070	1,368E-01	2050	3,028E-01	3550	2,529E-02	5050	5,170E-05
480	1,795E-01	780	2,880E-01	1080	1,355E-01	2100	3,221E-01	3600	2,587E-02	5100	2,262E-05
490	2,862E-01	790	1,602E-01	1090	1,347E-01	2150	3,373E-01	3650	2,724E-02	5150	7,095E-05

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm2 mm3 mm
$P_d = 0,878$	$d = 2,50 \text{ mm}$	Illuminant D65
Spectral values guaranteed	Density	x
$\tau_i (455 \text{ nm}) > 0,71$	$\rho = 3,49 \text{ g/cm}^3$	y
$\tau_i (580 \text{ nm}) = 0,002 \pm 0,002$	Knoop hardness	Y
$\tau_i (618 \text{ nm}) = 0,9 \pm 0,030$	HK[0.1/20]	λ_d
$\tau_i (550 \text{ nm}) > 0,76$		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	
$n_h (404,7 \text{ nm}) = 1,7067$	Transformation temperature	
$n_e (546 \text{ nm}) = 1,6878$	$T_g = 653 \text{ }^\circ\text{C}$	
$n_d (587,6 \text{ nm}) = 1,6847$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha (-30^\circ\text{C}/+70^\circ\text{C}) = 6,1$	
	$\alpha (20^\circ\text{C}/300^\circ\text{C}) = 7,3$	
Sellmeier coefficients	Chemical properties	
valid from 440 nm to 1550 nm	Chemical resistance	
$B_1 = 1,1147$	FR class = 4	
$B_2 = 0,6697$	SR class = 52.0	
$B_3 = 1,3665$	AR class = 1.3	
$C_1 = 1,721\text{E-}02 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,7511\text{E-}13 \text{ } \mu\text{m}^2$	Resistant glass	
$C_3 = 100,000 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
Internal quality		
Bubble class -		
		Notes
		Ionically colored glass
		Contrast enhancement filter
		ISO 23364:2021
		Disclaimer
		All data without tolerances are to be understood to be reference values.

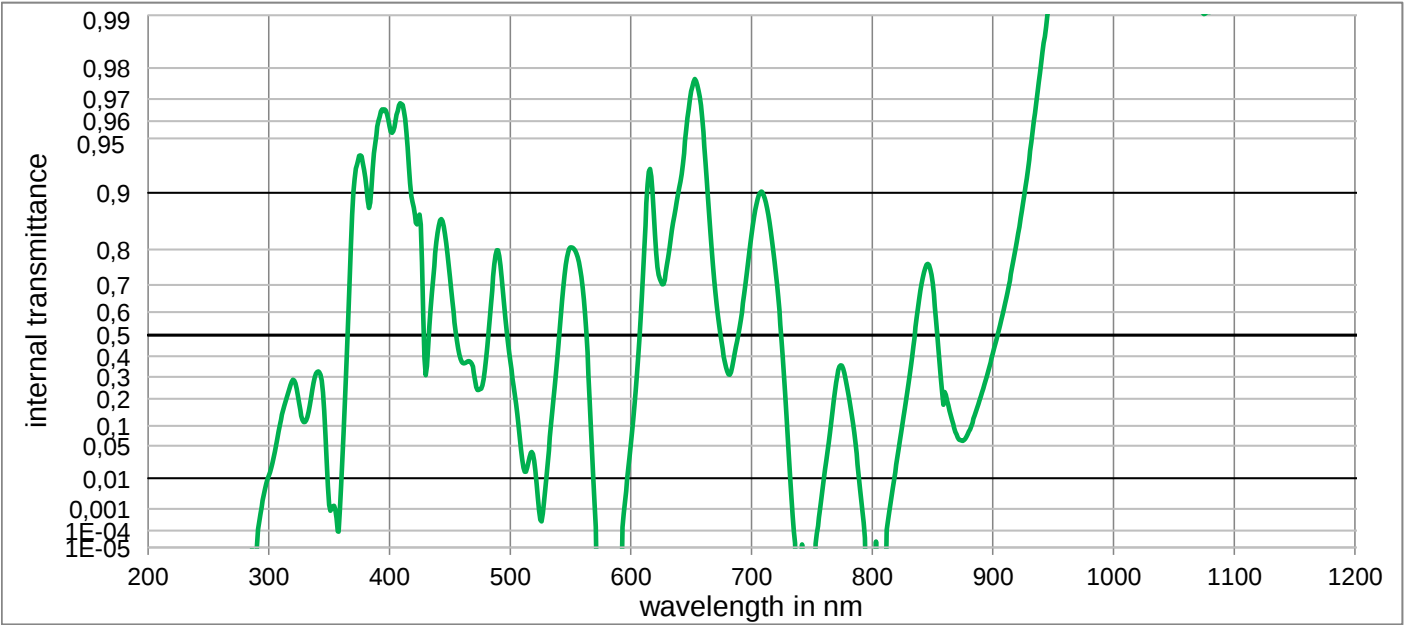


S8806A

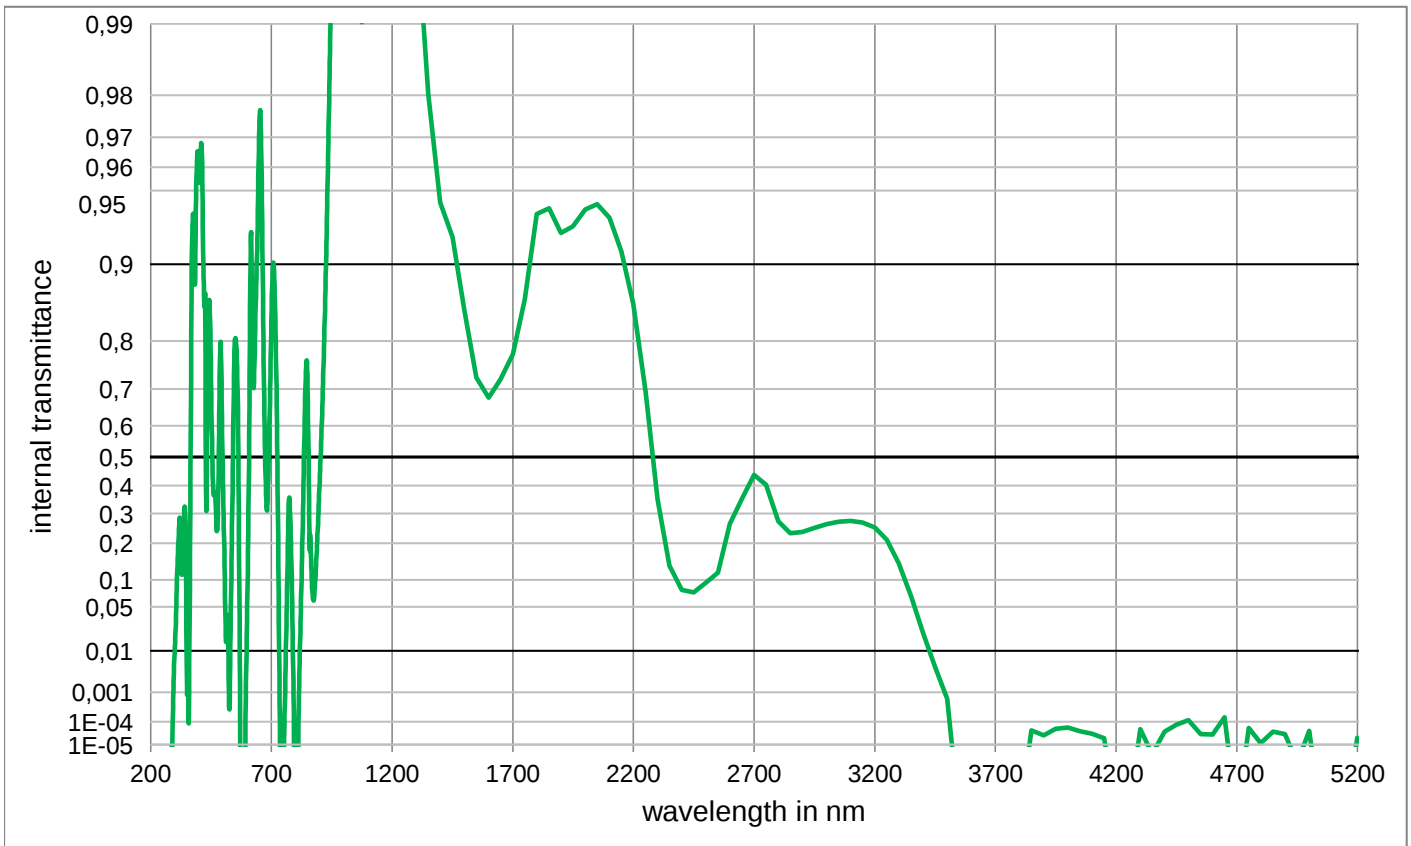


Internal transmittance τ_i at reference thickness							
The internal transmittance values, tabulated and graphically represented, are reference values only							
λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	3,756E-01	800	< 1,000E-05	1100	9,956E-01
210	< 1,0E-05	510	2,712E-02	810	< 1,000E-05	1110	9,973E-01
220	< 1,0E-05	520	2,623E-02	820	2,121E-02	1120	9,982E-01
230	< 1,0E-05	530	1,110E-02	830	2,662E-01	1130	9,988E-01
240	< 1,0E-05	540	4,537E-01	840	6,804E-01	1140	9,994E-01
250	< 1,0E-05	550	8,047E-01	850	7,069E-01	1150	9,997E-01
260	< 1,0E-05	560	6,925E-01	860	2,300E-01	1160	9,997E-01
270	< 1,0E-05	570	1,587E-03	870	7,556E-02	1170	9,992E-01
280	< 1,0E-05	580	< 1,000E-05	880	8,345E-02	1180	9,987E-01
290	< 1,0E-05	590	< 1,000E-05	890	2,096E-01	1190	9,971E-01
300	1,1E-02	600	5,053E-02	900	4,115E-01	1200	9,943E-01
310	1,2E-01	610	7,355E-01	910	6,332E-01	1250	9,918E-01
320	2,860E-01	620	8,329E-01	920	8,198E-01	1300	9,964E-01
330	1,121E-01	630	7,600E-01	930	9,342E-01	1350	9,802E-01
340	3,242E-01	640	9,060E-01	940	9,813E-01	1400	9,441E-01
350	1,408E-03	650	9,729E-01	950	9,930E-01	1450	9,226E-01
360	5,762E-03	660	9,540E-01	960	9,957E-01	1500	8,475E-01
370	9,007E-01	670	6,750E-01	970	9,957E-01	1550	7,267E-01
380	9,175E-01	680	3,253E-01	980	9,960E-01	1600	6,782E-01
390	9,571E-01	690	5,335E-01	990	9,954E-01	1650	7,230E-01
400	9,573E-01	700	8,328E-01	1000	9,952E-01	1700	7,761E-01
410	9,681E-01	710	8,975E-01	1010	9,953E-01	1750	8,624E-01
420	8,796E-01	720	7,394E-01	1020	9,956E-01	1800	9,376E-01
430	3,086E-01	730	7,187E-02	1030	9,963E-01	1850	9,409E-01
440	8,369E-01	740	< 1,000E-05	1040	9,961E-01	1900	9,254E-01
450	7,247E-01	750	< 1,000E-05	1050	9,950E-01	1950	9,299E-01
460	3,727E-01	760	9,719E-03	1060	9,928E-01	2000	9,400E-01
470	3,203E-01	770	2,723E-01	1070	9,904E-01	2050	9,430E-01
480	3,882E-01	780	2,269E-01	1080	9,904E-01	2100	9,352E-01
490	7,984E-01	790	5,137E-03	1090	9,931E-01	2150	9,113E-01
						2200	8,562E-01
						2250	6,926E-01
						2300	3,511E-01
						2350	1,347E-01
						2400	7,911E-02
						2450	7,437E-02
						2500	9,294E-02
						2550	1,174E-01
						2600	2,638E-01
						2650	3,548E-01
						2700	4,376E-01
						2750	4,029E-01
						2800	2,729E-01
						2850	2,329E-01
						2900	2,364E-01
						2950	2,500E-01
						3000	2,630E-01
						3050	2,713E-01
						3100	2,735E-01
						3150	2,685E-01
						3200	2,512E-01
						3250	2,105E-01
						3300	1,410E-01
						3350	6,710E-02
						3400	2,100E-02
						3450	4,390E-03
						3500	6,351E-04
						3550	
						3600	
						3650	
						3700	
						3750	
						3800	
						3850	4,460E-05
						3900	2,669E-05
						3950	5,235E-05
						4000	5,942E-05
						4050	4,125E-05
						4100	3,178E-05
						4150	2,013E-05
						4200	
						4250	
						4300	4,980E-05
						4350	< 1,000E-05
						4400	3,969E-05
						4450	7,509E-05
						4500	1,168E-04
						4550	3,056E-05
						4600	2,932E-05
						4650	1,461E-04
						4700	
						4750	5,584E-05
						4800	1,183E-05
						4850	3,964E-05
						4900	3,060E-05
						4950	< 1,000E-05
						5000	4,206E-05
						5050	
						5100	
						5150	

S8808

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm2 mm3 mm
$P_d = 0,906$	$d = 3,50 \text{ mm}$	Illuminant D65
Spectral values guaranteed	Density	x
$\tau_i (445 \text{ nm}) = 0,256 \pm 0,030$	$\rho = 2,91 \text{ g/cm}^3$	y
$\tau_i (555 \text{ nm}) = 0,32 \pm 0,015$	Knoop hardness	Y
$\tau_i (620 \text{ nm}) = 0,285 \pm 0,030$	$HK[0.1/20] = 474$	λ_d
$\tau_i (580 \text{ nm}) \leq 0,02$		P_e
	Thermal properties	Illuminant A
	Transformation temperature	x
	$T_g = 476 \text{ }^\circ\text{C}$	y
	Thermal expansion in $10^{-6}/\text{K}$	Y
Refractive indices		λ_d
$n_h (404,7 \text{ nm}) = 1,5895$	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 13,3$	P_e
$n_e (546 \text{ nm}) = 1,5726$		
$n_d (587,6 \text{ nm}) = 1,5698$		
	Chemical properties	Notes
Sellmeier coefficients	Chemical resistance	
valid from 440 nm to 1550 nm	FR class = 2	Ionically colored glass
$B_1 = 0,0144$	SR class = 5.4	Contrast enhancement filter
$B_2 = 1,4016$	AR class = 1.0	
$B_3 = 0,9378$	Resistance against humidity	ISO 23364:2021
$C_1 = 6,842\text{E-}03 \text{ } \mu\text{m}^2$	Resistant glass	
$C_2 = 1,2018\text{E-}02 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	Disclaimer
$C_3 = 128,775 \text{ } \mu\text{m}^2$		All data without tolerances are to be understood to be reference values.
Internal quality		
Bubble class 0		

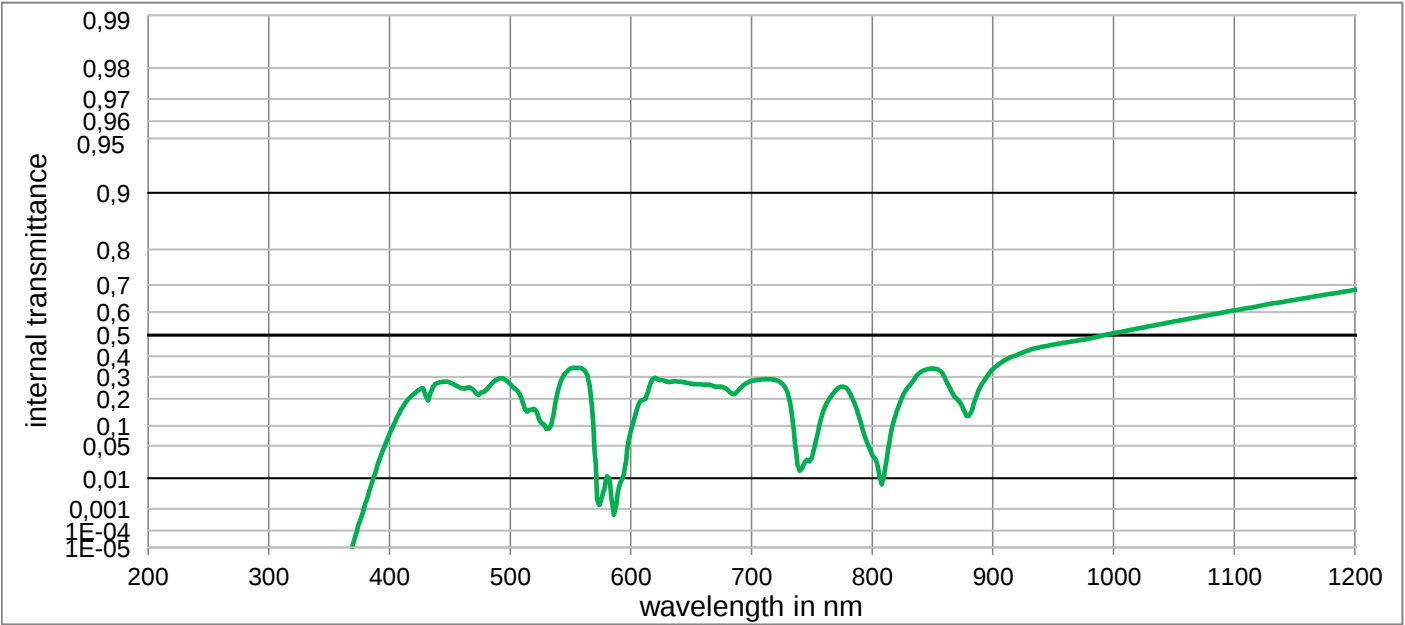


S8808

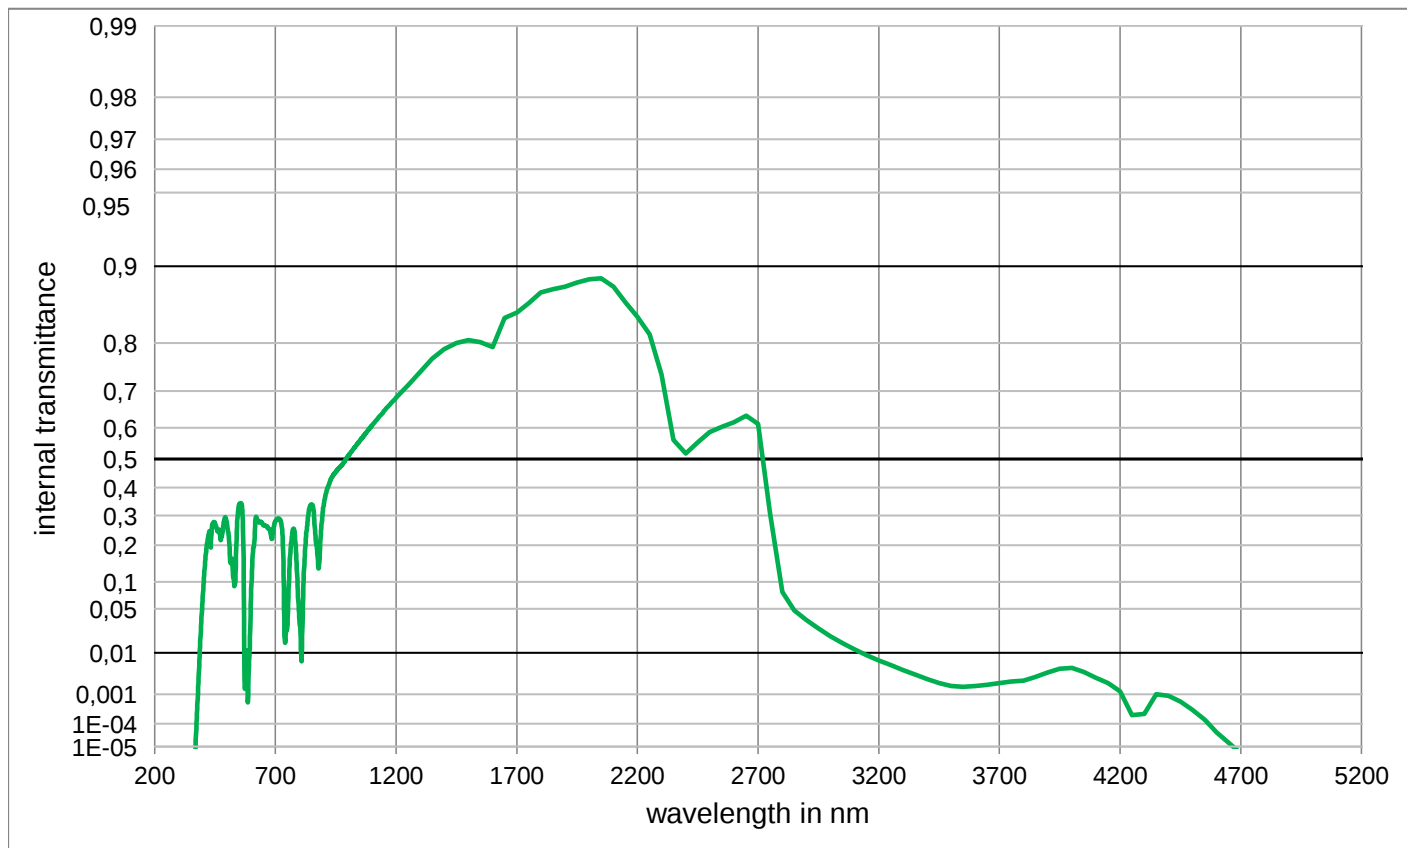Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	2,658E-01	800	3,340E-02	1100	6,066E-01	2200	8,417E-01	3700	2,024E-03
210	< 1,0E-05	510	1,906E-01	810	1,205E-02	1110	6,152E-01	2250	8,148E-01	3750	2,243E-03
220	< 1,0E-05	520	1,596E-01	820	1,434E-01	1120	6,238E-01	2300	7,380E-01	3800	2,380E-03
230	< 1,0E-05	530	9,089E-02	830	2,533E-01	1130	6,326E-01	2350	5,627E-01	3850	2,934E-03
240	< 1,0E-05	540	2,436E-01	840	3,224E-01	1140	6,399E-01	2400	5,192E-01	3900	3,803E-03
250	< 1,0E-05	550	3,396E-01	850	3,397E-01	1150	6,475E-01	2450	5,543E-01	3950	4,622E-03
260	< 1,0E-05	560	3,388E-01	860	2,978E-01	1160	6,552E-01	2500	5,867E-01	4000	4,753E-03
270	< 1,0E-05	570	3,964E-02	870	2,009E-01	1170	6,624E-01	2550	6,025E-01	4050	3,844E-03
280	< 1,0E-05	580	1,122E-02	880	1,332E-01	1180	6,697E-01	2600	6,161E-01	4100	2,771E-03
290	< 1,0E-05	590	5,390E-03	890	2,573E-01	1190	6,766E-01	2650	6,349E-01	4150	2,056E-03
300	< 1,0E-05	600	8,358E-02	900	3,362E-01	1200	6,835E-01	2700	6,120E-01	4200	1,208E-03
310	< 1,0E-05	610	1,944E-01	910	3,809E-01	1250	7,141E-01	2750	3,092E-01	4250	2,104E-04
320	< 1,000E-05	620	2,958E-01	920	4,066E-01	1300	7,438E-01	2800	7,872E-02	4300	2,283E-04
330	< 1,000E-05	630	2,764E-01	930	4,304E-01	1350	7,714E-01	2850	4,772E-02	4350	1,002E-03
340	< 1,000E-05	640	2,770E-01	940	4,446E-01	1400	7,889E-01	2900	3,552E-02	4400	8,931E-04
350	< 1,000E-05	650	2,671E-01	950	4,556E-01	1450	8,002E-01	2950	2,660E-02	4450	6,020E-04
360	< 1,000E-05	660	2,641E-01	960	4,655E-01	1500	8,052E-01	3000	1,993E-02	4500	3,256E-04
370	1,993E-05	670	2,546E-01	970	4,745E-01	1550	8,012E-01	3050	1,517E-02	4550	1,419E-04
380	1,618E-03	680	2,402E-01	980	4,839E-01	1600	7,926E-01	3100	1,163E-02	4600	4,506E-05
390	1,990E-02	690	2,435E-01	990	4,972E-01	1650	8,400E-01	3150	8,979E-03	4650	1,515E-05
400	7,673E-02	700	2,805E-01	1000	5,088E-01	1700	8,474E-01	3200	6,989E-03	4700	< 1,000E-05
410	1,583E-01	710	2,892E-01	1010	5,192E-01	1750	8,599E-01	3250	5,516E-03	4750	< 1,000E-05
420	2,205E-01	720	2,842E-01	1020	5,300E-01	1800	8,727E-01	3300	4,325E-03	4800	< 1,000E-05
430	2,123E-01	730	2,264E-01	1030	5,402E-01	1850	8,763E-01	3350	3,401E-03	4850	< 1,000E-05
440	2,705E-01	740	1,541E-02	1040	5,502E-01	1900	8,791E-01	3400	2,616E-03	4900	< 1,000E-05
450	2,731E-01	750	3,008E-02	1050	5,604E-01	1950	8,835E-01	3450	2,041E-03	4950	< 1,000E-05
460	2,466E-01	760	1,564E-01	1060	5,696E-01	2000	8,871E-01	3500	1,717E-03	5000	< 1,000E-05
470	2,368E-01	770	2,397E-01	1070	5,794E-01	2050	8,882E-01	3550	1,632E-03	5050	< 1,000E-05
480	2,381E-01	780	2,379E-01	1080	5,887E-01	2100	8,792E-01	3600	1,720E-03	5100	< 1,000E-05
490	2,901E-01	790	1,188E-01	1090	5,980E-01	2150	8,611E-01	3650	1,863E-03	5150	< 1,000E-05

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm2 mm3 mm				
P _d = 0,905		d = 2,20 mm		Illuminant D65	x	0,293	0,366	0,320
Spectral values guaranteed		Density			y	0,309	0,406	0,288
τ _i (440 nm) = 0,196 ± 0,033		ρ = 2,91 g/cm³			Y	35,9	18,8	12,9
τ _i (550 nm) = 0,234 ± 0,032		Knoop hardness			λ _d	477,2	572,0	
τ _i (620 nm) = 0,229 ± 0,027		HK[0.1/20]			P _e	0,091	0,365	0,093
		Thermal properties		Illuminant A	x	0,438	0,480	0,479
		Transformation temperature			y	0,393	0,436	0,368
		T _g = 459 °C			Y	35,1	19,3	13,4
		Thermal expansion in 10 ⁻⁶ /K			λ _d		581,7	
		α _(20°C/300°C) = 11,9			P _e	0,028	0,424	0,083
Refractive indices		Chemical properties		Notes				
n _h (404,7 nm) = 1,5933		Chemical resistance		Ionically colored glass				
n _e (546 nm) = 1,5765		FR class						
n _d (587,6 nm) = 1,5737		SR class						
		AR class		Contrast enhancement filter				
Sellmeier coefficients		Resistance against humidity <td colspan="4">ISO 23364:2021</td>		ISO 23364:2021				
valid from 440 nm to 1550 nm		Resistant glass		Disclaimer				
B ₁ 1,2022		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5						
B ₂ 0,2267				All data without tolerances are to be understood to be reference values.				
B ₃ 3,0814								
C ₁ 1,377E-02 μm²								
C ₂ 4,8304E-04 μm²								
C ₃ 394,060 μm²								
Internal quality								
Bubble class	-							

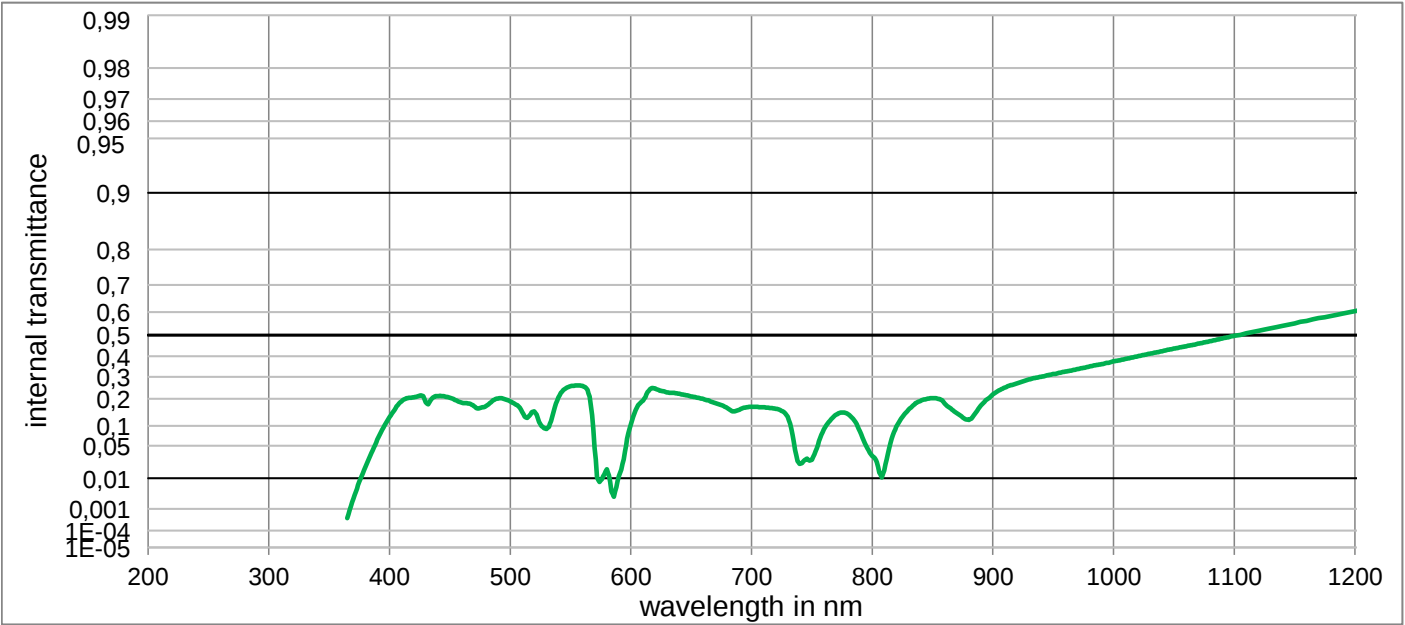

S8809

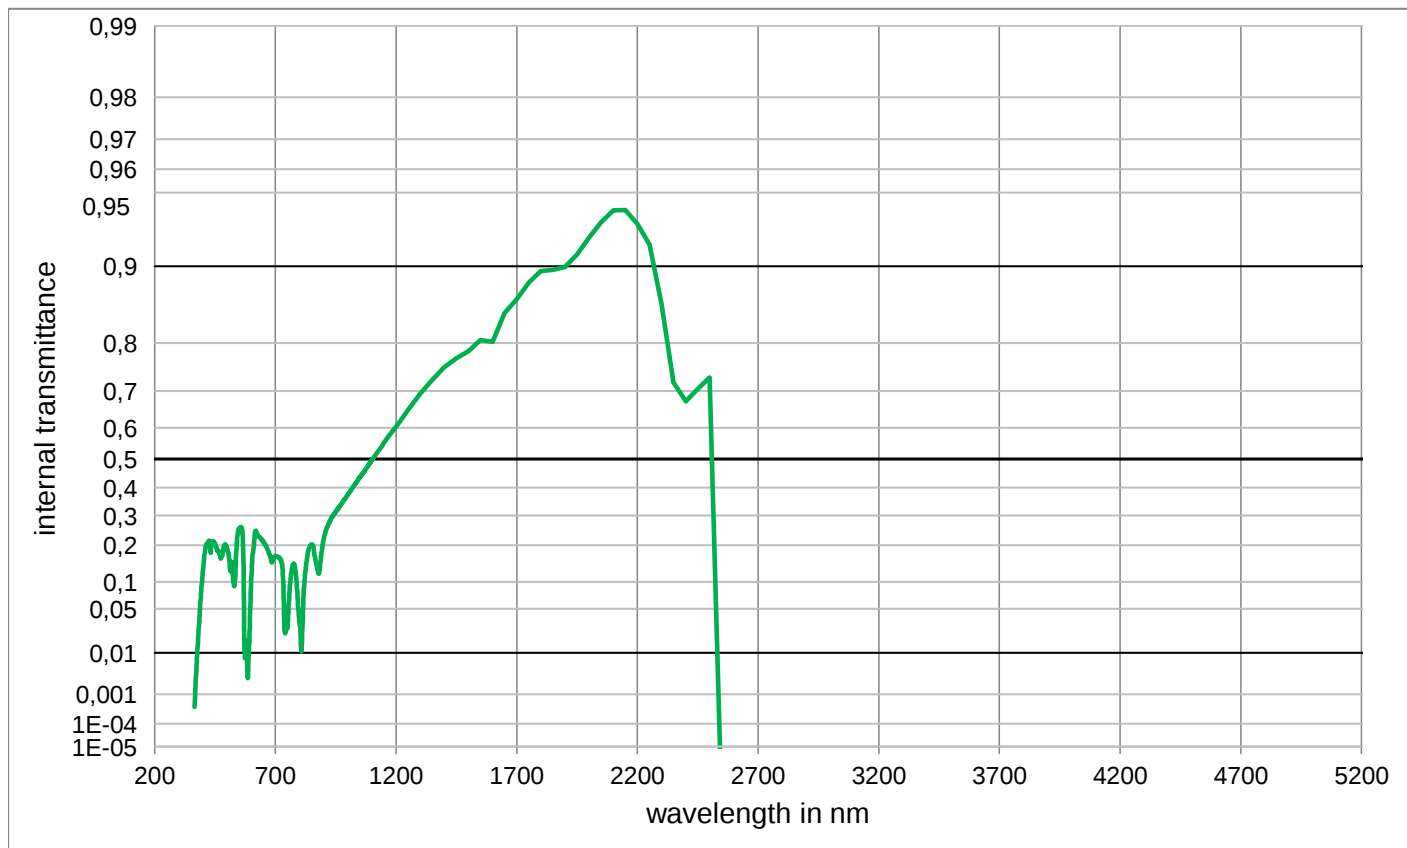
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	1,892E-01	800	3,197E-02	1100	4,965E-01	2200	9,327E-01	3700	
210	< 1,0E-05	510	1,470E-01	810	1,562E-02	1110	5,084E-01	2250	9,180E-01	3750	
220	< 1,0E-05	520	1,503E-01	820	9,677E-02	1120	5,200E-01	2300	8,590E-01	3800	
230	< 1,0E-05	530	9,059E-02	830	1,552E-01	1130	5,308E-01	2350	7,200E-01	3850	
240	< 1,0E-05	540	2,057E-01	840	1,911E-01	1140	5,419E-01	2400	6,736E-01	3900	
250	< 1,0E-05	550	2,561E-01	850	2,030E-01	1150	5,532E-01	2450	7,050E-01	3950	
260	< 1,0E-05	560	2,571E-01	860	1,797E-01	1160	5,639E-01	2500	7,315E-01	4000	
270	< 1,0E-05	570	4,613E-02	870	1,442E-01	1170	5,750E-01	2550		4050	
280	< 1,0E-05	580	1,691E-02	880	1,193E-01	1180	5,840E-01	2600		4100	
290	< 1,0E-05	590	1,121E-02	890	1,714E-01	1190	5,946E-01	2650		4150	
300	< 1,0E-05	600	1,025E-01	900	2,190E-01	1200	6,036E-01	2700		4200	
310	< 1,0E-05	610	1,928E-01	910	2,503E-01	1250	6,515E-01	2750		4250	
320	< 1,000E-05	620	2,458E-01	920	2,690E-01	1300	6,941E-01	2800		4300	
330	< 1,000E-05	630	2,280E-01	930	2,877E-01	1350	7,265E-01	2850		4350	
340	< 1,000E-05	640	2,216E-01	940	3,005E-01	1400	7,539E-01	2900		4400	
350	< 1,000E-05	650	2,103E-01	950	3,134E-01	1450	7,724E-01	2950		4450	
360	< 1,000E-05	660	1,988E-01	960	3,256E-01	1500	7,855E-01	3000		4500	
370	2,355E-03	670	1,818E-01	970	3,377E-01	1550	8,051E-01	3050		4550	
380	1,874E-02	680	1,619E-01	980	3,497E-01	1600	8,025E-01	3100		4600	
390	6,302E-02	690	1,566E-01	990	3,610E-01	1650	8,468E-01	3150		4650	
400	1,283E-01	700	1,669E-01	1000	3,748E-01	1700	8,651E-01	3200		4700	
410	1,895E-01	710	1,651E-01	1010	3,870E-01	1750	8,836E-01	3250		4750	
420	2,062E-01	720	1,594E-01	1020	3,999E-01	1800	8,956E-01	3300		4800	
430	1,849E-01	730	1,295E-01	1030	4,119E-01	1850	8,965E-01	3350		4850	
440	2,120E-01	740	2,216E-02	1040	4,244E-01	1900	8,993E-01	3400		4900	
450	2,043E-01	750	2,719E-02	1050	4,365E-01	1950	9,102E-01	3450		4950	
460	1,831E-01	760	8,913E-02	1060	4,478E-01	2000	9,235E-01	3500		5000	
470	1,702E-01	770	1,371E-01	1070	4,601E-01	2050	9,337E-01	3550		5050	
480	1,699E-01	780	1,396E-01	1080	4,717E-01	2100	9,408E-01	3600		5100	
490	2,016E-01	790	8,357E-02	1090	4,848E-01	2150	9,410E-01	3650		5150	

S8851

Optical properties		Mechanical properties		Colorimetric properties		
Reflection factor		Reference thickness		1 mm2 mm3 mm		
P _d = 0,880		d = 2,00 mm		Illuminant D65	x	
Spectral values guaranteed		Density			y	
τ _i (805 nm) = 0,414 ± 0,028		ρ = 3,58 g/cm³			Y	
τ _i (976 nm) = 0,578 ± 0,034		Knoop hardness			λ _d	
τ _i (1222 nm) = 0,323 ± 0,023		HK[0.1/20]			P _e	
τ _i (1945 nm) = 0,29 ± 0,023		Thermal properties		Illuminant A	x	
τ _i (710 nm) ≥ 0,966		Transformation temperature			y	
		T _g = 659 °C			Y	
Refractive indices		Thermal expansion in 10 ⁻⁶ /K			λ _d	
		α (20°C/300°C) = 7,2			P _e	
		Chemical properties		Notes		
Sellmeier coefficients		Chemical resistance		Ionically colored glass		
on request		Resistance against humidity				
		Resistant glass		ISO 23364:2021		
Internal quality		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		Disclaimer		
Bubble class	2			All data without tolerances are to be understood to be reference values.		

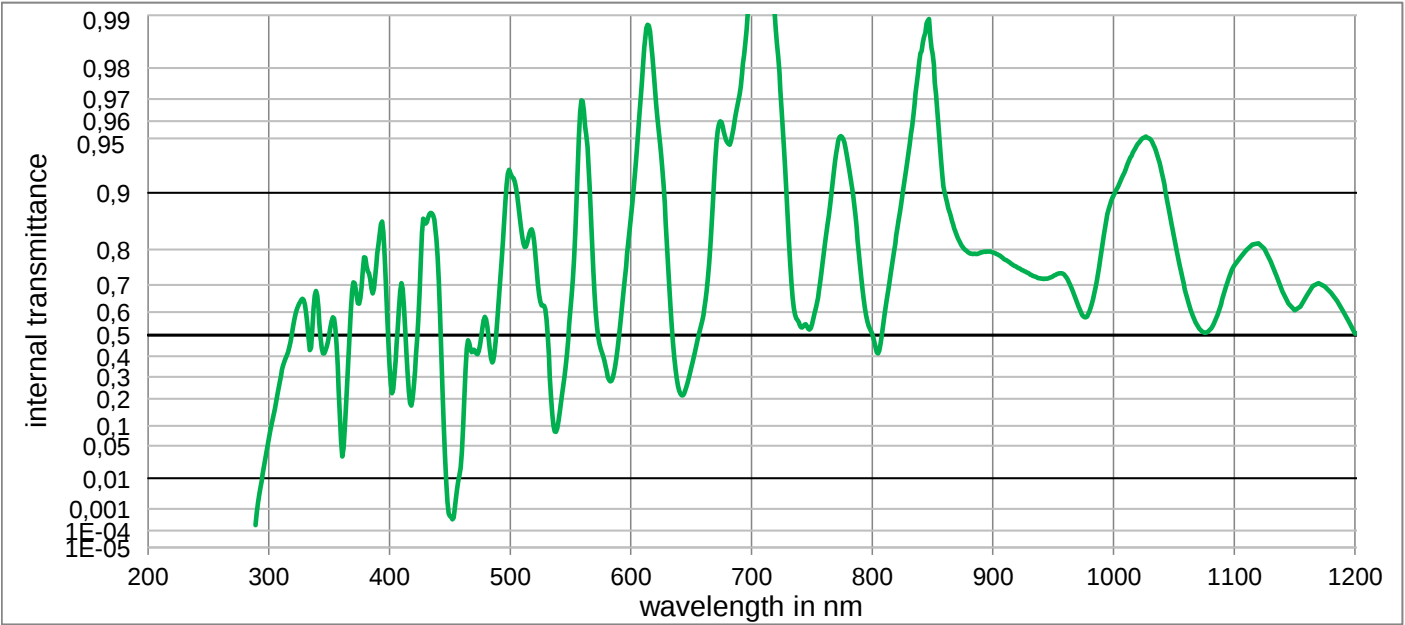

S8851

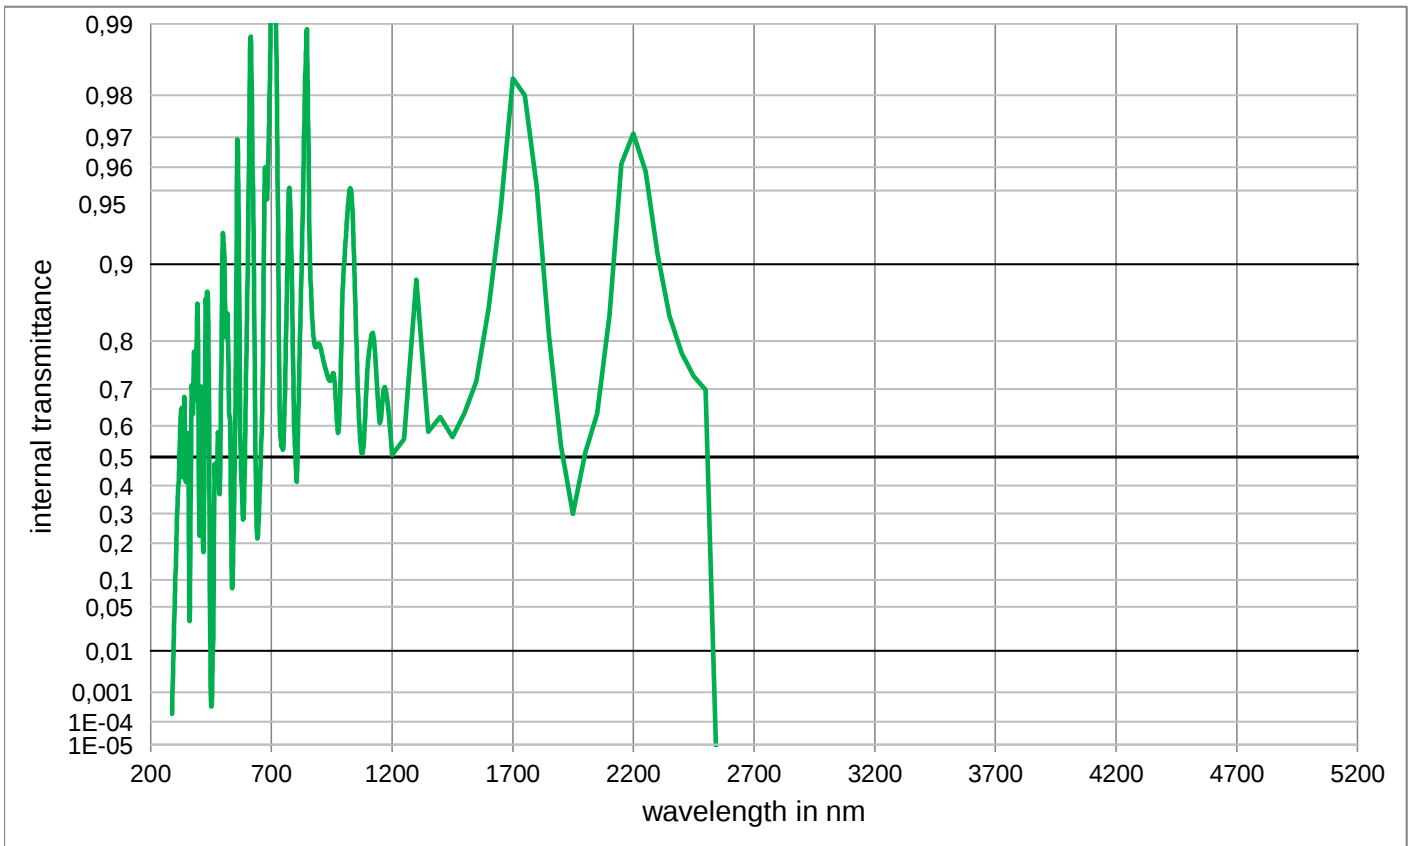
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,223E-01	800	5,049E-01	1100	7,593E-01	2200	9,710E-01	3700	
210	< 1,0E-05	510	8,278E-01	810	5,805E-01	1110	7,978E-01	2250	9,585E-01	3750	
220	< 1,0E-05	520	8,179E-01	820	8,305E-01	1120	8,142E-01	2300	9,092E-01	3800	
230	< 1,0E-05	530	5,710E-01	830	9,396E-01	1130	7,717E-01	2350	8,398E-01	3850	
240	< 1,0E-05	540	1,134E-01	840	9,835E-01	1140	6,787E-01	2400	7,774E-01	3900	
250	< 1,0E-05	550	6,050E-01	850	9,833E-01	1150	6,080E-01	2450	7,296E-01	3950	
260	< 1,0E-05	560	9,692E-01	860	9,003E-01	1160	6,624E-01	2500	6,979E-01	4000	
270	< 1,0E-05	570	6,676E-01	870	8,321E-01	1170	7,053E-01	2550		4050	
280	< 1,0E-05	580	3,229E-01	880	7,920E-01	1180	6,737E-01	2600		4100	
290	7,4E-04	590	4,870E-01	890	7,927E-01	1190	6,053E-01	2650		4150	
300	6,4E-02	600	8,614E-01	900	7,931E-01	1200	5,074E-01	2700		4200	
310	3,1E-01	610	9,807E-01	910	7,746E-01	1250	5,581E-01	2750		4250	
320	5,353E-01	620	9,737E-01	920	7,541E-01	1300	8,846E-01	2800		4300	
330	6,291E-01	630	8,132E-01	930	7,354E-01	1350	5,817E-01	2850		4350	
340	6,630E-01	640	2,353E-01	940	7,207E-01	1400	6,255E-01	2900		4400	
350	5,002E-01	650	3,410E-01	950	7,278E-01	1450	5,655E-01	2950		4450	
360	6,054E-02	660	5,866E-01	960	7,282E-01	1500	6,359E-01	3000		4500	
370	7,091E-01	670	9,356E-01	970	6,340E-01	1550	7,190E-01	3050		4550	
380	7,802E-01	680	9,473E-01	980	6,015E-01	1600	8,507E-01	3100		4600	
390	7,899E-01	690	9,717E-01	990	7,979E-01	1650	9,396E-01	3150		4650	
400	3,551E-01	700	9,941E-01	1000	8,961E-01	1700	9,830E-01	3200		4700	
410	7,061E-01	710	9,983E-01	1010	9,259E-01	1750	9,800E-01	3250		4750	
420	2,536E-01	720	9,879E-01	1020	9,464E-01	1800	9,516E-01	3300		4800	
430	8,538E-01	730	8,645E-01	1030	9,499E-01	1850	8,076E-01	3350		4850	
440	7,831E-01	740	5,461E-01	1040	9,218E-01	1900	5,381E-01	3400		4900	
450	5,000E-04	750	5,475E-01	1050	8,292E-01	1950	2,986E-01	3450		4950	
460	3,825E-02	760	7,924E-01	1060	6,715E-01	2000	5,150E-01	3500		5000	
470	4,309E-01	770	9,394E-01	1070	5,371E-01	2050	6,356E-01	3550		5050	
480	5,707E-01	780	9,316E-01	1080	5,246E-01	2100	8,405E-01	3600		5100	
490	6,053E-01	790	7,605E-01	1090	6,477E-01	2150	9,613E-01	3650		5150	

N-WG205

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm2 mm3 mm
$P_d = 0,929$	$d = 2,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 2 mm)	Density	x
$\lambda_{i,0,5} = 205 \text{ nm} \pm 10 \text{ nm}$	$\rho = 2,22 \text{ g/cm}^3$	y
$\lambda_p (\tau_{i,L} = 0,97) = 270 \text{ nm}$	Knoop hardness	Y
	$HK_{[0.1/20]}$	λ_d
		P_e
		Illuminant A
	Thermal properties	x
	Transformation temperature	y
	$T_g = 440 \text{ }^\circ\text{C}$	Y
	Thermal expansion in $10^{-6}/\text{K}$	λ_d
Refractive indices		P_e
$n_d (587,6 \text{ nm}) = 1,48$	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 4,1$	
$n_s (852 \text{ nm}) = 1,47$		
$n_t (1014 \text{ nm}) = 1,47$		
Sellmeier coefficients	Chemical properties	Notes
valid from 440 nm to 1550 nm	Chemical resistance	
$B_1 = 0,0144$	FR class = -	Ionically colored glass
$B_2 = 1,1393$	SR class = -	Longpass filter
$B_3 = 1,0869$	AR class = -	
$C_1 = 6,822\text{E-}03 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 8,6122\text{E-}03 \text{ } \mu\text{m}^2$	Resistant glass	contains strong striae
$C_3 = 109,981 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	ISO 23364:2021
Internal quality		Disclaimer
Bubble class -		All data without tolerances are to be understood to be reference values.

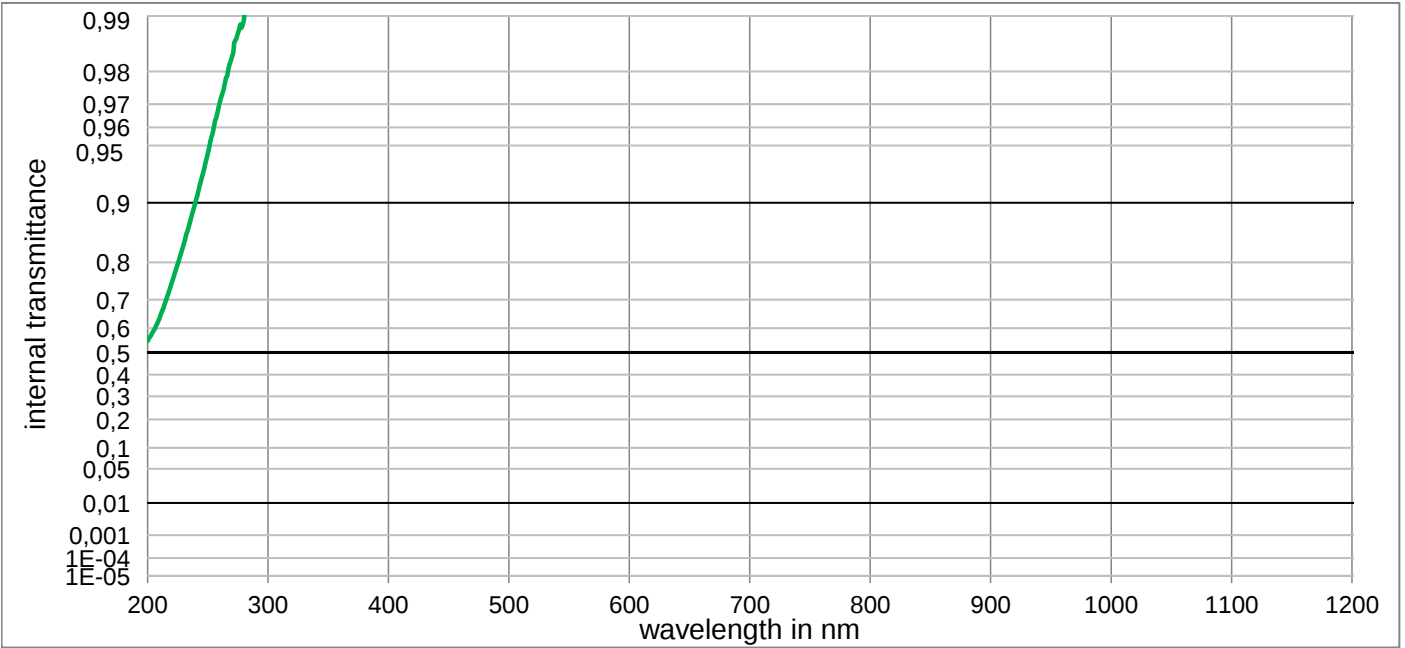

N-WG205

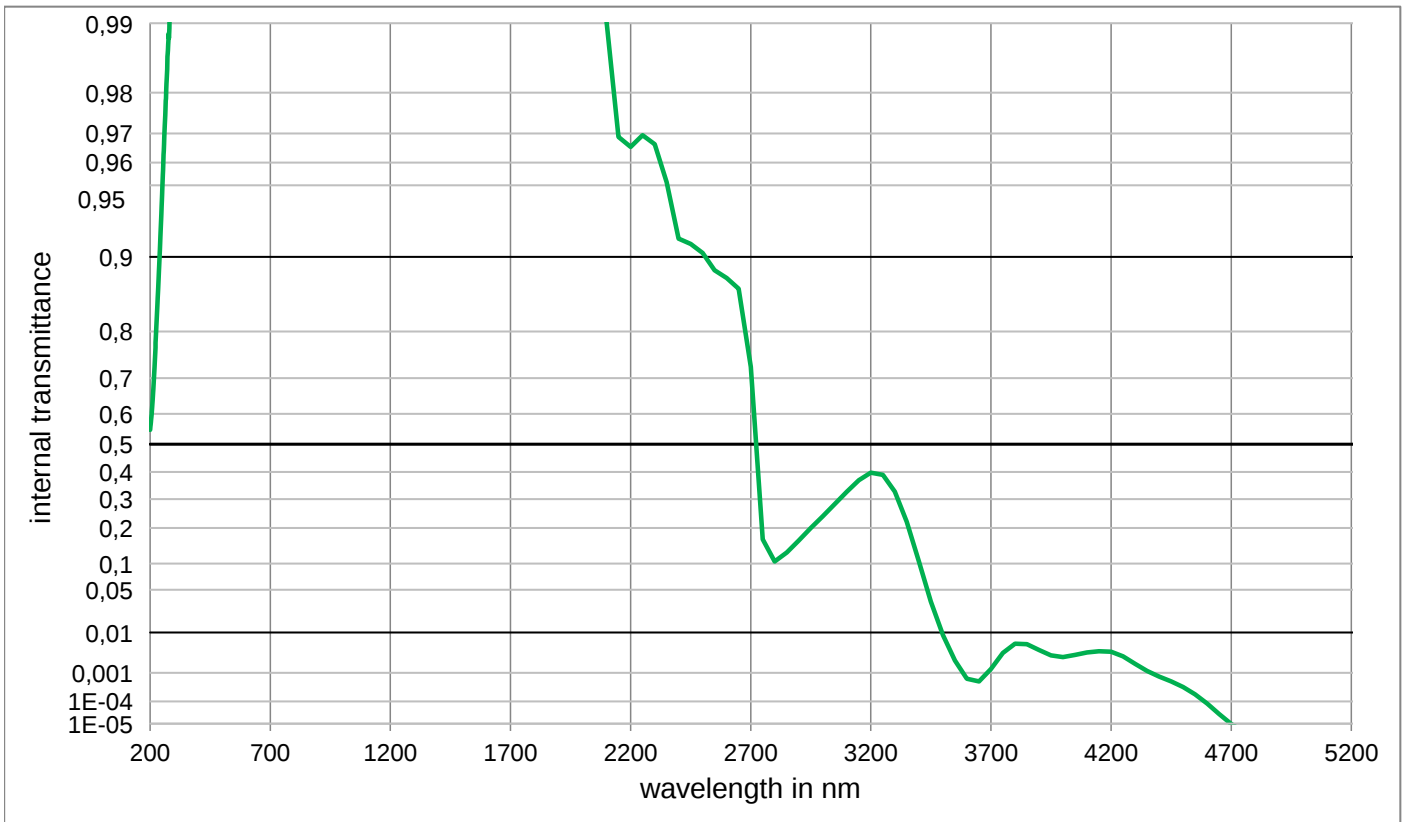
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	5,5E-01	500	1,000E+00	800	1,000E+00	1100	1,000E+00	2200	9,657E-01	3700	1,300E-03
210	6,4E-01	510	1,000E+00	810	1,000E+00	1110	1,000E+00	2250	9,694E-01	3750	3,496E-03
220	7,5E-01	520	1,000E+00	820	1,000E+00	1120	1,000E+00	2300	9,667E-01	3800	5,778E-03
230	8,4E-01	530	1,000E+00	830	1,000E+00	1130	1,000E+00	2350	9,516E-01	3850	5,658E-03
240	9,0E-01	540	1,000E+00	840	1,000E+00	1140	1,000E+00	2400	9,160E-01	3900	4,117E-03
250	9,5E-01	550	1,000E+00	850	1,000E+00	1150	1,000E+00	2450	9,116E-01	3950	3,029E-03
260	9,7E-01	560	1,000E+00	860	1,000E+00	1160	1,000E+00	2500	9,037E-01	4000	2,738E-03
270	9,8E-01	570	1,000E+00	870	1,000E+00	1170	1,000E+00	2550	8,864E-01	4050	3,110E-03
280	9,9E-01	580	1,000E+00	880	1,000E+00	1180	1,000E+00	2600	8,777E-01	4100	3,612E-03
290	9,9E-01	590	1,000E+00	890	1,000E+00	1190	1,000E+00	2650	8,648E-01	4150	3,861E-03
300	9,9E-01	600	1,000E+00	900	1,000E+00	1200	1,000E+00	2700	7,273E-01	4200	3,738E-03
310	9,9E-01	610	1,000E+00	910	1,000E+00	1250	1,000E+00	2750	1,646E-01	4250	2,866E-03
320	9,953E-01	620	1,000E+00	920	1,000E+00	1300	1,000E+00	2800	1,052E-01	4300	1,823E-03
330	9,968E-01	630	1,000E+00	930	1,000E+00	1350	1,000E+00	2850	1,276E-01	4350	1,145E-03
340	9,981E-01	640	1,000E+00	940	1,000E+00	1400	9,929E-01	2900	1,611E-01	4400	7,717E-04
350	9,987E-01	650	1,000E+00	950	1,000E+00	1450	9,988E-01	2950	1,992E-01	4450	5,340E-04
360	9,996E-01	660	1,000E+00	960	1,000E+00	1500	1,000E+00	3000	2,390E-01	4500	3,471E-04
370	9,994E-01	670	1,000E+00	970	1,000E+00	1550	1,000E+00	3050	2,823E-01	4550	1,909E-04
380	9,995E-01	680	1,000E+00	980	1,000E+00	1600	1,000E+00	3100	3,270E-01	4600	8,269E-05
390	9,993E-01	690	1,000E+00	990	1,000E+00	1650	1,000E+00	3150	3,692E-01	4650	2,901E-05
400	9,994E-01	700	1,000E+00	1000	1,000E+00	1700	1,000E+00	3200	3,970E-01	4700	< 1,000E-05
410	9,997E-01	710	1,000E+00	1010	1,000E+00	1750	1,000E+00	3250	3,890E-01	4750	< 1,000E-05
420	9,999E-01	720	1,000E+00	1020	1,000E+00	1800	1,000E+00	3300	3,273E-01	4800	< 1,000E-05
430	1,000E+00	730	1,000E+00	1030	1,000E+00	1850	1,000E+00	3350	2,200E-01	4850	< 1,000E-05
440	1,000E+00	740	1,000E+00	1040	1,000E+00	1900	9,999E-01	3400	1,048E-01	4900	< 1,000E-05
450	1,000E+00	750	1,000E+00	1050	1,000E+00	1950	9,981E-01	3450	3,420E-02	4950	< 1,000E-05
460	1,000E+00	760	1,000E+00	1060	1,000E+00	2000	9,933E-01	3500	8,818E-03	5000	< 1,000E-05
470	1,000E+00	770	1,000E+00	1070	1,000E+00	2050	9,933E-01	3550	2,255E-03	5050	< 1,000E-05
480	1,000E+00	780	1,000E+00	1080	1,000E+00	2100	9,902E-01	3600	6,575E-04	5100	< 1,000E-05
490	1,000E+00	790	1,000E+00	1090	1,000E+00	2150	9,690E-01	3650	5,338E-04	5150	< 1,000E-05

N-WG280

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,919$	$d = 2,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 2 mm)	Density	x
$\lambda_{i,0,5} = 280 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,51 \text{ g/cm}^3$	y
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 230 \text{ nm}$	Knoop hardness	Y
$\lambda_p (\tau_{i,L} = 0,99) = 380 \text{ nm}$	$HK_{[0.1/20]} = 610$	λ_d
		P_e
		Illuminant A
	Thermal properties	x
	Transformation temperature	y
	$T_g = 558 \text{ }^\circ\text{C}$	Y
	Thermal expansion in $10^{-6}/\text{K}$	λ_d
Refractive indices	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,1$	P_e
$n_d (587,6 \text{ nm}) = 1,52$	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 8,4$	
$n_s (852 \text{ nm}) = 1,51$	Temperature coefficient	
$n_t (1014 \text{ nm}) = 1,51$	$Tk = 0,06 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Notes
valid from 440 nm to 1550 nm	Chemical resistance	
$B_1 = 0,0123$	FR class = 0	Base glass
$B_2 = 0,5089$	SR class = 1	Longpass filter
$B_3 = 1,8825$	AR class = 2	
$C_1 = 1,388\text{E-}02 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,8223\text{E-}05 \text{ } \mu\text{m}^2$	Resistant glass	ISO 23364:2021
$C_3 = 202,101 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	Disclaimer
Internal quality		All data without tolerances are to be understood to be reference values.
Bubble class 1		

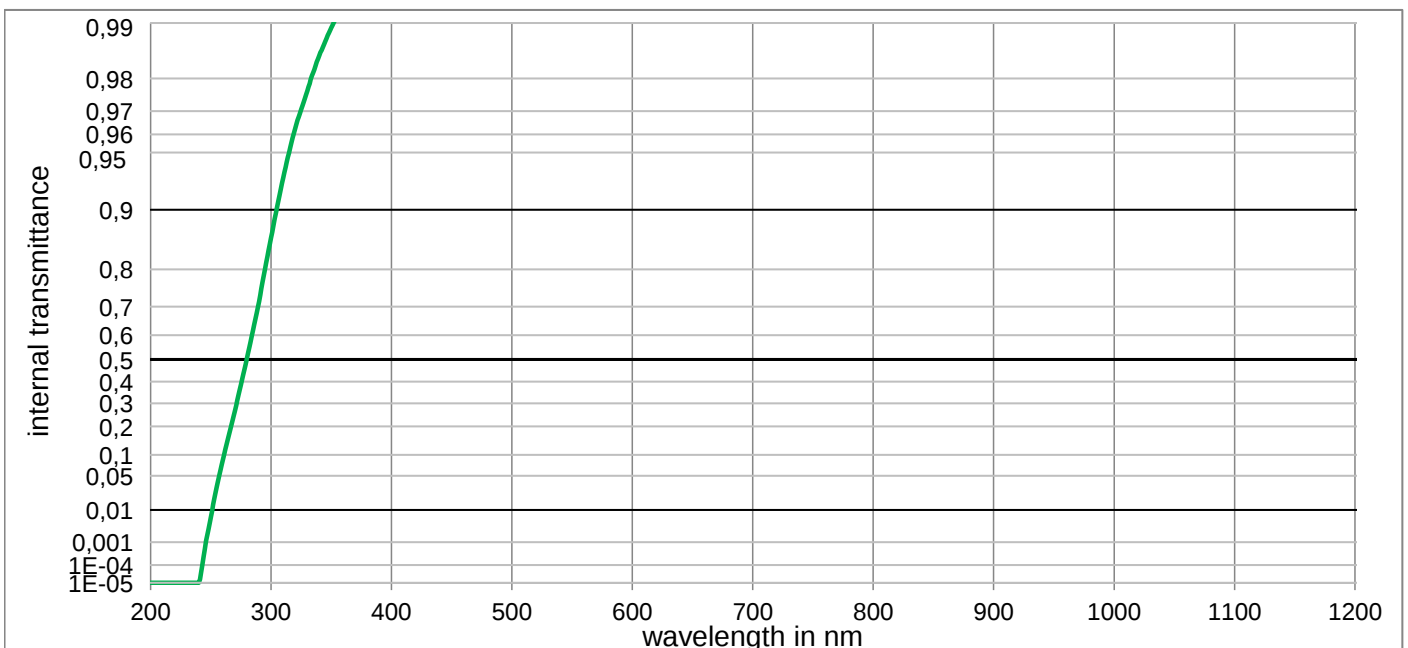

N-WG280

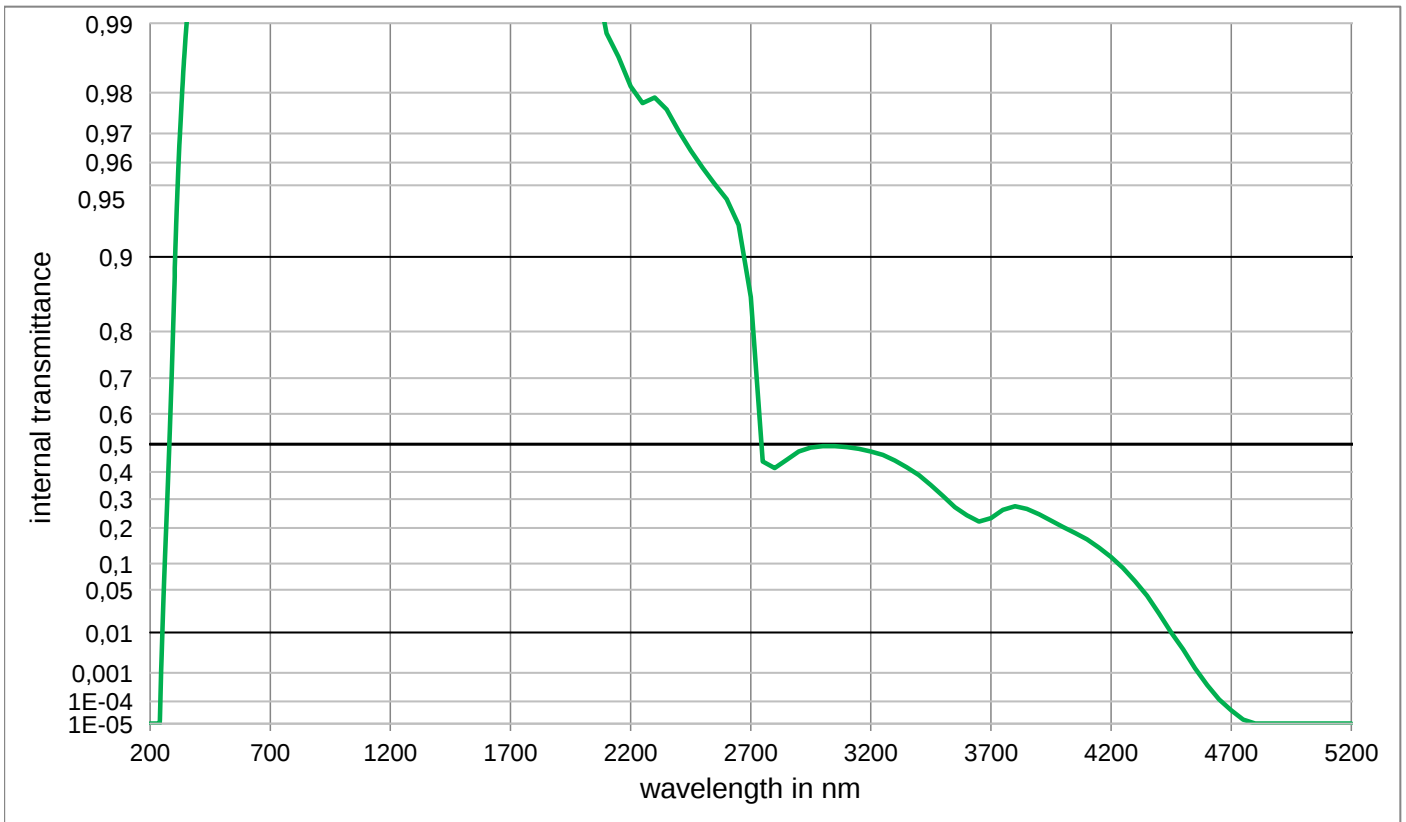
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,974E-01	800	9,999E-01	1100	9,999E-01	2200	9,812E-01	3700	2,325E-01
210	< 1,0E-05	510	9,976E-01	810	9,999E-01	1110	9,999E-01	2250	9,778E-01	3750	2,613E-01
220	< 1,0E-05	520	9,978E-01	820	9,999E-01	1120	9,999E-01	2300	9,790E-01	3800	2,746E-01
230	< 1,0E-05	530	9,980E-01	830	9,999E-01	1130	9,999E-01	2350	9,764E-01	3850	2,651E-01
240	< 1,0E-05	540	9,982E-01	840	9,999E-01	1140	9,999E-01	2400	9,708E-01	3900	2,462E-01
250	6,6E-03	550	9,983E-01	850	9,999E-01	1150	9,999E-01	2450	9,645E-01	3950	2,245E-01
260	8,6E-02	560	9,985E-01	860	9,999E-01	1160	9,999E-01	2500	9,579E-01	4000	2,037E-01
270	2,7E-01	570	9,986E-01	870	9,999E-01	1170	9,999E-01	2550	9,507E-01	4050	1,843E-01
280	5,1E-01	580	9,988E-01	880	9,999E-01	1180	9,999E-01	2600	9,427E-01	4100	1,645E-01
290	7,2E-01	590	9,989E-01	890	9,999E-01	1190	9,999E-01	2650	9,264E-01	4150	1,408E-01
300	8,6E-01	600	9,991E-01	900	9,999E-01	1200	9,999E-01	2700	8,540E-01	4200	1,155E-01
310	9,3E-01	610	9,992E-01	910	9,999E-01	1250	9,999E-01	2750	8,381E-01	4250	8,980E-02
320	9,62E-01	620	9,993E-01	920	9,999E-01	1300	9,999E-01	2800	4,145E-01	4300	6,370E-02
330	9,766E-01	630	9,995E-01	930	9,999E-01	1350	9,999E-01	2850	4,442E-01	4350	4,140E-02
340	9,849E-01	640	9,996E-01	940	9,999E-01	1400	9,993E-01	2900	4,740E-01	4400	2,230E-02
350	9,894E-01	650	9,997E-01	950	9,999E-01	1450	9,999E-01	2950	4,882E-01	4450	1,000E-02
360	9,916E-01	660	9,998E-01	960	9,999E-01	1500	9,999E-01	3000	4,934E-01	4500	4,310E-03
370	9,928E-01	670	9,998E-01	970	9,999E-01	1550	9,999E-01	3050	4,934E-01	4550	1,352E-03
380	9,936E-01	680	9,999E-01	980	9,999E-01	1600	9,999E-01	3100	4,900E-01	4600	4,070E-04
390	9,942E-01	690	9,999E-01	990	9,999E-01	1650	9,999E-01	3150	4,835E-01	4650	1,191E-04
400	9,946E-01	700	9,999E-01	1000	9,999E-01	1700	9,999E-01	3200	4,740E-01	4700	4,227E-05
410	9,950E-01	710	9,999E-01	1010	9,999E-01	1750	9,999E-01	3250	4,622E-01	4750	1,585E-05
420	9,954E-01	720	9,999E-01	1020	9,999E-01	1800	9,999E-01	3300	4,423E-01	4800	< 1,000E-05
430	9,957E-01	730	9,999E-01	1030	9,999E-01	1850	9,995E-01	3350	4,173E-01	4850	< 1,000E-05
440	9,960E-01	740	9,999E-01	1040	9,999E-01	1900	9,984E-01	3400	3,885E-01	4900	< 1,000E-05
450	9,962E-01	750	9,999E-01	1050	9,999E-01	1950	9,974E-01	3450	3,516E-01	4950	< 1,000E-05
460	9,965E-01	760	9,999E-01	1060	9,999E-01	2000	9,961E-01	3500	3,114E-01	5000	< 1,000E-05
470	9,967E-01	770	9,999E-01	1070	9,999E-01	2050	9,941E-01	3550	2,708E-01	5050	< 1,000E-05
480	9,970E-01	780	9,999E-01	1080	9,999E-01	2100	9,889E-01	3600	2,429E-01	5100	< 1,000E-05
490	9,972E-01	790	9,999E-01	1090	9,999E-01	2150	9,860E-01	3650	2,207E-01	5150	< 1,000E-05

N-WG295

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,919$	$d = 2,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 2 mm)	Density	x
$\lambda_{i0,5} = 295 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,51 \text{ g/cm}^3$	y
$\lambda_s (\tau_{i,U} = 1E-05) = 250 \text{ nm}$	Knoop hardness	Y
$\lambda_p (\tau_{i,L} = 0,99) = 400 \text{ nm}$	$HK_{[0.1/20]} = 610$	λ_d
		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	Notes
$n_d (587,6 \text{ nm}) = 1,52$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,51$	$T_g = 565 \text{ }^\circ\text{C}$	
$n_t (1014 \text{ nm}) = 1,51$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,2$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 8,4$	
	Temperature coefficient	
	$Tk = 0,06 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Base glass
valid from 440 nm to 1550 nm	Chemical resistance	Longpass filter
$B_1 = #####$	FR class = 0	
$B_2 = 0,5097$	SR class = 1	
$B_3 = 1,4617$	AR class = 2	
	Resistance against humidity	ISO 23364:2021
$C_2 = 1,9688E-02 \text{ } \mu\text{m}^2$	Resistant glass	Disclaimer
$C_3 = 100,000 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	All data without tolerances are to be understood to be reference values.
Internal quality		
Bubble class 1		

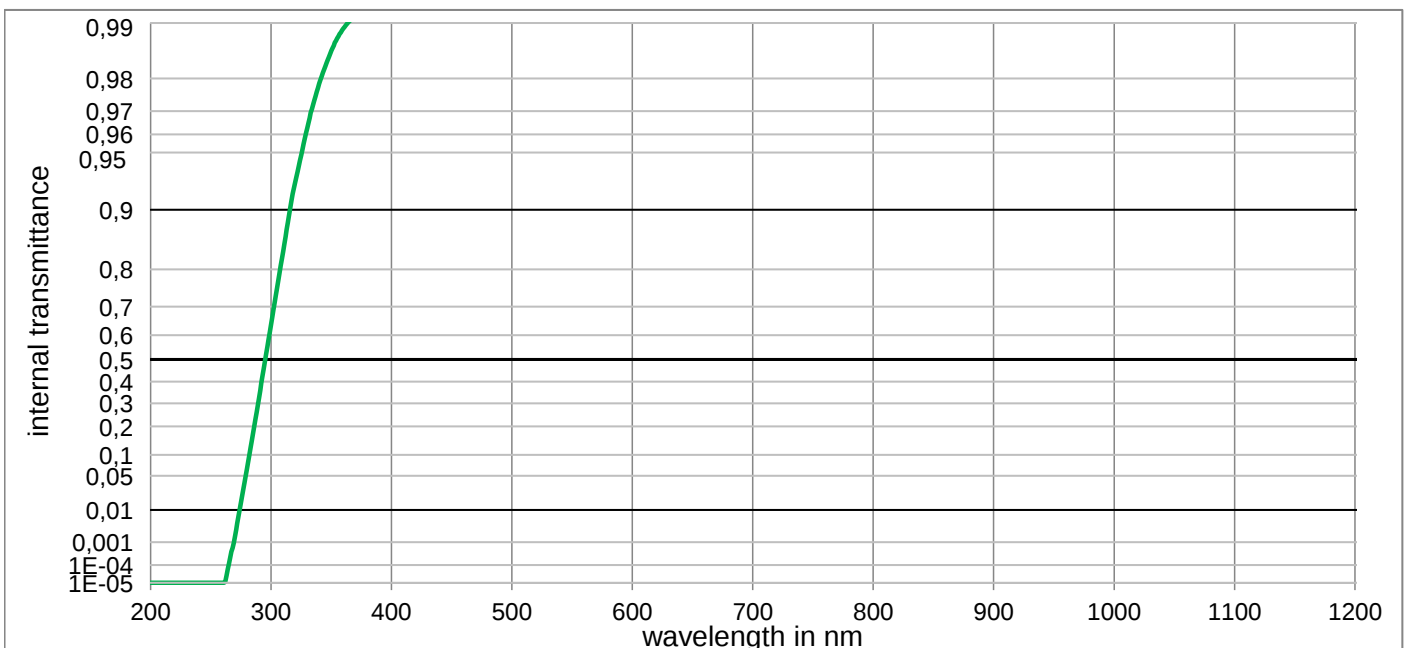

N-WG295

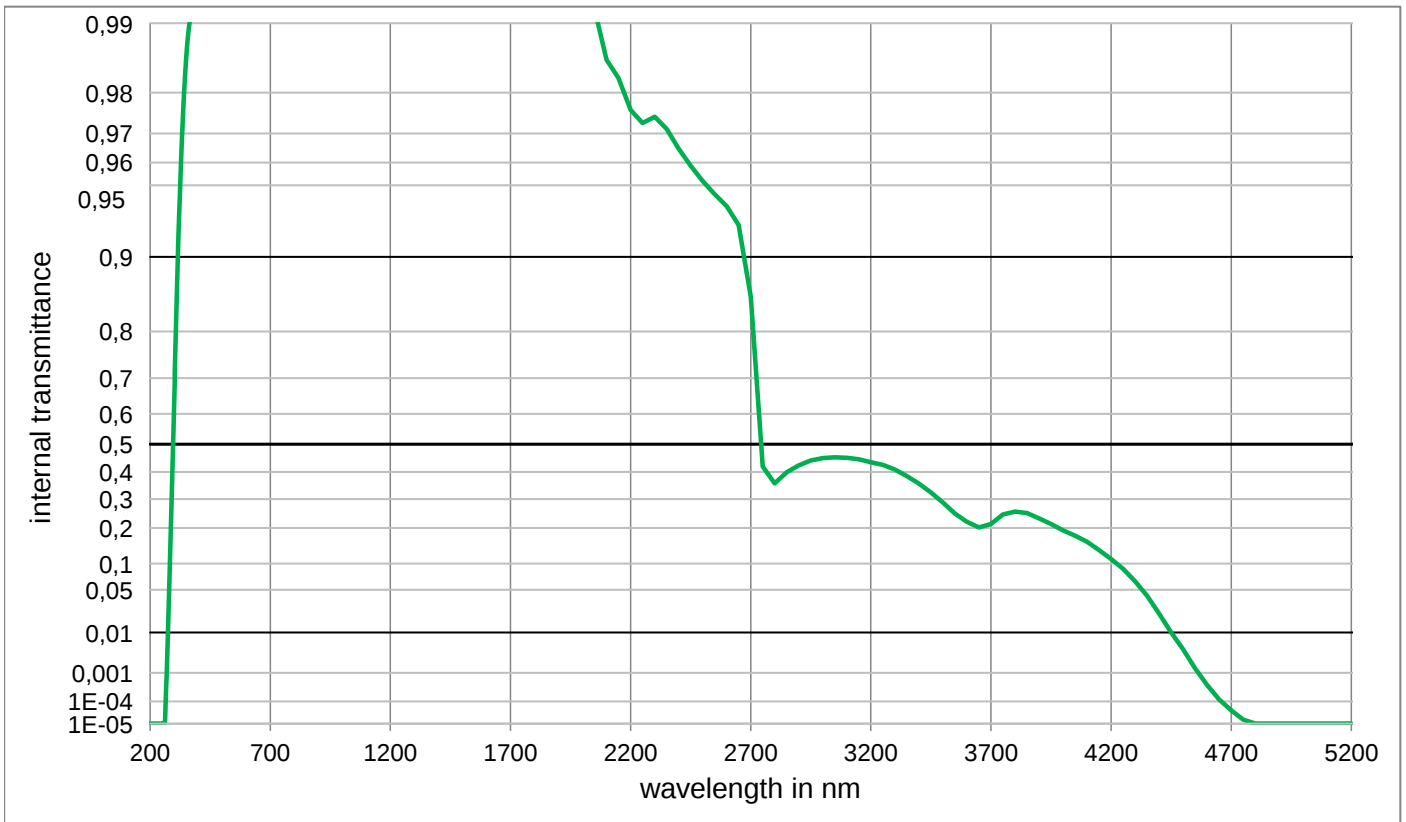
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,966E-01	800	9,999E-01	1100	9,999E-01	2200	9,762E-01	3700	2,127E-01
210	< 1,0E-05	510	9,968E-01	810	9,999E-01	1110	9,999E-01	2250	9,730E-01	3750	2,453E-01
220	< 1,0E-05	520	9,971E-01	820	9,999E-01	1120	9,999E-01	2300	9,746E-01	3800	2,557E-01
230	< 1,0E-05	530	9,973E-01	830	9,999E-01	1130	9,999E-01	2350	9,713E-01	3850	2,500E-01
240	< 1,0E-05	540	9,975E-01	840	9,999E-01	1140	9,999E-01	2400	9,651E-01	3900	2,320E-01
250	< 1,0E-05	550	9,977E-01	850	9,999E-01	1150	9,999E-01	2450	9,587E-01	3950	2,127E-01
260	< 1,0E-05	560	9,978E-01	860	9,999E-01	1160	9,999E-01	2500	9,521E-01	4000	1,921E-01
270	1,6E-03	570	9,980E-01	870	9,999E-01	1170	9,999E-01	2550	9,455E-01	4050	1,753E-01
280	6,4E-02	580	9,981E-01	880	9,999E-01	1180	9,999E-01	2600	9,387E-01	4100	1,574E-01
290	3,3E-01	590	9,982E-01	890	9,999E-01	1190	9,999E-01	2650	9,264E-01	4150	1,342E-01
300	6,4E-01	600	9,984E-01	900	9,999E-01	1200	9,999E-01	2700	8,540E-01	4200	1,111E-01
310	8,4E-01	610	9,985E-01	910	9,999E-01	1250	9,999E-01	2750	4,197E-01	4250	8,840E-02
320	9,279E-01	620	9,986E-01	920	9,999E-01	1300	9,999E-01	2800	3,578E-01	4300	6,370E-02
330	9,630E-01	630	9,987E-01	930	9,999E-01	1350	9,999E-01	2850	3,992E-01	4350	4,140E-02
340	9,787E-01	640	9,988E-01	940	9,999E-01	1400	9,985E-01	2900	4,244E-01	4400	2,230E-02
350	9,859E-01	650	9,989E-01	950	9,999E-01	1450	9,999E-01	2950	4,419E-01	4450	1,000E-02
360	9,893E-01	660	9,991E-01	960	9,999E-01	1500	9,999E-01	3000	4,509E-01	4500	4,310E-03
370	9,909E-01	670	9,992E-01	970	9,999E-01	1550	9,999E-01	3050	4,537E-01	4550	1,352E-03
380	9,919E-01	680	9,993E-01	980	9,999E-01	1600	9,999E-01	3100	4,518E-01	4600	4,070E-04
390	9,928E-01	690	9,994E-01	990	9,999E-01	1650	9,999E-01	3150	4,466E-01	4650	1,191E-04
400	9,934E-01	700	9,995E-01	1000	9,999E-01	1700	9,999E-01	3200	4,357E-01	4700	4,227E-05
410	9,939E-01	710	9,996E-01	1010	9,999E-01	1750	9,997E-01	3250	4,258E-01	4750	1,585E-05
420	9,942E-01	720	9,997E-01	1020	9,999E-01	1800	9,988E-01	3300	4,088E-01	4800	< 1,000E-05
430	9,946E-01	730	9,997E-01	1030	9,999E-01	1850	9,978E-01	3350	3,852E-01	4850	< 1,000E-05
440	9,949E-01	740	9,998E-01	1040	9,999E-01	1900	9,965E-01	3400	3,568E-01	4900	< 1,000E-05
450	9,951E-01	750	9,998E-01	1050	9,999E-01	1950	9,949E-01	3450	3,242E-01	4950	< 1,000E-05
460	9,955E-01	760	9,999E-01	1060	9,999E-01	2000	9,932E-01	3500	2,878E-01	5000	< 1,000E-05
470	9,957E-01	770	9,999E-01	1070	9,999E-01	2050	9,913E-01	3550	2,486E-01	5050	< 1,000E-05
480	9,960E-01	780	9,999E-01	1080	9,999E-01	2100	9,856E-01	3600	2,200E-01	5100	< 1,000E-05
490	9,963E-01	790	9,999E-01	1090	9,999E-01	2150	9,827E-01	3650	2,018E-01	5150	< 1,000E-05

N-WG305

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,918$	$d = 2,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 2 mm)	Density	x
$\lambda_{i0,5} = 305 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,51 \text{ g/cm}^3$	y
$\lambda_s (\tau_{i,U} = 1E-05) = 260 \text{ nm}$	Knoop hardness	Y
$\lambda_p (\tau_{i,L} = 0,99) = 420 \text{ nm}$	$HK_{[0.1/20]} = 610$	λ_d
		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	Notes
$n_d (587,6 \text{ nm}) = 1,52$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,52$	$T_g = 562 \text{ }^\circ\text{C}$	
$n_t (1014 \text{ nm}) = 1,51$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,1$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 8,4$	
	Temperature coefficient	
	$Tk = 0,06 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Base glass
valid from 440 nm to 1550 nm	Chemical resistance	Longpass filter
$B_1 = 1,2190$	FR class = 0	
$B_2 = 0,0699$	SR class = 1	
$B_3 = 106,2629$	AR class = 2	
$C_1 = 5,560E-03 \text{ } \mu\text{m}^2$	Resistance against humidity	ISO 23364:2021
$C_2 = 5,5370E-02 \text{ } \mu\text{m}^2$	Resistant glass	Disclaimer
$C_3 = 10043,976 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	All data without tolerances are to be understood to be reference values.
Internal quality		
Bubble class 1		

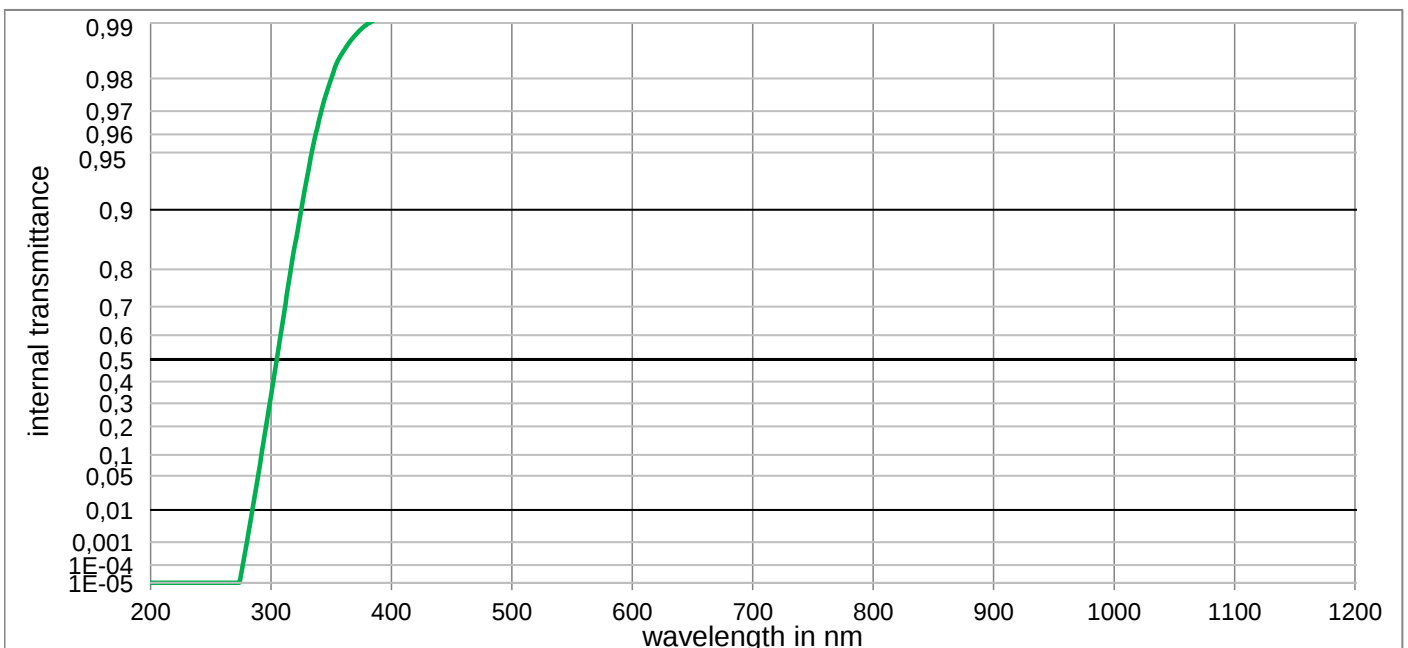

N-WG305

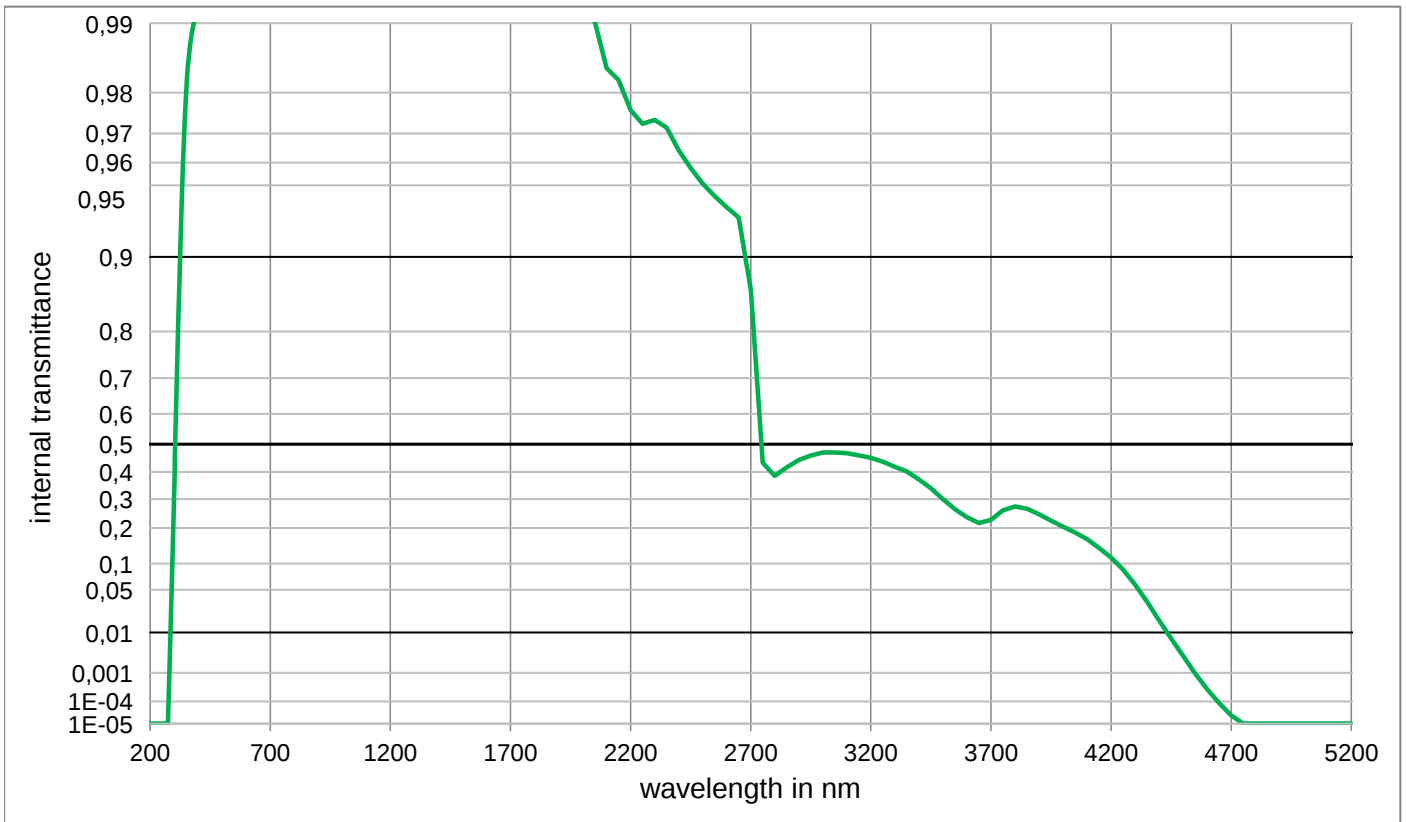
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,949E-01	800	9,987E-01	1100	9,999E-01	2200	9,762E-01	3700	2,268E-01
210	< 1,0E-05	510	9,952E-01	810	9,987E-01	1110	9,999E-01	2250	9,728E-01	3750	2,600E-01
220	< 1,0E-05	520	9,954E-01	820	9,988E-01	1120	9,999E-01	2300	9,738E-01	3800	2,730E-01
230	< 1,0E-05	530	9,957E-01	830	9,988E-01	1130	9,999E-01	2350	9,717E-01	3850	2,656E-01
240	< 1,0E-05	540	9,959E-01	840	9,989E-01	1140	9,999E-01	2400	9,647E-01	3900	2,457E-01
250	< 1,0E-05	550	9,961E-01	850	9,990E-01	1150	9,999E-01	2450	9,577E-01	3950	2,240E-01
260	< 1,0E-05	560	9,962E-01	860	9,990E-01	1160	9,999E-01	2500	9,508E-01	4000	2,042E-01
270	< 1,0E-05	570	9,964E-01	870	9,991E-01	1170	9,999E-01	2550	9,445E-01	4050	1,853E-01
280	1,0E-03	580	9,965E-01	880	9,991E-01	1180	9,999E-01	2600	9,380E-01	4100	1,650E-01
290	6,2E-02	590	9,967E-01	890	9,992E-01	1190	9,999E-01	2650	9,315E-01	4150	1,400E-01
300	3,4E-01	600	9,968E-01	900	9,993E-01	1200	9,999E-01	2700	8,640E-01	4200	1,144E-01
310	6,6E-01	610	9,970E-01	910	9,993E-01	1250	9,999E-01	2750	4,342E-01	4250	8,660E-02
320	8,507E-01	620	9,971E-01	920	9,994E-01	1300	9,999E-01	2800	3,856E-01	4300	5,780E-02
330	9,332E-01	630	9,972E-01	930	9,994E-01	1350	9,999E-01	2850	4,168E-01	4350	3,380E-02
340	9,668E-01	640	9,973E-01	940	9,995E-01	1400	9,970E-01	2900	4,433E-01	4400	1,700E-02
350	9,800E-01	650	9,975E-01	950	9,995E-01	1450	9,994E-01	2950	4,594E-01	4450	7,444E-03
360	9,857E-01	660	9,976E-01	960	9,996E-01	1500	9,999E-01	3000	4,707E-01	4500	2,938E-03
370	9,884E-01	670	9,977E-01	970	9,996E-01	1550	9,999E-01	3050	4,707E-01	4550	9,640E-04
380	9,899E-01	680	9,977E-01	980	9,997E-01	1600	9,999E-01	3100	4,679E-01	4600	2,931E-04
390	9,907E-01	690	9,978E-01	990	9,997E-01	1650	9,995E-01	3150	4,600E-01	4650	8,511E-05
400	9,914E-01	700	9,979E-01	1000	9,998E-01	1700	9,988E-01	3200	4,518E-01	4700	2,483E-05
410	9,920E-01	710	9,980E-01	1010	9,998E-01	1750	9,979E-01	3250	4,376E-01	4750	< 1,000E-05
420	9,924E-01	720	9,981E-01	1020	9,999E-01	1800	9,969E-01	3300	4,188E-01	4800	< 1,000E-05
430	9,928E-01	730	9,982E-01	1030	9,999E-01	1850	9,958E-01	3350	4,017E-01	4850	< 1,000E-05
440	9,931E-01	740	9,983E-01	1040	9,999E-01	1900	9,943E-01	3400	3,724E-01	4900	< 1,000E-05
450	9,935E-01	750	9,983E-01	1050	9,999E-01	1950	9,927E-01	3450	3,401E-01	4950	< 1,000E-05
460	9,937E-01	760	9,984E-01	1060	9,999E-01	2000	9,916E-01	3500	2,997E-01	5000	< 1,000E-05
470	9,940E-01	770	9,985E-01	1070	9,999E-01	2050	9,902E-01	3550	2,637E-01	5050	< 1,000E-05
480	9,943E-01	780	9,985E-01	1080	9,999E-01	2100	9,843E-01	3600	2,360E-01	5100	< 1,000E-05
490	9,946E-01	790	9,986E-01	1090	9,999E-01	2150	9,824E-01	3650	2,164E-01	5150	< 1,000E-05

N-WG320

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,913$	$d = 2,00 \text{ mm}$	
Spectral values guaranteed (d = 2 mm)	Density	Illuminant D65
$\lambda_{i0,5} = 320 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,51 \text{ g/cm}^3$	x
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 280 \text{ nm}$	Knoop hardness	y
$\lambda_p (\tau_{i,L} = 0,99) = 470 \text{ nm}$	$HK_{[0.1/20]} = 610$	Y
		λ_d
		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	Notes
$n_d (587,6 \text{ nm}) = 1,54$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,54$	$T_g = 563 \text{ }^\circ\text{C}$	
$n_t (1014 \text{ nm}) = 1,53$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,1$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 8,4$	
Sellmeier coefficients	Temperature coefficient	
valid from 440 nm to 1550 nm	$Tk = 0,06 \text{ nm/K}$	
$B_1 = 0,8861$	Chemical properties	Base glass
$B_2 = 0,4613$	Chemical resistance	Longpass filter
$B_3 = 29,7610$	FR class = 0	
$C_1 = 9,024\text{E-}03 \text{ } \mu\text{m}^2$	SR class = 1	
$C_2 = 8,3379\text{E-}03 \text{ } \mu\text{m}^2$	AR class = 2	
$C_3 = 3197,045 \text{ } \mu\text{m}^2$	Resistance against humidity	ISO 23364:2021
Internal quality	Resistant glass	Disclaimer
Bubble class 1	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	All data without tolerances are to be understood to be reference values.

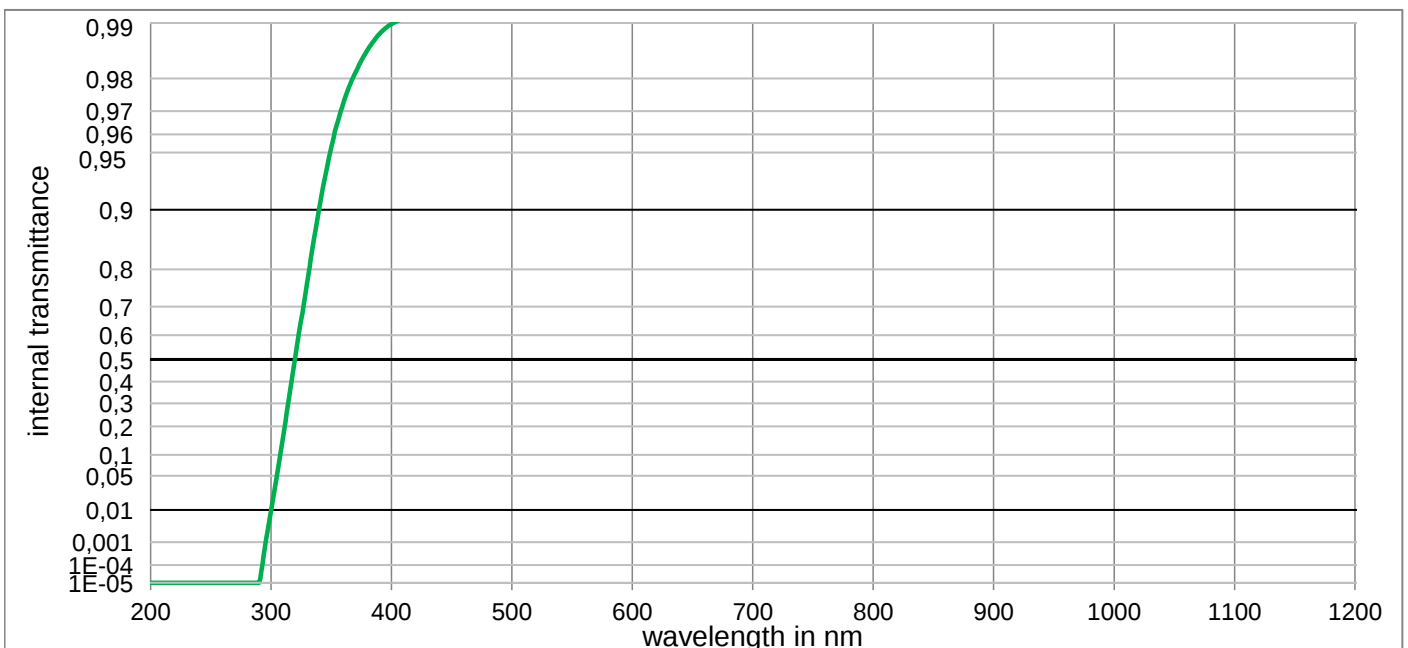

N-WG320

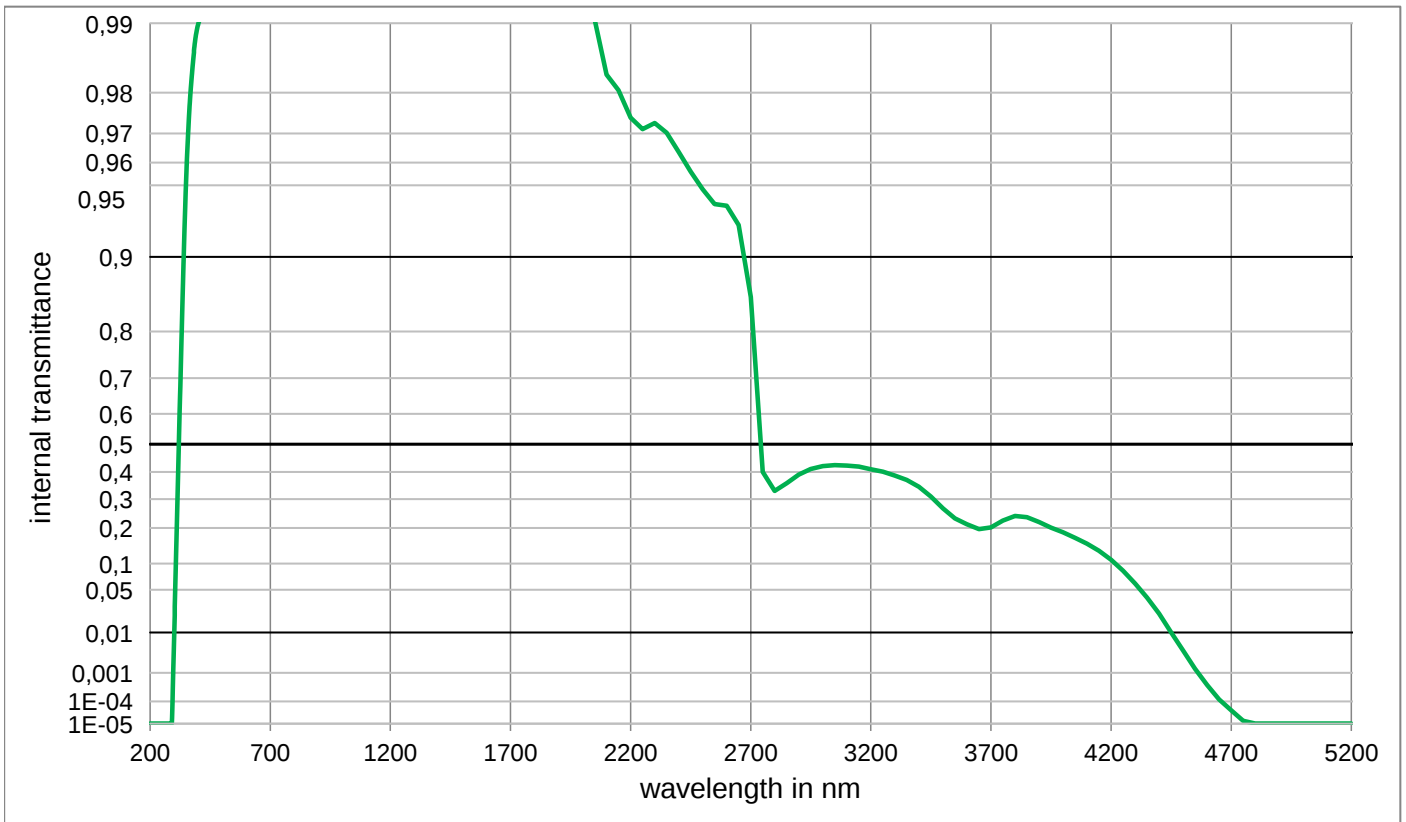
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,940E-01	800	9,983E-01	1100	9,997E-01	2200	9,743E-01	3700	2,020E-01
210	< 1,0E-05	510	9,942E-01	810	9,984E-01	1110	9,998E-01	2250	9,713E-01	3750	2,246E-01
220	< 1,0E-05	520	9,945E-01	820	9,985E-01	1120	9,998E-01	2300	9,729E-01	3800	2,400E-01
230	< 1,0E-05	530	9,948E-01	830	9,985E-01	1130	9,998E-01	2350	9,702E-01	3850	2,356E-01
240	< 1,0E-05	540	9,950E-01	840	9,986E-01	1140	9,999E-01	2400	9,641E-01	3900	2,195E-01
250	< 1,0E-05	550	9,953E-01	850	9,987E-01	1150	9,999E-01	2450	9,562E-01	3950	2,012E-01
260	< 1,0E-05	560	9,955E-01	860	9,987E-01	1160	9,999E-01	2500	9,480E-01	4000	1,864E-01
270	< 1,0E-05	570	9,957E-01	870	9,988E-01	1170	9,999E-01	2550	9,400E-01	4050	1,692E-01
280	< 1,0E-05	580	9,959E-01	880	9,988E-01	1180	9,999E-01	2600	9,389E-01	4100	1,516E-01
290	< 1,0E-05	590	9,960E-01	890	9,989E-01	1190	9,999E-01	2650	9,264E-01	4150	1,323E-01
300	9,6E-03	600	9,962E-01	900	9,989E-01	1200	9,999E-01	2700	8,540E-01	4200	1,092E-01
310	1,6E-01	610	9,964E-01	910	9,990E-01	1250	9,999E-01	2750	4,000E-01	4250	8,440E-02
320	5,066E-01	620	9,965E-01	920	9,990E-01	1300	9,999E-01	2800	3,300E-01	4300	5,970E-02
330	7,700E-01	630	9,967E-01	930	9,990E-01	1350	9,999E-01	2850	3,585E-01	4350	3,896E-02
340	9,013E-01	640	9,968E-01	940	9,991E-01	1400	9,975E-01	2900	3,900E-01	4400	2,230E-02
350	9,533E-01	650	9,969E-01	950	9,991E-01	1450	9,999E-01	2950	4,109E-01	4450	1,000E-02
360	9,728E-01	660	9,970E-01	960	9,992E-01	1500	9,999E-01	3000	4,219E-01	4500	4,000E-03
370	9,814E-01	670	9,971E-01	970	9,992E-01	1550	9,999E-01	3050	4,249E-01	4550	1,318E-03
380	9,859E-01	680	9,972E-01	980	9,993E-01	1600	9,999E-01	3100	4,236E-01	4600	4,070E-04
390	9,885E-01	690	9,973E-01	990	9,993E-01	1650	9,999E-01	3150	4,194E-01	4650	1,191E-04
400	9,899E-01	700	9,974E-01	1000	9,993E-01	1700	9,998E-01	3200	4,100E-01	4700	4,227E-05
410	9,906E-01	710	9,975E-01	1010	9,994E-01	1750	9,990E-01	3250	4,011E-01	4750	1,390E-05
420	9,911E-01	720	9,976E-01	1020	9,994E-01	1800	9,980E-01	3300	3,864E-01	4800	< 1,000E-05
430	9,916E-01	730	9,977E-01	1030	9,995E-01	1850	9,969E-01	3350	3,700E-01	4850	< 1,000E-05
440	9,920E-01	740	9,978E-01	1040	9,995E-01	1900	9,957E-01	3400	3,450E-01	4900	< 1,000E-05
450	9,924E-01	750	9,979E-01	1050	9,995E-01	1950	9,943E-01	3450	3,093E-01	4950	< 1,000E-05
460	9,928E-01	760	9,980E-01	1060	9,996E-01	2000	9,930E-01	3500	2,669E-01	5000	< 1,000E-05
470	9,931E-01	770	9,981E-01	1070	9,996E-01	2050	9,904E-01	3550	2,314E-01	5050	< 1,000E-05
480	9,934E-01	780	9,982E-01	1080	9,996E-01	2100	9,833E-01	3600	2,120E-01	5100	< 1,000E-05
490	9,937E-01	790	9,983E-01	1090	9,997E-01	2150	9,805E-01	3650	1,961E-01	5150	< 1,000E-05

N-WG360

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,917$	$d = 2,00 \text{ mm}$	x 0,313 0,313 0,313
Spectral values guaranteed (d = 2 mm)	Density	y 0,329 0,330 0,330
$\lambda_{i0,5} = 360 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,69 \text{ g/cm}^3$	Y 91,4 91,0 90,7
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 335 \text{ nm}$	Knoop hardness	λ_d 575 nm 575 nm 575 nm
$\lambda_p (\tau_{i,L} = 0,99) = 535 \text{ nm}$	$HK_{[0.1/20]} = 474$	P_e 0,001 0,003 0,004
		Illuminant A
		x 0,448 0,448 0,448
		y 0,408 0,408 0,408
		Y 91,4 91,0 90,7
		λ_d 585 nm 585 nm 585 nm
		P_e 0,002 0,004 0,006
Refractive indices	Thermal properties	Notes
$n_d (587,6 \text{ nm}) = 1,53$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,52$	$T_g = 522 \text{ }^\circ\text{C}$	Ionically colored glass
$n_t (1014 \text{ nm}) = 1,52$	Thermal expansion in $10^{-6}/\text{K}$	Longpass filter
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,8$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 8,9$	
Sellmeier coefficients	Chemical properties	
valid from 365 nm to 2325 nm	Chemical resistance	
$B_1 = 1,2534$	FR class = 0	
$B_2 = 0,0409$	SR class = 1.0	
$B_3 = 0,8749$	AR class = 2.0	
$C_1 = 8,285\text{E-}03 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 3,9133\text{E-}02 \text{ } \mu\text{m}^2$	Resistant glass	ISO 23364:2021
$C_3 = 106,087 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	Disclaimer
Internal quality		All data without tolerances are to be understood to be reference values.
Bubble class -		

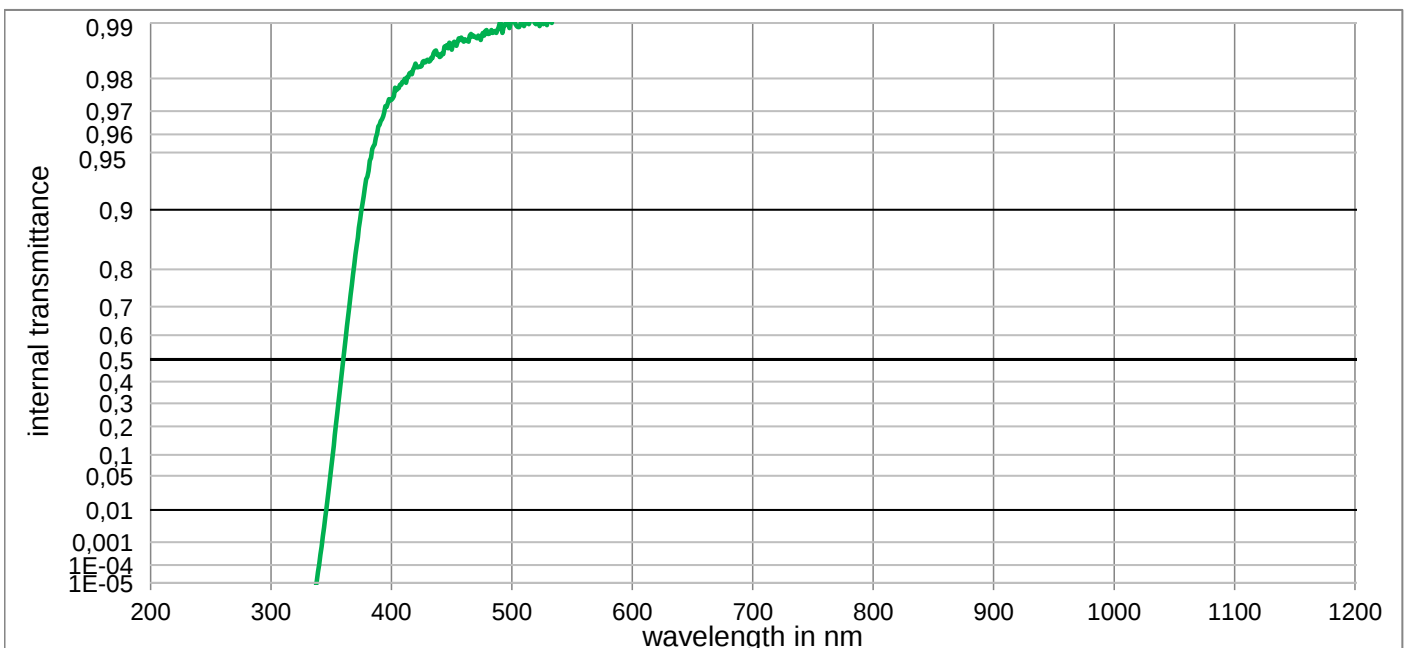


N-WG360

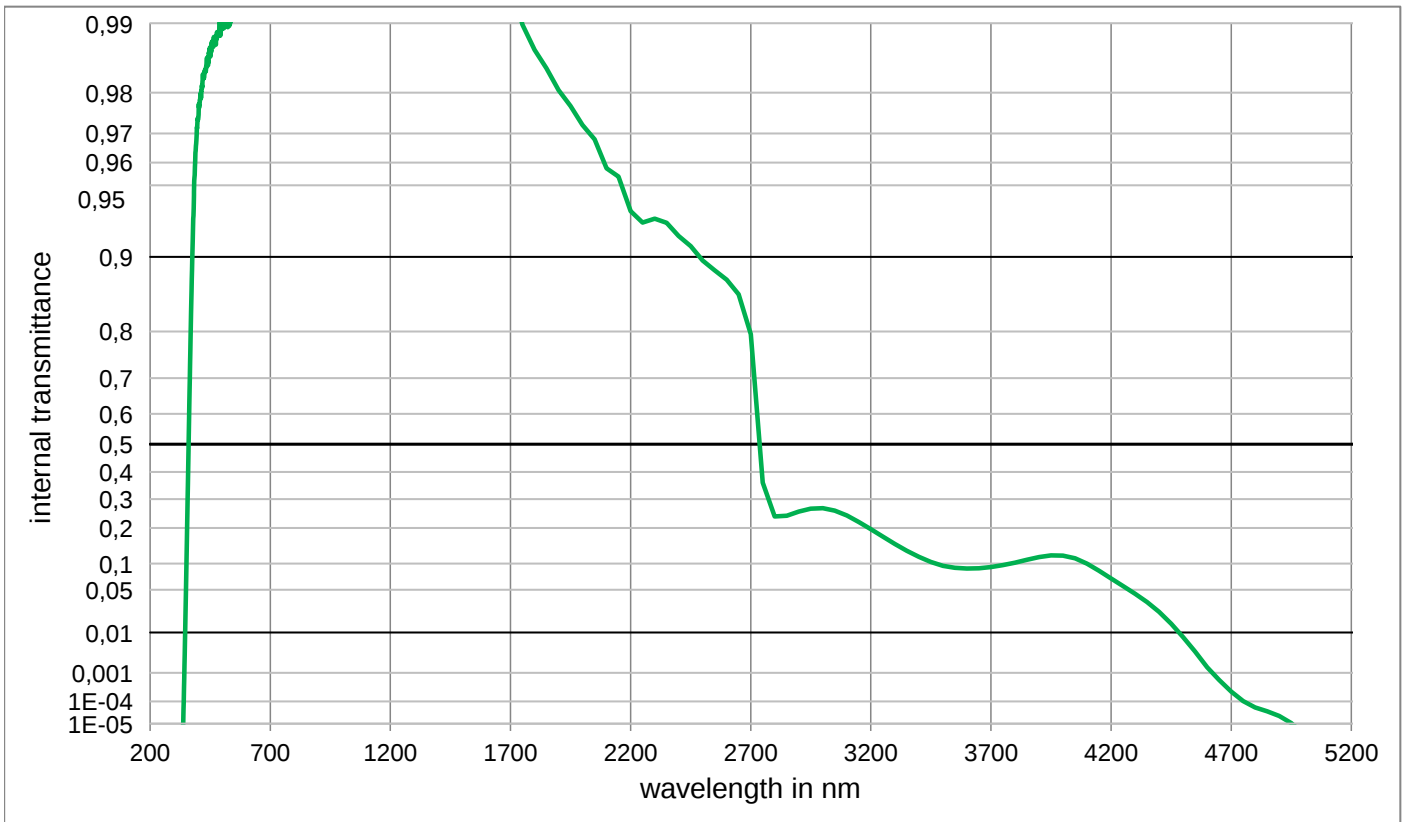Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,905E-01	800	9,965E-01	1100	9,974E-01	2200	9,357E-01	3700	9,206E-02
210	< 1,0E-05	510	9,896E-01	810	9,946E-01	1110	9,970E-01	2250	9,281E-01	3750	9,647E-02
220	< 1,0E-05	520	9,899E-01	820	9,954E-01	1120	9,965E-01	2300	9,308E-01	3800	1,023E-01
230	< 1,0E-05	530	9,907E-01	830	9,921E-01	1130	9,974E-01	2350	9,279E-01	3850	1,092E-01
240	< 1,0E-05	540	9,909E-01	840	9,979E-01	1140	9,967E-01	2400	9,181E-01	3900	1,158E-01
250	< 1,0E-05	550	9,913E-01	850	9,985E-01	1150	9,975E-01	2450	9,097E-01	3950	1,200E-01
260	< 1,0E-05	560	9,913E-01	860	9,952E-01	1160	9,970E-01	2500	8,964E-01	4000	1,195E-01
270	< 1,0E-05	570	9,916E-01	870	9,962E-01	1170	9,974E-01	2550	8,866E-01	4050	1,127E-01
280	< 1,0E-05	580	9,924E-01	880	9,942E-01	1180	9,979E-01	2600	8,759E-01	4100	9,989E-02
290	< 1,0E-05	590	9,920E-01	890	9,952E-01	1190	9,975E-01	2650	8,577E-01	4150	8,423E-02
300	< 1,0E-05	600	9,930E-01	900	9,961E-01	1200	9,974E-01	2700	7,951E-01	4200	6,895E-02
310	< 1,0E-05	610	9,918E-01	910	9,971E-01	1250	9,975E-01	2750	3,602E-01	4250	5,560E-02
320	< 1,00E-05	620	9,925E-01	920	9,965E-01	1300	9,975E-01	2800	2,381E-01	4300	4,425E-02
330	< 1,000E-05	630	9,930E-01	930	9,967E-01	1350	9,969E-01	2850	2,411E-01	4350	3,377E-02
340	1,057E-04	640	9,933E-01	940	9,959E-01	1400	9,942E-01	2900	2,553E-01	4400	2,368E-02
350	6,888E-02	650	9,930E-01	950	9,961E-01	1450	9,954E-01	2950	2,659E-01	4450	1,477E-02
360	5,004E-01	660	9,937E-01	960	9,965E-01	1500	9,971E-01	3000	2,677E-01	4500	8,017E-03
370	8,309E-01	670	9,940E-01	970	9,959E-01	1550	9,971E-01	3050	2,591E-01	4550	3,770E-03
380	9,328E-01	680	9,941E-01	980	9,955E-01	1600	9,950E-01	3100	2,422E-01	4600	1,463E-03
390	9,644E-01	690	9,948E-01	990	9,953E-01	1650	9,952E-01	3150	2,198E-01	4650	5,978E-04
400	9,739E-01	700	9,944E-01	1000	9,969E-01	1700	9,937E-01	3200	1,960E-01	4700	2,356E-04
410	9,792E-01	710	9,953E-01	1010	9,967E-01	1750	9,899E-01	3250	1,727E-01	4750	1,034E-04
420	9,834E-01	720	9,957E-01	1020	9,969E-01	1800	9,870E-01	3300	1,514E-01	4800	5,671E-05
430	9,842E-01	730	9,952E-01	1030	9,966E-01	1850	9,843E-01	3350	1,324E-01	4850	3,765E-05
440	9,847E-01	740	9,959E-01	1040	9,975E-01	1900	9,805E-01	3400	1,163E-01	4900	2,374E-05
450	9,860E-01	750	9,944E-01	1050	9,970E-01	1950	9,772E-01	3450	1,035E-01	4950	1,069E-05
460	9,873E-01	760	9,958E-01	1060	9,971E-01	2000	9,724E-01	3500	9,490E-02	5000	< 1,000E-05
470	9,880E-01	770	9,958E-01	1070	9,965E-01	2050	9,682E-01	3550	9,043E-02	5050	< 1,000E-05
480	9,885E-01	780	9,952E-01	1080	9,969E-01	2100	9,577E-01	3600	8,906E-02	5100	< 1,000E-05
490	9,901E-01	790	9,946E-01	1090	9,971E-01	2150	9,541E-01	3650	8,965E-02	5150	< 1,000E-05

Optical properties		Mechanical properties		Colormetric properties				
Reflection factor		Reference thickness						
P _d = 0,918		d = 3,00 mm						
Spectral values guaranteed (d = 3 mm)		Density		Illuminant D65		1 mm	2 mm	3 mm
λ _{i0,5} = 395 nm ± 6 nm		ρ = 2,55 g/cm³			x	0,314	0,315	0,316
λ _s (τ _{i,U} = 1E-05) = 340 nm		Knoop hardness			y	0,331	0,332	0,334
λ _p (τ _{i,L} = 0,92) = 480 nm		HK _[0.1/20] = 409			Y	91,1	90,5	89,8
					λ _d	570 nm	570 nm	571 nm
				P _e	0,008	0,016	0,023	
				Illuminant A	x	0,448	0,449	0,450
					y	0,408	0,409	0,410
					Y	91,1	90,6	90,0
					λ _d	581 nm	581 nm	581 nm
					P _e	0,010	0,020	0,030
Refractive indices		Thermal properties		Notes				
n _d (587,6 nm) = 1,52		Transformation temperature						
n _s (852 nm) = 1,52		Tg = 538 °C						
n _t (1014 nm) = 1,51		Thermal expansion in 10 ⁻⁶ /K						
		α (-30°C/+70°C) = 7,8						
		α (20°C/300°C) = 9,0						
		Temperature coefficient						
		Tk = 0,07 nm/K						
Sellmeier coefficients		Chemical properties		Stricking glass				
on request		Chemical resistance		Longpass filter				
		FR class = 0						
		SR class = 1						
		AR class = 1						
		Resistance against humidity						
		Robust glass		ISO 23364:2021				
Internal quality		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		Disclaimer				
Bubble class 3				All data without tolerances are to be understood to be reference values.				

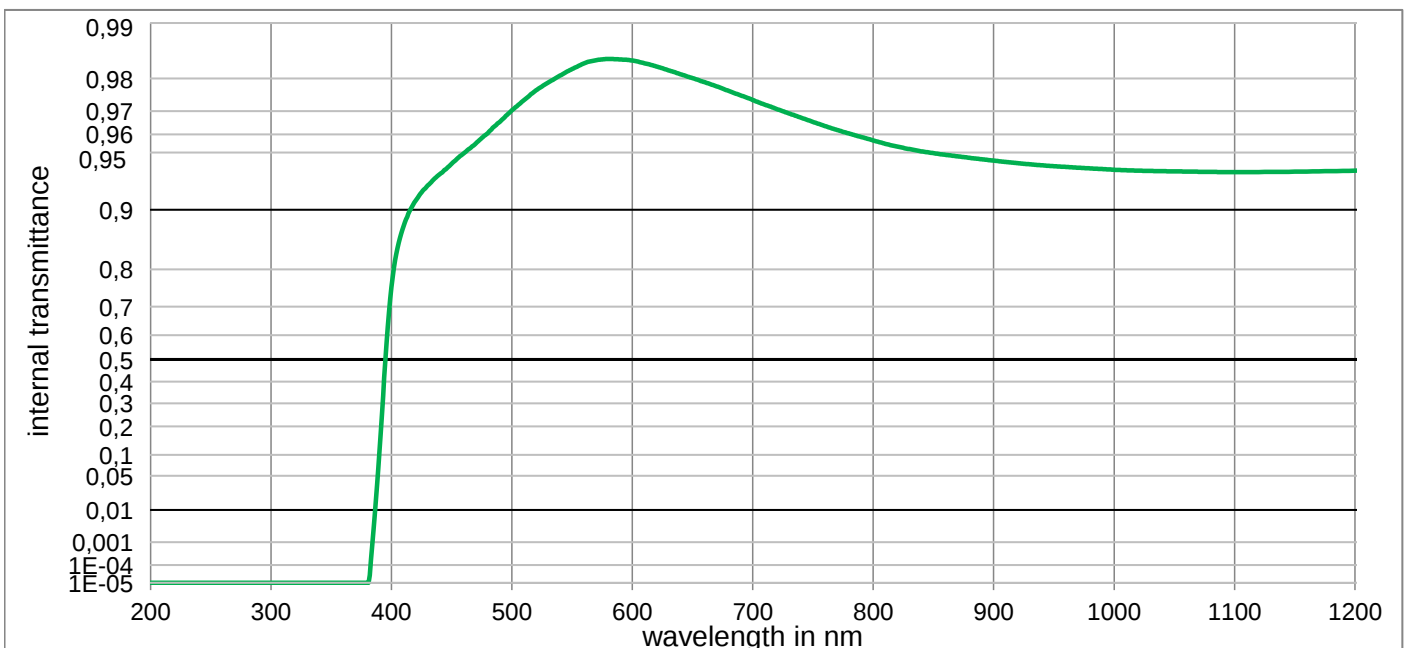

GG395

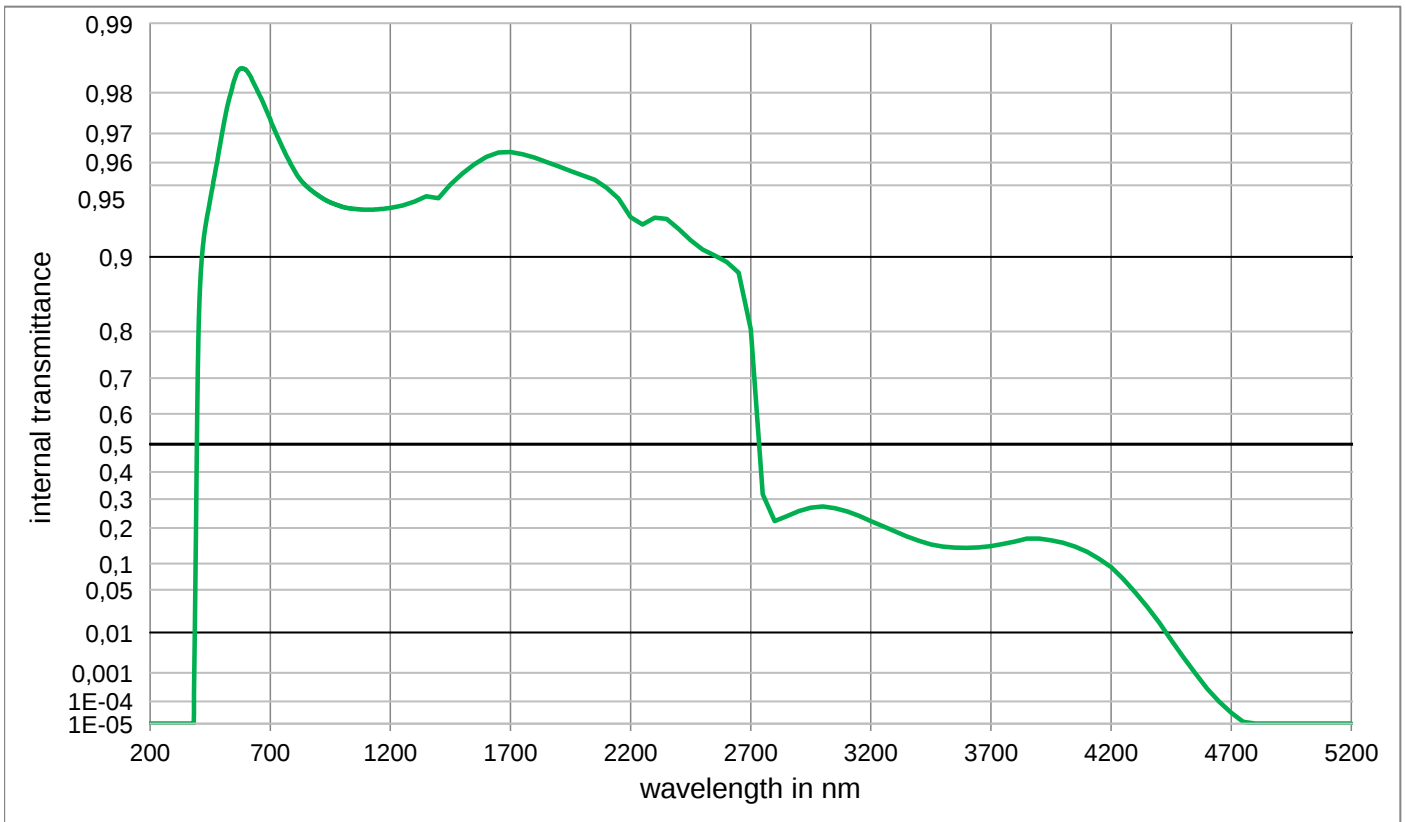
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,703E-01	800	9,569E-01	1100	9,365E-01	2200	9,318E-01	3700	1,448E-01
210	< 1,0E-05	510	9,738E-01	810	9,551E-01	1110	9,365E-01	2250	9,268E-01	3750	1,512E-01
220	< 1,0E-05	520	9,768E-01	820	9,535E-01	1120	9,366E-01	2300	9,315E-01	3800	1,583E-01
230	< 1,0E-05	530	9,789E-01	830	9,521E-01	1130	9,366E-01	2350	9,306E-01	3850	1,667E-01
240	< 1,0E-05	540	9,807E-01	840	9,507E-01	1140	9,367E-01	2400	9,235E-01	3900	1,668E-01
250	< 1,0E-05	550	9,823E-01	850	9,496E-01	1150	9,368E-01	2450	9,147E-01	3950	1,618E-01
260	< 1,0E-05	560	9,835E-01	860	9,486E-01	1160	9,369E-01	2500	9,067E-01	4000	1,544E-01
270	< 1,0E-05	570	9,841E-01	870	9,476E-01	1170	9,371E-01	2550	9,014E-01	4050	1,433E-01
280	< 1,0E-05	580	9,843E-01	880	9,467E-01	1180	9,372E-01	2600	8,950E-01	4100	1,295E-01
290	< 1,0E-05	590	9,842E-01	890	9,457E-01	1190	9,374E-01	2650	8,838E-01	4150	1,116E-01
300	< 1,0E-05	600	9,840E-01	900	9,448E-01	1200	9,376E-01	2700	8,040E-01	4200	9,191E-02
310	< 1,0E-05	610	9,835E-01	910	9,439E-01	1250	9,391E-01	2750	3,176E-01	4250	6,847E-02
320	< 1,00E-05	620	9,828E-01	920	9,431E-01	1300	9,414E-01	2800	2,228E-01	4300	4,612E-02
330	< 1,000E-05	630	9,819E-01	930	9,422E-01	1350	9,443E-01	2850	2,391E-01	4350	2,855E-02
340	< 1,000E-05	640	9,810E-01	940	9,416E-01	1400	9,433E-01	2900	2,571E-01	4400	1,568E-02
350	< 1,000E-05	650	9,801E-01	950	9,409E-01	1450	9,504E-01	2950	2,688E-01	4450	6,940E-03
360	< 1,000E-05	660	9,791E-01	960	9,404E-01	1500	9,555E-01	3000	2,738E-01	4500	2,800E-03
370	< 1,000E-05	670	9,779E-01	970	9,398E-01	1550	9,594E-01	3050	2,675E-01	4550	9,940E-04
380	< 1,000E-05	680	9,766E-01	980	9,393E-01	1600	9,622E-01	3100	2,561E-01	4600	3,013E-04
390	1,131E-01	690	9,753E-01	990	9,388E-01	1650	9,638E-01	3150	2,409E-01	4650	9,863E-05
400	7,568E-01	700	9,739E-01	1000	9,383E-01	1700	9,640E-01	3200	2,224E-01	4700	3,281E-05
410	8,785E-01	710	9,723E-01	1010	9,379E-01	1750	9,632E-01	3250	2,055E-01	4750	1,227E-05
420	9,102E-01	720	9,708E-01	1020	9,376E-01	1800	9,619E-01	3300	1,892E-01	4800	< 1,000E-05
430	9,252E-01	730	9,691E-01	1030	9,374E-01	1850	9,602E-01	3350	1,733E-01	4850	< 1,000E-05
440	9,348E-01	740	9,675E-01	1040	9,372E-01	1900	9,585E-01	3400	1,601E-01	4900	< 1,000E-05
450	9,427E-01	750	9,657E-01	1050	9,370E-01	1950	9,566E-01	3450	1,494E-01	4950	< 1,000E-05
460	9,495E-01	760	9,639E-01	1060	9,369E-01	2000	9,546E-01	3500	1,437E-01	5000	< 1,000E-05
470	9,553E-01	770	9,621E-01	1070	9,368E-01	2050	9,526E-01	3550	1,407E-01	5050	< 1,000E-05
480	9,606E-01	780	9,604E-01	1080	9,366E-01	2100	9,487E-01	3600	1,403E-01	5100	< 1,000E-05
490	9,658E-01	790	9,587E-01	1090	9,365E-01	2150	9,432E-01	3650	1,412E-01	5150	< 1,000E-05

GG400

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,918$	$d = 3,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 3 mm)	Density	x 0,314 0,315 0,316
$\lambda_{i0,5} = 400 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,55 \text{ g/cm}^3$	y 0,331 0,333 0,335
$\lambda_s(\tau_{i,U} = 1E-05) = 340 \text{ nm}$	Knoop hardness	Y 91,2 90,7 90,2
$\lambda_p(\tau_{i,L} = 0,93) = 480 \text{ nm}$	$HK_{[0.1/20]} = 463$	λ_d 570 nm 571 nm 571 nm
		P_e 0,009 0,017 0,025
		Illuminant A
	Thermal properties	x 0,448 0,449 0,450
	Transformation temperature	y 0,408 0,409 0,410
	$T_g = 537 \text{ }^\circ\text{C}$	Y 91,2 90,8 90,4
	Thermal expansion in $10^{-6}/\text{K}$	λ_d 581 nm 581 nm 581 nm
Refractive indices	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,9$	P_e 0,011 0,022 0,032
$n_d(587,6 \text{ nm}) = 1,52$	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,1$	
$n_s(852 \text{ nm}) = 1,52$	Temperature coefficient	
$n_t(1014 \text{ nm}) = 1,51$	$Tk = 0,07 \text{ nm/K}$	Notes
Sellmeier coefficients	Chemical properties	
on request	Chemical resistance	Stricking glass
	FR class = 0	Longpass filter
	SR class = 1	
	AR class = 1	
	Resistance against humidity	
	Robust glass	ISO 23364:2021
Internal quality	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	Disclaimer
Bubble class 3		All data without tolerances are to be understood to be reference values.

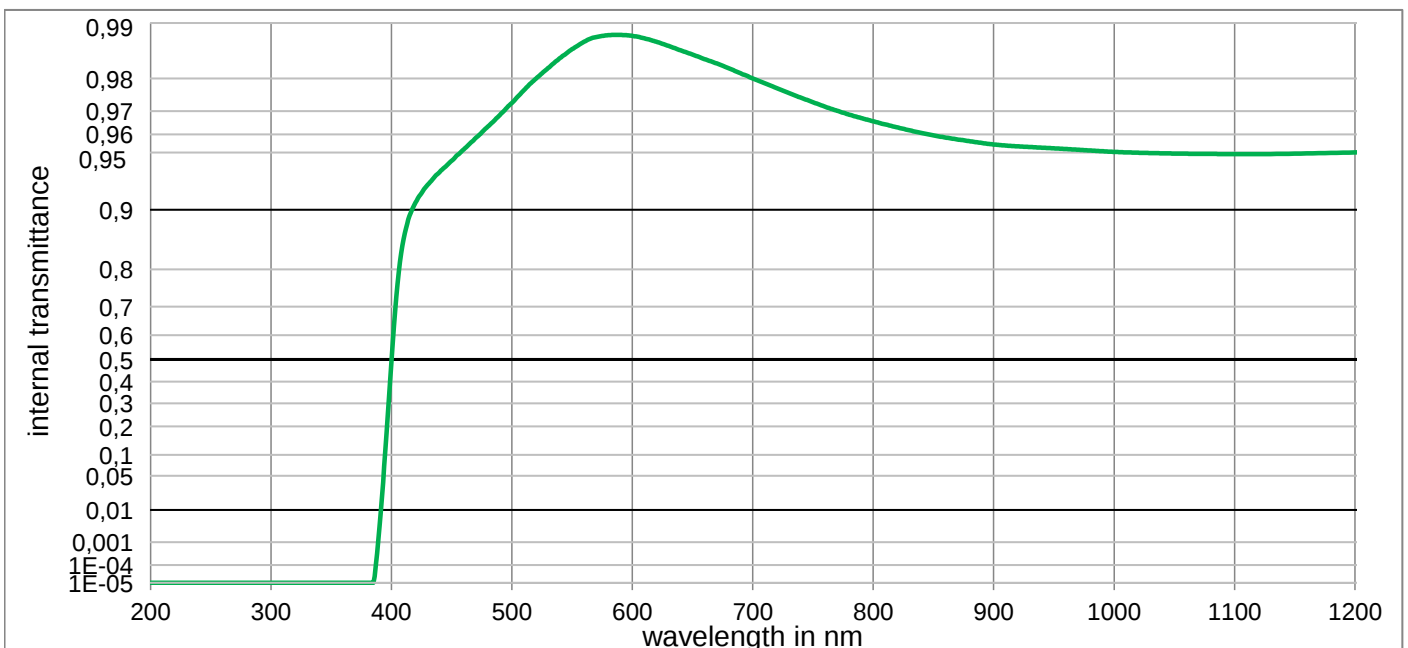


GG400

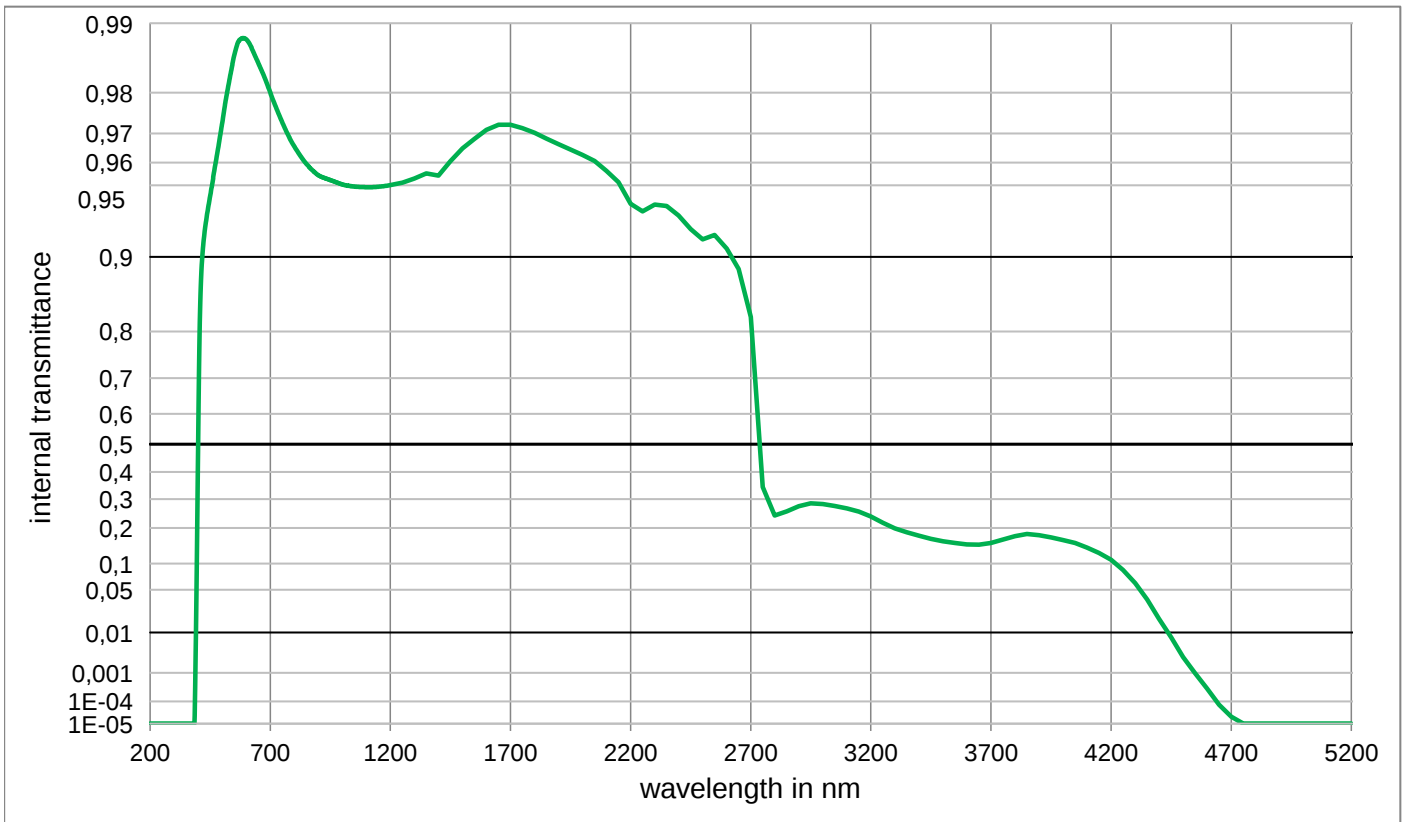Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,729E-01	800	9,660E-01	1100	9,491E-01	2200	9,401E-01	3700	1,537E-01
210	< 1,0E-05	510	9,769E-01	810	9,646E-01	1110	9,491E-01	2250	9,355E-01	3750	1,636E-01
220	< 1,0E-05	520	9,800E-01	820	9,633E-01	1120	9,491E-01	2300	9,397E-01	3800	1,740E-01
230	< 1,0E-05	530	9,825E-01	830	9,620E-01	1130	9,491E-01	2350	9,388E-01	3850	1,810E-01
240	< 1,0E-05	540	9,845E-01	840	9,607E-01	1140	9,492E-01	2400	9,329E-01	3900	1,771E-01
250	< 1,0E-05	550	9,861E-01	850	9,595E-01	1150	9,493E-01	2450	9,234E-01	3950	1,704E-01
260	< 1,0E-05	560	9,873E-01	860	9,584E-01	1160	9,494E-01	2500	9,154E-01	4000	1,625E-01
270	< 1,0E-05	570	9,881E-01	870	9,574E-01	1170	9,496E-01	2550	9,190E-01	4050	1,540E-01
280	< 1,0E-05	580	9,883E-01	880	9,565E-01	1180	9,497E-01	2600	9,076E-01	4100	1,405E-01
290	< 1,0E-05	590	9,884E-01	890	9,555E-01	1190	9,499E-01	2650	8,878E-01	4150	1,266E-01
300	< 1,0E-05	600	9,883E-01	900	9,547E-01	1200	9,501E-01	2700	8,248E-01	4200	1,089E-01
310	< 1,0E-05	610	9,879E-01	910	9,541E-01	1250	9,512E-01	2750	3,440E-01	4250	8,600E-02
320	< 1,00E-05	620	9,874E-01	920	9,537E-01	1300	9,533E-01	2800	2,420E-01	4300	6,050E-02
330	< 1,000E-05	630	9,867E-01	930	9,533E-01	1350	9,555E-01	2850	2,560E-01	4350	3,670E-02
340	< 1,000E-05	640	9,859E-01	940	9,529E-01	1400	9,545E-01	2900	2,740E-01	4400	1,800E-02
350	< 1,000E-05	650	9,852E-01	950	9,525E-01	1450	9,605E-01	2950	2,848E-01	4450	7,910E-03
360	< 1,000E-05	660	9,843E-01	960	9,521E-01	1500	9,652E-01	3000	2,819E-01	4500	2,760E-03
370	< 1,000E-05	670	9,834E-01	970	9,517E-01	1550	9,683E-01	3050	2,755E-01	4550	9,780E-04
380	< 1,000E-05	680	9,824E-01	980	9,512E-01	1600	9,710E-01	3100	2,667E-01	4600	3,000E-04
390	3,430E-03	690	9,812E-01	990	9,508E-01	1650	9,725E-01	3150	2,557E-01	4650	7,345E-05
400	4,907E-01	700	9,800E-01	1000	9,504E-01	1700	9,725E-01	3200	2,381E-01	4700	2,171E-05
410	8,588E-01	710	9,788E-01	1010	9,501E-01	1750	9,715E-01	3250	2,170E-01	4750	< 1,000E-05
420	9,082E-01	720	9,774E-01	1020	9,499E-01	1800	9,702E-01	3300	1,987E-01	4800	< 1,000E-05
430	9,259E-01	730	9,760E-01	1030	9,497E-01	1850	9,684E-01	3350	1,864E-01	4850	< 1,000E-05
440	9,365E-01	740	9,746E-01	1040	9,495E-01	1900	9,666E-01	3400	1,757E-01	4900	< 1,000E-05
450	9,448E-01	750	9,731E-01	1050	9,494E-01	1950	9,648E-01	3450	1,659E-01	4950	< 1,000E-05
460	9,518E-01	760	9,716E-01	1060	9,493E-01	2000	9,629E-01	3500	1,586E-01	5000	< 1,000E-05
470	9,583E-01	770	9,702E-01	1070	9,492E-01	2050	9,606E-01	3550	1,536E-01	5050	< 1,000E-05
480	9,636E-01	780	9,687E-01	1080	9,491E-01	2100	9,565E-01	3600	1,499E-01	5100	< 1,000E-05
490	9,686E-01	790	9,673E-01	1090	9,491E-01	2150	9,515E-01	3650	1,493E-01	5150	< 1,000E-05

Optical properties		Mechanical properties		Colormetric properties			
Reflection factor		Reference thickness					
P _d = 0,918		d = 3,00 mm					
Spectral values guaranteed (d = 3 mm)		Density		Illuminant D65			
λ _{i0,5} = 420 nm ± 6 nm		ρ = 2,55 g/cm³					
Knoop hardness							
HK _[0.1/20] = 503							
		Thermal properties		Illuminant A			
		Transformation temperature					
		Tg = 535 °C					
		Thermal expansion in 10 ⁻⁶ /K					
		α _(-30°C/+70°C) = 7,8					
Refractive indices		α _(20°C/300°C) = 9,0					
n _d (587,6 nm) = 1,52							
n _s (852 nm) = 1,52		Temperature coefficient					
n _t (1014 nm) = 1,51		Tk = 0,07 nm/K					
Sellmeier coefficients		Chemical properties		Notes			
on request		Chemical resistance					
		FR class = 0		Stricking glass			
		SR class = 1		Longpass filter			
		AR class = 1					
Internal quality		Resistance against humidity					
Bubble class 3		Robust glass		ISO 23364:2021			
		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		Disclaimer			
				All data without tolerances are to be understood to be reference values.			

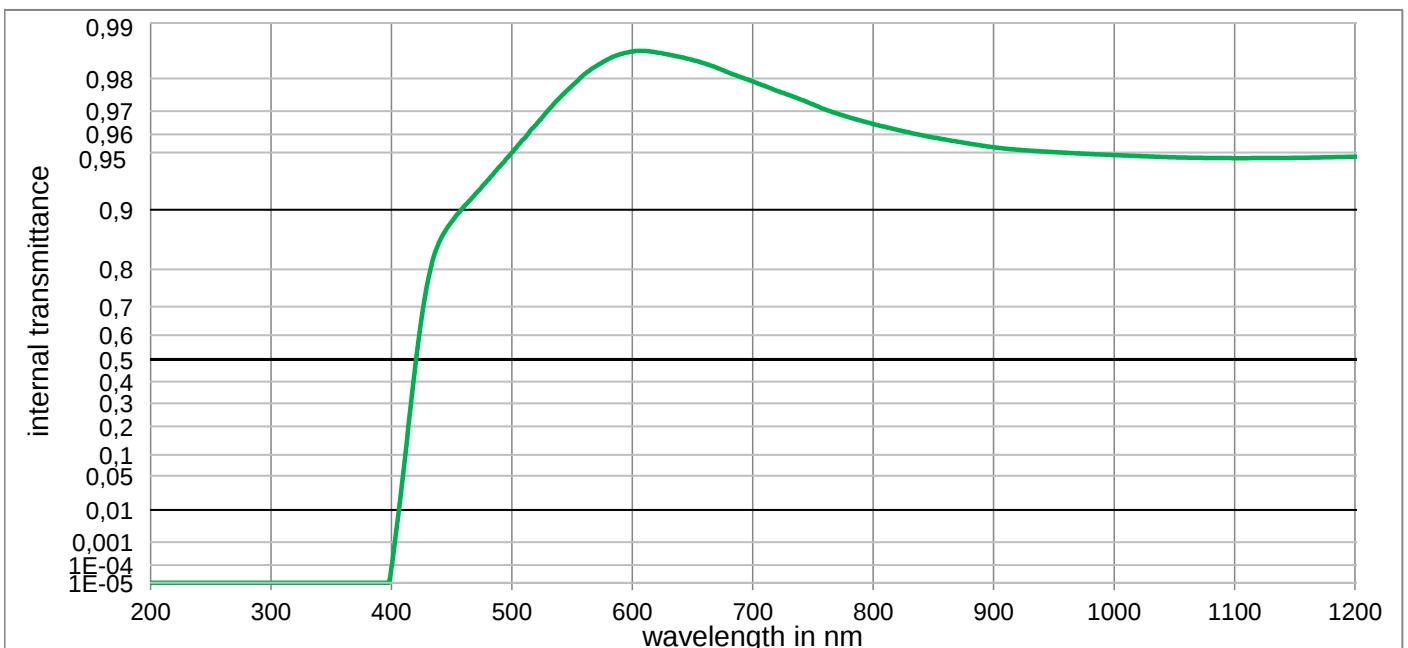


GG420

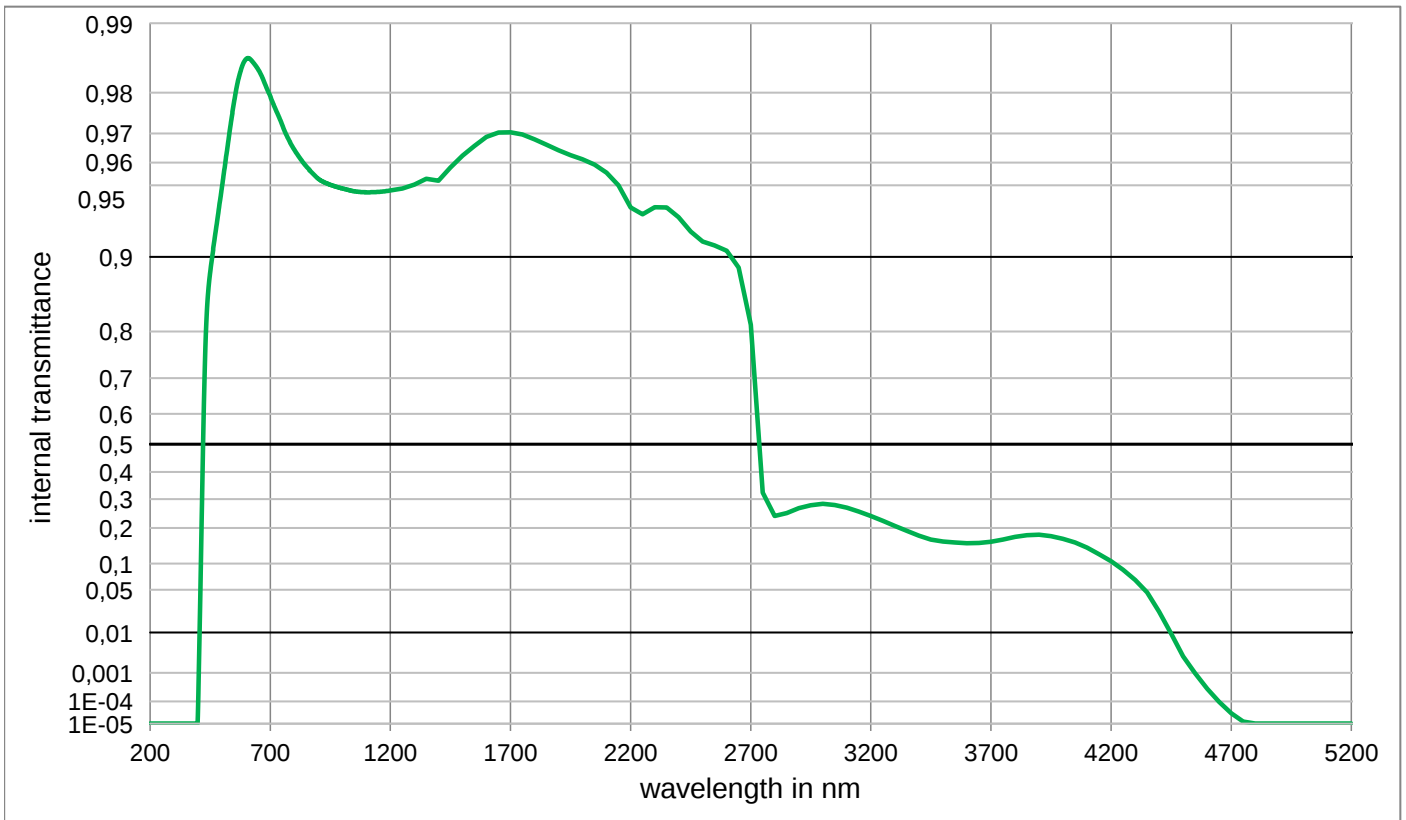Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,500E-01	800	9,649E-01	1100	9,465E-01	2200	9,379E-01	3700	1,571E-01
210	< 1,0E-05	510	9,578E-01	810	9,635E-01	1110	9,465E-01	2250	9,336E-01	3750	1,636E-01
220	< 1,0E-05	520	9,645E-01	820	9,622E-01	1120	9,465E-01	2300	9,381E-01	3800	1,720E-01
230	< 1,0E-05	530	9,703E-01	830	9,609E-01	1130	9,465E-01	2350	9,380E-01	3850	1,772E-01
240	< 1,0E-05	540	9,747E-01	840	9,596E-01	1140	9,466E-01	2400	9,317E-01	3900	1,785E-01
250	< 1,0E-05	550	9,781E-01	850	9,585E-01	1150	9,467E-01	2450	9,215E-01	3950	1,744E-01
260	< 1,0E-05	560	9,809E-01	860	9,574E-01	1160	9,468E-01	2500	9,136E-01	4000	1,660E-01
270	< 1,0E-05	570	9,829E-01	870	9,563E-01	1170	9,469E-01	2550	9,104E-01	4050	1,550E-01
280	< 1,0E-05	580	9,843E-01	880	9,552E-01	1180	9,470E-01	2600	9,056E-01	4100	1,410E-01
290	< 1,0E-05	590	9,852E-01	890	9,541E-01	1190	9,472E-01	2650	8,892E-01	4150	1,232E-01
300	< 1,0E-05	600	9,857E-01	900	9,531E-01	1200	9,474E-01	2700	8,120E-01	4200	1,053E-01
310	< 1,0E-05	610	9,858E-01	910	9,523E-01	1250	9,484E-01	2750	3,239E-01	4250	8,629E-02
320	< 1,00E-05	620	9,856E-01	920	9,517E-01	1300	9,504E-01	2800	2,398E-01	4300	6,632E-02
330	< 1,000E-05	630	9,852E-01	930	9,512E-01	1350	9,531E-01	2850	2,500E-01	4350	4,599E-02
340	< 1,000E-05	640	9,847E-01	940	9,507E-01	1400	9,522E-01	2900	2,672E-01	4400	2,394E-02
350	< 1,000E-05	650	9,841E-01	950	9,503E-01	1450	9,580E-01	2950	2,777E-01	4450	9,460E-03
360	< 1,000E-05	660	9,834E-01	960	9,499E-01	1500	9,626E-01	3000	2,832E-01	4500	2,866E-03
370	< 1,000E-05	670	9,825E-01	970	9,495E-01	1550	9,660E-01	3050	2,786E-01	4550	9,830E-04
380	< 1,000E-05	680	9,814E-01	980	9,491E-01	1600	9,690E-01	3100	2,687E-01	4600	3,006E-04
390	< 1,000E-05	690	9,803E-01	990	9,488E-01	1650	9,703E-01	3150	2,553E-01	4650	9,550E-05
400	7,048E-05	700	9,792E-01	1000	9,484E-01	1700	9,704E-01	3200	2,405E-01	4700	3,112E-05
410	6,112E-02	710	9,780E-01	1010	9,481E-01	1750	9,697E-01	3250	2,235E-01	4750	1,250E-05
420	4,792E-01	720	9,767E-01	1020	9,478E-01	1800	9,682E-01	3300	2,064E-01	4800	< 1,000E-05
430	7,703E-01	730	9,754E-01	1030	9,475E-01	1850	9,665E-01	3350	1,911E-01	4850	< 1,000E-05
440	8,551E-01	740	9,740E-01	1040	9,472E-01	1900	9,646E-01	3400	1,760E-01	4900	< 1,000E-05
450	8,849E-01	750	9,724E-01	1050	9,470E-01	1950	9,628E-01	3450	1,639E-01	4950	< 1,000E-05
460	9,032E-01	760	9,706E-01	1060	9,468E-01	2000	9,612E-01	3500	1,578E-01	5000	< 1,000E-05
470	9,176E-01	770	9,691E-01	1070	9,467E-01	2050	9,591E-01	3550	1,551E-01	5050	< 1,000E-05
480	9,300E-01	780	9,676E-01	1080	9,466E-01	2100	9,559E-01	3600	1,535E-01	5100	< 1,000E-05
490	9,409E-01	790	9,662E-01	1090	9,465E-01	2150	9,500E-01	3650	1,540E-01	5150	< 1,000E-05

Optical properties		Mechanical properties		Colormetric properties	
Reflection factor		Reference thickness			
P _d = 0,918		d = 3,00 mm		1 mm 2 mm 3 mm	
Spectral values guaranteed (d = 3 mm)		Density		Illuminant D65	x
λ _{i 0,5} = 435 nm ± 6 nm		ρ = 2,55 g/cm³			y
λ _s (τ _{i,U} = 1E-05) = 370 nm					Y
λ _p (τ _{i,L} = 0,92) = 520 nm					λ _d
					P _e
		Knoop hardness		Illuminant A	x
		HK _[0,1/20] = 449			y
		Thermal properties			Y
		Transformation temperature			λ _d
		Tg = 537 °C			P _e
		Thermal expansion in 10 ⁻⁶ /K			
Refractive indices		α _(-30°C/+70°C) = 7,8		Notes	
n _d (587,6 nm) = 1,52		α _(20°C/300°C) = 9,1			
n _s (852 nm) = 1,52					
n _t (1014 nm) = 1,51		Temperature coefficient			
		Tk = 0,08 nm/K			
Sellmeier coefficients		Chemical properties		Stricking glass	
on request		Chemical resistance		Longpass filter	
		FR class = 0			
		SR class = 1			
		AR class = 1			
		Resistance against humidity			
		Robust glass		ISO 23364:2021	
Internal quality		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		Disclaimer	
Bubble class 3				All data without tolerances are to be understood to be reference values.	

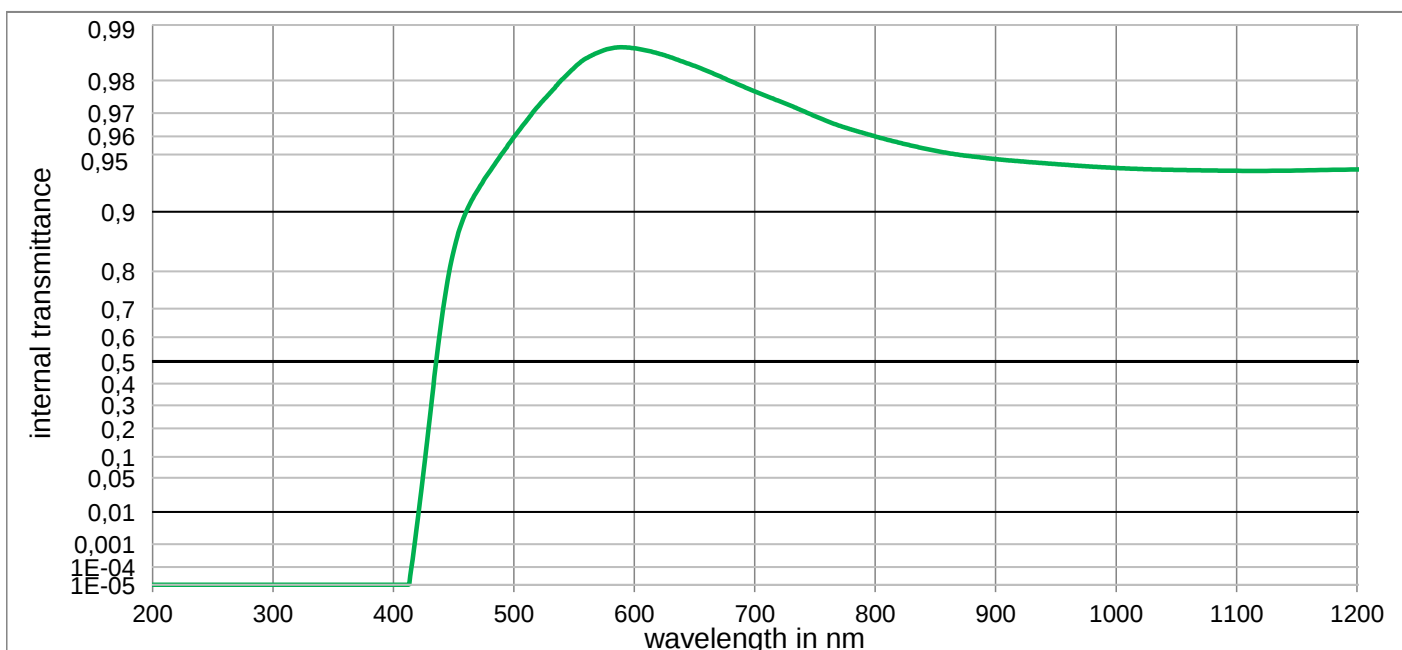

GG435

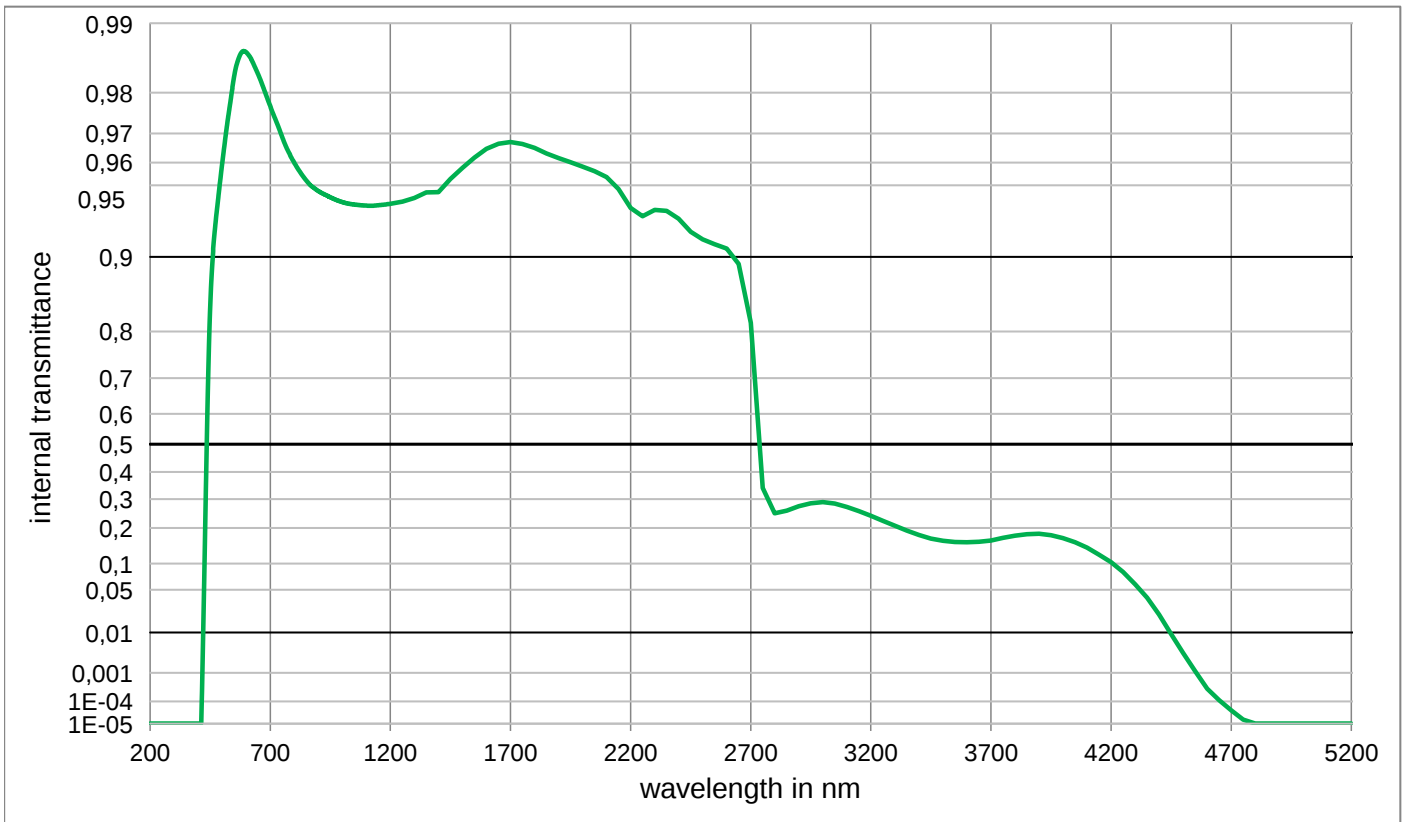
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,596E-01	800	9,600E-01	1100	9,390E-01	2200	9,376E-01	3700	1,608E-01
210	< 1,0E-05	510	9,667E-01	810	9,583E-01	1110	9,390E-01	2250	9,324E-01	3750	1,688E-01
220	< 1,0E-05	520	9,724E-01	820	9,568E-01	1120	9,389E-01	2300	9,365E-01	3800	1,759E-01
230	< 1,0E-05	530	9,767E-01	830	9,552E-01	1130	9,390E-01	2350	9,358E-01	3850	1,802E-01
240	< 1,0E-05	540	9,802E-01	840	9,537E-01	1140	9,391E-01	2400	9,307E-01	3900	1,817E-01
250	< 1,0E-05	550	9,829E-01	850	9,523E-01	1150	9,392E-01	2450	9,214E-01	3950	1,770E-01
260	< 1,0E-05	560	9,848E-01	860	9,510E-01	1160	9,394E-01	2500	9,154E-01	4000	1,683E-01
270	< 1,0E-05	570	9,859E-01	870	9,498E-01	1170	9,395E-01	2550	9,115E-01	4050	1,561E-01
280	< 1,0E-05	580	9,866E-01	880	9,489E-01	1180	9,397E-01	2600	9,076E-01	4100	1,404E-01
290	< 1,0E-05	590	9,868E-01	890	9,480E-01	1190	9,399E-01	2650	8,930E-01	4150	1,219E-01
300	< 1,0E-05	600	9,866E-01	900	9,471E-01	1200	9,401E-01	2700	8,152E-01	4200	1,034E-01
310	< 1,0E-05	610	9,862E-01	910	9,464E-01	1250	9,413E-01	2750	3,405E-01	4250	5,162E-02
320	< 1,00E-05	620	9,857E-01	920	9,457E-01	1300	9,434E-01	2800	2,494E-01	4300	8,873E-02
330	< 1,000E-05	630	9,850E-01	930	9,451E-01	1350	9,464E-01	2850	2,584E-01	4350	3,903E-02
340	< 1,000E-05	640	9,842E-01	940	9,444E-01	1400	9,466E-01	2900	2,745E-01	4400	2,142E-02
350	< 1,000E-05	650	9,833E-01	950	9,438E-01	1450	9,530E-01	2950	2,847E-01	4450	9,220E-03
360	< 1,000E-05	660	9,823E-01	960	9,432E-01	1500	9,579E-01	3000	2,890E-01	4500	3,490E-03
370	< 1,000E-05	670	9,811E-01	970	9,426E-01	1550	9,619E-01	3050	2,838E-01	4550	1,129E-03
380	< 1,000E-05	680	9,799E-01	980	9,420E-01	1600	9,651E-01	3100	2,715E-01	4600	3,010E-04
390	< 1,000E-05	690	9,785E-01	990	9,415E-01	1650	9,668E-01	3150	2,572E-01	4650	1,117E-04
400	< 1,000E-05	700	9,771E-01	1000	9,411E-01	1700	9,673E-01	3200	2,407E-01	4700	4,207E-05
410	< 1,000E-05	710	9,757E-01	1010	9,407E-01	1750	9,668E-01	3250	2,237E-01	4750	1,556E-05
420	5,714E-03	720	9,742E-01	1020	9,403E-01	1800	9,654E-01	3300	2,073E-01	4800	< 1,000E-05
430	2,404E-01	730	9,726E-01	1030	9,401E-01	1850	9,634E-01	3350	1,920E-01	4850	< 1,000E-05
440	6,640E-01	740	9,708E-01	1040	9,398E-01	1900	9,618E-01	3400	1,782E-01	4900	< 1,000E-05
450	8,424E-01	750	9,689E-01	1050	9,397E-01	1950	9,602E-01	3450	1,665E-01	4950	< 1,000E-05
460	8,986E-01	760	9,669E-01	1060	9,395E-01	2000	9,584E-01	3500	1,606E-01	5000	< 1,000E-05
470	9,230E-01	770	9,650E-01	1070	9,394E-01	2050	9,564E-01	3550	1,567E-01	5050	< 1,000E-05
480	9,386E-01	780	9,633E-01	1080	9,392E-01	2100	9,539E-01	3600	1,559E-01	5100	< 1,000E-05
490	9,506E-01	790	9,616E-01	1090	9,391E-01	2150	9,482E-01	3650	1,573E-01	5150	< 1,000E-05

GG455

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,918$	$d = 3,00 \text{ mm}$	x 0,344 0,354 0,361
Spectral values guaranteed (d = 3 mm)	Density	y 0,394 0,414 0,426
$\lambda_{i0,5} = 455 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,56 \text{ g/cm}^3$	Y 90,5 89,7 88,9
$\lambda_s(\tau_{i,U} = 1E-05) = 390 \text{ nm}$	Knoop hardness	λ_d 568 nm 568 nm 568 nm
$\lambda_p(\tau_{i,L} = 0,92) = 530 \text{ nm}$	$HK_{[0.1/20]} = 445$	P_e 0,270 0,355 0,408
		Illuminant D65
		x 0,465 0,470 0,473
		y 0,431 0,437 0,441
		Y 91,0 90,4 89,8
		λ_d 579 nm 580 nm 580 nm
		P_e 0,282 0,364 0,415
		Illuminant A
		x 0,465 0,470 0,473
		y 0,431 0,437 0,441
		Y 91,0 90,4 89,8
		λ_d 579 nm 580 nm 580 nm
		P_e 0,282 0,364 0,415
Refractive indices	Thermal properties	Notes
$n_d(587,6 \text{ nm}) = 1,52$	Transformation temperature	
$n_s(852 \text{ nm}) = 1,52$	$T_g = 529 \text{ }^\circ\text{C}$	Stricking glass
$n_t(1014 \text{ nm}) = 1,51$	Thermal expansion in $10^{-6}/\text{K}$	Longpass filter
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,2$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,5$	
Sellmeier coefficients	Temperature coefficient	
on request	$Tk = 0,09 \text{ nm/K}$	
	Chemical properties	
	Chemical resistance	
	FR class = 0	
	SR class = 1	
	AR class = 1	
	Resistance against humidity	
	Resistant glass	
Internal quality	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	ISO 23364:2021
Bubble class 3		Disclaimer
		All data without tolerances are to be understood to be reference values.

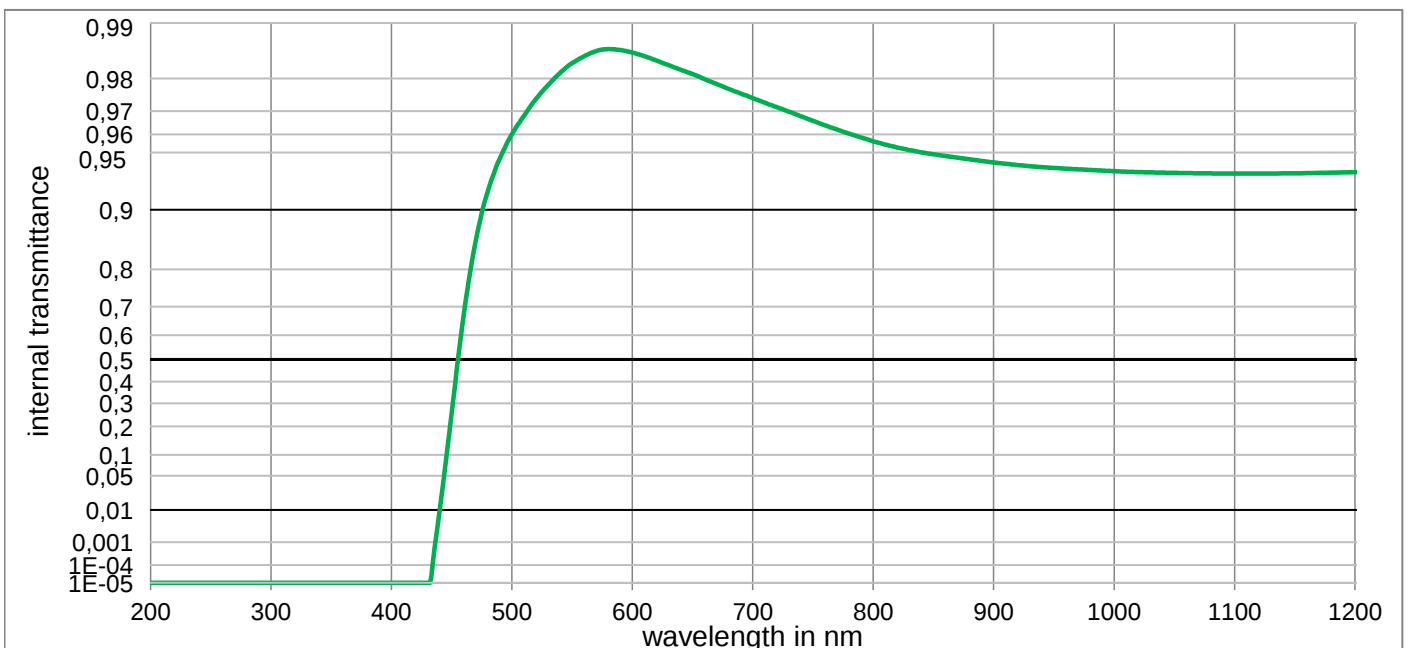

GG455

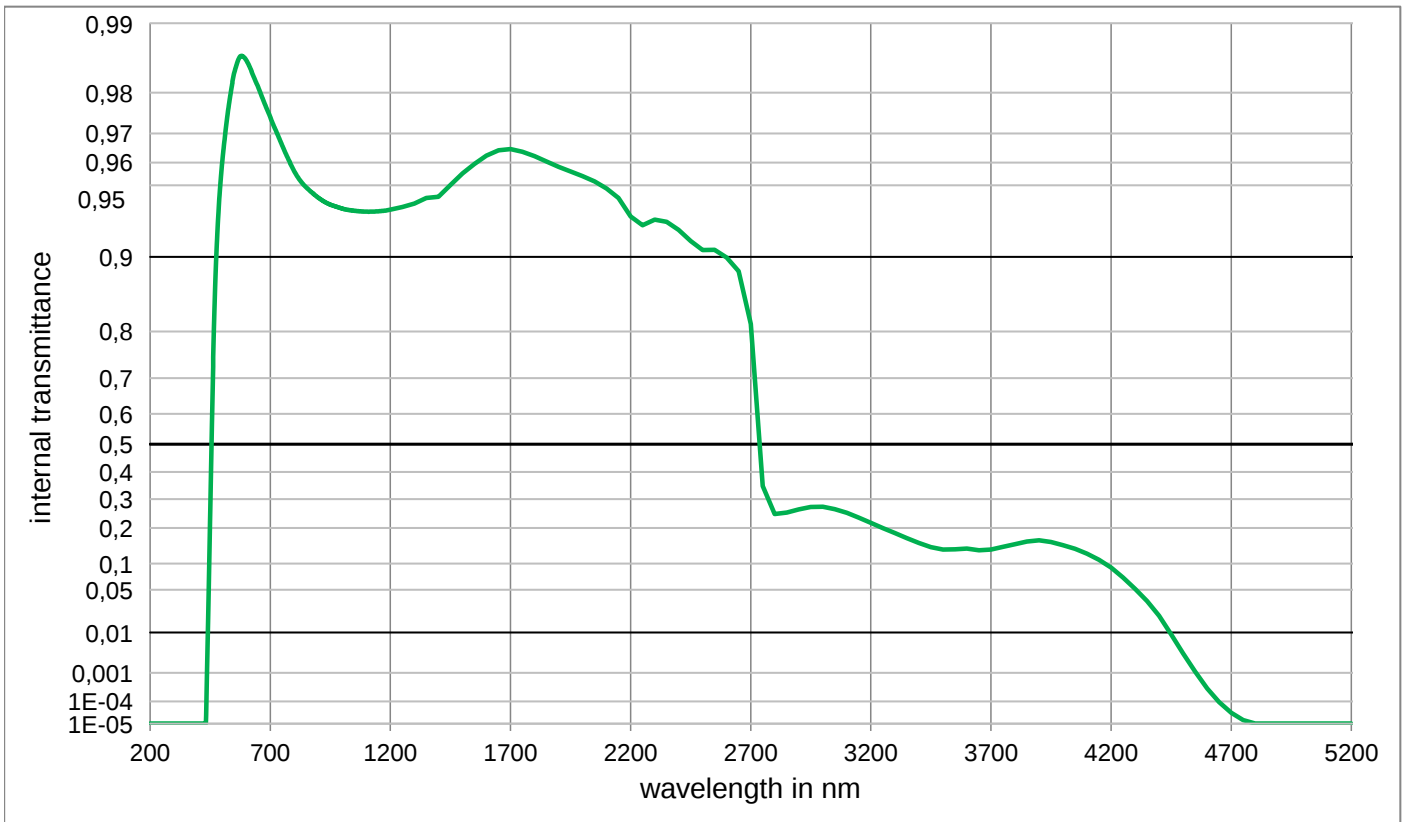
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,600E-01	800	9,565E-01	1100	9,353E-01	2200	9,323E-01	3700	1,353E-01
210	< 1,0E-05	510	9,681E-01	810	9,547E-01	1110	9,353E-01	2250	9,263E-01	3750	1,428E-01
220	< 1,0E-05	520	9,741E-01	820	9,530E-01	1120	9,353E-01	2300	9,301E-01	3800	1,502E-01
230	< 1,0E-05	530	9,783E-01	830	9,515E-01	1130	9,354E-01	2350	9,287E-01	3850	1,579E-01
240	< 1,0E-05	540	9,813E-01	840	9,501E-01	1140	9,355E-01	2400	9,228E-01	3900	1,614E-01
250	< 1,0E-05	550	9,835E-01	850	9,489E-01	1150	9,356E-01	2450	9,141E-01	3950	1,566E-01
260	< 1,0E-05	560	9,848E-01	860	9,478E-01	1160	9,357E-01	2500	9,062E-01	4000	1,474E-01
270	< 1,0E-05	570	9,858E-01	870	9,467E-01	1170	9,358E-01	2550	9,066E-01	4050	1,372E-01
280	< 1,0E-05	580	9,861E-01	880	9,457E-01	1180	9,360E-01	2600	8,992E-01	4100	1,244E-01
290	< 1,0E-05	590	9,860E-01	890	9,446E-01	1190	9,363E-01	2650	8,855E-01	4150	1,092E-01
300	< 1,0E-05	600	9,855E-01	900	9,436E-01	1200	9,365E-01	2700	8,129E-01	4200	9,100E-02
310	< 1,0E-05	610	9,849E-01	910	9,426E-01	1250	9,381E-01	2750	3,480E-01	4250	7,064E-02
320	< 1,00E-05	620	9,840E-01	920	9,417E-01	1300	9,402E-01	2800	2,470E-01	4300	5,106E-02
330	< 1,00E-05	630	9,831E-01	930	9,409E-01	1350	9,434E-01	2850	2,521E-01	4350	3,463E-02
340	< 1,00E-05	640	9,821E-01	940	9,402E-01	1400	9,440E-01	2900	2,632E-01	4400	2,040E-02
350	< 1,00E-05	650	9,811E-01	950	9,396E-01	1450	9,502E-01	2950	2,713E-01	4450	9,120E-03
360	< 1,00E-05	660	9,798E-01	960	9,391E-01	1500	9,556E-01	3000	2,723E-01	4500	3,420E-03
370	< 1,00E-05	670	9,786E-01	970	9,386E-01	1550	9,595E-01	3050	2,640E-01	4550	1,100E-03
380	< 1,00E-05	680	9,772E-01	980	9,382E-01	1600	9,627E-01	3100	2,507E-01	4600	3,097E-04
390	< 1,00E-05	690	9,759E-01	990	9,377E-01	1650	9,646E-01	3150	2,344E-01	4650	9,484E-05
400	< 1,00E-05	700	9,745E-01	1000	9,372E-01	1700	9,650E-01	3200	2,168E-01	4700	3,236E-05
410	< 1,00E-05	710	9,730E-01	1010	9,368E-01	1750	9,640E-01	3250	1,998E-01	4750	1,500E-05
420	< 1,00E-05	720	9,714E-01	1020	9,365E-01	1800	9,625E-01	3300	1,836E-01	4800	< 1,00E-05
430	< 1,00E-05	730	9,698E-01	1030	9,363E-01	1850	9,605E-01	3350	1,681E-01	4850	< 1,00E-05
440	9,602E-03	740	9,680E-01	1040	9,361E-01	1900	9,583E-01	3400	1,540E-01	4900	< 1,00E-05
450	2,603E-01	750	9,662E-01	1050	9,359E-01	1950	9,563E-01	3450	1,421E-01	4950	< 1,00E-05
460	6,726E-01	760	9,643E-01	1060	9,357E-01	2000	9,543E-01	3500	1,357E-01	5000	< 1,00E-05
470	8,568E-01	770	9,623E-01	1070	9,356E-01	2050	9,519E-01	3550	1,359E-01	5050	< 1,00E-05
480	9,199E-01	780	9,604E-01	1080	9,355E-01	2100	9,484E-01	3600	1,378E-01	5100	< 1,00E-05
490	9,464E-01	790	9,585E-01	1090	9,354E-01	2150	9,434E-01	3650	1,333E-01	5150	< 1,00E-05

GG475

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,918$	$d = 3,00 \text{ mm}$	x 0,381 0,394 0,401
Spectral values guaranteed (d = 3 mm)	Density	y 0,463 0,485 0,494
$\lambda_{i0,5} = 475 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,56 \text{ g/cm}^3$	Y 89,5 88,5 87,7
$\lambda_s(\tau_{i,U} = 1E-05) = 410 \text{ nm}$	Knoop hardness	λ_d 568 nm 569 nm 569 nm
$\lambda_p(\tau_{i,L} = 0,92) = 550 \text{ nm}$	$HK_{[0.1/20]} = 451$	P_e 0,567 0,664 0,709
		Illuminant D65
		x 0,483 0,489 0,492
		y 0,453 0,460 0,463
		Y 90,7 90,0 89,4
		λ_d 580 nm 580 nm 580 nm
		P_e 0,560 0,648 0,689
		Illuminant A
		x 0,483 0,489 0,492
		y 0,453 0,460 0,463
		Y 90,7 90,0 89,4
		λ_d 580 nm 580 nm 580 nm
		P_e 0,560 0,648 0,689
Refractive indices	Thermal properties	Notes
$n_d(587,6 \text{ nm}) = 1,52$	Transformation temperature	
$n_s(852 \text{ nm}) = 1,52$	$T_g = 531 \text{ }^\circ\text{C}$	
$n_t(1014 \text{ nm}) = 1,51$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,2$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,4$	
	Temperature coefficient	
	$Tk = 0,09 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Stricking glass
on request	Chemical resistance	Longpass filter
	FR class = 0	
	SR class = 1	
	AR class = 1	
	Resistance against humidity	
	Resistant glass	
	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	ISO 23364:2021
Internal quality		Disclaimer
Bubble class 3		All data without tolerances are to be understood to be reference values.

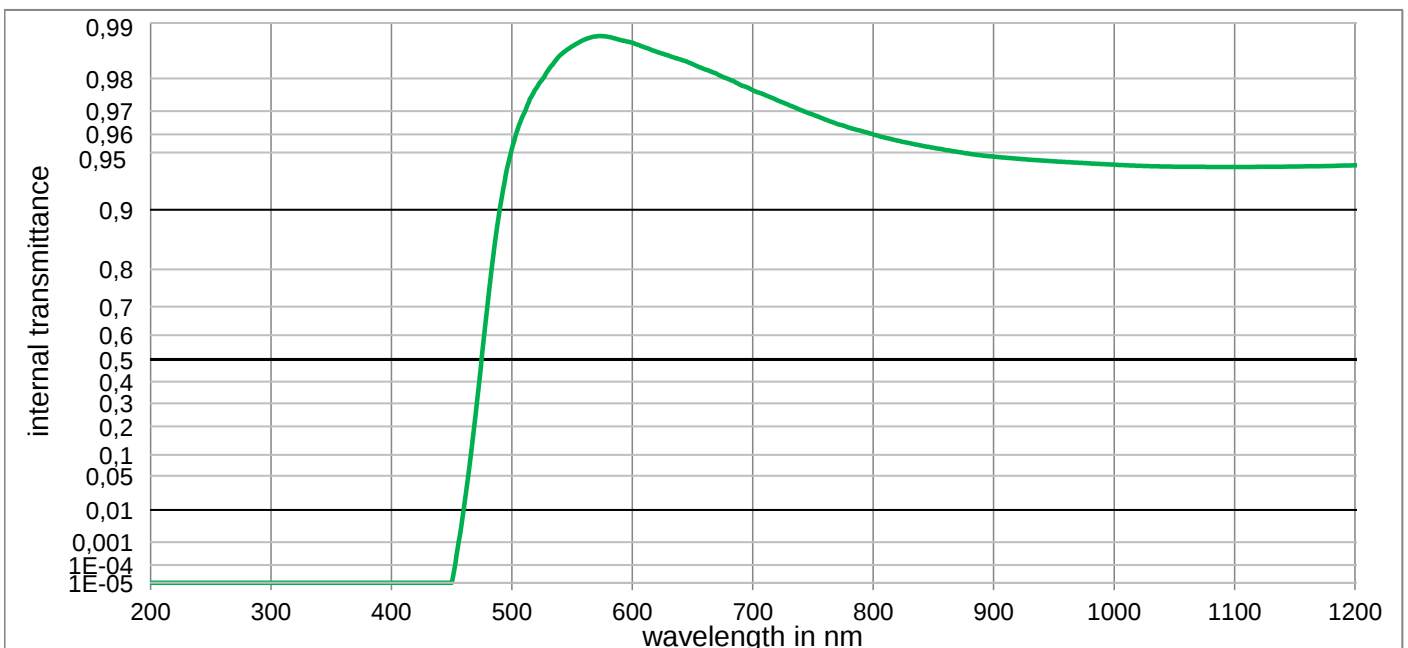

GG475

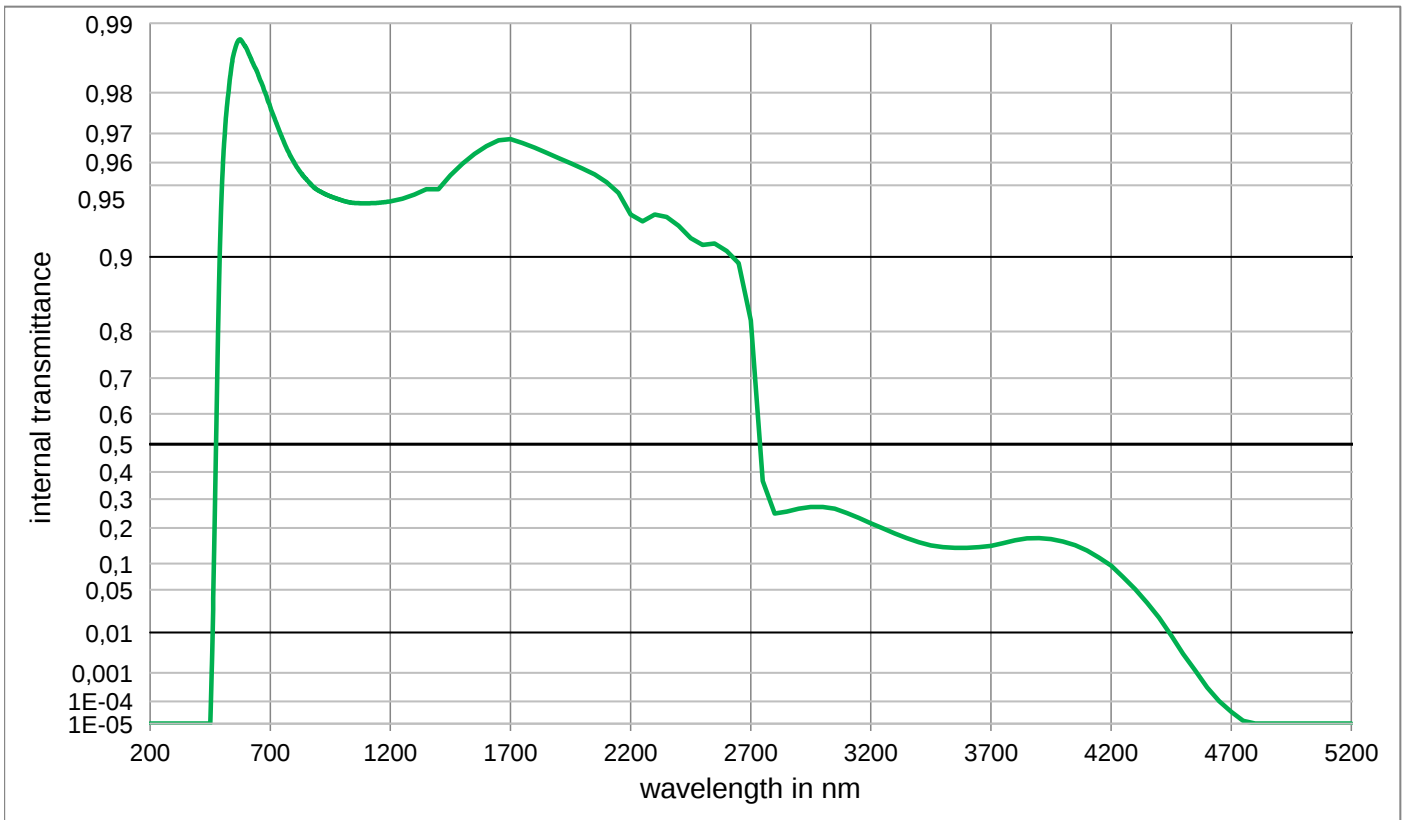
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,523E-01	800	9,600E-01	1100	9,404E-01	2200	9,336E-01	3700	1,458E-01
210	< 1,0E-05	510	9,691E-01	810	9,583E-01	1110	9,404E-01	2250	9,290E-01	3750	1,530E-01
220	< 1,0E-05	520	9,773E-01	820	9,568E-01	1120	9,404E-01	2300	9,335E-01	3800	1,617E-01
230	< 1,0E-05	530	9,819E-01	830	9,554E-01	1130	9,405E-01	2350	9,320E-01	3850	1,674E-01
240	< 1,0E-05	540	9,850E-01	840	9,541E-01	1140	9,406E-01	2400	9,259E-01	3900	1,685E-01
250	< 1,0E-05	550	9,866E-01	850	9,529E-01	1150	9,407E-01	2450	9,164E-01	3950	1,656E-01
260	< 1,0E-05	560	9,877E-01	860	9,516E-01	1160	9,408E-01	2500	9,109E-01	4000	1,582E-01
270	< 1,0E-05	570	9,882E-01	870	9,504E-01	1170	9,409E-01	2550	9,120E-01	4050	1,473E-01
280	< 1,0E-05	580	9,881E-01	880	9,492E-01	1180	9,411E-01	2600	9,054E-01	4100	1,326E-01
290	< 1,0E-05	590	9,876E-01	890	9,482E-01	1190	9,413E-01	2650	8,939E-01	4150	1,147E-01
300	< 1,0E-05	600	9,872E-01	900	9,474E-01	1200	9,415E-01	2700	8,190E-01	4200	9,520E-02
310	< 1,0E-05	610	9,864E-01	910	9,468E-01	1250	9,430E-01	2750	3,672E-01	4250	7,140E-02
320	< 1,00E-05	620	9,857E-01	920	9,461E-01	1300	9,453E-01	2800	2,487E-01	4300	5,080E-02
330	< 1,000E-05	630	9,850E-01	930	9,454E-01	1350	9,481E-01	2850	2,550E-01	4350	3,277E-02
340	< 1,000E-05	640	9,842E-01	940	9,449E-01	1400	9,481E-01	2900	2,658E-01	4400	1,894E-02
350	< 1,000E-05	650	9,833E-01	950	9,443E-01	1450	9,546E-01	2950	2,713E-01	4450	8,760E-03
360	< 1,000E-05	660	9,822E-01	960	9,438E-01	1500	9,596E-01	3000	2,719E-01	4500	3,295E-03
370	< 1,000E-05	670	9,811E-01	970	9,434E-01	1550	9,633E-01	3050	2,657E-01	4550	1,200E-03
380	< 1,000E-05	680	9,799E-01	980	9,429E-01	1600	9,660E-01	3100	2,506E-01	4600	3,357E-04
390	< 1,000E-05	690	9,783E-01	990	9,424E-01	1650	9,679E-01	3150	2,333E-01	4650	1,035E-04
400	< 1,000E-05	700	9,769E-01	1000	9,420E-01	1700	9,683E-01	3200	2,158E-01	4700	3,656E-05
410	< 1,000E-05	710	9,754E-01	1010	9,416E-01	1750	9,671E-01	3250	1,989E-01	4750	1,393E-05
420	< 1,000E-05	720	9,739E-01	1020	9,412E-01	1800	9,655E-01	3300	1,827E-01	4800	< 1,000E-05
430	< 1,000E-05	730	9,722E-01	1030	9,409E-01	1850	9,638E-01	3350	1,680E-01	4850	< 1,000E-05
440	< 1,000E-05	740	9,704E-01	1040	9,407E-01	1900	9,618E-01	3400	1,558E-01	4900	< 1,000E-05
450	< 1,000E-05	750	9,686E-01	1050	9,406E-01	1950	9,598E-01	3450	1,467E-01	4950	< 1,000E-05
460	1,043E-02	760	9,667E-01	1060	9,405E-01	2000	9,575E-01	3500	1,419E-01	5000	< 1,000E-05
470	2,606E-01	770	9,649E-01	1070	9,404E-01	2050	9,551E-01	3550	1,402E-01	5050	< 1,000E-05
480	7,129E-01	780	9,632E-01	1080	9,404E-01	2100	9,516E-01	3600	1,403E-01	5100	< 1,000E-05
490	9,022E-01	790	9,616E-01	1090	9,404E-01	2150	9,462E-01	3650	1,418E-01	5150	< 1,000E-05

GG495

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	
$P_d = 0,917$	$d = 3,00 \text{ mm}$	
Spectral values guaranteed (d = 3 mm)	Density	
$\lambda_{i0,5} = 495 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,56 \text{ g/cm}^3$	
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 430 \text{ nm}$	Knoop hardness	
$\lambda_p (\tau_{i,L} = 0,92) = 560 \text{ nm}$	$HK_{[0.1/20]} = 501$	
Refractive indices	Thermal properties	
$n_d (587,6 \text{ nm}) = 1,52$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,52$	$T_g = 535 \text{ }^\circ\text{C}$	
$n_t (1014 \text{ nm}) = 1,51$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,1$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,4$	
	Temperature coefficient	
	$Tk = 0,1 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	
valid from 400 nm to 2400 nm	Chemical resistance	
$B_1 = 1,2863$	FR class = 0	
$B_2 = 0,0012$	SR class = 1	
$B_3 = 0,8815$	AR class = 1	
$C_1 = 9,397\text{E-}03 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,5104\text{E-}01 \text{ } \mu\text{m}^2$	Resistant glass	
$C_3 = 106,389 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
Internal quality		
Bubble class 3		
		Notes
		Stricking glass
		Longpass filter
		ISO 23364:2021
		Disclaimer
		All data without tolerances are to be understood to be reference values.

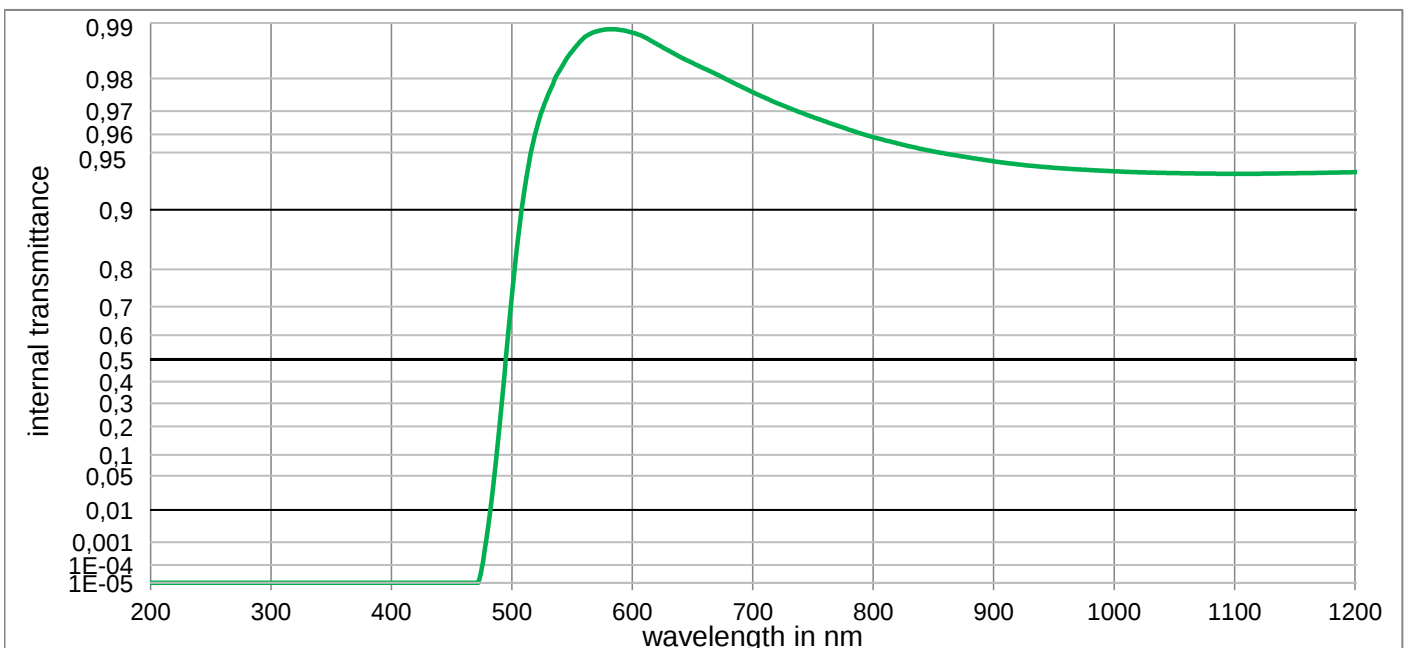

GG495

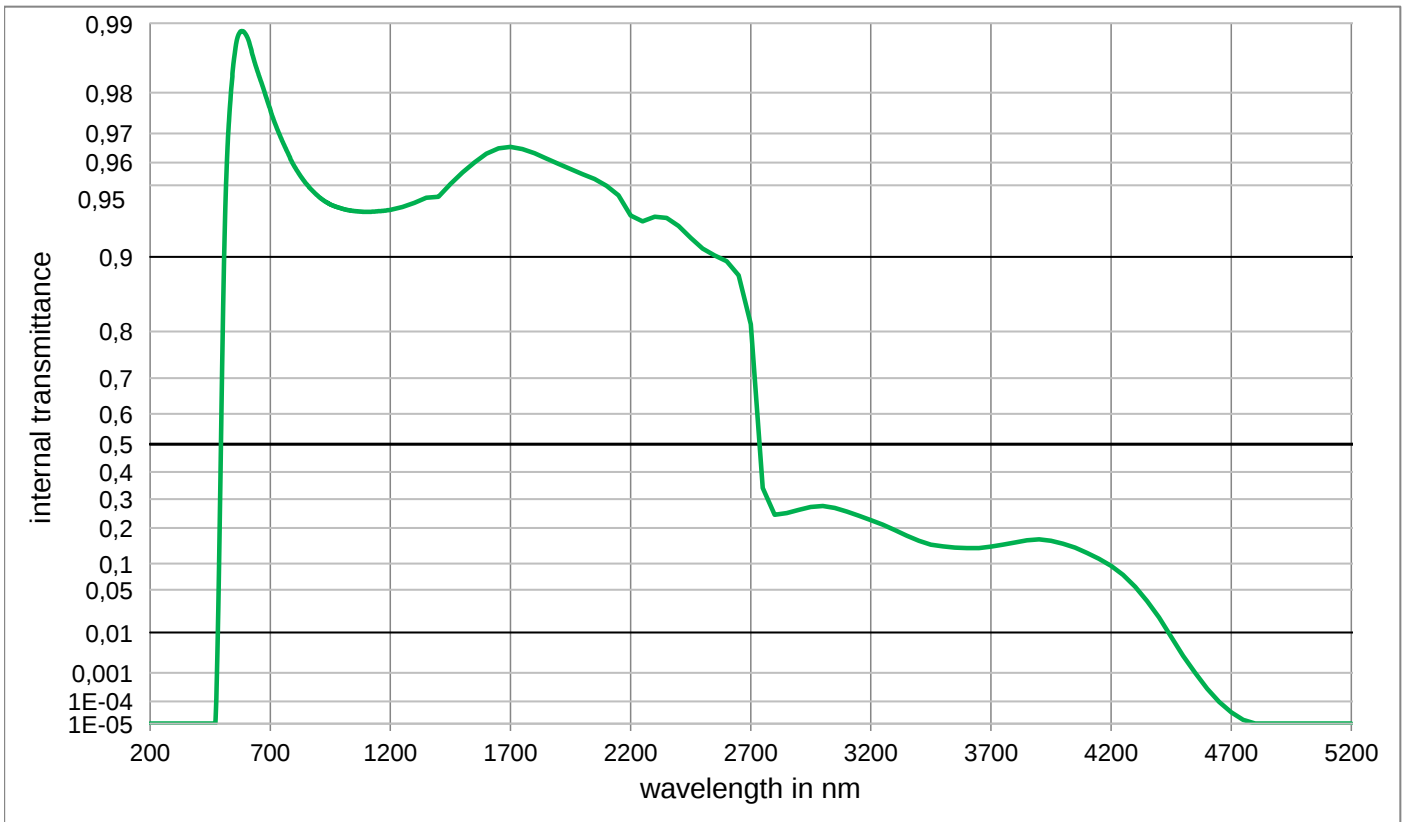
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	7,321E-01	800	9,586E-01	1100	9,352E-01	2200	9,329E-01	3700	1,435E-01
210	< 1,0E-05	510	9,185E-01	810	9,569E-01	1110	9,352E-01	2250	9,289E-01	3750	1,488E-01
220	< 1,0E-05	520	9,617E-01	820	9,553E-01	1120	9,352E-01	2300	9,320E-01	3800	1,553E-01
230	< 1,0E-05	530	9,755E-01	830	9,537E-01	1130	9,353E-01	2350	9,313E-01	3850	1,619E-01
240	< 1,0E-05	540	9,821E-01	840	9,522E-01	1140	9,355E-01	2400	9,256E-01	3900	1,643E-01
250	< 1,0E-05	550	9,858E-01	850	9,507E-01	1150	9,356E-01	2450	9,166E-01	3950	1,600E-01
260	< 1,0E-05	560	9,880E-01	860	9,493E-01	1160	9,357E-01	2500	9,077E-01	4000	1,521E-01
270	< 1,0E-05	570	9,889E-01	870	9,481E-01	1170	9,359E-01	2550	9,014E-01	4050	1,405E-01
280	< 1,0E-05	580	9,892E-01	880	9,468E-01	1180	9,360E-01	2600	8,958E-01	4100	1,265E-01
290	< 1,0E-05	590	9,891E-01	890	9,456E-01	1190	9,362E-01	2650	8,808E-01	4150	1,113E-01
300	< 1,0E-05	600	9,887E-01	900	9,443E-01	1200	9,364E-01	2700	8,125E-01	4200	9,490E-02
310	< 1,0E-05	610	9,881E-01	910	9,432E-01	1250	9,382E-01	2750	3,410E-01	4250	5,570E-02
320	< 1,00E-05	620	9,870E-01	920	9,422E-01	1300	9,407E-01	2800	2,445E-01	4300	5,470E-02
330	< 1,00E-05	630	9,859E-01	930	9,413E-01	1350	9,435E-01	2850	2,499E-01	4350	3,490E-02
340	< 1,00E-05	640	9,847E-01	940	9,405E-01	1400	9,441E-01	2900	2,611E-01	4400	1,910E-02
350	< 1,00E-05	650	9,835E-01	950	9,398E-01	1450	9,506E-01	2950	2,714E-01	4450	8,150E-03
360	< 1,00E-05	660	9,823E-01	960	9,391E-01	1500	9,560E-01	3000	2,751E-01	4500	2,939E-03
370	< 1,00E-05	670	9,810E-01	970	9,386E-01	1550	9,601E-01	3050	2,686E-01	4550	1,008E-03
380	< 1,00E-05	680	9,795E-01	980	9,381E-01	1600	9,634E-01	3100	2,558E-01	4600	3,020E-04
390	< 1,00E-05	690	9,779E-01	990	9,376E-01	1650	9,653E-01	3150	2,409E-01	4650	9,616E-05
400	< 1,00E-05	700	9,763E-01	1000	9,371E-01	1700	9,657E-01	3200	2,257E-01	4700	3,420E-05
410	< 1,00E-05	710	9,746E-01	1010	9,367E-01	1750	9,650E-01	3250	2,105E-01	4750	1,528E-05
420	< 1,00E-05	720	9,729E-01	1020	9,364E-01	1800	9,636E-01	3300	1,931E-01	4800	< 1,00E-05
430	< 1,00E-05	730	9,712E-01	1030	9,361E-01	1850	9,616E-01	3350	1,754E-01	4850	< 1,00E-05
440	< 1,00E-05	740	9,695E-01	1040	9,359E-01	1900	9,595E-01	3400	1,601E-01	4900	< 1,00E-05
450	< 1,00E-05	750	9,677E-01	1050	9,357E-01	1950	9,574E-01	3450	1,487E-01	4950	< 1,00E-05
460	< 1,00E-05	760	9,659E-01	1060	9,356E-01	2000	9,552E-01	3500	1,438E-01	5000	< 1,00E-05
470	< 1,00E-05	770	9,641E-01	1070	9,354E-01	2050	9,530E-01	3550	1,410E-01	5050	< 1,00E-05
480	2,765E-03	780	9,623E-01	1080	9,353E-01	2100	9,498E-01	3600	1,393E-01	5100	< 1,00E-05
490	2,183E-01	790	9,604E-01	1090	9,352E-01	2150	9,449E-01	3650	1,396E-01	5150	< 1,00E-05

OG515

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,921$	$d = 3,00 \text{ mm}$	x 0,448 0,465 0,473
Spectral values guaranteed (d = 3 mm)	Density	y 0,516 0,519 0,515
$\lambda_{i,0,5} = 515 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,56 \text{ g/cm}^3$	Y 81,5 77,9 75,4
$\lambda_s(\tau_{i,U} = 1\text{E-}05) = 440 \text{ nm}$	Knoop hardness	λ_d 573 nm 574 nm 575 nm
$\lambda_p(\tau_{i,L} = 0,93) = 580 \text{ nm}$	$HK_{[0.1/20]} = 455$	P_e 0,902 0,958 0,969
		Illuminant A
		x 0,516 0,525 0,530
		y 0,468 0,466 0,463
		Y 86,5 84,1 82,3
		λ_d 582 nm 583 nm 583 nm
		P_e 0,896 0,945 0,957
Refractive indices	Thermal properties	Notes
$n_d(587,6 \text{ nm}) = 1,51$	Transformation temperature	
$n_s(852 \text{ nm}) = 1,51$	$T_g = 509 \text{ }^\circ\text{C}$	Stricking glass
$n_t(1014 \text{ nm}) = 1,50$	Thermal expansion in $10^{-6}/\text{K}$	Longpass filter
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,9$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,0$	
Sellmeier coefficients	Temperature coefficient	
on request	$Tk = 0,11 \text{ nm/K}$	ISO 23364:2021
	Chemical properties	Disclaimer
	Chemical resistance	All data without tolerances are to be understood to be reference values.
	FR class = 0	
	SR class = 1	
	AR class = 1	
	Resistance against humidity	
	Resistant glass	
Internal quality	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
Bubble class 3		

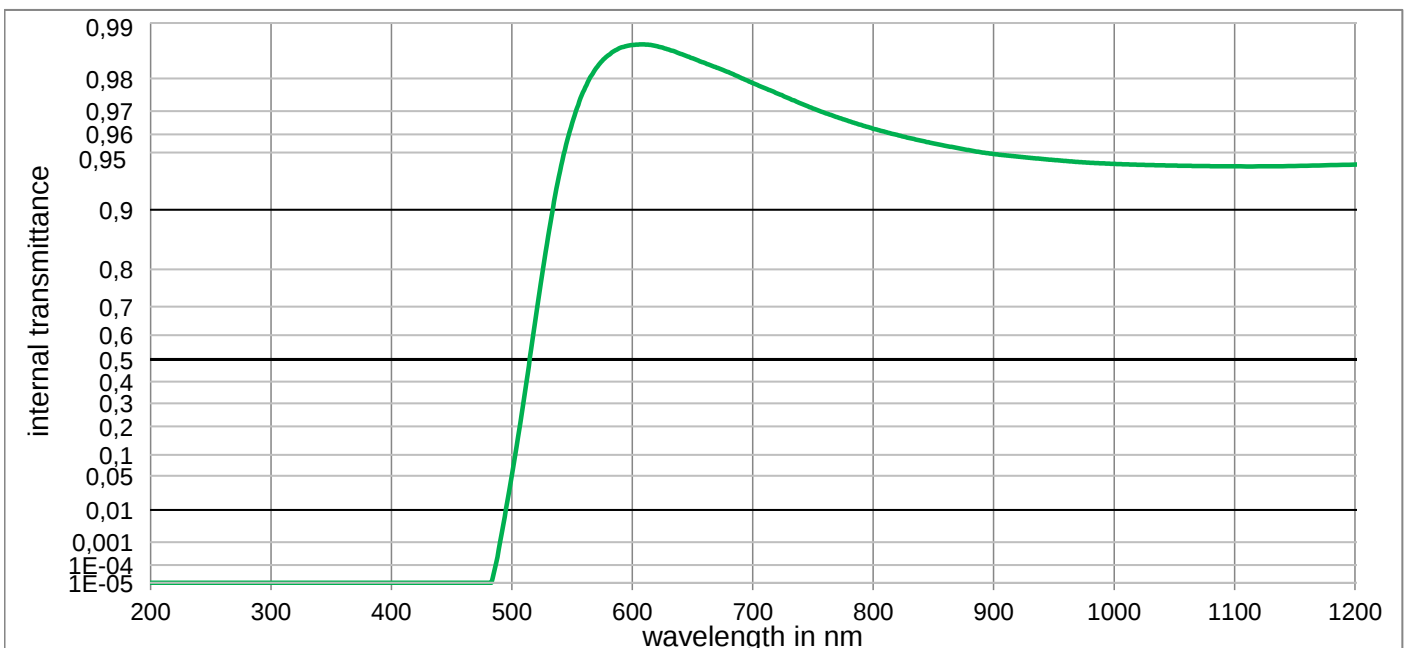

OG515

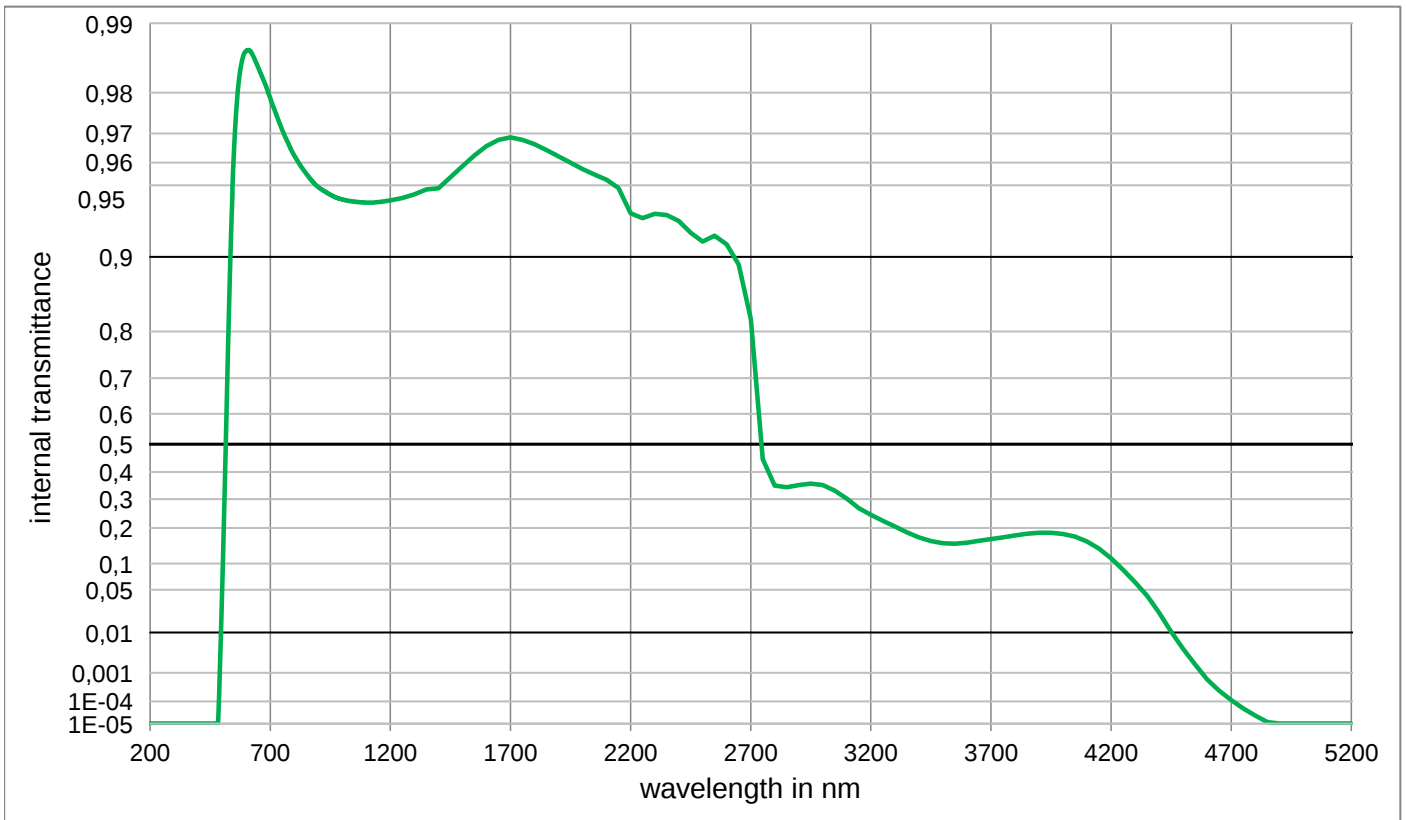
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	5,093E-02	800	9,627E-01	1100	9,408E-01	2200	9,342E-01	3700	1,653E-01
210	< 1,0E-05	510	3,219E-01	810	9,612E-01	1110	9,408E-01	2250	9,311E-01	3750	1,708E-01
220	< 1,0E-05	520	6,692E-01	820	9,597E-01	1120	9,408E-01	2300	9,339E-01	3800	1,767E-01
230	< 1,0E-05	530	8,627E-01	830	9,582E-01	1130	9,408E-01	2350	9,332E-01	3850	1,817E-01
240	< 1,0E-05	540	9,370E-01	840	9,568E-01	1140	9,409E-01	2400	9,292E-01	3900	1,850E-01
250	< 1,0E-05	550	9,652E-01	850	9,553E-01	1150	9,411E-01	2450	9,207E-01	3950	1,850E-01
260	< 1,0E-05	560	9,769E-01	860	9,540E-01	1160	9,413E-01	2500	9,136E-01	4000	1,811E-01
270	< 1,0E-05	570	9,824E-01	870	9,527E-01	1170	9,414E-01	2550	9,185E-01	4050	1,729E-01
280	< 1,0E-05	580	9,850E-01	880	9,514E-01	1180	9,416E-01	2600	9,111E-01	4100	1,582E-01
290	< 1,0E-05	590	9,864E-01	890	9,501E-01	1190	9,418E-01	2650	8,926E-01	4150	1,380E-01
300	< 1,0E-05	600	9,868E-01	900	9,491E-01	1200	9,421E-01	2700	8,215E-01	4200	1,127E-01
310	< 1,0E-05	610	9,869E-01	910	9,482E-01	1250	9,434E-01	2750	4,471E-01	4250	8,609E-02
320	< 1,00E-05	620	9,867E-01	920	9,474E-01	1300	9,454E-01	2800	3,500E-01	4300	6,209E-02
330	< 1,00E-05	630	9,861E-01	930	9,467E-01	1350	9,479E-01	2850	3,433E-01	4350	4,140E-02
340	< 1,00E-05	640	9,853E-01	940	9,459E-01	1400	9,486E-01	2900	3,513E-01	4400	2,314E-02
350	< 1,00E-05	650	9,844E-01	950	9,452E-01	1450	9,538E-01	2950	3,569E-01	4450	1,039E-02
360	< 1,00E-05	660	9,835E-01	960	9,445E-01	1500	9,586E-01	3000	3,519E-01	4500	4,394E-03
370	< 1,00E-05	670	9,825E-01	970	9,439E-01	1550	9,628E-01	3050	3,310E-01	4550	1,743E-03
380	< 1,00E-05	680	9,815E-01	980	9,433E-01	1600	9,660E-01	3100	3,011E-01	4600	6,152E-04
390	< 1,00E-05	690	9,802E-01	990	9,429E-01	1650	9,680E-01	3150	2,673E-01	4650	2,588E-04
400	< 1,00E-05	700	9,789E-01	1000	9,426E-01	1700	9,688E-01	3200	2,440E-01	4700	1,117E-04
410	< 1,00E-05	710	9,774E-01	1010	9,422E-01	1750	9,681E-01	3250	2,238E-01	4750	5,117E-05
420	< 1,00E-05	720	9,760E-01	1020	9,419E-01	1800	9,666E-01	3300	2,048E-01	4800	2,449E-05
430	< 1,00E-05	730	9,744E-01	1030	9,417E-01	1850	9,647E-01	3350	1,862E-01	4850	1,211E-05
440	< 1,00E-05	740	9,727E-01	1040	9,415E-01	1900	9,624E-01	3400	1,707E-01	4900	< 1,00E-05
450	< 1,00E-05	750	9,710E-01	1050	9,413E-01	1950	9,599E-01	3450	1,598E-01	4950	< 1,00E-05
460	< 1,00E-05	760	9,693E-01	1060	9,412E-01	2000	9,574E-01	3500	1,533E-01	5000	< 1,00E-05
470	< 1,00E-05	770	9,676E-01	1070	9,410E-01	2050	9,549E-01	3550	1,517E-01	5050	< 1,00E-05
480	< 1,00E-05	780	9,660E-01	1080	9,409E-01	2100	9,526E-01	3600	1,549E-01	5100	< 1,00E-05
490	9,674E-04	790	9,644E-01	1090	9,408E-01	2150	9,486E-01	3650	1,601E-01	5150	< 1,00E-05

OG530

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,921$	$d = 3,00 \text{ mm}$	x 0,476 0,496 0,505
Spectral values guaranteed (d = 3 mm)	Density	y 0,501 0,498 0,490
$\lambda_{i0,5} = 530 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,56 \text{ g/cm}^3$	Y 73,6 68,7 65,6
$\lambda_s(\tau_{i,U} = 1E-05) = 460 \text{ nm}$	Knoop hardness	λ_d 576 nm 578 nm 579 nm
$\lambda_p(\tau_{i,L} = 0,93) = 600 \text{ nm}$	$HK_{[0.1/20]} = 450$	P_e 0,938 0,985 0,990
		Illuminant D65
		x 0,534 0,545 0,550
		y 0,457 0,452 0,447
		Y 81,4 77,8 75,4
		λ_d 584 nm 585 nm 586 nm
		P_e 0,943 0,979 0,984
		Illuminant A
		x 0,534 0,545 0,550
		y 0,457 0,452 0,447
		Y 81,4 77,8 75,4
		λ_d 584 nm 585 nm 586 nm
		P_e 0,943 0,979 0,984
Refractive indices	Thermal properties	Notes
$n_d(587,6 \text{ nm}) = 1,51$	Transformation temperature	
$n_s(852 \text{ nm}) = 1,51$	$T_g = 506 \text{ }^\circ\text{C}$	
$n_t(1014 \text{ nm}) = 1,50$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,9$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,0$	
	Temperature coefficient	
	$Tk = 0,11 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Stricking glass
on request	Chemical resistance	Longpass filter
	FR class = 0	
	SR class = 1	
	AR class = 1	
	Resistance against humidity	
	Resistant glass	
	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	ISO 23364:2021
Internal quality		Disclaimer
Bubble class 3		All data without tolerances are to be understood to be reference values.

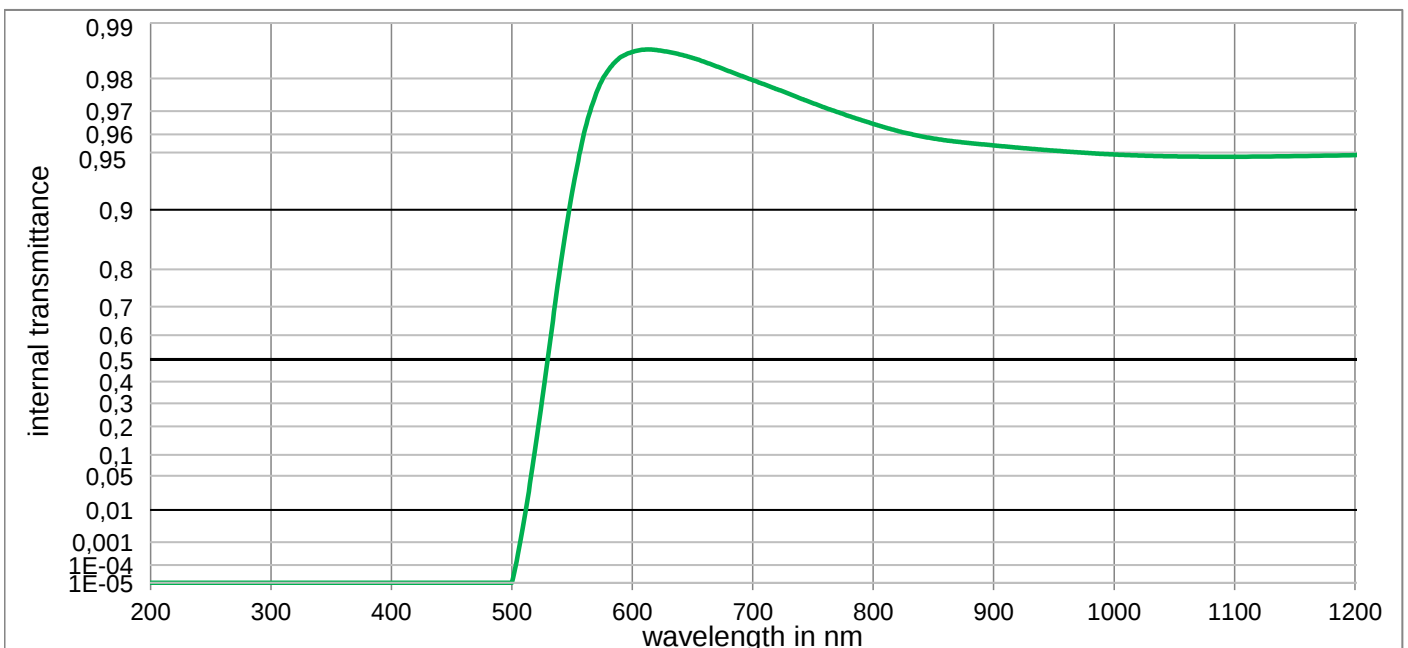

OG530

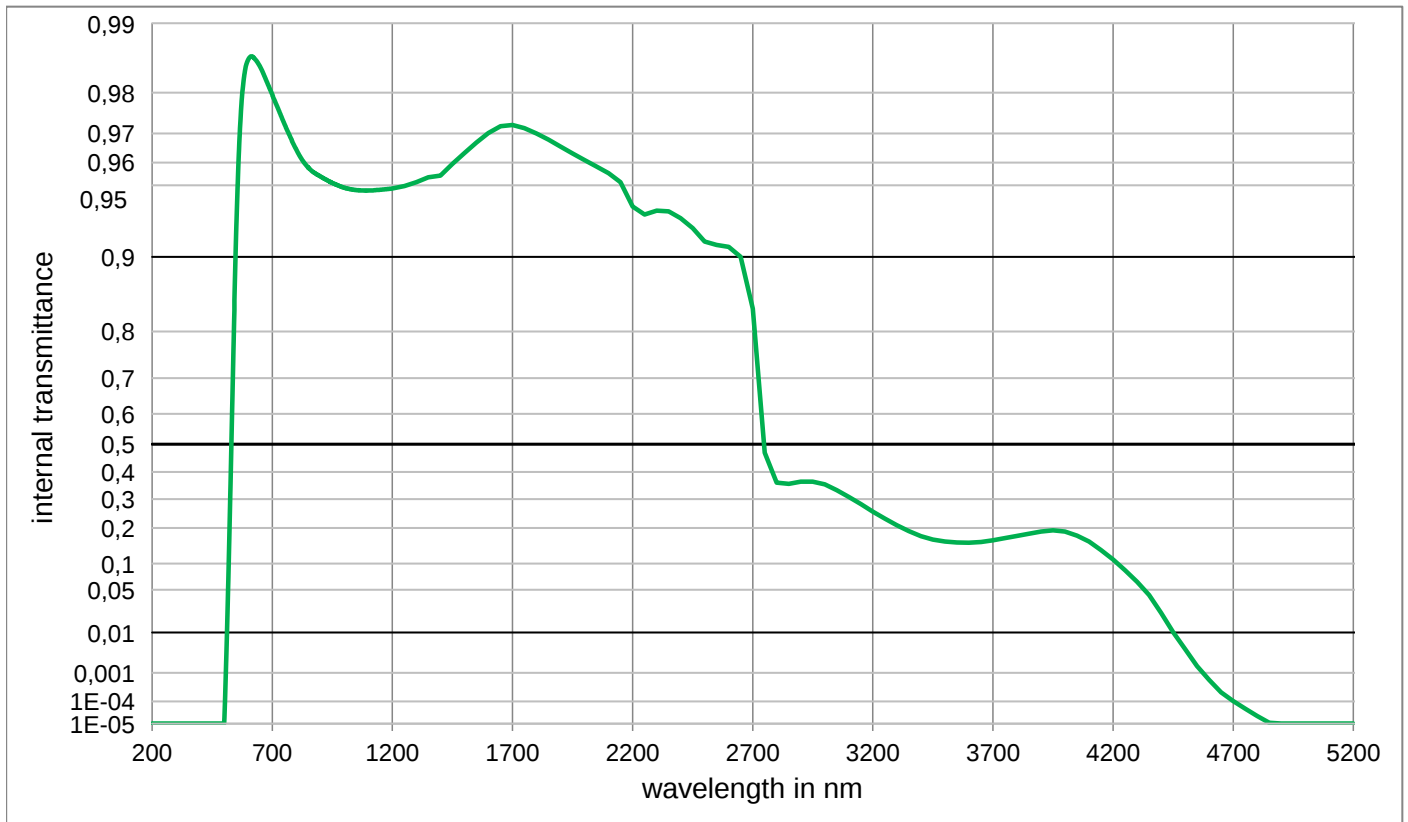
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,649E-01	1100	9,474E-01	2200	9,385E-01	3700	1,617E-01
210	< 1,0E-05	510	5,189E-03	810	9,633E-01	1110	9,474E-01	2250	9,335E-01	3750	1,681E-01
220	< 1,0E-05	520	1,364E-01	820	9,617E-01	1120	9,475E-01	2300	9,360E-01	3800	1,751E-01
230	< 1,0E-05	530	5,140E-01	830	9,603E-01	1130	9,476E-01	2350	9,356E-01	3850	1,819E-01
240	< 1,0E-05	540	8,018E-01	840	9,591E-01	1140	9,477E-01	2400	9,311E-01	3900	1,888E-01
250	< 1,0E-05	550	9,191E-01	850	9,579E-01	1150	9,478E-01	2450	9,242E-01	3950	1,925E-01
260	< 1,0E-05	560	9,608E-01	860	9,570E-01	1160	9,479E-01	2500	9,136E-01	4000	1,884E-01
270	< 1,0E-05	570	9,760E-01	870	9,562E-01	1170	9,480E-01	2550	9,108E-01	4050	1,758E-01
280	< 1,0E-05	580	9,819E-01	880	9,555E-01	1180	9,481E-01	2600	9,091E-01	4100	1,579E-01
290	< 1,0E-05	590	9,846E-01	890	9,548E-01	1190	9,482E-01	2650	8,999E-01	4150	1,342E-01
300	< 1,0E-05	600	9,856E-01	900	9,542E-01	1200	9,484E-01	2700	8,375E-01	4200	1,099E-01
310	< 1,0E-05	610	9,861E-01	910	9,536E-01	1250	9,496E-01	2750	4,700E-01	4250	8,523E-02
320	< 1,000E-05	620	9,860E-01	920	9,529E-01	1300	9,515E-01	2800	3,608E-01	4300	6,292E-02
330	< 1,000E-05	630	9,856E-01	930	9,523E-01	1350	9,537E-01	2850	3,563E-01	4350	4,250E-02
340	< 1,000E-05	640	9,852E-01	940	9,517E-01	1400	9,545E-01	2900	3,638E-01	4400	2,287E-02
350	< 1,000E-05	650	9,845E-01	950	9,512E-01	1450	9,595E-01	2950	3,642E-01	4450	1,006E-02
360	< 1,000E-05	660	9,837E-01	960	9,506E-01	1500	9,637E-01	3000	3,540E-01	4500	4,333E-03
370	< 1,000E-05	670	9,828E-01	970	9,501E-01	1550	9,672E-01	3050	3,325E-01	4550	1,581E-03
380	< 1,000E-05	680	9,818E-01	980	9,497E-01	1600	9,701E-01	3100	3,076E-01	4600	5,943E-04
390	< 1,000E-05	690	9,807E-01	990	9,492E-01	1650	9,721E-01	3150	2,820E-01	4650	2,254E-04
400	< 1,000E-05	700	9,796E-01	1000	9,488E-01	1700	9,725E-01	3200	2,556E-01	4700	1,028E-04
410	< 1,000E-05	710	9,784E-01	1010	9,484E-01	1750	9,716E-01	3250	2,313E-01	4750	4,932E-05
420	< 1,000E-05	720	9,771E-01	1020	9,482E-01	1800	9,700E-01	3300	2,090E-01	4800	2,377E-05
430	< 1,000E-05	730	9,758E-01	1030	9,479E-01	1850	9,681E-01	3350	1,900E-01	4850	1,109E-05
440	< 1,000E-05	740	9,743E-01	1040	9,477E-01	1900	9,658E-01	3400	1,744E-01	4900	< 1,000E-05
450	< 1,000E-05	750	9,728E-01	1050	9,476E-01	1950	9,634E-01	3450	1,637E-01	4950	< 1,000E-05
460	< 1,000E-05	760	9,713E-01	1060	9,475E-01	2000	9,610E-01	3500	1,583E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,697E-01	1070	9,474E-01	2050	9,584E-01	3550	1,556E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,681E-01	1080	9,474E-01	2100	9,556E-01	3600	1,548E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,665E-01	1090	9,474E-01	2150	9,515E-01	3650	1,570E-01	5150	< 1,000E-05

OG550

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,920$	$d = 3,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 3 mm)	Density	x 0,521 0,547 0,557
$\lambda_{i0,5} = 550 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,56 \text{ g/cm}^3$	y 0,459 0,451 0,441
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 480 \text{ nm}$	Knoop hardness	Y 58,3 52,3 48,9
$\lambda_p (\tau_{i,L} = 0,93) = 620 \text{ nm}$	$HK_{[0.1/20]} = 462$	λ_d 583 nm 586 nm 587 nm
		P_e 0,948 0,996 0,998
		Illuminant A
		x 0,565 0,580 0,587
		y 0,429 0,419 0,412
		Y 69,8 64,8 61,7
		λ_d 589 nm 591 nm 592 nm
		P_e 0,963 0,995 0,997
Refractive indices	Thermal properties	Notes
$n_d (587,6 \text{ nm}) = 1,51$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,5$	$T_g = 507 \text{ }^\circ\text{C}$	Stricking glass
$n_t (1014 \text{ nm}) = 1,50$	Thermal expansion in $10^{-6}/\text{K}$	Longpass filter
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,9$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,0$	
Sellmeier coefficients	Temperature coefficient	
valid from 580 nm to 2330 nm	$Tk = 0,12 \text{ nm/K}$	ISO 23364:2021
$B_1 = 1,2525$	Chemical properties	Disclaimer
$B_2 = 0,0009$	Chemical resistance	All data without tolerances are to be understood to be reference values.
$B_3 = 0,8269$	FR class = 0	
$C_1 = 9,542\text{E-}03 \text{ } \mu\text{m}^2$	SR class = 1	
$C_2 = 1,8891\text{E-}01 \text{ } \mu\text{m}^2$	AR class = 1	
$C_3 = 101,937 \text{ } \mu\text{m}^2$	Resistance against humidity	
Internal quality	Resistant glass	
Bubble class 3	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

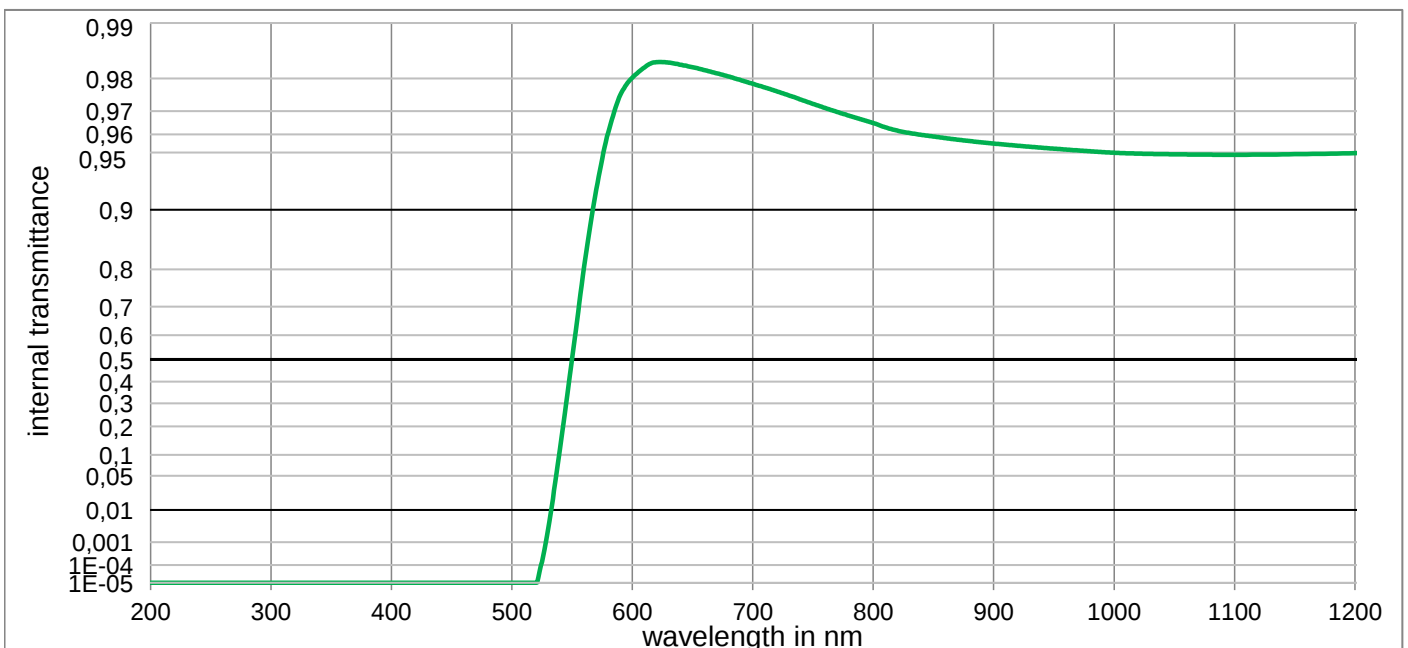

OG550

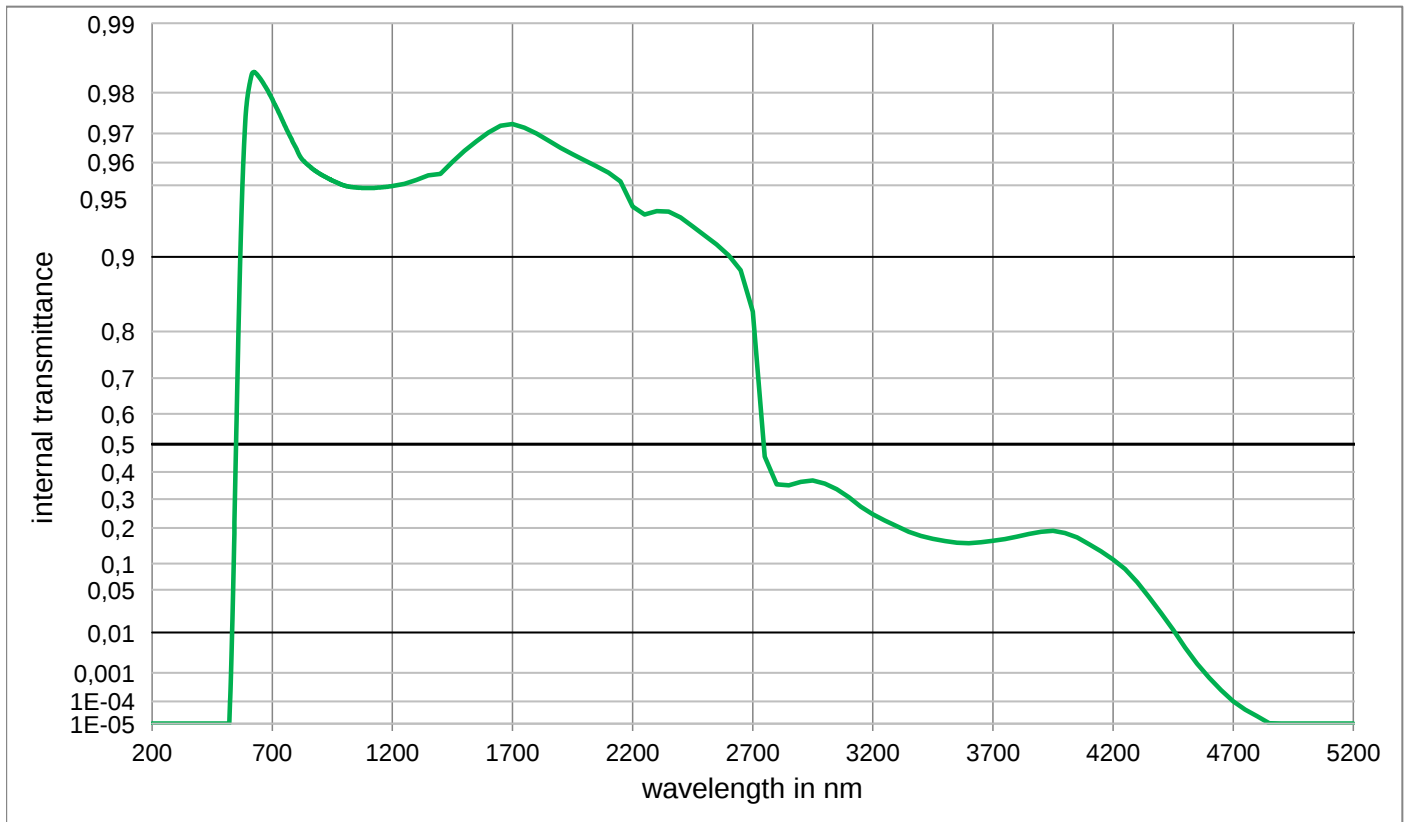Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,652E-01	1100	9,486E-01	2200	9,385E-01	3700	1,601E-01
210	< 1,0E-05	510	< 1,000E-05	810	9,633E-01	1110	9,486E-01	2250	9,335E-01	3750	1,653E-01
220	< 1,0E-05	520	< 1,000E-05	820	9,618E-01	1120	9,487E-01	2300	9,356E-01	3800	1,725E-01
230	< 1,0E-05	530	2,837E-03	830	9,607E-01	1130	9,488E-01	2350	9,353E-01	3850	1,806E-01
240	< 1,0E-05	540	1,194E-01	840	9,597E-01	1140	9,489E-01	2400	9,316E-01	3900	1,878E-01
250	< 1,0E-05	550	5,076E-01	850	9,589E-01	1150	9,490E-01	2450	9,254E-01	3950	1,905E-01
260	< 1,0E-05	560	8,065E-01	860	9,581E-01	1160	9,491E-01	2500	9,186E-01	4000	1,842E-01
270	< 1,0E-05	570	9,217E-01	870	9,573E-01	1170	9,492E-01	2550	9,112E-01	4050	1,706E-01
280	< 1,0E-05	580	9,608E-01	880	9,566E-01	1180	9,493E-01	2600	9,015E-01	4100	1,507E-01
290	< 1,0E-05	590	9,755E-01	890	9,559E-01	1190	9,495E-01	2650	8,864E-01	4150	1,305E-01
300	< 1,0E-05	600	9,802E-01	900	9,552E-01	1200	9,496E-01	2700	8,330E-01	4200	1,098E-01
310	< 1,0E-05	610	9,826E-01	910	9,546E-01	1250	9,507E-01	2750	4,559E-01	4250	8,790E-02
320	< 1,000E-05	620	9,837E-01	920	9,540E-01	1300	9,525E-01	2800	3,545E-01	4300	6,225E-02
330	< 1,000E-05	630	9,836E-01	930	9,534E-01	1350	9,547E-01	2850	3,508E-01	4350	3,942E-02
340	< 1,000E-05	640	9,832E-01	940	9,529E-01	1400	9,553E-01	2900	3,630E-01	4400	2,259E-02
350	< 1,000E-05	650	9,826E-01	950	9,523E-01	1450	9,602E-01	2950	3,684E-01	4450	1,125E-02
360	< 1,000E-05	660	9,820E-01	960	9,518E-01	1500	9,644E-01	3000	3,570E-01	4500	4,721E-03
370	< 1,000E-05	670	9,813E-01	970	9,513E-01	1550	9,676E-01	3050	3,358E-01	4550	1,845E-03
380	< 1,000E-05	680	9,805E-01	980	9,508E-01	1600	9,703E-01	3100	3,065E-01	4600	7,031E-04
390	< 1,000E-05	690	9,796E-01	990	9,503E-01	1650	9,722E-01	3150	2,725E-01	4650	2,704E-04
400	< 1,000E-05	700	9,786E-01	1000	9,499E-01	1700	9,727E-01	3200	2,459E-01	4700	9,979E-05
410	< 1,000E-05	710	9,776E-01	1010	9,496E-01	1750	9,717E-01	3250	2,244E-01	4750	4,519E-05
420	< 1,000E-05	720	9,765E-01	1020	9,493E-01	1800	9,700E-01	3300	2,055E-01	4800	2,259E-05
430	< 1,000E-05	730	9,753E-01	1030	9,492E-01	1850	9,678E-01	3350	1,881E-01	4850	1,052E-05
440	< 1,000E-05	740	9,740E-01	1040	9,490E-01	1900	9,655E-01	3400	1,749E-01	4900	< 1,000E-05
450	< 1,000E-05	750	9,726E-01	1050	9,489E-01	1950	9,632E-01	3450	1,660E-01	4950	< 1,000E-05
460	< 1,000E-05	760	9,711E-01	1060	9,488E-01	2000	9,609E-01	3500	1,599E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,697E-01	1070	9,487E-01	2050	9,585E-01	3550	1,546E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,682E-01	1080	9,487E-01	2100	9,558E-01	3600	1,533E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,668E-01	1090	9,486E-01	2150	9,519E-01	3650	1,558E-01	5150	< 1,000E-05

Optical properties	
Reflection factor	
$P_d = 0,921$	
Spectral values guaranteed (d = 3 mm)	
$\lambda_{i0,5} = 570 \text{ nm} \pm 6 \text{ nm}$	
$\lambda_s (\tau_{i,U} = 1E-05) = 500 \text{ nm}$	
$\lambda_p (\tau_{i,L} = 0,93) = 640 \text{ nm}$	
Refractive indices	
$n_d (587,6 \text{ nm}) = 1,51$	
$n_s (852 \text{ nm}) = 1,51$	
$n_t (1014 \text{ nm}) = 1,50$	
Sellmeier coefficients	
on request	
Internal quality	
Bubble class 3	


Mechanical properties	
Reference thickness	
$d = 3,00 \text{ mm}$	
Density	
$\rho = 2,74 \text{ g/cm}^3$	
Knoop hardness	
$HK_{[0,1/20]} = 455$	

Thermal properties	
Transformation temperature	
$T_g = 510 \text{ }^\circ\text{C}$	
Thermal expansion in $10^{-6}/\text{K}$	
$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,9$	
$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,0$	
Temperature coefficient	
$Tk = 0,12 \text{ nm/K}$	


Chemical properties	
Chemical resistance	
FR class = 0	
SR class = 1	
AR class = 1	
Resistance against humidity	
Resistant glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colormetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x	0,566	0,600	0,611
	y	0,412	0,399	0,389
	Y	42,7	36,1	32,9
	λ_d	591 nm	595 nm	597 nm
	P_e	0,941	0,998	1,000
Illuminant A	x	0,600	0,619	0,627
	y	0,394	0,380	0,372
	Y	55,7	49,4	46,0
	λ_d	596 nm	598 nm	600 nm
	P_e	0,964	0,999	1,000

Notes
Stricking glass
Longpass filter
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

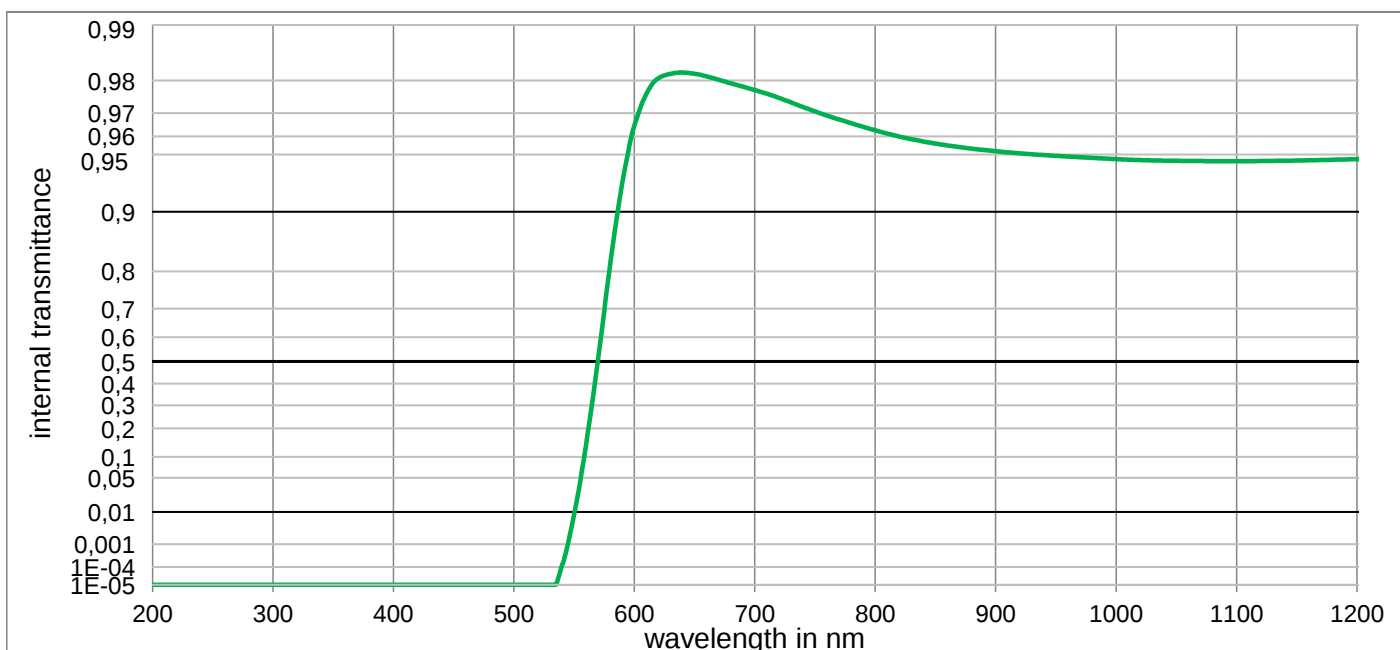

OG570

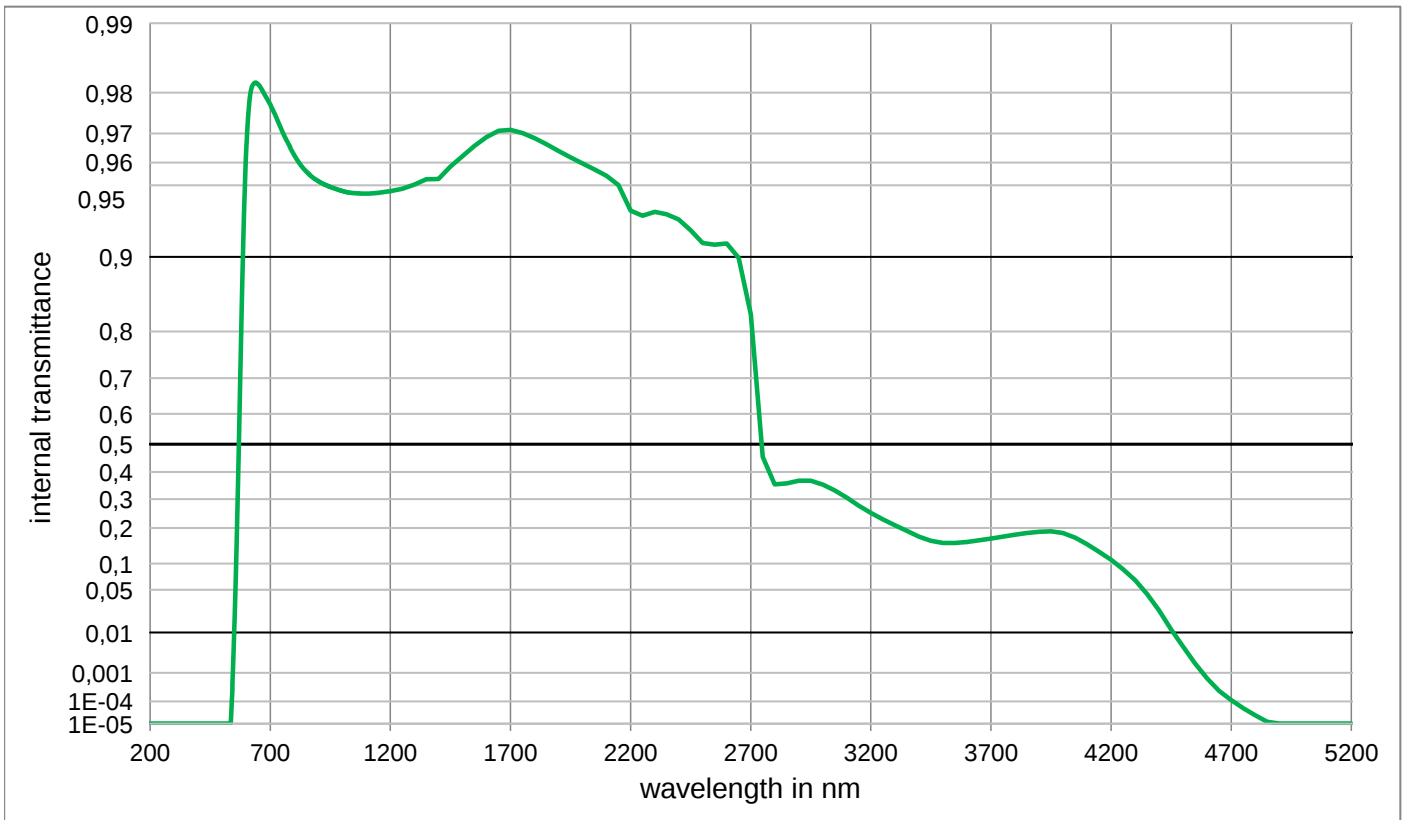
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,629E-01	1100	9,457E-01	2200	9,360E-01	3700	1,671E-01
210	< 1,0E-05	510	< 1,000E-05	810	9,613E-01	1110	9,458E-01	2250	9,328E-01	3750	1,730E-01
220	< 1,0E-05	520	< 1,000E-05	820	9,599E-01	1120	9,458E-01	2300	9,352E-01	3800	1,787E-01
230	< 1,0E-05	530	< 1,000E-05	830	9,586E-01	1130	9,459E-01	2350	9,337E-01	3850	1,839E-01
240	< 1,0E-05	540	1,275E-04	840	9,574E-01	1140	9,461E-01	2400	9,302E-01	3900	1,879E-01
250	< 1,0E-05	550	8,832E-03	850	9,563E-01	1150	9,462E-01	2450	9,224E-01	3950	1,893E-01
260	< 1,0E-05	560	1,386E-01	860	9,553E-01	1160	9,464E-01	2500	9,125E-01	4000	1,838E-01
270	< 1,0E-05	570	5,166E-01	870	9,544E-01	1170	9,465E-01	2550	9,111E-01	4050	1,700E-01
280	< 1,0E-05	580	8,155E-01	880	9,535E-01	1180	9,467E-01	2600	9,121E-01	4100	1,503E-01
290	< 1,0E-05	590	9,299E-01	890	9,527E-01	1190	9,469E-01	2650	8,991E-01	4150	1,297E-01
300	< 1,0E-05	600	9,649E-01	900	9,520E-01	1200	9,470E-01	2700	8,288E-01	4200	1,090E-01
310	< 1,0E-05	610	9,764E-01	910	9,513E-01	1250	9,483E-01	2750	4,551E-01	4250	8,758E-02
320	< 1,000E-05	620	9,806E-01	920	9,507E-01	1300	9,503E-01	2800	3,544E-01	4300	6,582E-02
330	< 1,000E-05	630	9,816E-01	930	9,502E-01	1350	9,529E-01	2850	3,574E-01	4350	4,375E-02
340	< 1,000E-05	640	9,819E-01	940	9,497E-01	1400	9,529E-01	2900	3,675E-01	4400	2,518E-02
350	< 1,000E-05	650	9,816E-01	950	9,492E-01	1450	9,584E-01	2950	3,676E-01	4450	1,145E-02
360	< 1,000E-05	660	9,810E-01	960	9,488E-01	1500	9,625E-01	3000	3,531E-01	4500	4,940E-03
370	< 1,000E-05	670	9,802E-01	970	9,483E-01	1550	9,661E-01	3050	3,320E-01	4550	1,875E-03
380	< 1,000E-05	680	9,793E-01	980	9,479E-01	1600	9,689E-01	3100	3,052E-01	4600	6,610E-04
390	< 1,000E-05	690	9,784E-01	990	9,475E-01	1650	9,708E-01	3150	2,759E-01	4650	2,500E-04
400	< 1,000E-05	700	9,775E-01	1000	9,471E-01	1700	9,711E-01	3200	2,507E-01	4700	1,134E-04
410	< 1,000E-05	710	9,764E-01	1010	9,468E-01	1750	9,701E-01	3250	2,286E-01	4750	5,284E-05
420	< 1,000E-05	720	9,752E-01	1020	9,465E-01	1800	9,686E-01	3300	2,093E-01	4800	2,512E-05
430	< 1,000E-05	730	9,737E-01	1030	9,463E-01	1850	9,666E-01	3350	1,906E-01	4850	1,226E-05
440	< 1,000E-05	740	9,722E-01	1040	9,461E-01	1900	9,643E-01	3400	1,730E-01	4900	< 1,000E-05
450	< 1,000E-05	750	9,706E-01	1050	9,460E-01	1950	9,620E-01	3450	1,604E-01	4950	< 1,000E-05
460	< 1,000E-05	760	9,691E-01	1060	9,459E-01	2000	9,597E-01	3500	1,540E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,676E-01	1070	9,458E-01	2050	9,572E-01	3550	1,536E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,661E-01	1080	9,458E-01	2100	9,544E-01	3600	1,568E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,644E-01	1090	9,457E-01	2150	9,502E-01	3650	1,618E-01	5150	< 1,000E-05

OG590

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,921$	$d = 3,00 \text{ mm}$	x 0,610 0,652 0,661
Spectral values guaranteed (d = 3 mm)	Density	y 0,361 0,347 0,338
$\lambda_{i0,5} = 590 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,56 \text{ g/cm}^3$	Y 27,3 21,5 19,2
$\lambda_s (\tau_{i,U} = 1E-05) = 510 \text{ nm}$	Knoop hardness	λ_d 602 nm 606 nm 609 nm
$\lambda_p (\tau_{i,L} = 0,93) = 660 \text{ nm}$	$HK_{[0.1/20]} = 448$	P_e 0,920 0,998 1,000
		Illuminant D65
		x 0,639 0,662 0,669
		y 0,354 0,338 0,331
		Y 39,2 32,7 29,8
		λ_d 605 nm 609 nm 611 nm
		P_e 0,956 0,998 0,999
		Illuminant A
		x 0,639 0,662 0,669
		y 0,354 0,338 0,331
		Y 39,2 32,7 29,8
		λ_d 605 nm 609 nm 611 nm
		P_e 0,956 0,998 0,999
Refractive indices	Thermal properties	Notes
$n_d (587,6 \text{ nm}) = 1,51$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,51$	$T_g = 506 \text{ }^\circ\text{C}$	
$n_t (1014 \text{ nm}) = 1,50$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,9$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,0$	
	Temperature coefficient	
	$Tk = 0,13 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Stricking glass
on request	Chemical resistance	Longpass filter
	FR class = 0	
	SR class = 1	
	AR class = 1	
	Resistance against humidity	
	Resistant glass	
	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	ISO 23364:2021
Internal quality		Disclaimer
Bubble class 3		All data without tolerances are to be understood to be reference values.

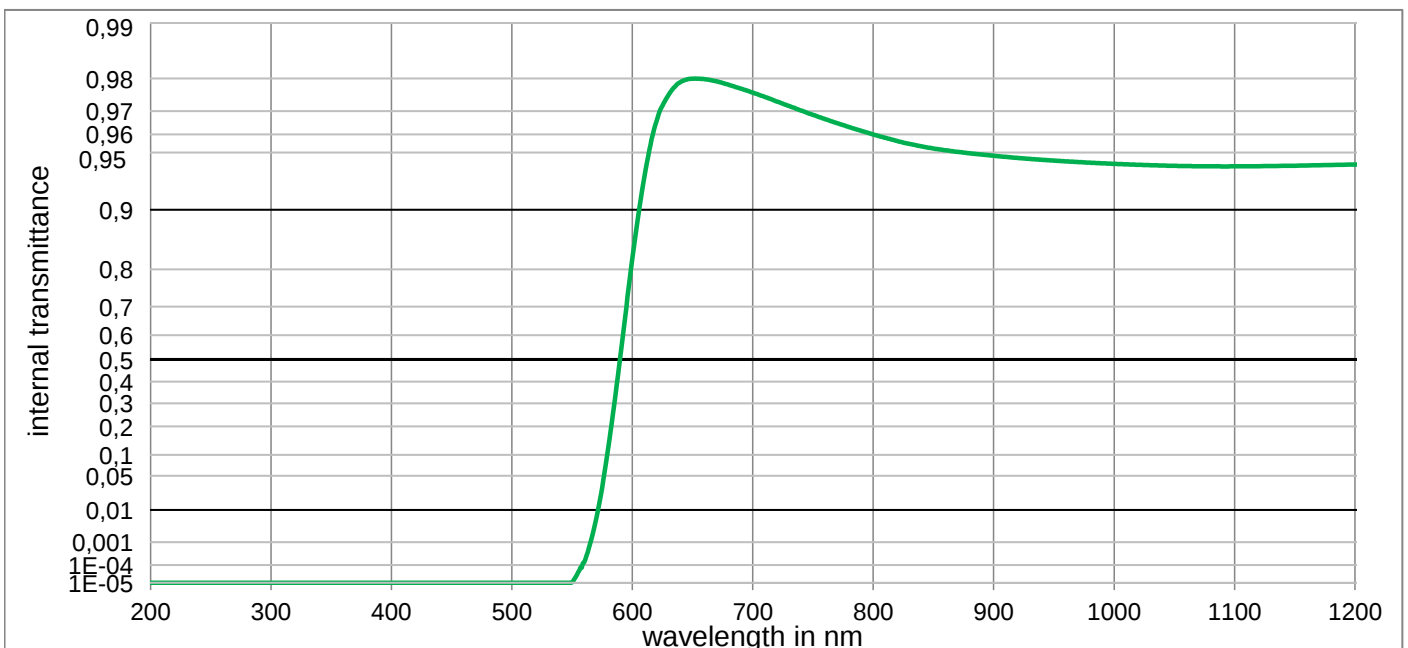

OG590

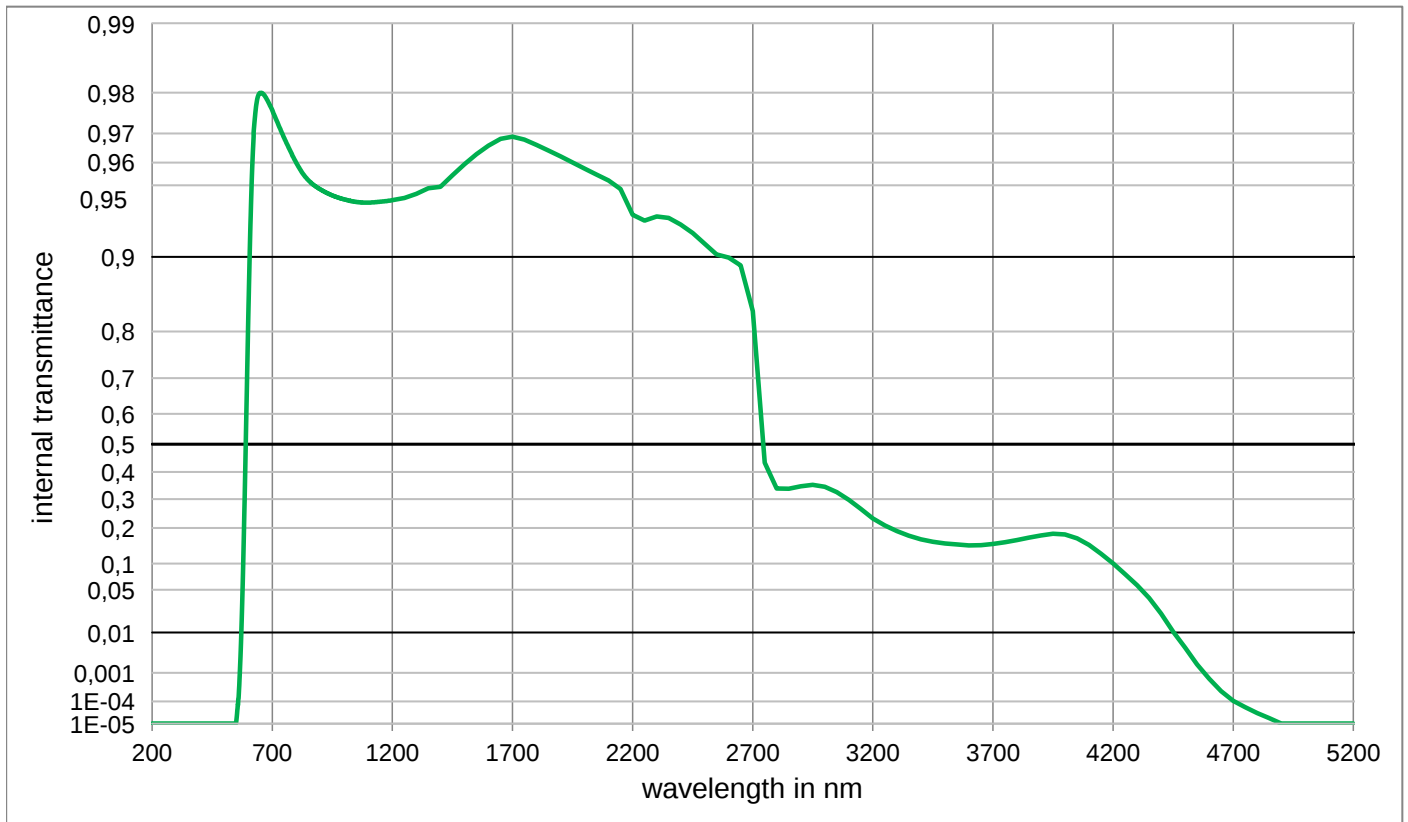
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,600E-01	1100	9,408E-01	2200	9,334E-01	3700	1,509E-01
210	< 1,0E-05	510	< 1,000E-05	810	9,583E-01	1110	9,408E-01	2250	9,295E-01	3750	1,558E-01
220	< 1,0E-05	520	< 1,000E-05	820	9,566E-01	1120	9,409E-01	2300	9,323E-01	3800	1,624E-01
230	< 1,0E-05	530	< 1,000E-05	830	9,551E-01	1130	9,410E-01	2350	9,313E-01	3850	1,697E-01
240	< 1,0E-05	540	< 1,000E-05	840	9,537E-01	1140	9,411E-01	2400	9,267E-01	3900	1,765E-01
250	< 1,0E-05	550	1,060E-05	850	9,524E-01	1150	9,413E-01	2450	9,205E-01	3950	1,813E-01
260	< 1,0E-05	560	1,311E-04	860	9,514E-01	1160	9,414E-01	2500	9,117E-01	4000	1,794E-01
270	< 1,0E-05	570	5,941E-03	870	9,504E-01	1170	9,416E-01	2550	9,024E-01	4050	1,678E-01
280	< 1,0E-05	580	1,208E-01	880	9,495E-01	1180	9,418E-01	2600	8,992E-01	4100	1,480E-01
290	< 1,0E-05	590	5,150E-01	890	9,488E-01	1190	9,420E-01	2650	8,917E-01	4150	1,246E-01
300	< 1,0E-05	600	8,226E-01	900	9,480E-01	1200	9,421E-01	2700	8,337E-01	4200	1,006E-01
310	< 1,0E-05	610	9,329E-01	910	9,473E-01	1250	9,434E-01	2750	4,344E-01	4250	7,750E-02
320	< 1,000E-05	620	9,658E-01	920	9,466E-01	1300	9,457E-01	2800	3,392E-01	4300	5,680E-02
330	< 1,000E-05	630	9,755E-01	930	9,459E-01	1350	9,485E-01	2850	3,381E-01	4350	3,854E-02
340	< 1,000E-05	640	9,791E-01	940	9,454E-01	1400	9,493E-01	2900	3,473E-01	4400	2,229E-02
350	< 1,000E-05	650	9,800E-01	950	9,448E-01	1450	9,547E-01	2950	3,524E-01	4450	1,033E-02
360	< 1,000E-05	660	9,798E-01	960	9,443E-01	1500	9,594E-01	3000	3,453E-01	4500	4,710E-03
370	< 1,000E-05	670	9,793E-01	970	9,438E-01	1550	9,632E-01	3050	3,252E-01	4550	1,742E-03
380	< 1,000E-05	680	9,784E-01	980	9,434E-01	1600	9,662E-01	3100	2,969E-01	4600	6,577E-04
390	< 1,000E-05	690	9,773E-01	990	9,430E-01	1650	9,684E-01	3150	2,648E-01	4650	2,483E-04
400	< 1,000E-05	700	9,762E-01	1000	9,426E-01	1700	9,690E-01	3200	2,322E-01	4700	1,059E-04
410	< 1,000E-05	710	9,748E-01	1010	9,422E-01	1750	9,681E-01	3250	2,078E-01	4750	5,728E-05
420	< 1,000E-05	720	9,734E-01	1020	9,419E-01	1800	9,664E-01	3300	1,899E-01	4800	3,214E-05
430	< 1,000E-05	730	9,718E-01	1030	9,416E-01	1850	9,645E-01	3350	1,755E-01	4850	1,832E-05
440	< 1,000E-05	740	9,702E-01	1040	9,414E-01	1900	9,623E-01	3400	1,643E-01	4900	< 1,000E-05
450	< 1,000E-05	750	9,686E-01	1050	9,412E-01	1950	9,600E-01	3450	1,571E-01	4950	< 1,000E-05
460	< 1,000E-05	760	9,669E-01	1060	9,410E-01	2000	9,576E-01	3500	1,528E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,652E-01	1070	9,409E-01	2050	9,550E-01	3550	1,494E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,635E-01	1080	9,408E-01	2100	9,523E-01	3600	1,469E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,617E-01	1090	9,408E-01	2150	9,482E-01	3650	1,478E-01	5150	< 1,000E-05

RG610

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,920$	$d = 3,00 \text{ mm}$	x 0,629 0,684 0,693
Spectral values guaranteed (d = 3 mm)	Density	y 0,330 0,315 0,307
$\lambda_{i0,5} = 610 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,65 \text{ g/cm}^3$	Y 17,4 11,9 9,9
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 530 \text{ nm}$	Knoop hardness	λ_d 611 nm 617 nm 621 nm
$\lambda_p (\tau_{i,L} = 0,94) = 690 \text{ nm}$	$HK_{[0.1/20]} = 448$	P_e 0,886 0,996 1,000
		Illuminant A
		x 0,663 0,690 0,697
		y 0,328 0,310 0,303
		Y 26,5 19,7 16,8
		λ_d 614 nm 619 nm 623 nm
		P_e 0,939 0,998 0,999
Refractive indices	Thermal properties	Notes
$n_d (587,6 \text{ nm}) = 1,51$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,51$	$T_g = 520 \text{ }^\circ\text{C}$	Stricking glass
$n_t (1014 \text{ nm}) = 1,50$	Thermal expansion in $10^{-6}/\text{K}$	Longpass filter
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,0$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,2$	
Sellmeier coefficients	Temperature coefficient	
valid from 580 nm to 2330 nm	$Tk = 0,14 \text{ nm/K}$	
$B_1 = 1,2549$	Chemical properties	
$B_2 = 0,0002$	Chemical resistance	
$B_3 = 0,7981$	FR class	
$C_1 = 9,761\text{E-}03 \text{ } \mu\text{m}^2$	SR class = 1	
$C_2 = 2,8886\text{E-}01 \text{ } \mu\text{m}^2$	AR class = 1	
$C_3 = 98,991 \text{ } \mu\text{m}^2$	Resistance against humidity	ISO 23364:2021
Internal quality	Resistant glass	Disclaimer
Bubble class 3	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	All data without tolerances are to be understood to be reference values.

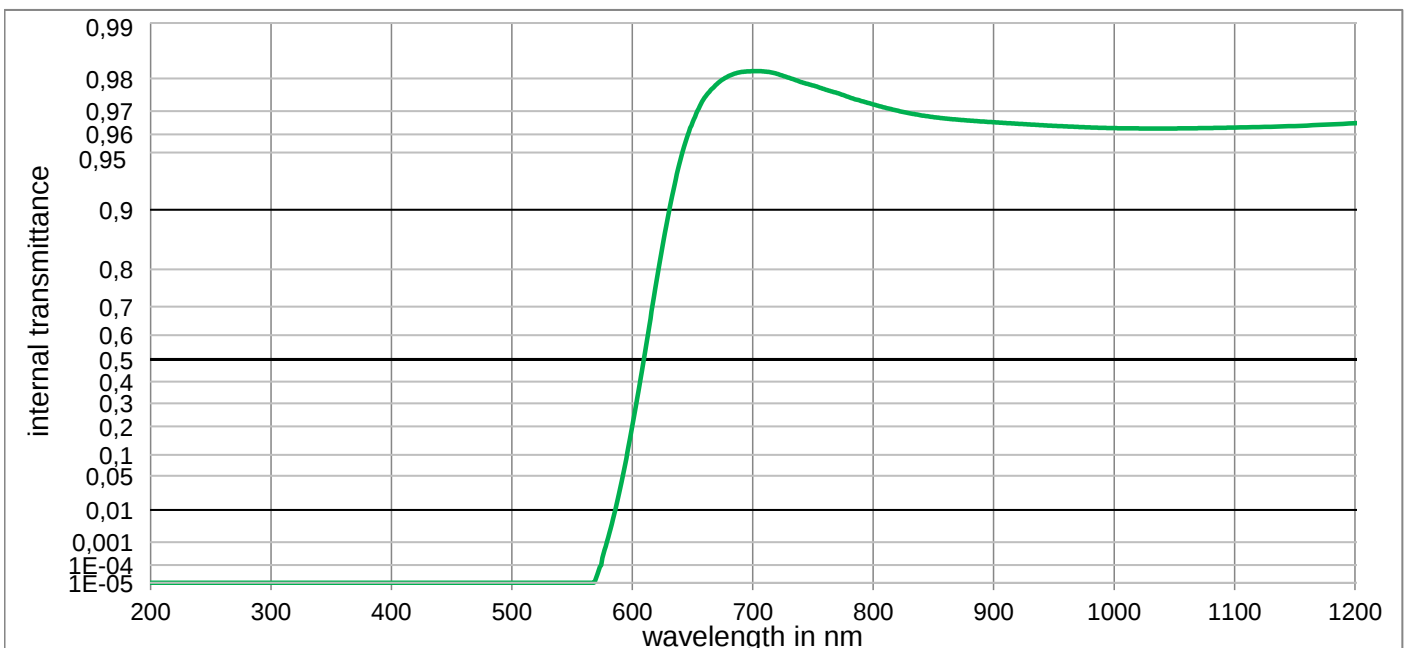

RG610

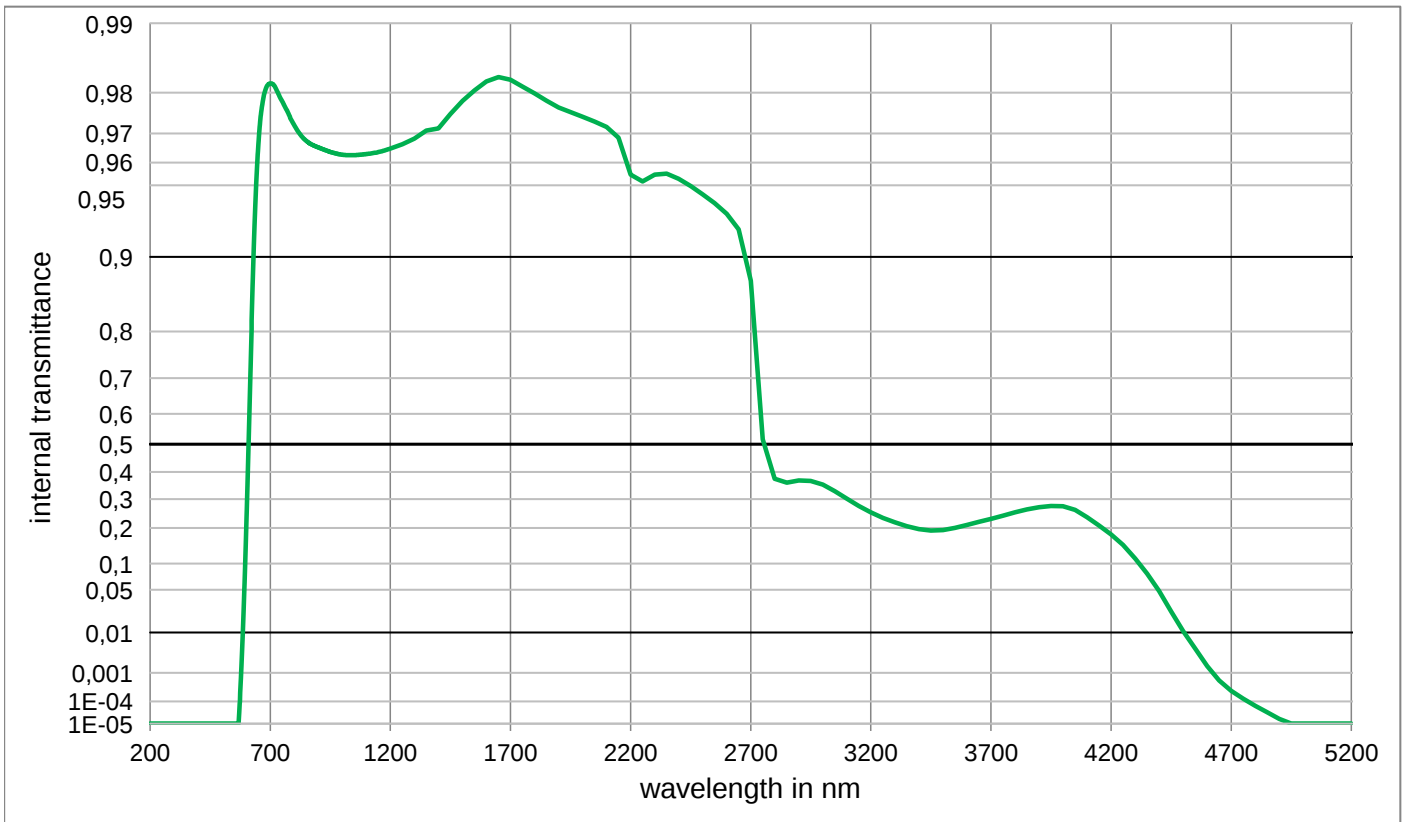
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,724E-01	1100	9,632E-01	2200	9,550E-01	3700	2,302E-01
210	< 1,0E-05	510	< 1,000E-05	810	9,713E-01	1110	9,633E-01	2250	9,519E-01	3750	2,411E-01
220	< 1,0E-05	520	< 1,000E-05	820	9,702E-01	1120	9,635E-01	2300	9,550E-01	3800	2,527E-01
230	< 1,0E-05	530	< 1,000E-05	830	9,692E-01	1130	9,636E-01	2350	9,554E-01	3850	2,631E-01
240	< 1,0E-05	540	< 1,000E-05	840	9,684E-01	1140	9,637E-01	2400	9,532E-01	3900	2,708E-01
250	< 1,0E-05	550	< 1,000E-05	850	9,677E-01	1150	9,639E-01	2450	9,496E-01	3950	2,756E-01
260	< 1,0E-05	560	< 1,000E-05	860	9,671E-01	1160	9,641E-01	2500	9,454E-01	4000	2,742E-01
270	< 1,0E-05	570	2,118E-05	870	9,667E-01	1170	9,644E-01	2550	9,405E-01	4050	2,614E-01
280	< 1,0E-05	580	1,470E-03	880	9,663E-01	1180	9,646E-01	2600	9,339E-01	4100	2,362E-01
290	< 1,0E-05	590	3,112E-02	890	9,659E-01	1190	9,649E-01	2650	9,232E-01	4150	2,080E-01
300	< 1,0E-05	600	2,019E-01	900	9,656E-01	1200	9,652E-01	2700	8,746E-01	4200	1,793E-01
310	< 1,0E-05	610	5,164E-01	910	9,653E-01	1250	9,666E-01	2750	5,165E-01	4250	1,482E-01
320	< 1,000E-05	620	7,703E-01	920	9,649E-01	1300	9,685E-01	2800	3,748E-01	4300	1,123E-01
330	< 1,000E-05	630	8,948E-01	930	9,646E-01	1350	9,708E-01	2850	3,606E-01	4350	7,840E-02
340	< 1,000E-05	640	9,454E-01	940	9,643E-01	1400	9,715E-01	2900	3,684E-01	4400	4,815E-02
350	< 1,000E-05	650	9,655E-01	950	9,640E-01	1450	9,753E-01	2950	3,671E-01	4450	2,387E-02
360	< 1,000E-05	660	9,746E-01	960	9,638E-01	1500	9,783E-01	3000	3,529E-01	4500	1,073E-02
370	< 1,000E-05	670	9,785E-01	970	9,635E-01	1550	9,804E-01	3050	3,291E-01	4550	4,530E-03
380	< 1,000E-05	680	9,806E-01	980	9,633E-01	1600	9,821E-01	3100	3,018E-01	4600	1,580E-03
390	< 1,000E-05	690	9,815E-01	990	9,631E-01	1650	9,829E-01	3150	2,753E-01	4650	5,741E-04
400	< 1,000E-05	700	9,817E-01	1000	9,630E-01	1700	9,824E-01	3200	2,529E-01	4700	2,512E-04
410	< 1,000E-05	710	9,817E-01	1010	9,629E-01	1750	9,812E-01	3250	2,334E-01	4750	1,279E-04
420	< 1,000E-05	720	9,812E-01	1020	9,628E-01	1800	9,799E-01	3300	2,183E-01	4800	6,668E-05
430	< 1,000E-05	730	9,802E-01	1030	9,628E-01	1850	9,783E-01	3350	2,060E-01	4850	3,420E-05
440	< 1,000E-05	740	9,791E-01	1040	9,628E-01	1900	9,768E-01	3400	1,965E-01	4900	1,687E-05
450	< 1,000E-05	750	9,782E-01	1050	9,628E-01	1950	9,757E-01	3450	1,917E-01	4950	< 1,000E-05
460	< 1,000E-05	760	9,771E-01	1060	9,629E-01	2000	9,746E-01	3500	1,933E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,761E-01	1070	9,630E-01	2050	9,733E-01	3550	1,999E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,748E-01	1080	9,630E-01	2100	9,719E-01	3600	2,098E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,736E-01	1090	9,631E-01	2150	9,688E-01	3650	2,201E-01	5150	< 1,000E-05

RG630

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,918$	$d = 3,00 \text{ mm}$	x 0,624 0,708 0,716
Spectral values guaranteed (d = 3 mm)	Density	y 0,305 0,289 0,284
$\lambda_{i,0,5} = 630 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,65 \text{ g/cm}^3$	Y 9,3 5,1 4,0
$\lambda_s(\tau_{i,U} = 1E-05) = 540 \text{ nm}$	Knoop hardness	λ_d 625 nm 633 nm 637 nm
$\lambda_p(\tau_{i,L} = 0,94) = 710 \text{ nm}$	$HK_{[0.1/20]} = 456$	P_e 0,802 0,992 1,000
		Illuminant A
		x 0,678 0,712 0,718
		y 0,307 0,287 0,282
		Y 14,8 9,4 7,6
		λ_d 627 nm 634 nm 639 nm
		P_e 0,899 0,996 0,999
Refractive indices	Thermal properties	Notes
$n_d(587,6 \text{ nm}) = 1,52$	Transformation temperature	
$n_s(852 \text{ nm}) = 1,52$	$T_g = 527 \text{ }^\circ\text{C}$	Stricking glass
$n_t(1014 \text{ nm}) = 1,51$	Thermal expansion in $10^{-6}/\text{K}$	Longpass filter
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,0$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,2$	
Sellmeier coefficients	Temperature coefficient	
on request	$Tk = 0,14 \text{ nm/K}$	ISO 23364:2021
		Disclaimer
	Chemical properties	All data without tolerances are to be understood to be reference values.
	Chemical resistance	
	FR class = 0	
	SR class = 1	
	AR class = 1	
	Resistance against humidity	
	Resistant glass	
Internal quality	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
Bubble class 3		

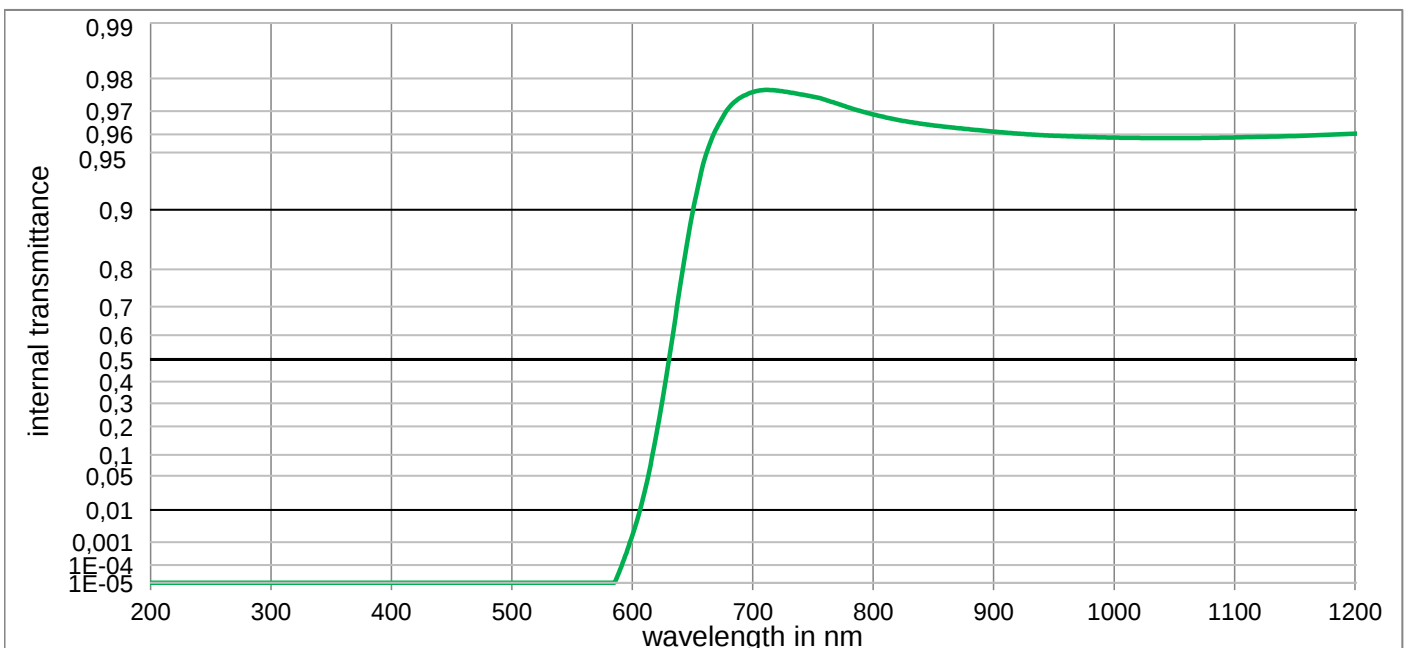

RG630

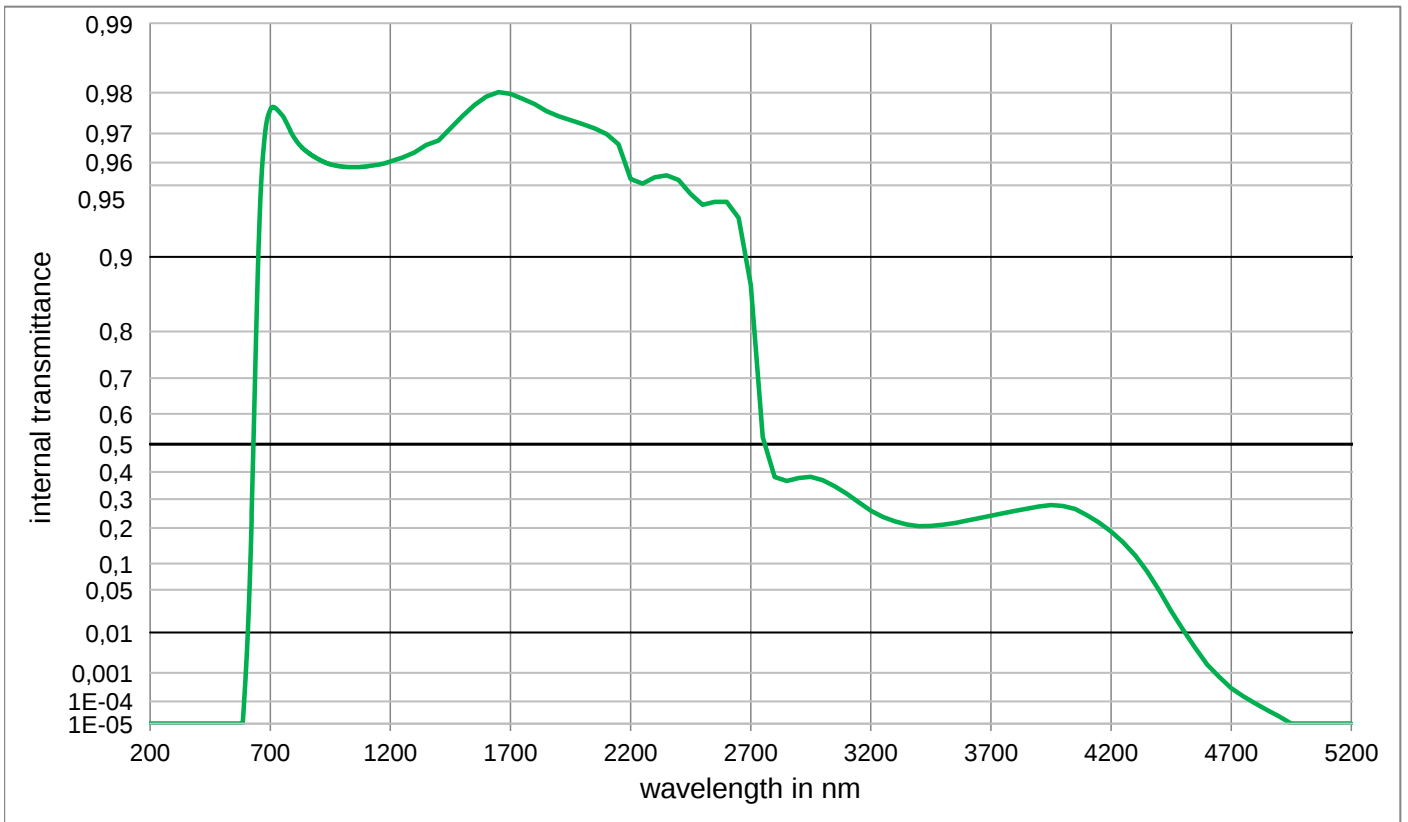
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,688E-01	1100	9,585E-01	2200	9,530E-01	3700	2,410E-01
210	< 1,0E-05	510	< 1,000E-05	810	9,676E-01	1110	9,586E-01	2250	9,509E-01	3750	2,495E-01
220	< 1,0E-05	520	< 1,000E-05	820	9,666E-01	1120	9,587E-01	2300	9,537E-01	3800	2,579E-01
230	< 1,0E-05	530	< 1,000E-05	830	9,657E-01	1130	9,589E-01	2350	9,546E-01	3850	2,660E-01
240	< 1,0E-05	540	< 1,000E-05	840	9,649E-01	1140	9,590E-01	2400	9,525E-01	3900	2,735E-01
250	< 1,0E-05	550	< 1,000E-05	850	9,642E-01	1150	9,592E-01	2450	9,456E-01	3950	2,783E-01
260	< 1,0E-05	560	< 1,000E-05	860	9,636E-01	1160	9,594E-01	2500	9,395E-01	4000	2,755E-01
270	< 1,0E-05	570	< 1,000E-05	870	9,630E-01	1170	9,596E-01	2550	9,412E-01	4050	2,645E-01
280	< 1,0E-05	580	< 1,000E-05	880	9,625E-01	1180	9,598E-01	2600	9,412E-01	4100	2,425E-01
290	< 1,0E-05	590	6,236E-05	890	9,619E-01	1190	9,601E-01	2650	9,312E-01	4150	2,177E-01
300	< 1,0E-05	600	1,716E-03	900	9,614E-01	1200	9,604E-01	2700	8,695E-01	4200	1,884E-01
310	< 1,0E-05	610	2,467E-02	910	9,608E-01	1250	9,619E-01	2750	5,243E-01	4250	1,559E-01
320	< 1,000E-05	620	1,692E-01	920	9,604E-01	1300	9,638E-01	2800	3,813E-01	4300	1,198E-01
330	< 1,000E-05	630	4,871E-01	930	9,600E-01	1350	9,664E-01	2850	3,670E-01	4350	8,250E-02
340	< 1,000E-05	640	7,652E-01	940	9,596E-01	1400	9,678E-01	2900	3,776E-01	4400	4,948E-02
350	< 1,000E-05	650	8,970E-01	950	9,593E-01	1450	9,715E-01	2950	3,817E-01	4450	2,448E-02
360	< 1,000E-05	660	9,457E-01	960	9,591E-01	1500	9,748E-01	3000	3,698E-01	4500	1,133E-02
370	< 1,000E-05	670	9,631E-01	970	9,589E-01	1550	9,774E-01	3050	3,471E-01	4550	4,684E-03
380	< 1,000E-05	680	9,711E-01	980	9,587E-01	1600	9,792E-01	3100	3,189E-01	4600	1,739E-03
390	< 1,000E-05	690	9,747E-01	990	9,585E-01	1650	9,801E-01	3150	2,884E-01	4650	7,540E-04
400	< 1,000E-05	700	9,763E-01	1000	9,584E-01	1700	9,798E-01	3200	2,589E-01	4700	3,162E-04
410	< 1,000E-05	710	9,769E-01	1010	9,583E-01	1750	9,788E-01	3250	2,366E-01	4750	1,596E-04
420	< 1,000E-05	720	9,768E-01	1020	9,582E-01	1800	9,776E-01	3300	2,219E-01	4800	8,375E-05
430	< 1,000E-05	730	9,763E-01	1030	9,582E-01	1850	9,760E-01	3350	2,117E-01	4850	4,355E-05
440	< 1,000E-05	740	9,756E-01	1040	9,582E-01	1900	9,747E-01	3400	2,061E-01	4900	2,203E-05
450	< 1,000E-05	750	9,749E-01	1050	9,581E-01	1950	9,737E-01	3450	2,064E-01	4950	< 1,000E-05
460	< 1,000E-05	760	9,740E-01	1060	9,582E-01	2000	9,727E-01	3500	2,103E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,727E-01	1070	9,582E-01	2050	9,715E-01	3550	2,160E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,713E-01	1080	9,583E-01	2100	9,698E-01	3600	2,240E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,700E-01	1090	9,584E-01	2150	9,666E-01	3650	2,323E-01	5150	< 1,000E-05

RG645

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,918$	$d = 3,00 \text{ mm}$	x 0,584 0,717 0,726
Spectral values guaranteed (d = 3 mm)	Density	y 0,298 0,278 0,274
$\lambda_{i,0,5} = 645 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,65 \text{ g/cm}^3$	Y 5,4 2,4 1,8
$\lambda_s(\tau_{i,U} = 1\text{E-}05) = 560 \text{ nm}$	Knoop hardness	λ_d 638 nm 645 nm 650 nm
$\lambda_p(\tau_{i,L} = 0,94) = 720 \text{ nm}$	$HK_{[0.1/20]} = 456$	P_e 0,670 0,984 0,999
		Illuminant D65
		x 0,672 0,722 0,726
		y 0,303 0,277 0,274
		Y 8,6 4,7 3,6
		λ_d 640 nm 647 nm 651 nm
		P_e 0,828 0,993 0,999
		Illuminant A
		x 0,672 0,722 0,726
		y 0,303 0,277 0,274
		Y 8,6 4,7 3,6
		λ_d 640 nm 647 nm 651 nm
		P_e 0,828 0,993 0,999
Refractive indices	Thermal properties	Notes
$n_d(587,6 \text{ nm}) = 1,52$	Transformation temperature	
$n_s(852 \text{ nm}) = 1,52$	$T_g = 519 \text{ }^\circ\text{C}$	Stricking glass
$n_t(1014 \text{ nm}) = 1,51$	Thermal expansion in $10^{-6}/\text{K}$	Longpass filter
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,0$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,2$	
Sellmeier coefficients	Temperature coefficient	
on request	$Tk = 0,16 \text{ nm/K}$	
	Chemical properties	
	Chemical resistance	
	FR class = 0	
	SR class = 1	
	AR class = 1	
	Resistance against humidity	
	Resistant glass	
Internal quality	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	ISO 23364:2021
Bubble class 3		Disclaimer
		All data without tolerances are to be understood to be reference values.

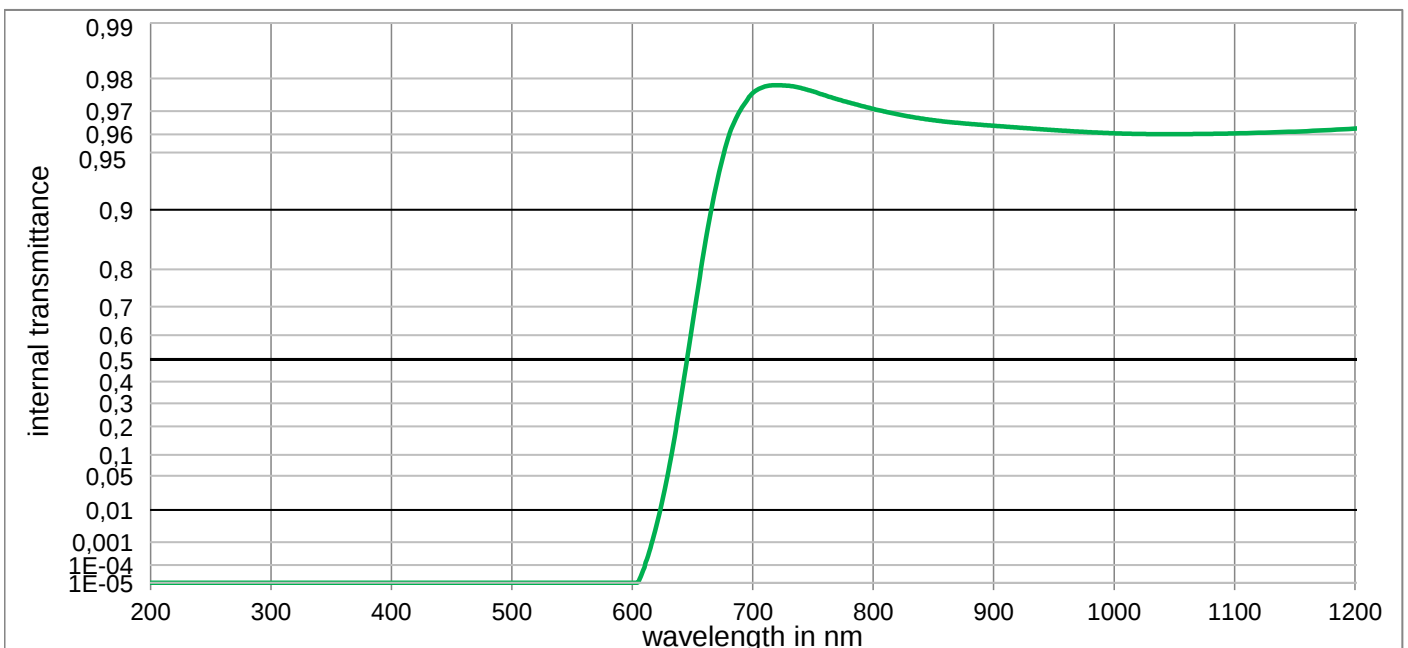

RG645

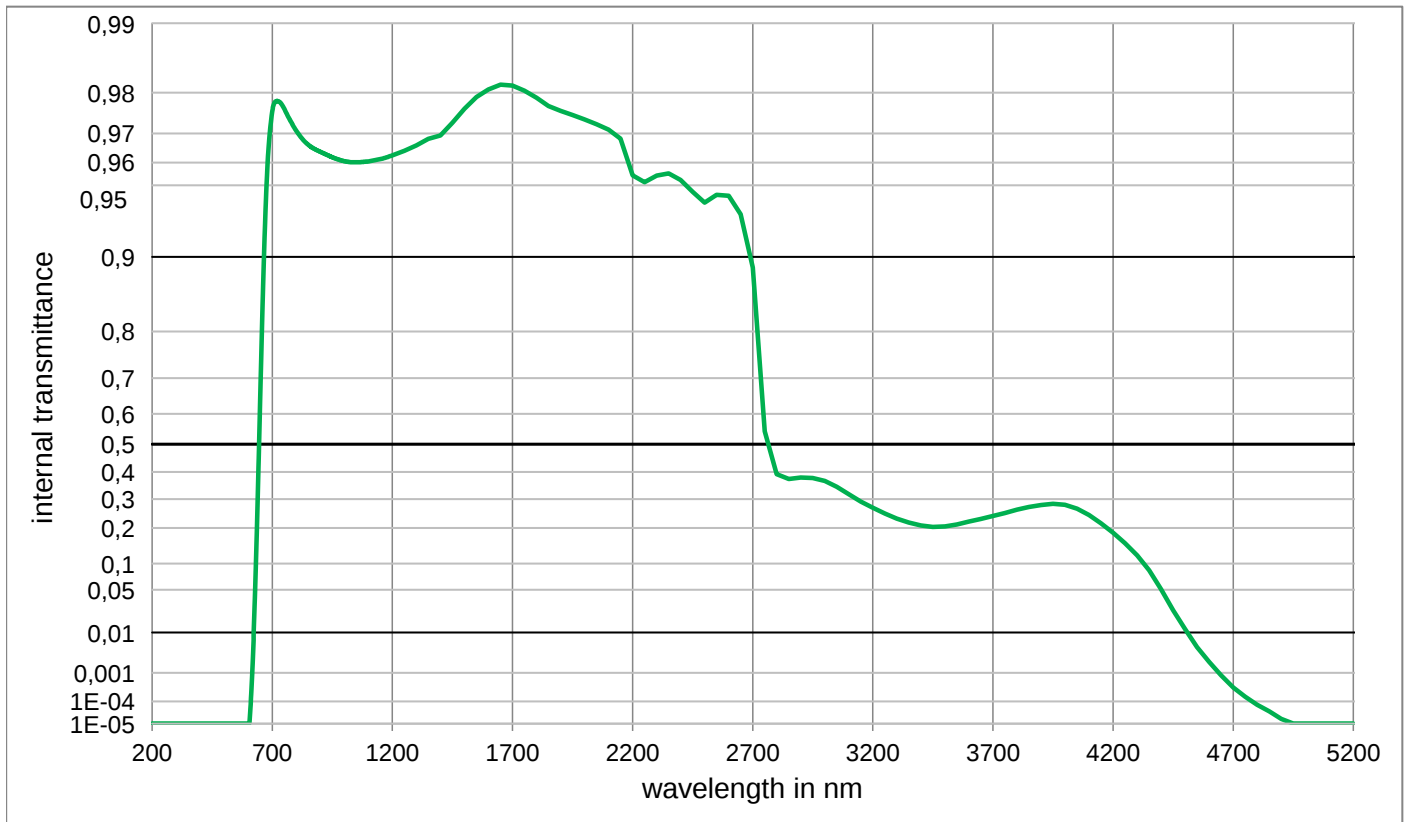
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,708E-01	1100	9,605E-01	2200	9,547E-01	3700	2,399E-01
210	< 1,0E-05	510	< 1,000E-05	810	9,698E-01	1110	9,606E-01	2250	9,516E-01	3750	2,503E-01
220	< 1,0E-05	520	< 1,000E-05	820	9,688E-01	1120	9,608E-01	2300	9,545E-01	3800	2,623E-01
230	< 1,0E-05	530	< 1,000E-05	830	9,679E-01	1130	9,610E-01	2350	9,555E-01	3850	2,714E-01
240	< 1,0E-05	540	< 1,000E-05	840	9,671E-01	1140	9,611E-01	2400	9,525E-01	3900	2,787E-01
250	< 1,0E-05	550	< 1,000E-05	850	9,664E-01	1150	9,613E-01	2450	9,466E-01	3950	2,827E-01
260	< 1,0E-05	560	< 1,000E-05	860	9,658E-01	1160	9,616E-01	2500	9,408E-01	4000	2,792E-01
270	< 1,0E-05	570	< 1,000E-05	870	9,653E-01	1170	9,618E-01	2550	9,451E-01	4050	2,656E-01
280	< 1,0E-05	580	< 1,000E-05	880	9,649E-01	1180	9,621E-01	2600	9,447E-01	4100	2,436E-01
290	< 1,0E-05	590	< 1,000E-05	890	9,644E-01	1190	9,624E-01	2650	9,337E-01	4150	2,152E-01
300	< 1,0E-05	600	< 1,000E-05	900	9,641E-01	1200	9,628E-01	2700	8,894E-01	4200	1,844E-01
310	< 1,0E-05	610	7,607E-05	910	9,636E-01	1250	9,644E-01	2750	5,439E-01	4250	1,529E-01
320	< 1,000E-05	620	3,586E-03	920	9,632E-01	1300	9,662E-01	2800	3,916E-01	4300	1,199E-01
330	< 1,000E-05	630	6,056E-02	930	9,628E-01	1350	9,684E-01	2850	3,738E-01	4350	8,517E-02
340	< 1,000E-05	640	3,112E-01	940	9,624E-01	1400	9,694E-01	2900	3,791E-01	4400	5,083E-02
350	< 1,000E-05	650	6,454E-01	950	9,621E-01	1450	9,730E-01	2950	3,779E-01	4450	2,517E-02
360	< 1,000E-05	660	8,449E-01	960	9,617E-01	1500	9,765E-01	3000	3,671E-01	4500	1,162E-02
370	< 1,000E-05	670	9,271E-01	970	9,614E-01	1550	9,791E-01	3050	3,455E-01	4550	4,841E-03
380	< 1,000E-05	680	9,589E-01	980	9,611E-01	1600	9,806E-01	3100	3,177E-01	4600	2,037E-03
390	< 1,000E-05	690	9,706E-01	990	9,608E-01	1650	9,815E-01	3150	2,911E-01	4650	8,337E-04
400	< 1,000E-05	700	9,760E-01	1000	9,605E-01	1700	9,814E-01	3200	2,687E-01	4700	3,327E-04
410	< 1,000E-05	710	9,779E-01	1010	9,604E-01	1750	9,804E-01	3250	2,482E-01	4750	1,524E-04
420	< 1,000E-05	720	9,783E-01	1020	9,602E-01	1800	9,789E-01	3300	2,309E-01	4800	7,289E-05
430	< 1,000E-05	730	9,781E-01	1030	9,602E-01	1850	9,772E-01	3350	2,176E-01	4850	3,837E-05
440	< 1,000E-05	740	9,775E-01	1040	9,601E-01	1900	9,760E-01	3400	2,081E-01	4900	1,694E-05
450	< 1,000E-05	750	9,765E-01	1050	9,601E-01	1950	9,750E-01	3450	2,036E-01	4950	< 1,000E-05
460	< 1,000E-05	760	9,754E-01	1060	9,602E-01	2000	9,739E-01	3500	2,049E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,742E-01	1070	9,602E-01	2050	9,726E-01	3550	2,113E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,730E-01	1080	9,603E-01	2100	9,711E-01	3600	2,208E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,719E-01	1090	9,604E-01	2150	9,684E-01	3650	2,302E-01	5150	< 1,000E-05

RG665

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,918$	$d = 3,00 \text{ mm}$	x 0,487 0,711 0,731
Spectral values guaranteed (d = 3 mm)	Density	y 0,305 0,272 0,268
$\lambda_{i,0,5} = 665 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,77 \text{ g/cm}^3$	Y 3,2 0,8 0,5
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 580 \text{ nm}$	Knoop hardness	λ_d 654 nm 662 nm 668 nm
$\lambda_p (\tau_{i,L} = 0,96) = 750 \text{ nm}$	$HK_{[0.1/20]} = 453$	P_e 0,420 0,954 0,998
		Illuminant A
		x 0,631 0,726 0,732
		y 0,318 0,272 0,268
		Y 4,5 1,6 1,2
		λ_d 656 nm 664 nm 671 nm
		P_e 0,654 0,982 0,999
Refractive indices	Thermal properties	Notes
$n_d (587,6 \text{ nm}) = 1,52$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,51$	$T_g = 527 \text{ }^\circ\text{C}$	Stricking glass
$n_t (1014 \text{ nm}) = 1,51$	Thermal expansion in $10^{-6}/\text{K}$	Longpass filter
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,1$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,4$	
Sellmeier coefficients	Temperature coefficient	
valid from 350 nm to 2400 nm	$Tk = 0,17 \text{ nm/K}$	ISO 23364:2021
$B_1 = 0,7958$	Chemical properties	Disclaimer
$B_2 = 0,4847$	Chemical resistance	All data without tolerances are to be understood to be reference values.
$B_3 = 0,8880$	FR class = 0	
$C_1 = 5,130\text{E-}03 \text{ } \mu\text{m}^2$	SR class = 1	
$C_2 = 1,8116\text{E-}02 \text{ } \mu\text{m}^2$	AR class = 1	
$C_3 = 117,823 \text{ } \mu\text{m}^2$	Resistance against humidity	
Internal quality	Robust glass	
Bubble class 3	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

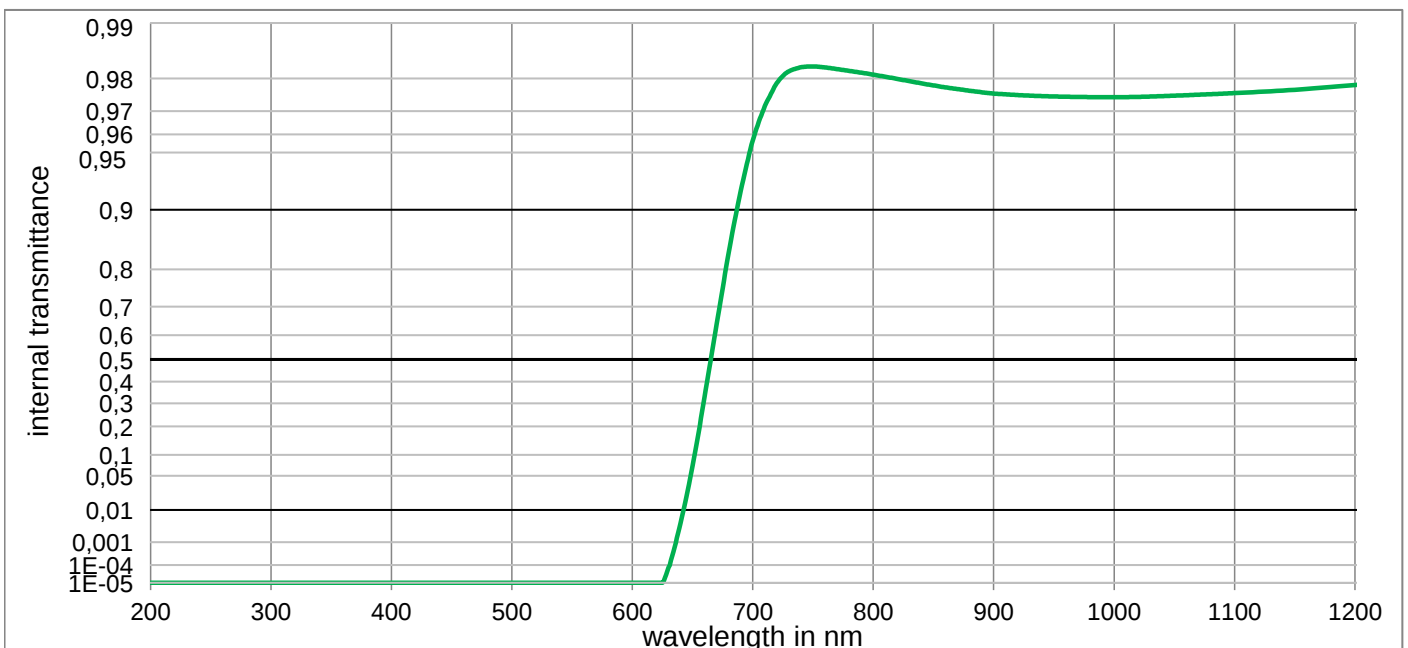

RG665

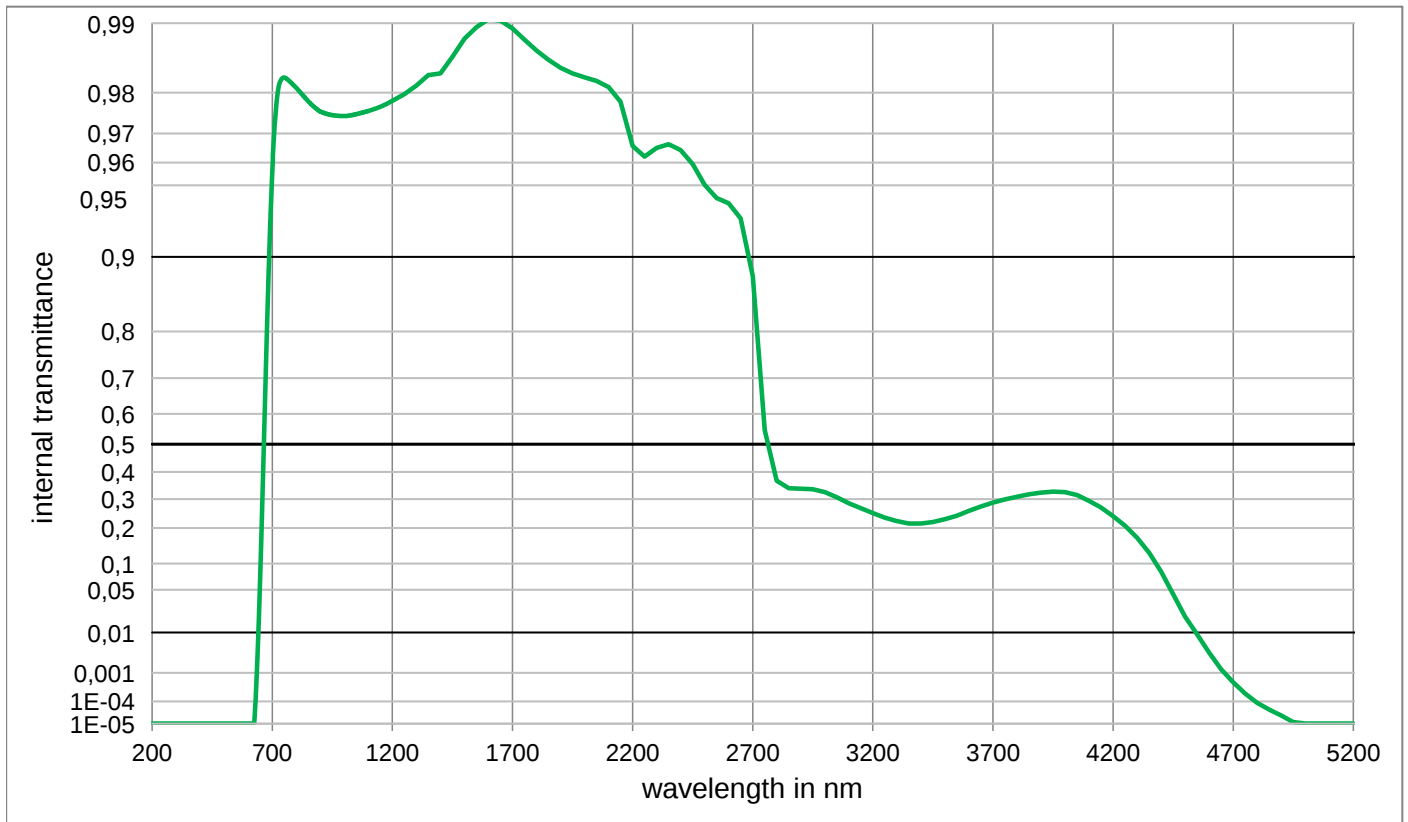
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,809E-01	1100	9,760E-01	2200	9,661E-01	3700	2,872E-01
210	< 1,0E-05	510	< 1,000E-05	810	9,804E-01	1110	9,762E-01	2250	9,623E-01	3750	2,991E-01
220	< 1,0E-05	520	< 1,000E-05	820	9,799E-01	1120	9,764E-01	2300	9,655E-01	3800	3,090E-01
230	< 1,0E-05	530	< 1,000E-05	830	9,793E-01	1130	9,766E-01	2350	9,666E-01	3850	3,173E-01
240	< 1,0E-05	540	< 1,000E-05	840	9,788E-01	1140	9,768E-01	2400	9,646E-01	3900	3,241E-01
250	< 1,0E-05	550	< 1,000E-05	850	9,782E-01	1150	9,770E-01	2450	9,594E-01	3950	3,273E-01
260	< 1,0E-05	560	< 1,000E-05	860	9,777E-01	1160	9,772E-01	2500	9,503E-01	4000	3,259E-01
270	< 1,0E-05	570	< 1,000E-05	870	9,772E-01	1170	9,775E-01	2550	9,434E-01	4050	3,147E-01
280	< 1,0E-05	580	< 1,000E-05	880	9,767E-01	1180	9,777E-01	2600	9,403E-01	4100	2,940E-01
290	< 1,0E-05	590	< 1,000E-05	890	9,763E-01	1190	9,780E-01	2650	9,310E-01	4150	2,697E-01
300	< 1,0E-05	600	< 1,000E-05	900	9,759E-01	1200	9,783E-01	2700	8,797E-01	4200	2,395E-01
310	< 1,0E-05	610	< 1,000E-05	910	9,756E-01	1250	9,797E-01	2750	5,478E-01	4250	2,072E-01
320	< 1,000E-05	620	< 1,000E-05	920	9,754E-01	1300	9,814E-01	2800	3,680E-01	4300	1,688E-01
330	< 1,000E-05	630	7,438E-05	930	9,752E-01	1350	9,832E-01	2850	3,399E-01	4350	1,267E-01
340	< 1,000E-05	640	4,275E-03	940	9,751E-01	1400	9,835E-01	2900	3,380E-01	4400	8,260E-02
350	< 1,000E-05	650	7,177E-02	950	9,750E-01	1450	9,860E-01	2950	3,359E-01	4450	4,350E-02
360	< 1,000E-05	660	3,297E-01	960	9,749E-01	1500	9,883E-01	3000	3,259E-01	4500	1,970E-02
370	< 1,000E-05	670	6,426E-01	970	9,748E-01	1550	9,896E-01	3050	3,067E-01	4550	9,240E-03
380	< 1,000E-05	680	8,339E-01	980	9,748E-01	1600	9,904E-01	3100	2,847E-01	4600	3,528E-03
390	< 1,000E-05	690	9,205E-01	990	9,748E-01	1650	9,903E-01	3150	2,670E-01	4650	1,277E-03
400	< 1,000E-05	700	9,567E-01	1000	9,748E-01	1700	9,895E-01	3200	2,501E-01	4700	4,966E-04
410	< 1,000E-05	710	9,719E-01	1010	9,748E-01	1750	9,882E-01	3250	2,347E-01	4750	2,028E-04
420	< 1,000E-05	720	9,788E-01	1020	9,749E-01	1800	9,869E-01	3300	2,224E-01	4800	8,730E-05
430	< 1,000E-05	730	9,817E-01	1030	9,750E-01	1850	9,856E-01	3350	2,148E-01	4850	4,477E-05
440	< 1,000E-05	740	9,826E-01	1040	9,751E-01	1900	9,844E-01	3400	2,144E-01	4900	2,472E-05
450	< 1,000E-05	750	9,828E-01	1050	9,752E-01	1950	9,835E-01	3450	2,198E-01	4950	1,183E-05
460	< 1,000E-05	760	9,826E-01	1060	9,754E-01	2000	9,828E-01	3500	2,290E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,822E-01	1070	9,755E-01	2050	9,822E-01	3550	2,412E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,818E-01	1080	9,757E-01	2100	9,811E-01	3600	2,577E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,814E-01	1090	9,758E-01	2150	9,781E-01	3650	2,734E-01	5150	< 1,000E-05

RG695

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,915$	$d = 3,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 3 mm)	Density	x
$\lambda_{i0,5} = 695 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,76 \text{ g/cm}^3$	y
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 610 \text{ nm}$	Knoop hardness	Y
$\lambda_p (\tau_{i,L} = 0,96) = 780 \text{ nm}$	$HK_{[0.1/20]} = 459$	λ_d
		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	Notes
$n_d (587,6 \text{ nm}) = 1,53$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,53$	$T_g = 532 \text{ }^\circ\text{C}$	
$n_t (1014 \text{ nm}) = 1,52$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,1$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,4$	
	Temperature coefficient	
	$Tk = 0,18 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Stricking glass
valid from 440 nm to 1550 nm	Chemical resistance	Longpass filter
$B_1 = 0,6009$	FR class = 0	
$B_2 = 0,7114$	SR class = 1	
$B_3 = 25,2603$	AR class = 1	
$C_1 = 1,682\text{E-}02 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 4,0132\text{E-}03 \text{ } \mu\text{m}^2$	Resistant glass	ISO 23364:2021
$C_3 = 4853,501 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	Disclaimer
Internal quality		All data without tolerances are to be understood to be reference values.
Bubble class 3		

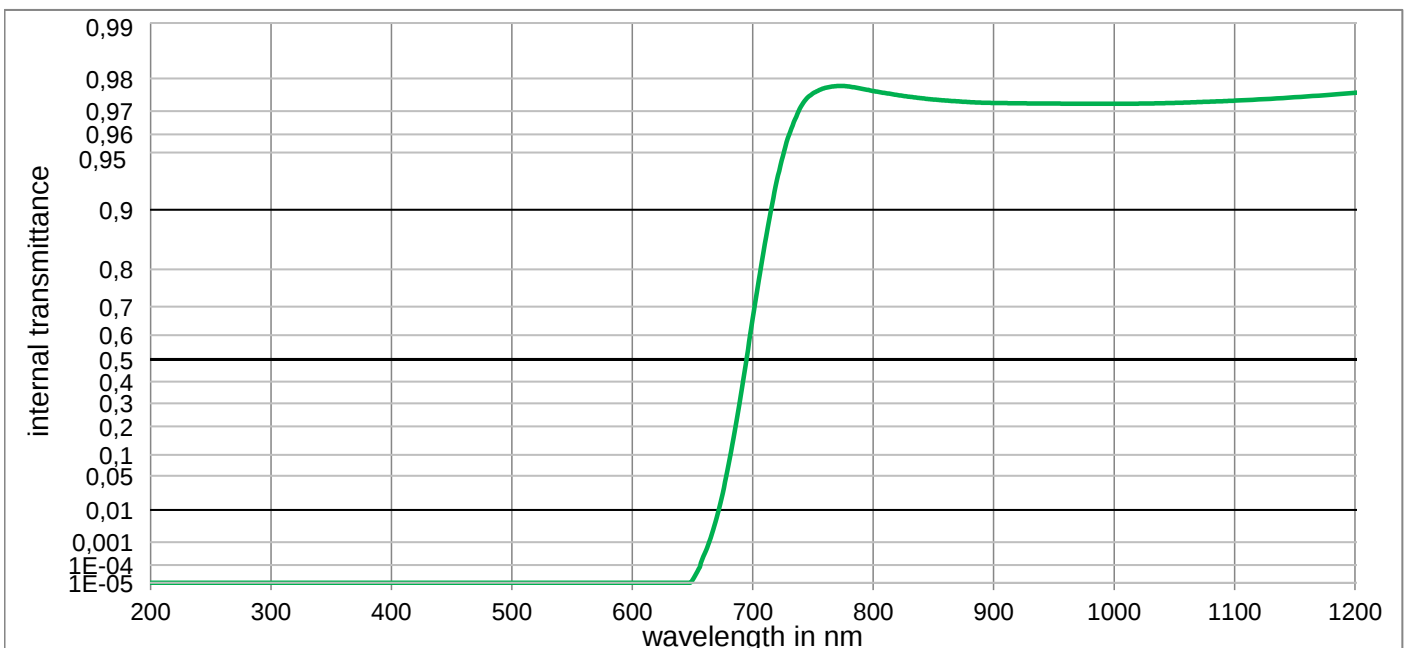

RG695

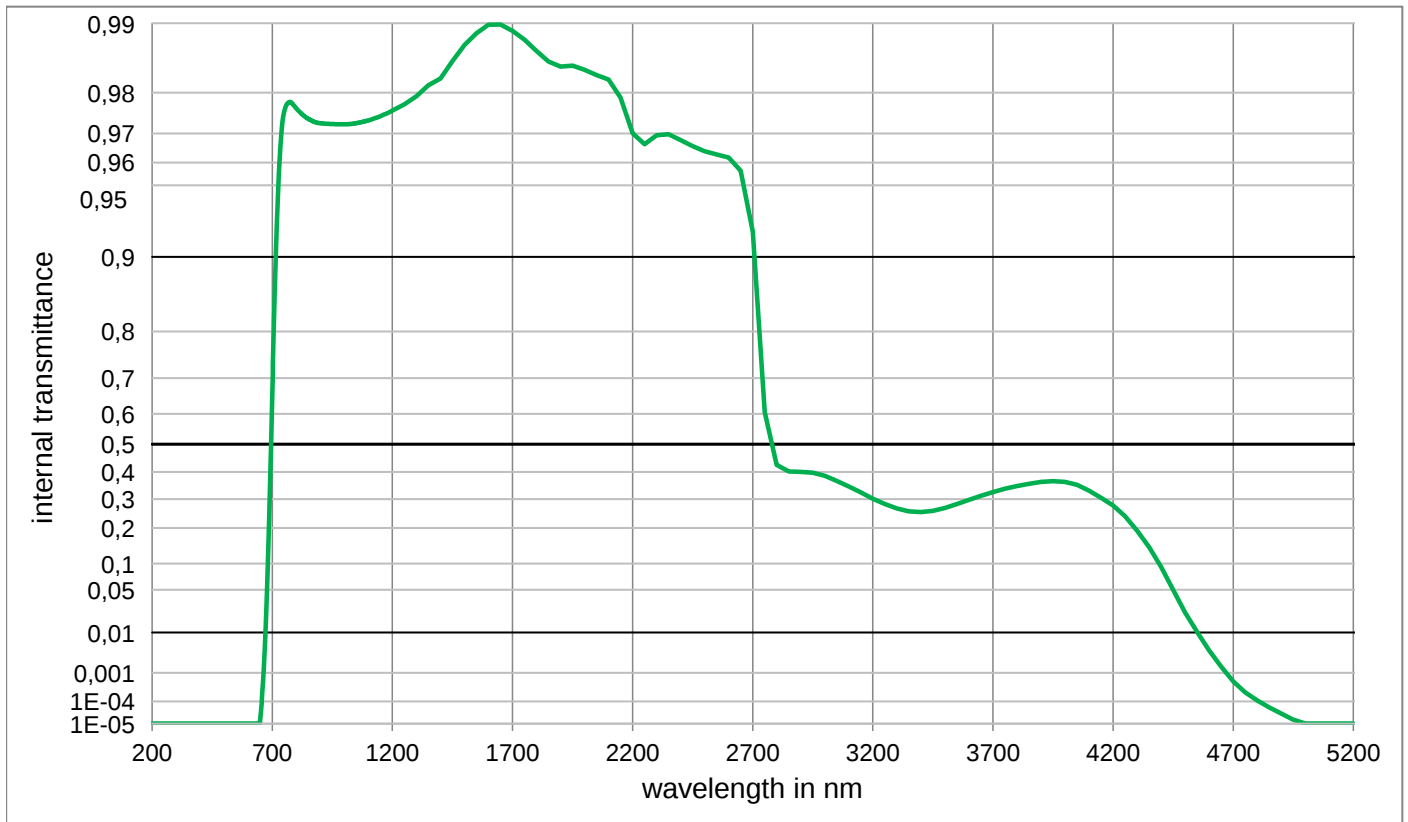
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,766E-01	1100	9,736E-01	2200	9,700E-01	3700	3,257E-01
210	< 1,0E-05	510	< 1,000E-05	810	9,760E-01	1110	9,738E-01	2250	9,666E-01	3750	3,377E-01
220	< 1,0E-05	520	< 1,000E-05	820	9,754E-01	1120	9,740E-01	2300	9,695E-01	3800	3,478E-01
230	< 1,0E-05	530	< 1,000E-05	830	9,749E-01	1130	9,743E-01	2350	9,698E-01	3850	3,564E-01
240	< 1,0E-05	540	< 1,000E-05	840	9,744E-01	1140	9,745E-01	2400	9,679E-01	3900	3,633E-01
250	< 1,0E-05	550	< 1,000E-05	850	9,740E-01	1150	9,747E-01	2450	9,660E-01	3950	3,659E-01
260	< 1,0E-05	560	< 1,000E-05	860	9,737E-01	1160	9,750E-01	2500	9,642E-01	4000	3,632E-01
270	< 1,0E-05	570	< 1,000E-05	870	9,734E-01	1170	9,752E-01	2550	9,631E-01	4050	3,523E-01
280	< 1,0E-05	580	< 1,000E-05	880	9,732E-01	1180	9,755E-01	2600	9,619E-01	4100	3,308E-01
290	< 1,0E-05	590	< 1,000E-05	890	9,730E-01	1190	9,758E-01	2650	9,567E-01	4150	3,050E-01
300	< 1,0E-05	600	< 1,000E-05	900	9,729E-01	1200	9,761E-01	2700	9,214E-01	4200	2,770E-01
310	< 1,0E-05	610	< 1,000E-05	910	9,728E-01	1250	9,775E-01	2750	6,057E-01	4250	2,394E-01
320	< 1,000E-05	620	< 1,000E-05	920	9,728E-01	1300	9,793E-01	2800	4,261E-01	4300	1,911E-01
330	< 1,000E-05	630	< 1,000E-05	930	9,727E-01	1350	9,814E-01	2850	4,014E-01	4350	1,424E-01
340	< 1,000E-05	640	< 1,000E-05	940	9,727E-01	1400	9,826E-01	2900	4,002E-01	4400	9,250E-02
350	< 1,000E-05	650	1,534E-05	950	9,727E-01	1450	9,854E-01	2950	3,970E-01	4450	4,970E-02
360	< 1,000E-05	660	3,350E-04	960	9,727E-01	1500	9,876E-01	3000	3,859E-01	4500	2,317E-02
370	< 1,000E-05	670	6,330E-03	970	9,726E-01	1550	9,889E-01	3050	3,665E-01	4550	1,037E-02
380	< 1,000E-05	680	7,498E-02	980	9,726E-01	1600	9,899E-01	3100	3,462E-01	4600	4,025E-03
390	< 1,000E-05	690	3,367E-01	990	9,726E-01	1650	9,899E-01	3150	3,243E-01	4650	1,530E-03
400	< 1,000E-05	700	6,612E-01	1000	9,726E-01	1700	9,892E-01	3200	3,018E-01	4700	5,346E-04
410	< 1,000E-05	710	8,508E-01	1010	9,726E-01	1750	9,882E-01	3250	2,824E-01	4750	2,234E-04
420	< 1,000E-05	720	9,295E-01	1020	9,727E-01	1800	9,868E-01	3300	2,667E-01	4800	1,104E-04
430	< 1,000E-05	730	9,596E-01	1030	9,727E-01	1850	9,853E-01	3350	2,563E-01	4850	5,636E-05
440	< 1,000E-05	740	9,716E-01	1040	9,728E-01	1900	9,846E-01	3400	2,535E-01	4900	3,062E-05
450	< 1,000E-05	750	9,759E-01	1050	9,729E-01	1950	9,847E-01	3450	2,581E-01	4950	1,570E-05
460	< 1,000E-05	760	9,775E-01	1060	9,730E-01	2000	9,841E-01	3500	2,681E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,780E-01	1070	9,732E-01	2050	9,832E-01	3550	2,819E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,779E-01	1080	9,733E-01	2100	9,825E-01	3600	2,973E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,773E-01	1090	9,735E-01	2150	9,790E-01	3650	3,121E-01	5150	< 1,000E-05

RG715

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,914$	$d = 3,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 3 mm)	Density	x
$\lambda_{i0,5} = 715 \text{ nm} \pm 9 \text{ nm}$	$\rho = 2,76 \text{ g/cm}^3$	y
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 620 \text{ nm}$	Knoop hardness	Y
$\lambda_p (\tau_{i,L} = 0,96) = 810 \text{ nm}$	$HK_{[0.1/20]} = 545$	λ_d
		P_e
		Illuminant A
	Thermal properties	x
	Transformation temperature	y
	$T_g = 532 \text{ }^\circ\text{C}$	Y
	Thermal expansion in $10^{-6}/\text{K}$	λ_d
Refractive indices	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,1$	P_e
$n_d (587,6 \text{ nm}) = 1,54$	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,4$	
$n_s (852 \text{ nm}) = 1,53$	Temperature coefficient	
$n_t (1014 \text{ nm}) = 1,53$	$Tk = 0,18 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Notes
valid from 440 nm to 1550 nm	Chemical resistance	
$B_1 = 0,8330$	FR class = 0	Stricking glass
$B_2 = 0,4883$	SR class = 1	Longpass filter
$B_3 = 6,5998$	AR class = 1	
$C_1 = 1,082\text{E-}02 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,1301\text{E-}02 \text{ } \mu\text{m}^2$	Resistant glass	
$C_3 = 855,262 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	ISO 23364:2021
Internal quality		Disclaimer
Bubble class 3		All data without tolerances are to be understood to be reference values.

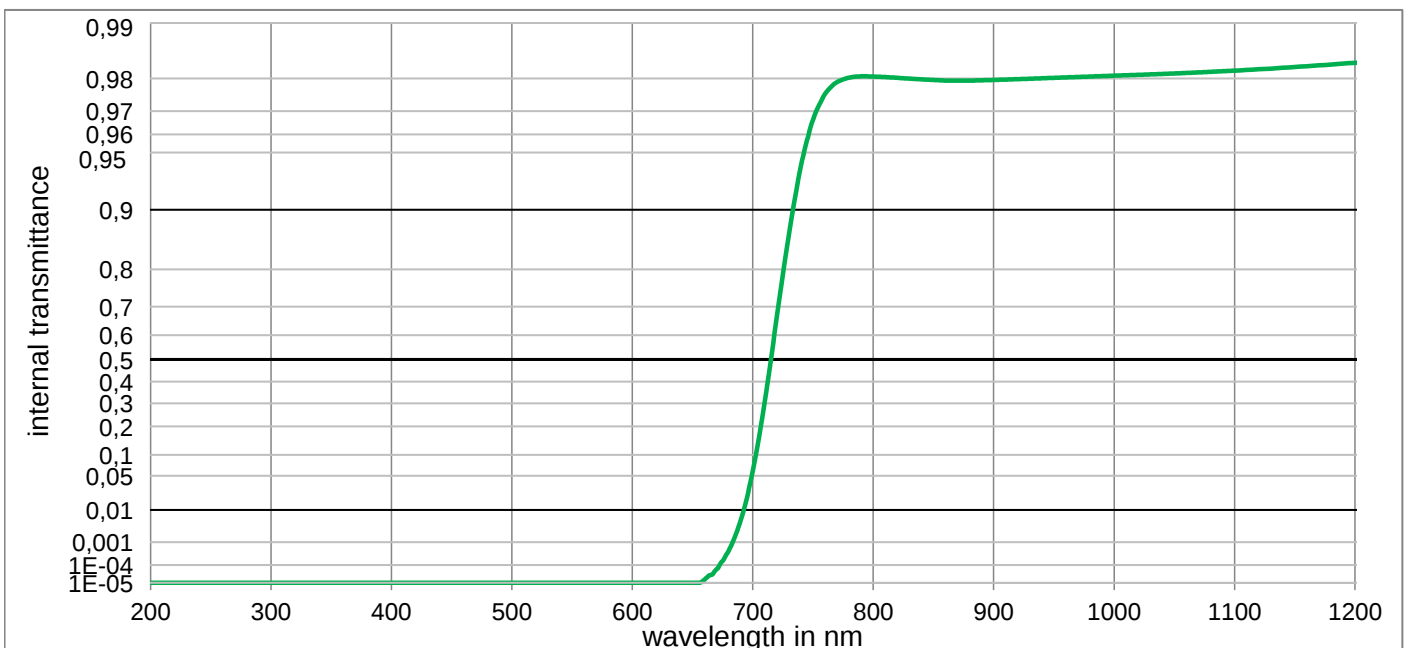


RG715

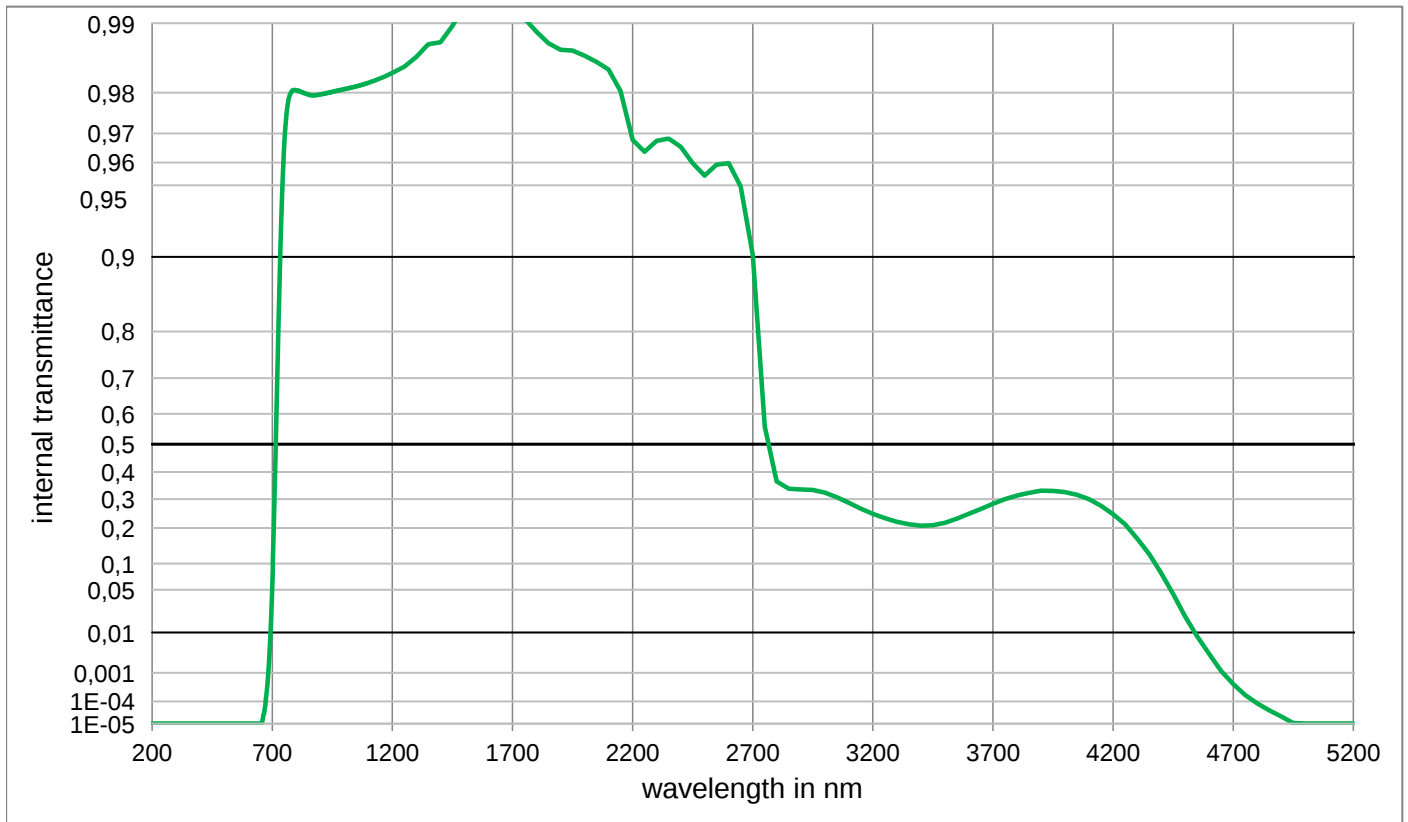Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	9,805E-01	1100	9,819E-01	2200	9,680E-01	3700	2,827E-01
210	< 1,0E-05	510	< 1,000E-05	810	9,804E-01	1110	9,820E-01	2250	9,641E-01	3750	2,995E-01
220	< 1,0E-05	520	< 1,000E-05	820	9,802E-01	1120	9,822E-01	2300	9,678E-01	3800	3,127E-01
230	< 1,0E-05	530	< 1,000E-05	830	9,800E-01	1130	9,823E-01	2350	9,684E-01	3850	3,232E-01
240	< 1,0E-05	540	< 1,000E-05	840	9,798E-01	1140	9,825E-01	2400	9,658E-01	3900	3,305E-01
250	< 1,0E-05	550	< 1,000E-05	850	9,796E-01	1150	9,827E-01	2450	9,598E-01	3950	3,302E-01
260	< 1,0E-05	560	< 1,000E-05	860	9,795E-01	1160	9,828E-01	2500	9,545E-01	4000	3,252E-01
270	< 1,0E-05	570	< 1,000E-05	870	9,794E-01	1170	9,830E-01	2550	9,592E-01	4050	3,154E-01
280	< 1,0E-05	580	< 1,000E-05	880	9,795E-01	1180	9,832E-01	2600	9,597E-01	4100	2,993E-01
290	< 1,0E-05	590	< 1,000E-05	890	9,795E-01	1190	9,834E-01	2650	9,495E-01	4150	2,758E-01
300	< 1,0E-05	600	< 1,000E-05	900	9,796E-01	1200	9,836E-01	2700	9,017E-01	4200	2,464E-01
310	< 1,0E-05	610	< 1,000E-05	910	9,797E-01	1250	9,846E-01	2750	5,597E-01	4250	2,120E-01
320	< 1,000E-05	620	< 1,000E-05	920	9,798E-01	1300	9,860E-01	2800	3,653E-01	4300	1,666E-01
330	< 1,000E-05	630	< 1,000E-05	930	9,799E-01	1350	9,877E-01	2850	3,378E-01	4350	1,238E-01
340	< 1,000E-05	640	< 1,000E-05	940	9,801E-01	1400	9,879E-01	2900	3,356E-01	4400	7,960E-02
350	< 1,000E-05	650	< 1,000E-05	950	9,802E-01	1450	9,897E-01	2950	3,336E-01	4450	4,376E-02
360	< 1,000E-05	660	1,589E-05	960	9,803E-01	1500	9,917E-01	3000	3,236E-01	4500	1,980E-02
370	< 1,000E-05	670	6,257E-05	970	9,804E-01	1550	9,927E-01	3050	3,067E-01	4550	8,430E-03
380	< 1,000E-05	680	4,487E-04	980	9,805E-01	1600	9,932E-01	3100	2,864E-01	4600	3,292E-03
390	< 1,000E-05	690	5,351E-03	990	9,806E-01	1650	9,929E-01	3150	2,660E-01	4650	1,132E-03
400	< 1,000E-05	700	5,900E-02	1000	9,807E-01	1700	9,919E-01	3200	2,477E-01	4700	4,375E-04
410	< 1,000E-05	710	3,110E-01	1010	9,808E-01	1750	9,905E-01	3250	2,325E-01	4750	1,791E-04
420	< 1,000E-05	720	6,665E-01	1020	9,809E-01	1800	9,891E-01	3300	2,202E-01	4800	8,337E-05
430	< 1,000E-05	730	8,663E-01	1030	9,810E-01	1850	9,878E-01	3350	2,120E-01	4850	4,236E-05
440	< 1,000E-05	740	9,410E-01	1040	9,811E-01	1900	9,869E-01	3400	2,072E-01	4900	2,218E-05
450	< 1,000E-05	750	9,666E-01	1050	9,812E-01	1950	9,869E-01	3450	2,093E-01	4950	1,076E-05
460	< 1,000E-05	760	9,757E-01	1060	9,813E-01	2000	9,862E-01	3500	2,171E-01	5000	< 1,000E-05
470	< 1,000E-05	770	9,791E-01	1070	9,815E-01	2050	9,853E-01	3550	2,313E-01	5050	< 1,000E-05
480	< 1,000E-05	780	9,802E-01	1080	9,816E-01	2100	9,841E-01	3600	2,476E-01	5100	< 1,000E-05
490	< 1,000E-05	790	9,805E-01	1090	9,817E-01	2150	9,803E-01	3650	2,649E-01	5150	< 1,000E-05

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,920$	$d = 3,00 \text{ mm}$	
Spectral values guaranteed	Density	Illuminant D65
$\tau_i (720 \text{ nm}) \leq 0,45$	$\rho = 2,58 \text{ g/cm}^3$	x
$\tau_i (800 \text{ nm}) \geq 0,92$	Knoop hardness	y
$\tau_i (1060 \text{ nm}) \leq 0,4$	$HK[0.1/20] = 459$	Y
		λ_d
		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	
$n_F (486 \text{ nm}) = 1,521$	Transformation temperature	
$n_e (546 \text{ nm}) = 1,517$	$T_g = 519 \text{ }^\circ\text{C}$	
$n_d (587,6 \text{ nm}) = 1,515$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 7,9$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 9,0$	
Sellmeier coefficients	Temperature coefficient	
valid from 440 nm to 1550 nm	$Tk = 0,06 \text{ nm/K}$	
$B_1 = 0,6332$	Chemical properties	
$B_2 = 0,6287$	Chemical resistance	
$B_3 = 64,3526$	FR class = 0	
$C_1 = 9,656\text{E-}03 \text{ } \mu\text{m}^2$	SR class = 1	
$C_2 = 9,6564\text{E-}03 \text{ } \mu\text{m}^2$	AR class = 1	
$C_3 = 7257,357 \text{ } \mu\text{m}^2$	Resistance against humidity	
Internal quality	Robust glass	
Bubble class 3	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
		Notes
		Bandpass filter / Longpass filter
		ISO 23364:2021
		Disclaimer
		All data without tolerances are to be understood to be reference values.

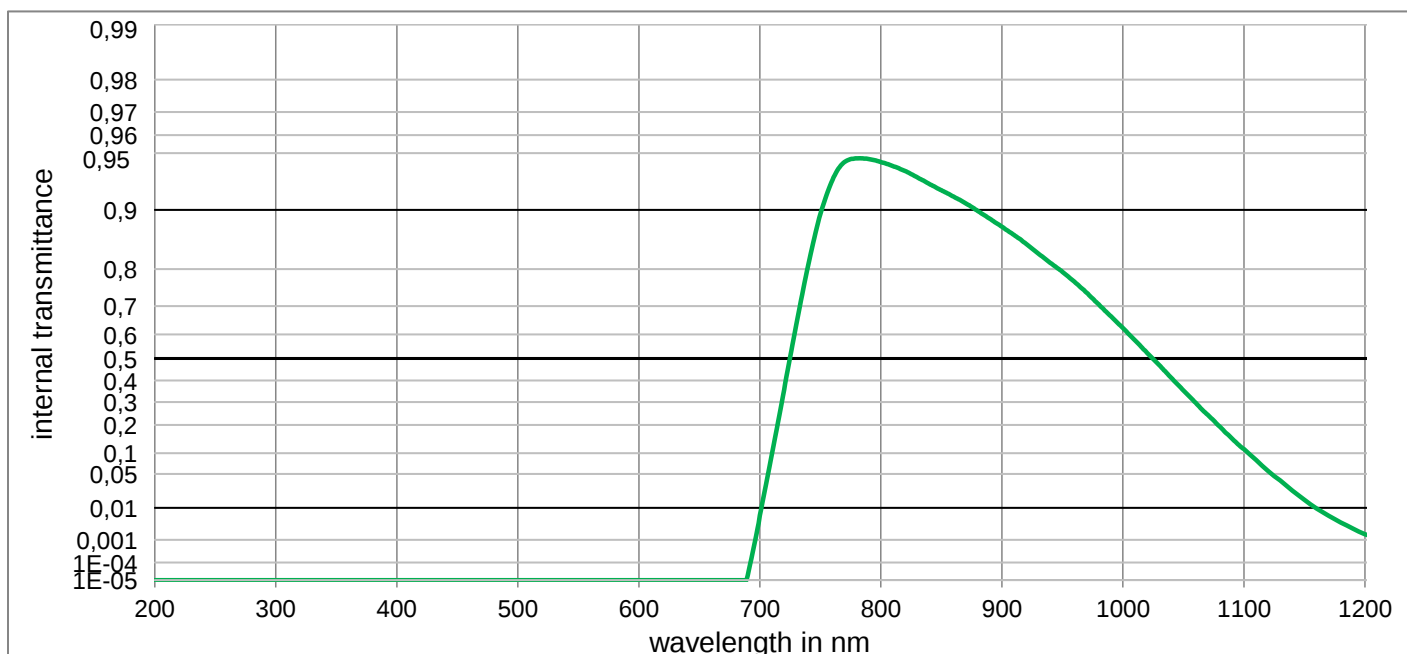

RG9

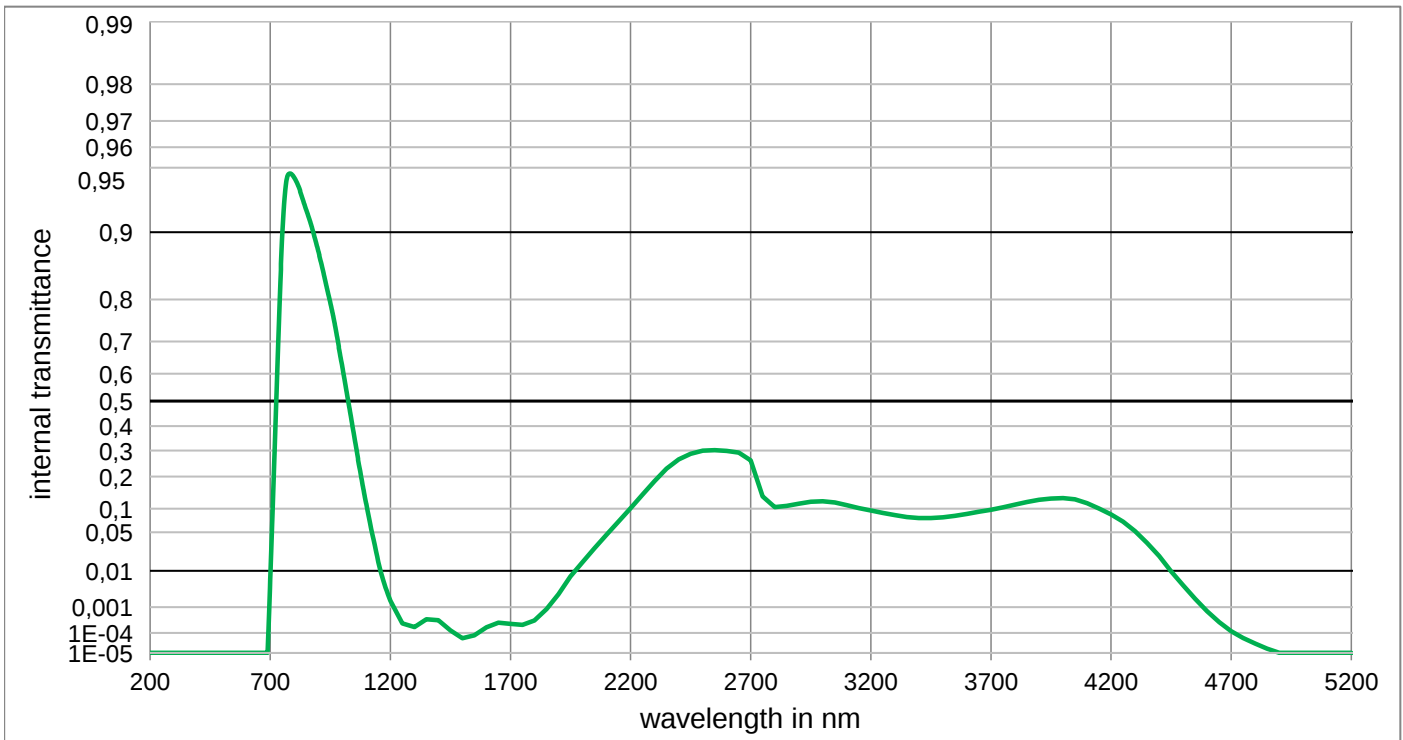
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	< 1,000E-05	800	9,442E-01	1100	1,124E-01	2200	1,008E-01	3700	9,734E-02
210	< 1,000E-05	510	< 1,000E-05	810	9,414E-01	1110	8,093E-02	2250	1,400E-01	3750	1,032E-01
220	< 1,000E-05	520	< 1,000E-05	820	9,377E-01	1120	5,559E-02	2300	1,844E-01	3800	1,105E-01
230	< 1,000E-05	530	< 1,000E-05	830	9,327E-01	1130	3,853E-02	2350	2,288E-01	3850	1,182E-01
240	< 1,000E-05	540	< 1,000E-05	840	9,271E-01	1140	2,454E-02	2400	2,643E-01	3900	1,239E-01
250	< 1,000E-05	550	< 1,000E-05	850	9,212E-01	1150	1,553E-02	2450	2,870E-01	3950	1,281E-01
260	< 1,000E-05	560	< 1,000E-05	860	9,148E-01	1160	9,600E-03	2500	2,997E-01	4000	1,292E-01
270	< 1,000E-05	570	< 1,000E-05	870	9,076E-01	1170	6,124E-03	2550	3,020E-01	4050	1,255E-01
280	< 1,000E-05	580	< 1,000E-05	880	8,989E-01	1180	3,890E-03	2600	2,991E-01	4100	1,144E-01
290	< 1,000E-05	590	< 1,000E-05	890	8,889E-01	1190	2,500E-03	2650	2,922E-01	4150	1,006E-01
300	< 1,000E-05	600	< 1,000E-05	900	8,776E-01	1200	1,611E-03	2700	2,612E-01	4200	8,570E-02
310	< 1,000E-05	610	< 1,000E-05	910	8,651E-01	1250	2,518E-04	2750	1,342E-01	4250	6,981E-02
320	< 1,000E-05	620	< 1,000E-05	920	8,505E-01	1300	1,782E-04	2800	1,042E-01	4300	5,190E-02
330	< 1,000E-05	630	< 1,000E-05	930	8,328E-01	1350	3,698E-04	2850	1,074E-01	4350	3,430E-02
340	< 1,000E-05	640	< 1,000E-05	940	8,137E-01	1400	3,388E-04	2900	1,136E-01	4400	2,019E-02
350	< 1,000E-05	650	< 1,000E-05	950	7,936E-01	1450	1,272E-04	2950	1,185E-01	4450	9,760E-03
360	< 1,000E-05	660	< 1,000E-05	960	7,697E-01	1500	5,674E-05	3000	1,203E-01	4500	4,410E-03
370	< 1,000E-05	670	< 1,000E-05	970	7,403E-01	1550	7,805E-05	3050	1,164E-01	4550	1,840E-03
380	< 1,000E-05	680	< 1,000E-05	980	7,052E-01	1600	1,738E-04	3100	1,094E-01	4600	7,240E-04
390	< 1,000E-05	690	1,925E-05	990	6,662E-01	1650	2,710E-04	3150	1,016E-01	4650	2,825E-04
400	< 1,000E-05	700	6,397E-03	1000	6,249E-01	1700	2,449E-04	3200	9,522E-02	4700	1,191E-04
410	< 1,000E-05	710	9,896E-02	1010	5,770E-01	1750	2,216E-04	3250	8,942E-02	4750	5,808E-05
420	< 1,000E-05	720	3,571E-01	1020	5,244E-01	1800	3,322E-04	3300	8,429E-02	4800	3,162E-05
430	< 1,000E-05	730	6,334E-01	1030	4,702E-01	1850	8,561E-04	3350	7,998E-02	4850	1,690E-05
440	< 1,000E-05	740	8,095E-01	1040	4,126E-01	1900	2,534E-03	3400	7,746E-02	4900	< 1,000E-05
450	< 1,000E-05	750	8,952E-01	1050	3,537E-01	1950	7,370E-03	3450	7,752E-02	4950	< 1,000E-05
460	< 1,000E-05	760	9,306E-01	1060	2,968E-01	2000	1,525E-02	3500	7,945E-02	5000	< 1,000E-05
470	< 1,000E-05	770	9,442E-01	1070	2,425E-01	2050	2,800E-02	3550	8,240E-02	5050	< 1,000E-05
480	< 1,000E-05	780	9,467E-01	1080	1,938E-01	2100	4,638E-02	3600	8,704E-02	5100	< 1,000E-05
490	< 1,000E-05	790	9,462E-01	1090	1,483E-01	2150	7,040E-02	3650	9,214E-02	5150	< 1,000E-05

RG780

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,908$	$d = 3,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 3 mm)	Density	x
$\lambda_{i0,5} = 780 \text{ nm} \pm 9 \text{ nm}$	$\rho = 2,94 \text{ g/cm}^3$	y
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 610 \text{ nm}$	Knoop hardness	Y
$\lambda_p (\tau_{i,L} = 0,97) = 900 \text{ nm}$	$HK_{[0.1/20]}$	λ_d
		P_e
		Illuminant A
	Thermal properties	x
	Transformation temperature	y
	$T_g = 552 \text{ }^\circ\text{C}$	Y
	Thermal expansion in $10^{-6}/\text{K}$	λ_d
Refractive indices	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 9,5$	P_e
$n_d (587,6 \text{ nm}) = 1,56$	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 10,5$	
$n_s (852 \text{ nm}) = 1,55$	Temperature coefficient	
$n_t (1014 \text{ nm}) = 1,55$	$Tk = 0,22 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Notes
valid from 440 nm to 1550 nm	Chemical resistance	Stricking glass
$B_1 = 0,4066$	FR class = 5	Longpass filter
$B_2 = 0,9852$	SR class = 53.4	
$B_3 = 0,3548$	AR class = 1.3	
$C_1 = 1,139\text{E-}02 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,2050\text{E-}02 \text{ } \mu\text{m}^2$	Robust glass	ISO 23364:2021
$C_3 = 55,081 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	Disclaimer
Internal quality		All data without tolerances are to be understood to be reference values.
Bubble class 3		

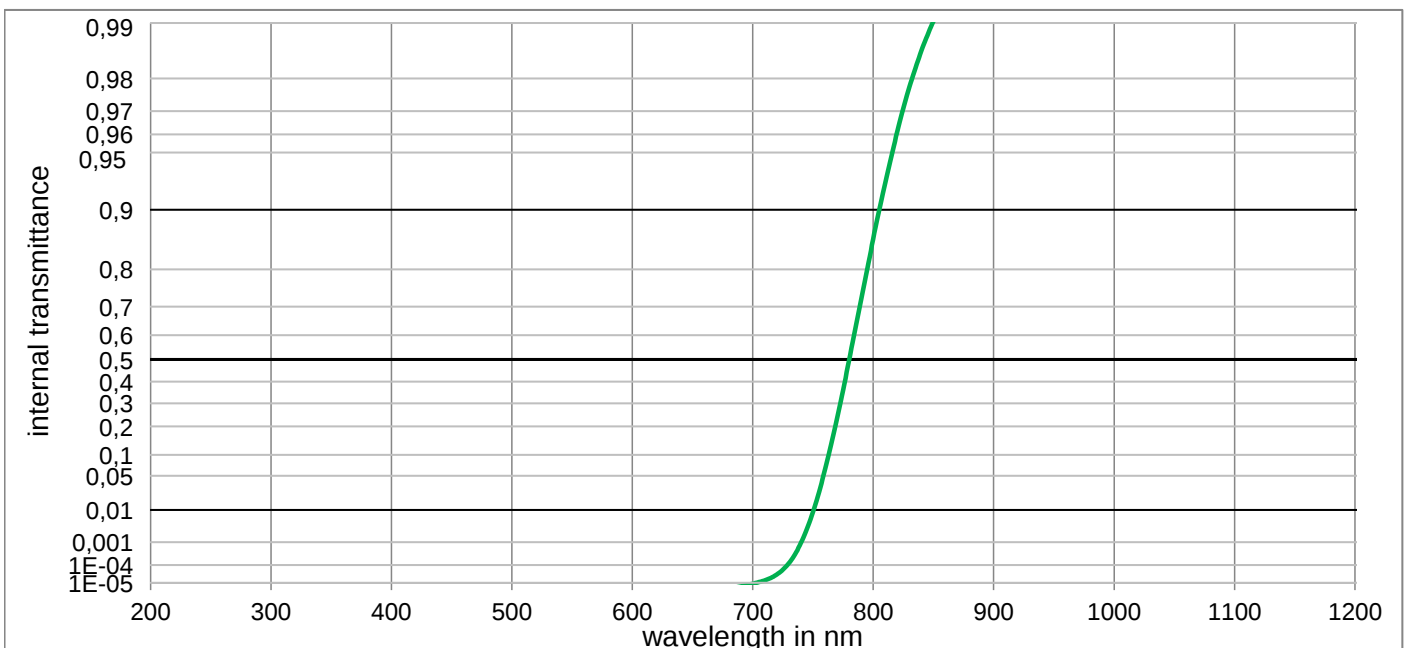

RG780

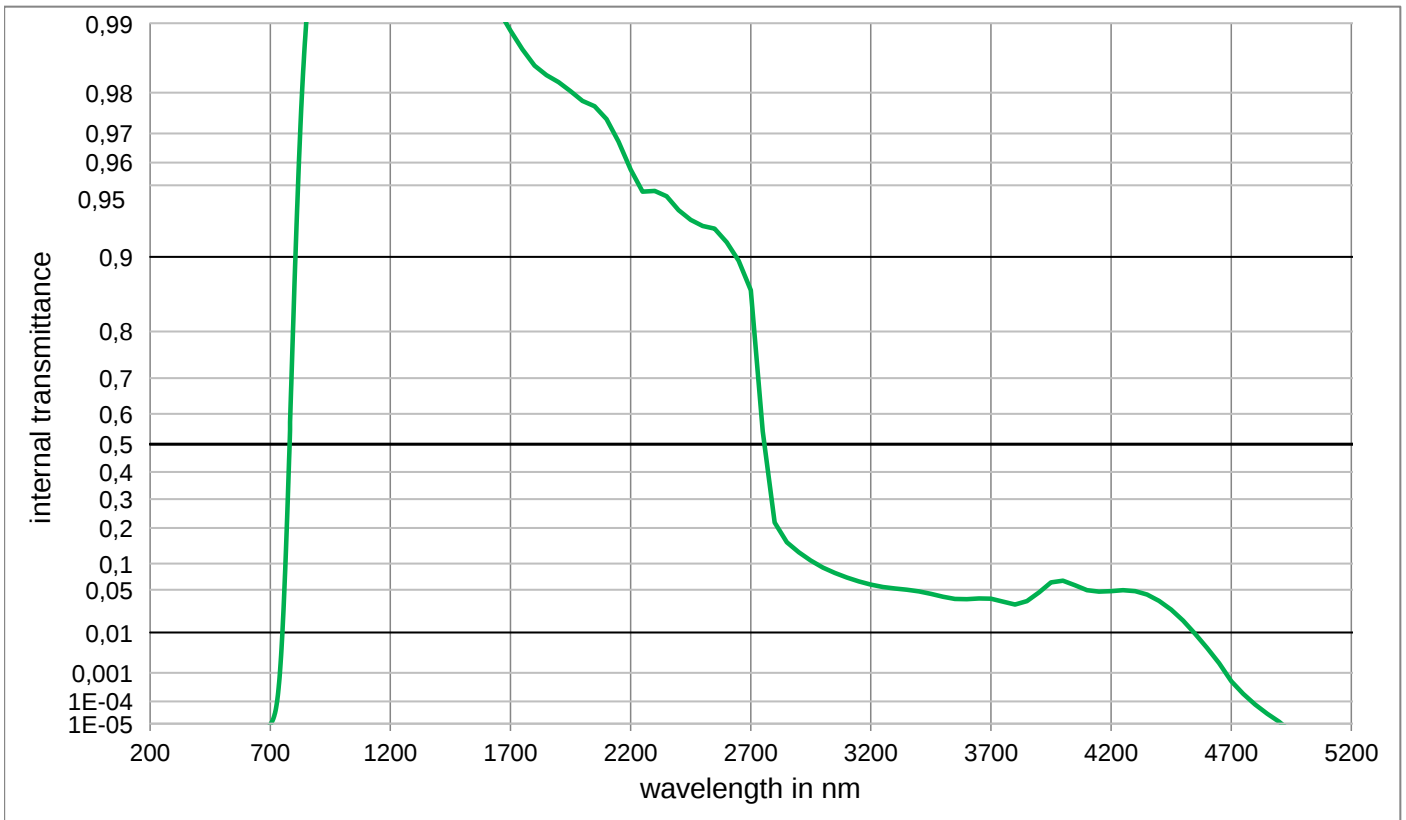
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	8,585E-01	1100	9,944E-01	2200	9,571E-01	3700	3,777E-02
210	< 1,0E-05	510	< 1,000E-05	810	9,277E-01	1110	9,944E-01	2250	9,468E-01	3750	3,428E-02
220	< 1,0E-05	520	< 1,000E-05	820	9,614E-01	1120	9,944E-01	2300	9,472E-01	3800	3,105E-02
230	< 1,0E-05	530	< 1,000E-05	830	9,778E-01	1130	9,945E-01	2350	9,443E-01	3850	3,484E-02
240	< 1,0E-05	540	< 1,000E-05	840	9,858E-01	1140	9,945E-01	2400	9,363E-01	3900	4,632E-02
250	< 1,0E-05	550	< 1,000E-05	850	9,902E-01	1150	9,945E-01	2450	9,300E-01	3950	6,186E-02
260	< 1,0E-05	560	< 1,000E-05	860	9,910E-01	1160	9,945E-01	2500	9,257E-01	4000	6,493E-02
270	< 1,0E-05	570	< 1,000E-05	870	9,919E-01	1170	9,945E-01	2550	9,238E-01	4050	5,684E-02
280	< 1,0E-05	580	< 1,000E-05	880	9,924E-01	1180	9,946E-01	2600	9,131E-01	4100	4,949E-02
290	< 1,0E-05	590	< 1,000E-05	890	9,927E-01	1190	9,946E-01	2650	8,962E-01	4150	4,707E-02
300	< 1,0E-05	600	< 1,000E-05	900	9,929E-01	1200	9,947E-01	2700	8,629E-01	4200	4,802E-02
310	< 1,0E-05	610	< 1,000E-05	910	9,930E-01	1250	9,948E-01	2750	5,436E-01	4250	4,921E-02
320	< 1,000E-05	620	< 1,000E-05	920	9,931E-01	1300	9,950E-01	2800	2,180E-01	4300	4,794E-02
330	< 1,000E-05	630	< 1,000E-05	930	9,931E-01	1350	9,951E-01	2850	1,559E-01	4350	4,304E-02
340	< 1,000E-05	640	< 1,000E-05	940	9,931E-01	1400	9,930E-01	2900	1,279E-01	4400	3,517E-02
350	< 1,000E-05	650	< 1,000E-05	950	9,930E-01	1450	9,933E-01	2950	1,071E-01	4450	2,583E-02
360	< 1,000E-05	660	< 1,000E-05	960	9,930E-01	1500	9,942E-01	3000	9,129E-02	4500	1,685E-02
370	< 1,000E-05	670	< 1,000E-05	970	9,933E-01	1550	9,938E-01	3050	7,961E-02	4550	9,430E-03
380	< 1,000E-05	680	< 1,000E-05	980	9,937E-01	1600	9,927E-01	3100	7,064E-02	4600	4,586E-03
390	< 1,000E-05	690	< 1,000E-05	990	9,939E-01	1650	9,912E-01	3150	6,354E-02	4650	1,887E-03
400	< 1,000E-05	700	< 1,000E-05	1000	9,940E-01	1700	9,892E-01	3200	5,827E-02	4700	5,470E-04
410	< 1,000E-05	710	1,422E-05	1010	9,941E-01	1750	9,870E-01	3250	5,439E-02	4750	1,991E-04
420	< 1,000E-05	720	3,155E-05	1020	9,942E-01	1800	9,847E-01	3300	5,195E-02	4800	7,430E-05
430	< 1,000E-05	730	1,255E-04	1030	9,942E-01	1850	9,832E-01	3350	5,008E-02	4850	2,958E-05
440	< 1,000E-05	740	9,334E-04	1040	9,942E-01	1900	9,820E-01	3400	4,755E-02	4900	1,222E-05
450	< 1,000E-05	750	8,941E-03	1050	9,943E-01	1950	9,803E-01	3450	4,414E-02	4950	< 1,000E-05
460	< 1,000E-05	760	6,268E-02	1060	9,943E-01	2000	9,783E-01	3500	4,020E-02	5000	< 1,000E-05
470	< 1,000E-05	770	2,345E-01	1070	9,943E-01	2050	9,771E-01	3550	3,737E-02	5050	< 1,000E-05
480	< 1,000E-05	780	4,959E-01	1080	9,943E-01	2100	9,739E-01	3600	3,722E-02	5100	< 1,000E-05
490	< 1,000E-05	790	7,222E-01	1090	9,944E-01	2150	9,675E-01	3650	3,809E-02	5150	< 1,000E-05

RG830

Optical properties		Mechanical properties		Colorimetric properties	
Reflection factor		Reference thickness		1 mm 2 mm 3 mm	
P _d = 0,909		d = 3,00 mm		Illuminant D65	x
Spectral values guaranteed (d = 3 mm)		Density			y
λ _{i 0,5} = 830 nm ± 9 nm		ρ = 2,94 g/cm ³			Y
λ _s (τ _{i,U} = 1E-05) = 670 nm		Knoop hardness			λ _d
λ _p (τ _{i,L} = 0,97) = 950 nm		HK _[0.1/20] = 436			P _e
				Illuminant A	x
					y
					Y
					λ _d
					P _e
Refractive indices		Thermal properties		Notes	
n _d (587,6 nm) = 1,56		Transformation temperature			
n _s (852 nm) = 1,55		Tg = 554 °C			
n _t (1014 nm) = 1,55		Thermal expansion in 10 ⁻⁶ /K			
		α (-30°C/+70°C) = 9,5			
		α (20°C/300°C) = 10,5			
		Temperature coefficient		Stricking glass	
Sellmeier coefficients		Tk = 0,23 nm/K		Longpass filter	
on request		Chemical properties			
		Chemical resistance			
		FR class = 5			
		SR class = 53.4			
		AR class = 1.3			
		Resistance against humidity		ISO 23364:2021	
		Robust glass		Disclaimer	
Internal quality		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		All data without tolerances are to be understood to be reference values.	
Bubble class 3					

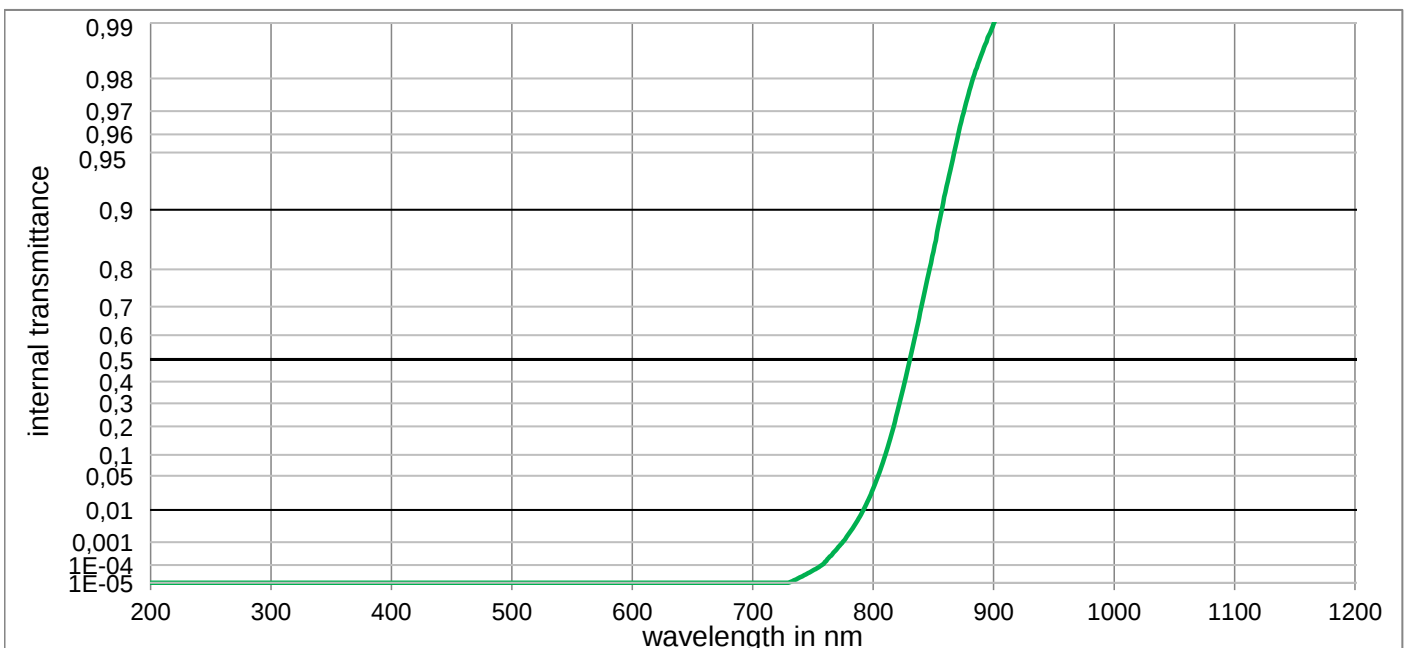

RG830

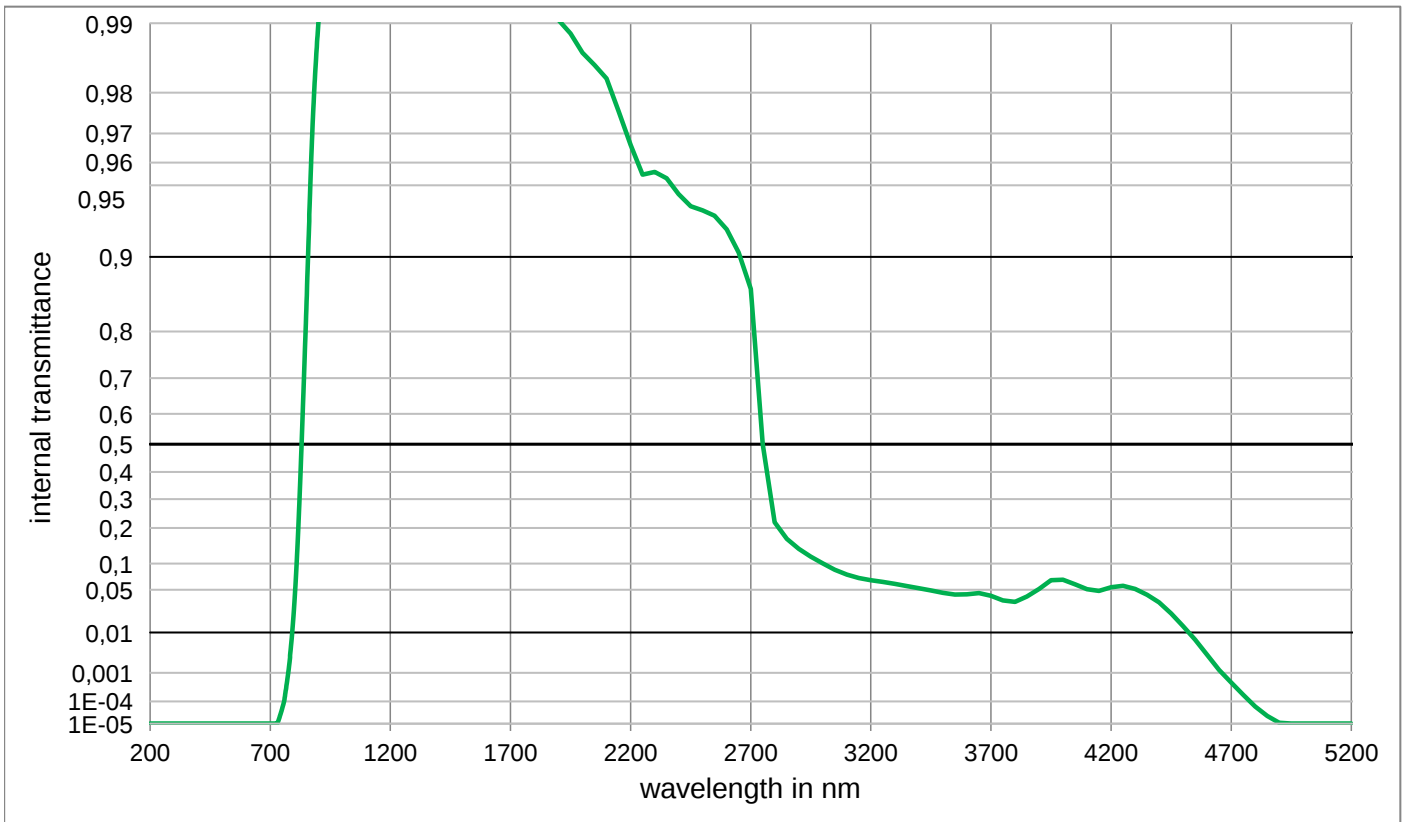
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	2,968E-02	1100	9,971E-01	2200	9,664E-01	3700	4,138E-02
210	< 1,0E-05	510	< 1,000E-05	810	9,936E-02	1110	9,971E-01	2250	9,550E-01	3750	3,550E-02
220	< 1,0E-05	520	< 1,000E-05	820	2,604E-01	1120	9,972E-01	2300	9,562E-01	3800	3,400E-02
230	< 1,0E-05	530	< 1,000E-05	830	4,901E-01	1130	9,973E-01	2350	9,533E-01	3850	4,058E-02
240	< 1,0E-05	540	< 1,000E-05	840	6,987E-01	1140	9,973E-01	2400	9,455E-01	3900	5,135E-02
250	< 1,0E-05	550	< 1,000E-05	850	8,366E-01	1150	9,974E-01	2450	9,387E-01	3950	6,590E-02
260	< 1,0E-05	560	< 1,000E-05	860	9,189E-01	1160	9,975E-01	2500	9,361E-01	4000	6,660E-02
270	< 1,0E-05	570	< 1,000E-05	870	9,582E-01	1170	9,976E-01	2550	9,326E-01	4050	5,851E-02
280	< 1,0E-05	580	< 1,000E-05	880	9,768E-01	1180	9,976E-01	2600	9,232E-01	4100	5,083E-02
290	< 1,0E-05	590	< 1,000E-05	890	9,852E-01	1190	9,977E-01	2650	9,041E-01	4150	4,831E-02
300	< 1,0E-05	600	< 1,000E-05	900	9,899E-01	1200	9,978E-01	2700	8,646E-01	4200	5,371E-02
310	< 1,0E-05	610	< 1,000E-05	910	9,927E-01	1250	9,983E-01	2750	5,000E-01	4250	5,637E-02
320	< 1,000E-05	620	< 1,000E-05	920	9,943E-01	1300	9,989E-01	2800	2,183E-01	4300	5,122E-02
330	< 1,000E-05	630	< 1,000E-05	930	9,951E-01	1350	9,997E-01	2850	1,663E-01	4350	4,271E-02
340	< 1,000E-05	640	< 1,000E-05	940	9,954E-01	1400	9,985E-01	2900	1,371E-01	4400	3,328E-02
350	< 1,000E-05	650	< 1,000E-05	950	9,956E-01	1450	9,987E-01	2950	1,170E-01	4450	2,234E-02
360	< 1,000E-05	660	< 1,000E-05	960	9,958E-01	1500	9,998E-01	3000	1,002E-01	4500	1,333E-02
370	< 1,000E-05	670	< 1,000E-05	970	9,959E-01	1550	9,999E-01	3050	8,620E-02	4550	7,120E-03
380	< 1,000E-05	680	< 1,000E-05	980	9,960E-01	1600	9,997E-01	3100	7,650E-02	4600	3,120E-03
390	< 1,000E-05	690	< 1,000E-05	990	9,961E-01	1650	9,984E-01	3150	6,962E-02	4650	1,208E-03
400	< 1,000E-05	700	< 1,000E-05	1000	9,962E-01	1700	9,965E-01	3200	6,599E-02	4700	4,875E-04
410	< 1,000E-05	710	< 1,000E-05	1010	9,963E-01	1750	9,942E-01	3250	6,294E-02	4750	1,828E-04
420	< 1,000E-05	720	< 1,000E-05	1020	9,964E-01	1800	9,924E-01	3300	5,949E-02	4800	6,152E-05
430	< 1,000E-05	730	1,025E-05	1030	9,965E-01	1850	9,911E-01	3350	5,595E-02	4850	2,366E-05
440	< 1,000E-05	740	2,262E-05	1040	9,966E-01	1900	9,903E-01	3400	5,237E-02	4900	1,099E-05
450	< 1,000E-05	750	5,207E-05	1050	9,967E-01	1950	9,889E-01	3450	4,889E-02	4950	< 1,000E-05
460	< 1,000E-05	760	1,421E-04	1060	9,967E-01	2000	9,866E-01	3500	4,561E-02	5000	< 1,000E-05
470	< 1,000E-05	770	5,562E-04	1070	9,968E-01	2050	9,848E-01	3550	4,294E-02	5050	< 1,000E-05
480	< 1,000E-05	780	2,044E-03	1080	9,969E-01	2100	9,826E-01	3600	4,356E-02	5100	< 1,000E-05
490	< 1,000E-05	790	7,784E-03	1090	9,970E-01	2150	9,760E-01	3650	4,528E-02	5150	< 1,000E-05

RG850

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,909$	$d = 3,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 3 mm)	Density	x
$\lambda_{i0,5} = 850 \text{ nm} \pm 9 \text{ nm}$	$\rho = 2,93 \text{ g/cm}^3$	y
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 700 \text{ nm}$	Knoop hardness	Y
$\lambda_p (\tau_{i,L} = 0,90) = 950 \text{ nm}$	$HK_{[0.1/20]} = 441$	λ_d
$\lambda_p (\tau_{i,L} = 0,97) = 1200 \text{ nm}$		P_e
		Illuminant A
	Thermal properties	x
	Transformation temperature	y
	$T_g = 554 \text{ }^\circ\text{C}$	Y
	Thermal expansion in $10^{-6}/\text{K}$	λ_d
Refractive indices	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 9,4$	P_e
$n_d (587,6 \text{ nm}) = 1,56$	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 10,4$	
$n_s (852 \text{ nm}) = 1,55$	Temperature coefficient	
$n_t (1014 \text{ nm}) = 1,55$	$Tk = 0,24 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Notes
on request	Chemical resistance	Stricking glass
	FR class = 5	Longpass filter
	SR class = 53.4	
	AR class = 1.3	
	Resistance against humidity	
	Robust glass	ISO 23364:2021
Internal quality	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	Disclaimer
Bubble class 3		All data without tolerances are to be understood to be reference values.

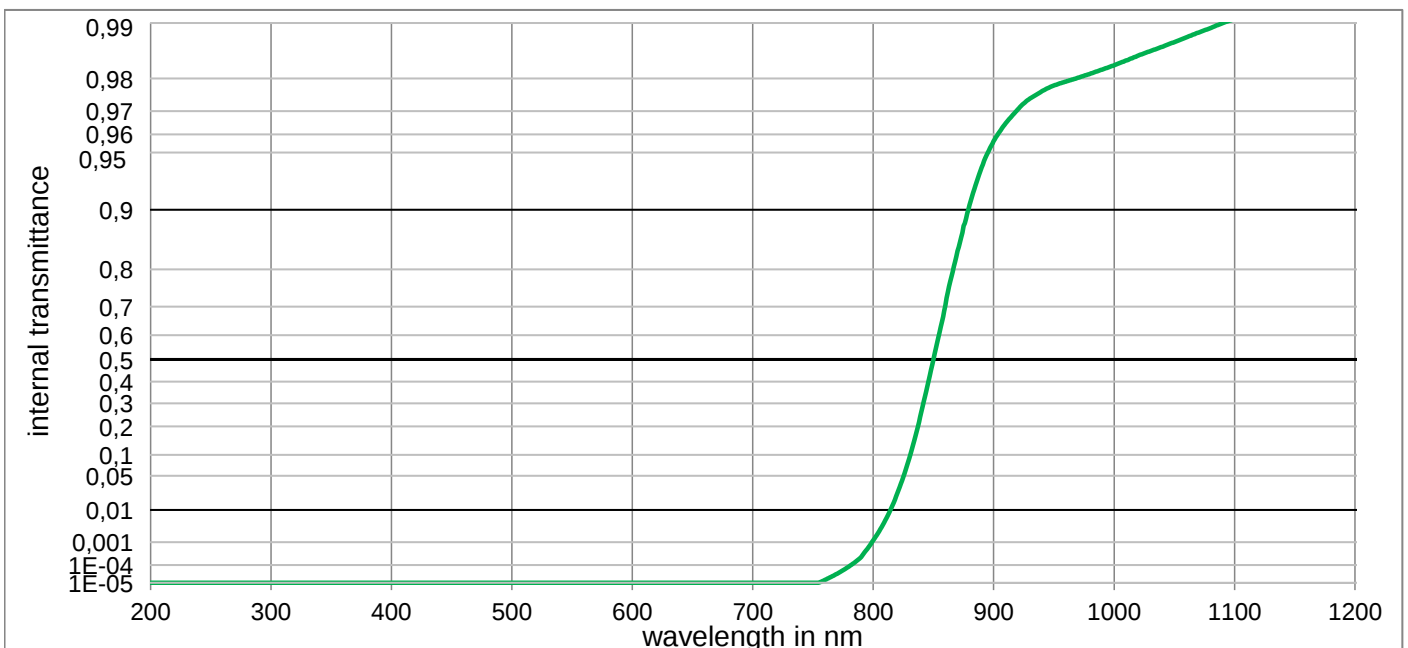


RG850

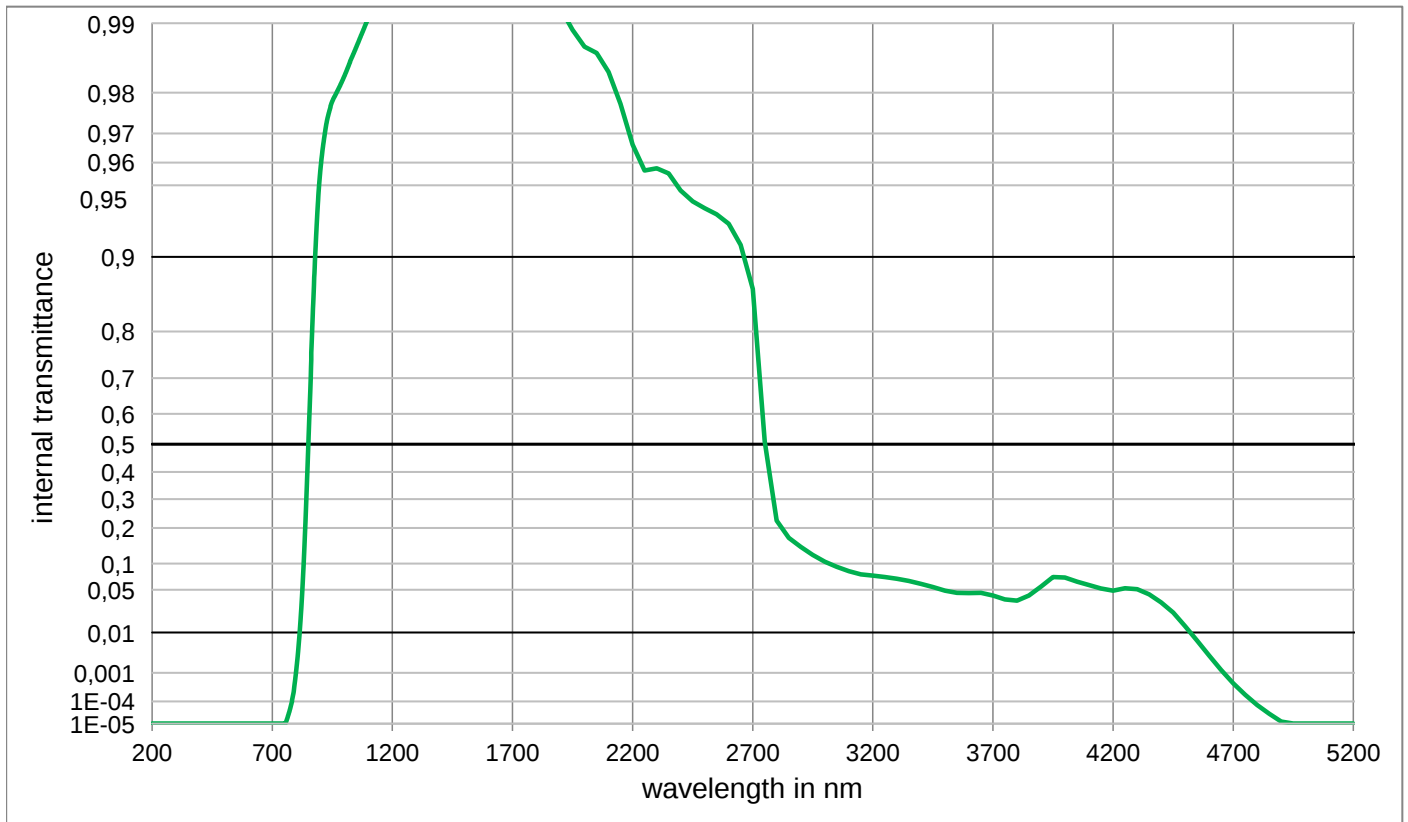Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	1,156E-03	1100	9,905E-01	2200	9,665E-01	3700	4,170E-02
210	< 1,0E-05	510	< 1,000E-05	810	5,250E-03	1110	9,909E-01	2250	9,567E-01	3750	3,687E-02
220	< 1,0E-05	520	< 1,000E-05	820	2,363E-02	1120	9,914E-01	2300	9,577E-01	3800	3,540E-02
230	< 1,0E-05	530	< 1,000E-05	830	9,140E-02	1130	9,918E-01	2350	9,555E-01	3850	4,188E-02
240	< 1,0E-05	540	< 1,000E-05	840	2,610E-01	1140	9,923E-01	2400	9,474E-01	3900	5,486E-02
250	< 1,0E-05	550	< 1,000E-05	850	5,003E-01	1150	9,927E-01	2450	9,414E-01	3950	7,151E-02
260	< 1,0E-05	560	< 1,000E-05	860	7,037E-01	1160	9,931E-01	2500	9,375E-01	4000	7,070E-02
270	< 1,0E-05	570	< 1,000E-05	870	8,376E-01	1170	9,935E-01	2550	9,336E-01	4050	6,328E-02
280	< 1,0E-05	580	< 1,000E-05	880	9,053E-01	1180	9,939E-01	2600	9,272E-01	4100	5,719E-02
290	< 1,0E-05	590	< 1,000E-05	890	9,399E-01	1190	9,943E-01	2650	9,108E-01	4150	5,179E-02
300	< 1,0E-05	600	< 1,000E-05	900	9,565E-01	1200	9,946E-01	2700	8,646E-01	4200	4,878E-02
310	< 1,0E-05	610	< 1,000E-05	910	9,651E-01	1250	9,960E-01	2750	5,095E-01	4250	5,219E-02
320	< 1,000E-05	620	< 1,000E-05	920	9,706E-01	1300	9,973E-01	2800	2,243E-01	4300	5,097E-02
330	< 1,000E-05	630	< 1,000E-05	930	9,743E-01	1350	9,984E-01	2850	1,689E-01	4350	4,352E-02
340	< 1,000E-05	640	< 1,000E-05	940	9,765E-01	1400	9,974E-01	2900	1,425E-01	4400	3,343E-02
350	< 1,000E-05	650	< 1,000E-05	950	9,782E-01	1450	9,984E-01	2950	1,212E-01	4450	2,305E-02
360	< 1,000E-05	660	< 1,000E-05	960	9,792E-01	1500	9,997E-01	3000	1,043E-01	4500	1,334E-02
370	< 1,000E-05	670	< 1,000E-05	970	9,802E-01	1550	9,999E-01	3050	9,268E-02	4550	6,780E-03
380	< 1,000E-05	680	< 1,000E-05	980	9,811E-01	1600	9,998E-01	3100	8,310E-02	4600	2,980E-03
390	< 1,000E-05	690	< 1,000E-05	990	9,821E-01	1650	9,986E-01	3150	7,685E-02	4650	1,211E-03
400	< 1,000E-05	700	< 1,000E-05	1000	9,830E-01	1700	9,968E-01	3200	7,425E-02	4700	4,656E-04
410	< 1,000E-05	710	< 1,000E-05	1010	9,840E-01	1750	9,950E-01	3250	7,161E-02	4750	1,803E-04
420	< 1,000E-05	720	< 1,000E-05	1020	9,850E-01	1800	9,933E-01	3300	6,837E-02	4800	7,194E-05
430	< 1,000E-05	730	< 1,000E-05	1030	9,858E-01	1850	9,922E-01	3350	6,445E-02	4850	2,958E-05
440	< 1,000E-05	740	< 1,000E-05	1040	9,865E-01	1900	9,914E-01	3400	5,946E-02	4900	1,282E-05
450	< 1,000E-05	750	< 1,000E-05	1050	9,873E-01	1950	9,893E-01	3450	5,405E-02	4950	< 1,000E-05
460	< 1,000E-05	760	1,507E-05	1060	9,880E-01	2000	9,874E-01	3500	4,881E-02	5000	< 1,000E-05
470	< 1,000E-05	770	3,444E-05	1070	9,887E-01	2050	9,865E-01	3550	4,544E-02	5050	< 1,000E-05
480	< 1,000E-05	780	8,542E-05	1080	9,894E-01	2100	9,837E-01	3600	4,510E-02	5100	< 1,000E-05
490	< 1,000E-05	790	2,412E-04	1090	9,900E-01	2150	9,776E-01	3650	4,534E-02	5150	< 1,000E-05

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,921$	$d = 4,00 \text{ mm}$	
Spectral values guaranteed	Density	Illuminant D65
$\tau_i (405 \text{ nm}) \leq 0,002$	$\rho = 2,54 \text{ g/cm}^3$	x
$\tau_i (490 \text{ nm}) \leq 0,08$	Knoop hardness	y
$\tau_i (645 \text{ nm}) \leq 0,002$	$HK[0.1/20] = 438$	Y
$\tau_i (905 \text{ nm}) \geq 0,97$		λ_d
		P_e
	Thermal properties	Illuminant A
	Transformation temperature	x
	$T_g = 481 \text{ }^\circ\text{C}$	y
	Thermal expansion in $10^{-6}/\text{K}$	Y
Refractive indices	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 8,7$	λ_d
$n_F (486 \text{ nm}) = 1,516$	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 10,0$	P_e
$n_e (546 \text{ nm}) = 1,512$		
$n_d (587,6 \text{ nm}) = 1,51$		
Sellmeier coefficients	Chemical properties	Notes
valid from 440 nm to 1550 nm	Chemical resistance	
$B_1 = 0,6150$	FR class = 0	
$B_2 = 0,6285$	SR class = 1.0	
$B_3 = 13,7990$	AR class = 1.0	
$C_1 = 1,035\text{E-}02 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,0302\text{E-}02 \text{ } \mu\text{m}^2$		
$C_3 = 1939,581 \text{ } \mu\text{m}^2$		
Internal quality		
Bubble class -		
		Bandpass filter / Longpass filter
		ISO 23364:2021
		Disclaimer
		All data without tolerances are to be understood to be reference values.

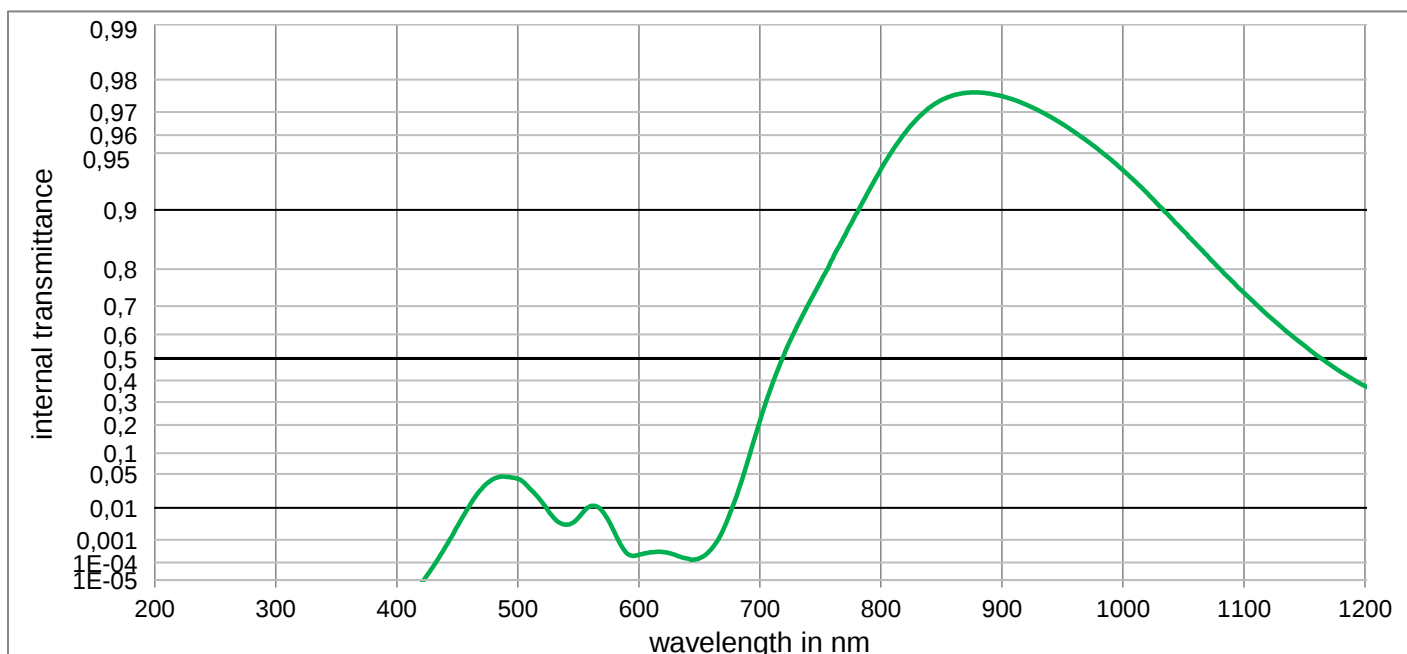

RG905

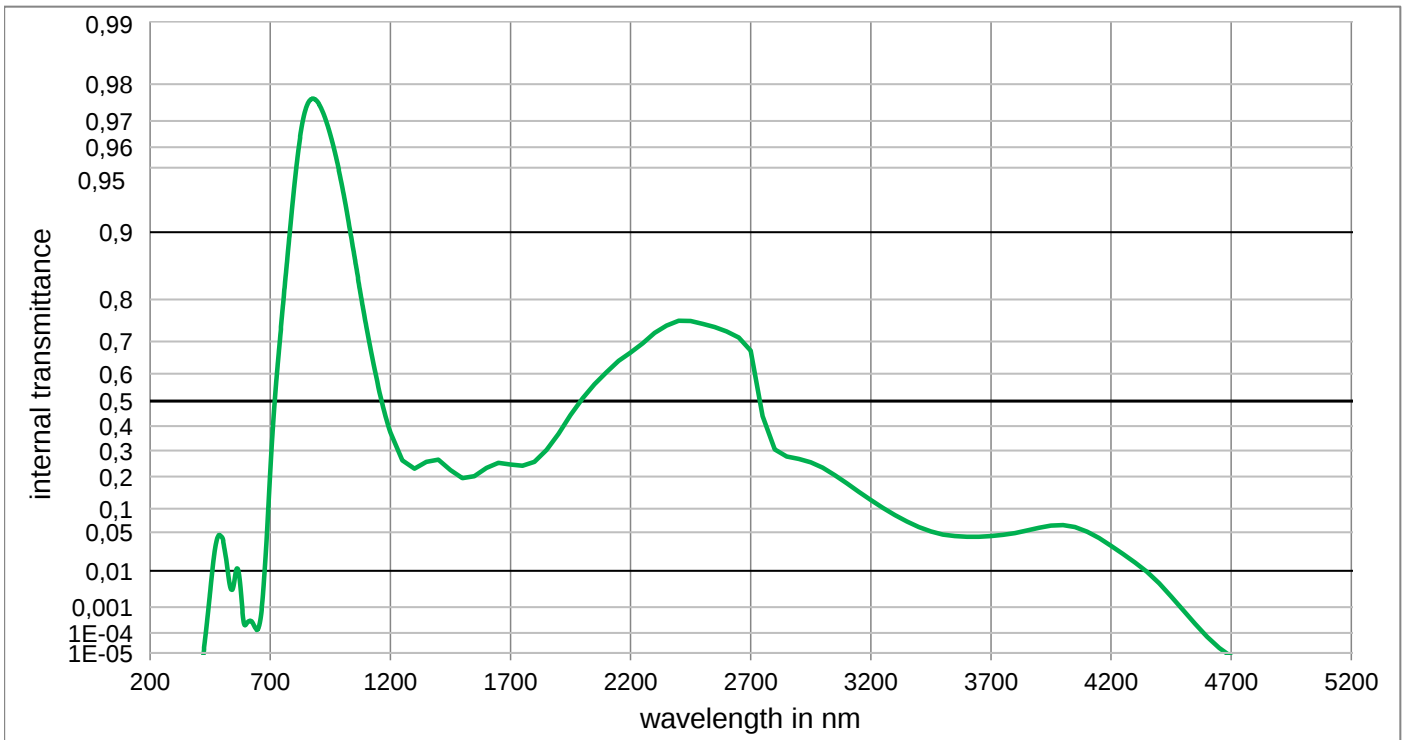
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	4,144E-02	800	9,390E-01	1100	7,396E-01	2200	6,679E-01	3700	4,391E-02
210	< 1,000E-05	510	2,703E-02	810	9,520E-01	1110	7,055E-01	2250	6,951E-01	3750	4,577E-02
220	< 1,000E-05	520	1,361E-02	820	9,611E-01	1120	6,691E-01	2300	7,234E-01	3800	4,874E-02
230	< 1,000E-05	530	5,249E-03	830	9,674E-01	1130	6,316E-01	2350	7,420E-01	3850	5,293E-02
240	< 1,000E-05	540	3,344E-03	840	9,715E-01	1140	5,930E-01	2400	7,535E-01	3900	5,778E-02
250	< 1,000E-05	550	5,402E-03	850	9,741E-01	1150	5,546E-01	2450	7,528E-01	3950	6,183E-02
260	< 1,000E-05	560	1,107E-02	860	9,757E-01	1160	5,149E-01	2500	7,462E-01	4000	6,292E-02
270	< 1,000E-05	570	8,130E-03	870	9,764E-01	1170	4,769E-01	2550	7,382E-01	4050	5,930E-02
280	< 1,000E-05	580	1,843E-03	880	9,765E-01	1180	4,398E-01	2600	7,270E-01	4100	5,118E-02
290	< 1,000E-05	590	2,794E-04	890	9,762E-01	1190	4,054E-01	2650	7,110E-01	4150	4,086E-02
300	< 1,000E-05	600	2,365E-04	900	9,754E-01	1200	3,741E-01	2700	6,734E-01	4200	3,081E-02
310	< 1,000E-05	610	3,064E-04	910	9,742E-01	1250	2,610E-01	2750	4,409E-01	4250	2,192E-02
320	< 1,000E-05	620	3,155E-04	920	9,727E-01	1300	2,294E-01	2800	3,043E-01	4300	1,498E-02
330	< 1,000E-05	630	2,321E-04	930	9,706E-01	1350	2,554E-01	2850	2,767E-01	4350	9,436E-03
340	< 1,000E-05	640	1,576E-04	940	9,682E-01	1400	2,637E-01	2900	2,666E-01	4400	5,022E-03
350	< 1,000E-05	650	1,604E-04	950	9,651E-01	1450	2,237E-01	2950	2,536E-01	4450	2,197E-03
360	< 1,000E-05	660	4,276E-04	960	9,615E-01	1500	1,946E-01	3000	2,324E-01	4500	7,882E-04
370	< 1,000E-05	670	2,431E-03	970	9,572E-01	1550	2,015E-01	3050	2,053E-01	4550	2,409E-04
380	< 1,000E-05	680	1,696E-02	980	9,520E-01	1600	2,316E-01	3100	1,763E-01	4600	6,732E-05
390	< 1,000E-05	690	7,804E-02	990	9,458E-01	1650	2,511E-01	3150	1,484E-01	4650	1,888E-05
400	< 1,000E-05	700	2,159E-01	1000	9,384E-01	1700	2,453E-01	3200	1,232E-01	4700	< 1,000E-05
410	< 1,000E-05	710	3,800E-01	1010	9,293E-01	1750	2,398E-01	3250	1,019E-01	4750	< 1,000E-05
420	< 1,000E-05	720	5,179E-01	1020	9,183E-01	1800	2,556E-01	3300	8,420E-02	4800	< 1,000E-05
430	6,155E-05	730	6,230E-01	1030	9,046E-01	1850	3,022E-01	3350	7,017E-02	4850	< 1,000E-05
440	5,118E-04	740	7,044E-01	1040	8,896E-01	1900	3,686E-01	3400	5,923E-02	4900	< 1,000E-05
450	2,924E-03	750	7,693E-01	1050	8,716E-01	1950	4,445E-01	3450	5,152E-02	4950	< 1,000E-05
460	1,124E-02	760	8,221E-01	1060	8,510E-01	2000	5,108E-01	3500	4,635E-02	5000	< 1,000E-05
470	2,674E-02	770	8,634E-01	1070	8,273E-01	2050	5,626E-01	3550	4,383E-02	5050	< 1,000E-05
480	4,130E-02	780	8,957E-01	1080	8,012E-01	2100	6,059E-01	3600	4,281E-02	5100	< 1,000E-05
490	4,486E-02	790	9,207E-01	1090	7,714E-01	2150	6,425E-01	3650	4,292E-02	5150	< 1,000E-05

RG1000

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,913$	$d = 3,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed (d = 3 mm)	Density	
$\lambda_{i0,5} = 1000 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,73 \text{ g/cm}^3$	
$\lambda_s (\tau_{i,U} = 1\text{E-}05) = 730 \text{ nm}$	Knoop hardness	
$\lambda_p (\tau_{i,L} = 0,90) = 1300 \text{ nm}$	$HK_{[0.1/20]} = 460$	
		Illuminant A
Refractive indices	Thermal properties	
$n_d (587,6 \text{ nm}) = 1,54$	Transformation temperature	
$n_s (852 \text{ nm}) = 1,53$	$T_g = 476 \text{ }^\circ\text{C}$	
$n_t (1014 \text{ nm}) = 1,53$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 9,0$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 10,2$	
	Temperature coefficient	
	$Tk = 0,41 \text{ nm/K}$	
Sellmeier coefficients	Chemical properties	Notes
valid from 440 nm to 1550 nm	Chemical resistance	
$B_1 = 0,8970$	FR class = 0	Ionically colored glass
$B_2 = 0,4353$	SR class = 1	Longpass filter
$B_3 = 1,1960$	AR class = 1	
$C_1 = 1,087\text{E-}02 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,1835\text{E-}02 \text{ } \mu\text{m}^2$	Robust glass	
$C_3 = 142,345 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	ISO 23364:2021
Internal quality		Disclaimer
Bubble class 3		All data without tolerances are to be understood to be reference values.

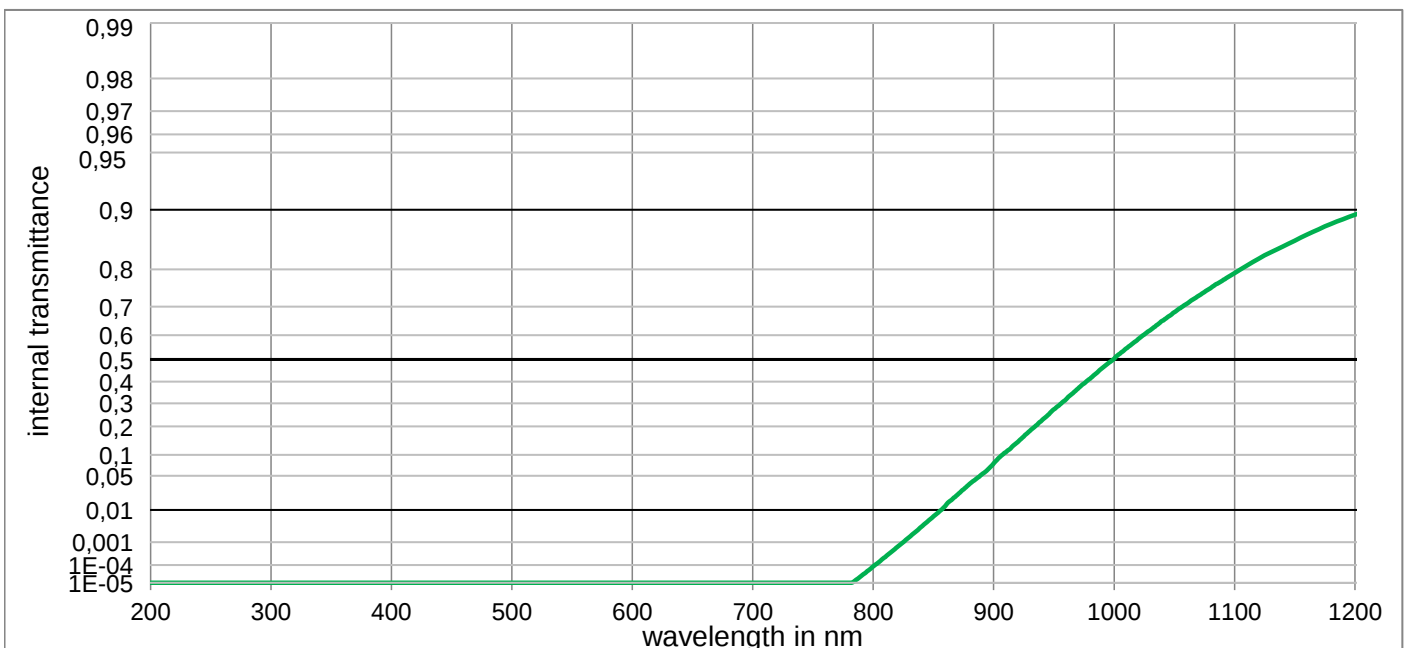

RG1000

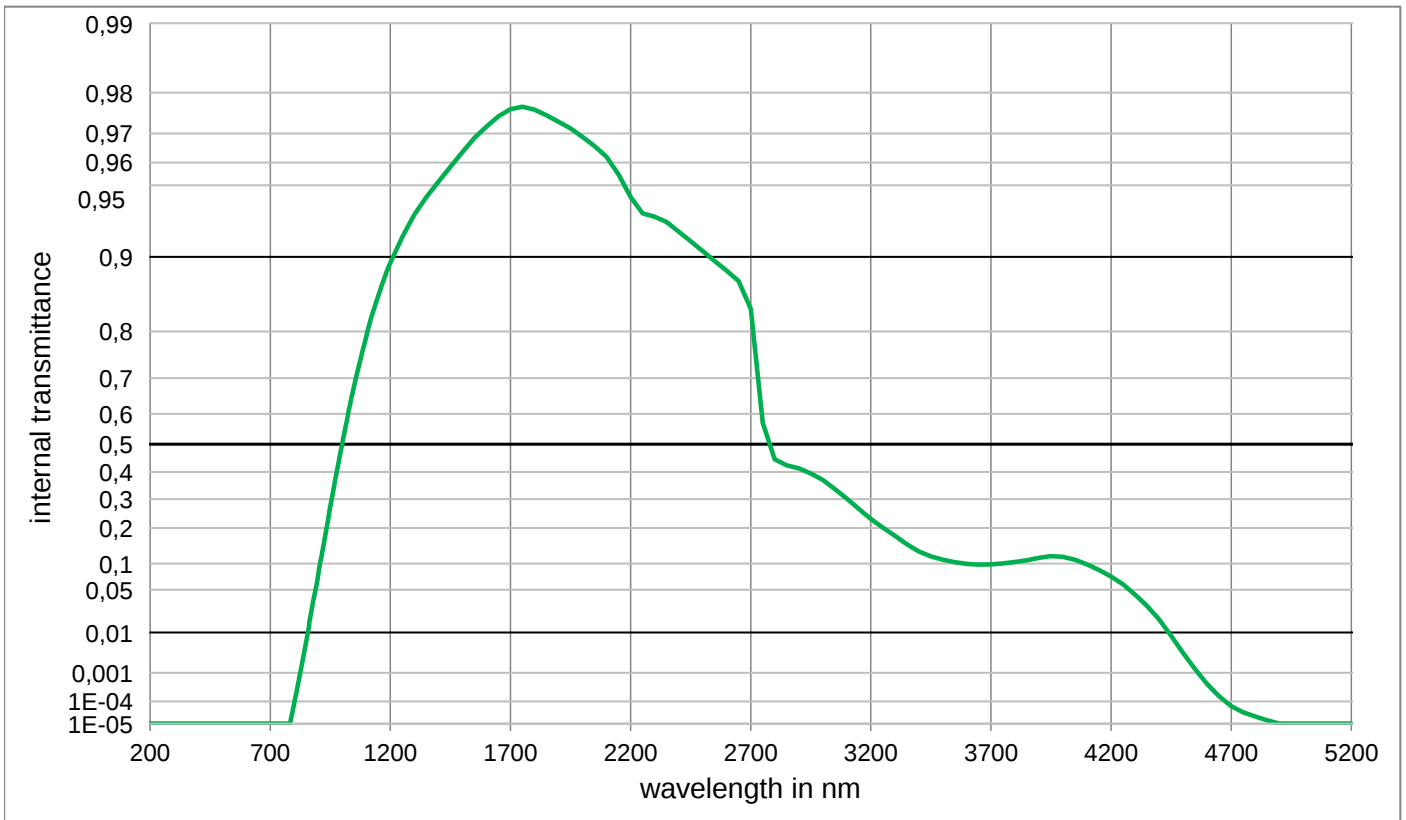
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	< 1,000E-05	800	8,394E-05	1100	7,917E-01	2200	9,439E-01	3700	9,800E-02
210	< 1,0E-05	510	< 1,000E-05	810	2,455E-04	1110	8,080E-01	2250	9,342E-01	3750	1,002E-01
220	< 1,0E-05	520	< 1,000E-05	820	6,502E-04	1120	8,226E-01	2300	9,320E-01	3800	1,036E-01
230	< 1,0E-05	530	< 1,000E-05	830	1,551E-03	1130	8,350E-01	2350	9,284E-01	3850	1,080E-01
240	< 1,0E-05	540	< 1,000E-05	840	3,371E-03	1140	8,459E-01	2400	9,216E-01	3900	1,136E-01
250	< 1,0E-05	550	< 1,000E-05	850	6,757E-03	1150	8,561E-01	2450	9,138E-01	3950	1,179E-01
260	< 1,0E-05	560	< 1,000E-05	860	1,254E-02	1160	8,656E-01	2500	9,054E-01	4000	1,161E-01
270	< 1,0E-05	570	< 1,000E-05	870	2,229E-02	1170	8,739E-01	2550	8,959E-01	4050	1,089E-01
280	< 1,0E-05	580	< 1,000E-05	880	3,617E-02	1180	8,816E-01	2600	8,861E-01	4100	9,840E-02
290	< 1,0E-05	590	< 1,000E-05	890	5,218E-02	1190	8,879E-01	2650	8,740E-01	4150	8,574E-02
300	< 1,0E-05	600	< 1,000E-05	900	7,670E-02	1200	8,940E-01	2700	8,370E-01	4200	7,245E-02
310	< 1,0E-05	610	< 1,000E-05	910	1,073E-01	1250	9,176E-01	2750	5,716E-01	4250	5,855E-02
320	< 1,000E-05	620	< 1,000E-05	920	1,407E-01	1300	9,335E-01	2800	4,462E-01	4300	4,286E-02
330	< 1,000E-05	630	< 1,000E-05	930	1,822E-01	1350	9,438E-01	2850	4,240E-01	4350	2,926E-02
340	< 1,000E-05	640	< 1,000E-05	940	2,248E-01	1400	9,518E-01	2900	4,138E-01	4400	1,762E-02
350	< 1,000E-05	650	< 1,000E-05	950	2,726E-01	1450	9,583E-01	2950	3,942E-01	4450	8,530E-03
360	< 1,000E-05	660	< 1,000E-05	960	3,177E-01	1500	9,640E-01	3000	3,704E-01	4500	3,477E-03
370	< 1,000E-05	670	< 1,000E-05	970	3,676E-01	1550	9,687E-01	3050	3,373E-01	4550	1,300E-03
380	< 1,000E-05	680	< 1,000E-05	980	4,135E-01	1600	9,720E-01	3100	3,015E-01	4600	4,406E-04
390	< 1,000E-05	690	< 1,000E-05	990	4,614E-01	1650	9,747E-01	3150	2,644E-01	4650	1,603E-04
400	< 1,000E-05	700	< 1,000E-05	1000	5,029E-01	1700	9,764E-01	3200	2,303E-01	4700	6,397E-05
410	< 1,000E-05	710	< 1,000E-05	1010	5,464E-01	1750	9,770E-01	3250	2,013E-01	4750	3,404E-05
420	< 1,000E-05	720	< 1,000E-05	1020	5,848E-01	1800	9,763E-01	3300	1,753E-01	4800	2,249E-05
430	< 1,000E-05	730	< 1,000E-05	1030	6,192E-01	1850	9,750E-01	3350	1,507E-01	4850	1,445E-05
440	< 1,000E-05	740	< 1,000E-05	1040	6,527E-01	1900	9,733E-01	3400	1,302E-01	4900	< 1,000E-05
450	< 1,000E-05	750	< 1,000E-05	1050	6,821E-01	1950	9,715E-01	3450	1,174E-01	4950	< 1,000E-05
460	< 1,000E-05	760	< 1,000E-05	1060	7,085E-01	2000	9,690E-01	3500	1,088E-01	5000	< 1,000E-05
470	< 1,000E-05	770	< 1,000E-05	1070	7,320E-01	2050	9,660E-01	3550	1,030E-01	5050	< 1,000E-05
480	< 1,000E-05	780	< 1,000E-05	1080	7,538E-01	2100	9,622E-01	3600	9,915E-02	5100	< 1,000E-05
490	< 1,000E-05	790	2,575E-05	1090	7,734E-01	2150	9,551E-01	3650	9,763E-02	5150	< 1,000E-05

S7000

Optical properties	Mechanical properties	Colorimetric properties
Reflection factor	Reference thickness	1 mm2 mm3 mm
$P_d = 0,908$	$d = 2,00 \text{ mm}$	x0,3130,3130,313
Spectral values guaranteed (d = 2 mm)	Density	y0,3290,3290,330
$\lambda_{i0,5} = 340 \text{ nm} \pm 6 \text{ nm}$	$\rho = 2,83 \text{ g/cm}^3$	Y90,890,790,7
$\lambda_s(\tau_{i,U} = 1E-05) = 260 \text{ nm}$	Knoop hardness	λ_d 574 nm574 nm575 nm
$\lambda_p(\tau_{i,L} = 0,99) = 420 \text{ nm}$	$HK_{[0.1/20]} = 525$	P_e 0,0010,0020,004
		Illuminant D65
		x0,4480,4480,448
		y0,4080,4080,408
		Y90,890,790,7
		λ_d 584 nm584 nm584 nm
		P_e 0,0020,0030,005
		Illuminant A
		x0,4480,4480,448
		y0,4080,4080,408
		Y90,890,790,7
		λ_d 584 nm584 nm584 nm
		P_e 0,0020,0030,005
Refractive indices	Thermal properties	Notes
$n_d(587,6 \text{ nm}) = 1,56$	Transformation temperature	
	$T_g = 452 \text{ }^\circ\text{C}$	
	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 11,1$	
Sellmeier coefficients	Chemical properties	
on request	Chemical resistance	
	FR class = 1	
	SR class = 1.2	
	AR class = 1.0	
	Resistance against humidity	
	Resistant glass	
	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
Internal quality		
Bubble class -		

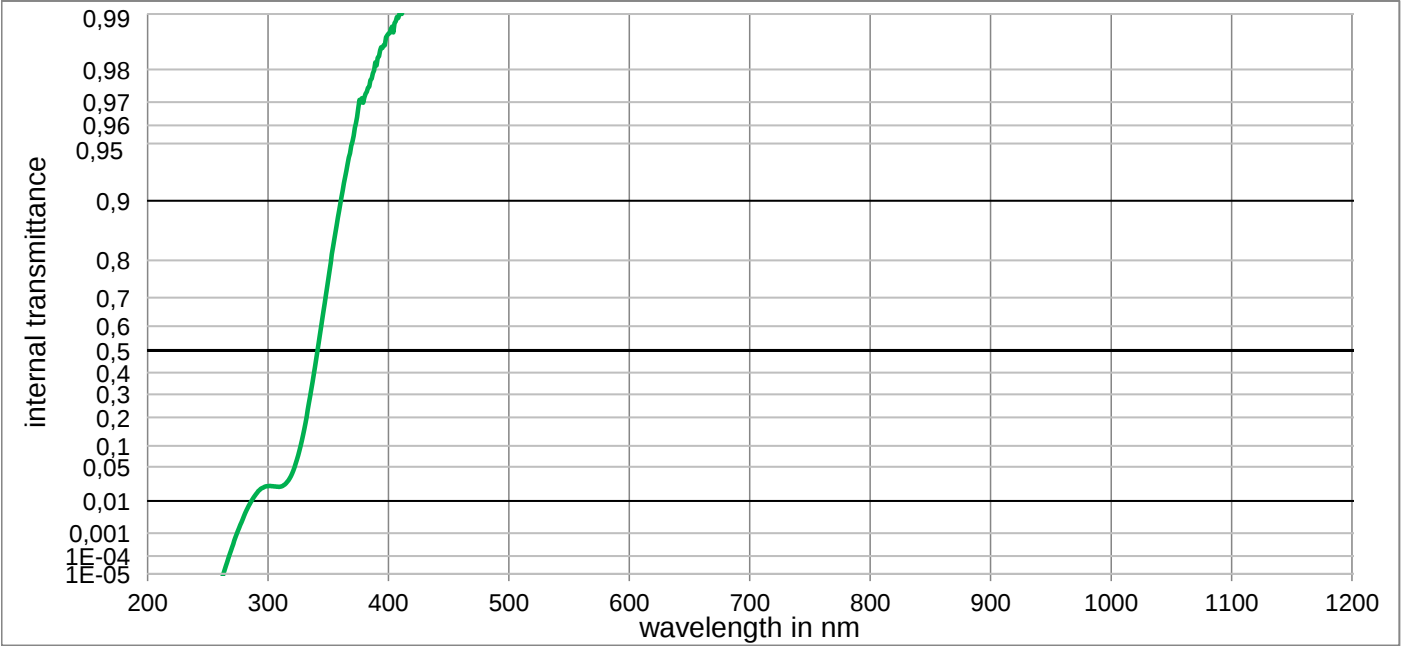


S7000

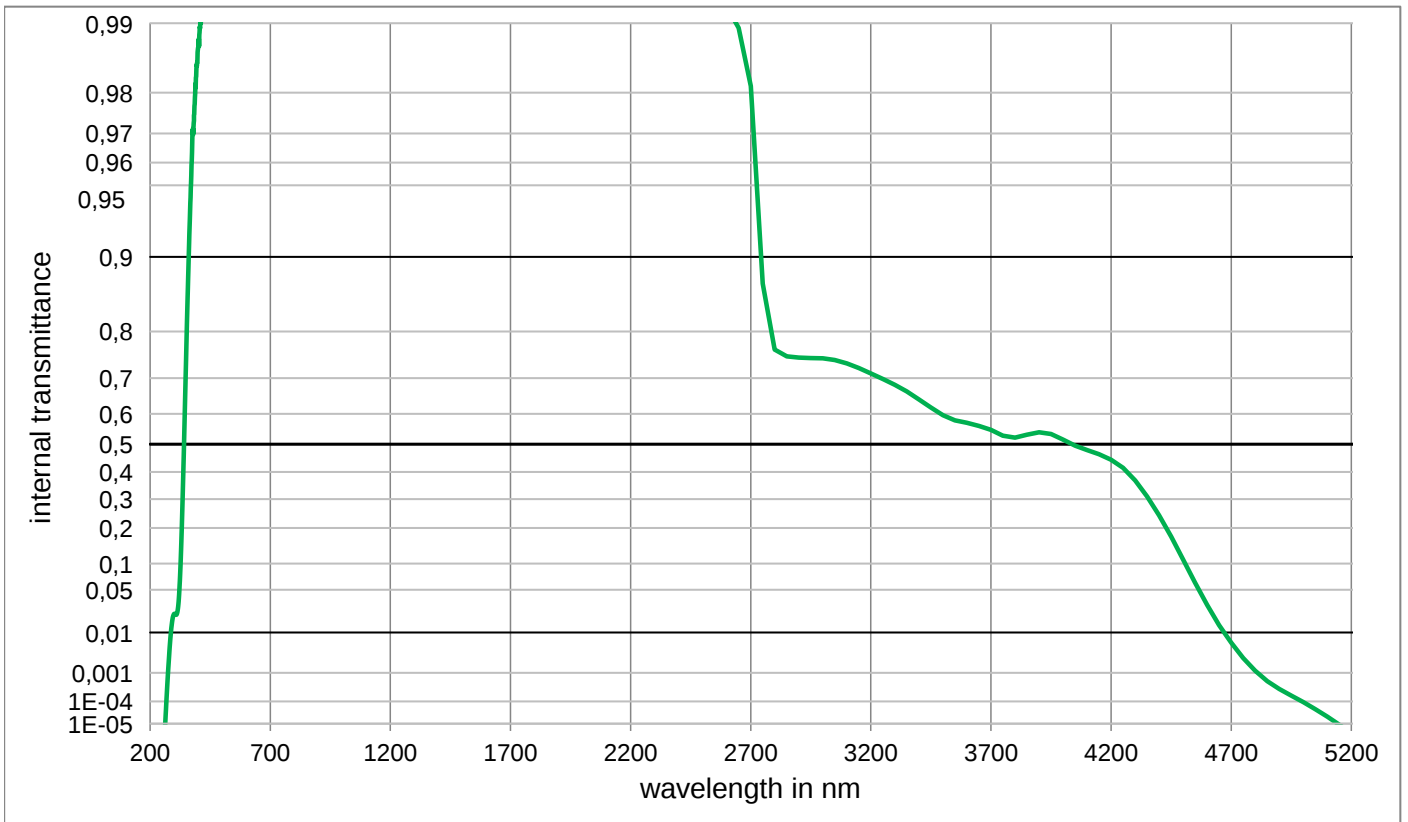Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	9,965E-01	800	9,939E-01	1100	9,973E-01	2200	9,949E-01	3700	5,490E-01
210	< 1,0E-05	510	9,972E-01	810	9,958E-01	1110	9,972E-01	2250	9,915E-01	3750	5,293E-01
220	< 1,0E-05	520	9,979E-01	820	9,942E-01	1120	9,975E-01	2300	9,923E-01	3800	5,223E-01
230	< 1,0E-05	530	9,982E-01	830	9,951E-01	1130	9,976E-01	2350	9,915E-01	3850	5,329E-01
240	< 1,0E-05	540	9,989E-01	840	9,956E-01	1140	9,974E-01	2400	9,995E-01	3900	5,403E-01
250	< 1,0E-05	550	9,994E-01	850	9,939E-01	1150	9,975E-01	2450	9,976E-01	3950	5,346E-01
260	< 1,0E-05	560	9,919E-01	860	9,940E-01	1160	9,975E-01	2500	9,945E-01	4000	5,156E-01
270	2,5E-04	570	9,997E-01	870	9,964E-01	1170	9,976E-01	2550	9,931E-01	4050	4,951E-01
280	3,8E-03	580	9,995E-01	880	9,970E-01	1180	9,975E-01	2600	9,915E-01	4100	4,796E-01
290	1,5E-02	590	9,998E-01	890	9,965E-01	1190	9,978E-01	2650	9,895E-01	4150	4,652E-01
300	2,2E-02	600	9,916E-01	900	9,965E-01	1200	9,976E-01	2700	9,813E-01	4200	4,449E-01
310	2,1E-02	610	9,917E-01	910	9,967E-01	1250	9,977E-01	2750	8,713E-01	4250	4,150E-01
320	3,831E-02	620	9,915E-01	920	9,973E-01	1300	9,977E-01	2800	7,654E-01	4300	3,683E-01
330	1,542E-01	630	9,920E-01	930	9,970E-01	1350	9,988E-01	2850	7,508E-01	4350	3,098E-01
340	4,615E-01	640	9,923E-01	940	9,970E-01	1400	9,980E-01	2900	7,483E-01	4400	2,423E-01
350	7,547E-01	650	9,927E-01	950	9,973E-01	1450	9,978E-01	2950	7,474E-01	4450	1,724E-01
360	8,962E-01	660	9,930E-01	960	9,970E-01	1500	9,983E-01	3000	7,466E-01	4500	1,097E-01
370	9,511E-01	670	9,926E-01	970	9,969E-01	1550	9,983E-01	3050	7,431E-01	4550	6,139E-02
380	9,717E-01	680	9,933E-01	980	9,965E-01	1600	9,984E-01	3100	7,354E-01	4600	3,030E-02
390	9,810E-01	690	9,933E-01	990	9,968E-01	1650	9,983E-01	3150	7,247E-01	4650	1,385E-02
400	9,872E-01	700	9,933E-01	1000	9,968E-01	1700	9,978E-01	3200	7,118E-01	4700	6,063E-03
410	9,906E-01	710	9,923E-01	1010	9,970E-01	1750	9,977E-01	3250	6,980E-01	4750	2,611E-03
420	9,929E-01	720	9,933E-01	1020	9,971E-01	1800	9,975E-01	3300	6,829E-01	4800	1,160E-03
430	9,933E-01	730	9,942E-01	1030	9,973E-01	1850	9,969E-01	3350	6,653E-01	4850	5,507E-04
440	9,946E-01	740	9,930E-01	1040	9,974E-01	1900	9,969E-01	3400	6,429E-01	4900	2,942E-04
450	9,947E-01	750	9,944E-01	1050	9,972E-01	1950	9,969E-01	3450	6,193E-01	4950	1,688E-04
460	9,951E-01	760	9,922E-01	1060	9,972E-01	2000	9,981E-01	3500	5,955E-01	5000	9,375E-05
470	9,968E-01	770	9,949E-01	1070	9,971E-01	2050	9,977E-01	3550	5,800E-01	5050	4,751E-05
480	9,978E-01	780	9,933E-01	1080	9,971E-01	2100	9,955E-01	3600	5,717E-01	5100	2,188E-05
490	9,968E-01	790	9,928E-01	1090	9,973E-01	2150	9,949E-01	3650	5,619E-01	5150	< 1,000E-05

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm		2 mm	3 mm	
P _d = 0,920		d = 2,00 mm		Illuminant D65	x	0,311	0,309	0,307
Spectral values guaranteed		Density			y	0,330	0,331	0,332
τ _i (365 nm)	≥ 0,89	ρ = 2,52 g/cm³			Y	88,7	85,6	82,6
τ _i (500 nm)	≥ 0,92	Knoop hardness			λ _d	497 nm	497 nm	498 nm
τ _i (600 nm)	≥ 0,88	HK[0.1/20] = 456			P _e	0,006	0,013	0,018
τ _i (700 nm)	≤ 0,68	Thermal properties		Illuminant A	x	0,444	0,441	0,438
τ _i (800 nm)	≤ 0,33	Transformation temperature			y	0,409	0,411	0,413
τ _i (900 nm)	≤ 0,1	Tg = 599 °C			Y	88,4	84,9	81,6
τ _i (1060 nm)	≤ 0,02	Thermal expansion in 10 ⁻⁶ /K			λ _d	505 nm	505 nm	505 nm
τ _i (2200 nm)	≤ 0,06	α _{-30°C/+70°C} = 5,3			P _e	0,007	0,014	0,021
Refractive indices		α _{20°C/300°C} = 6,1		Notes				
n _F (486 nm)	= 1,516			UV				
n _e (546 nm)	= 1,513			Transmission changes are possible under the action of intense ultraviolet radiation.				
n _d (587,6 nm)	= 1,511			Ionically colored glass				
Sellmeier coefficients				Shortpass filter				
valid from 400 nm to 1550 nm								
B ₁	0,3376	Chemical properties		Heat protection filter				
B ₂	0,9188	Chemical resistance		ISO 23364:2021				
B ₃	1,8816	FR class = 0						
C ₁	3,461E-03 μm²	SR class = 2		Disclaimer				
C ₂	9,9076E-03 μm²	AR class = 3		All data without tolerances are to be understood to be reference values.				
C ₃	181,405 μm²	Resistance against humidity						
Internal quality		Delicate glass						
Bubble class 3		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5						

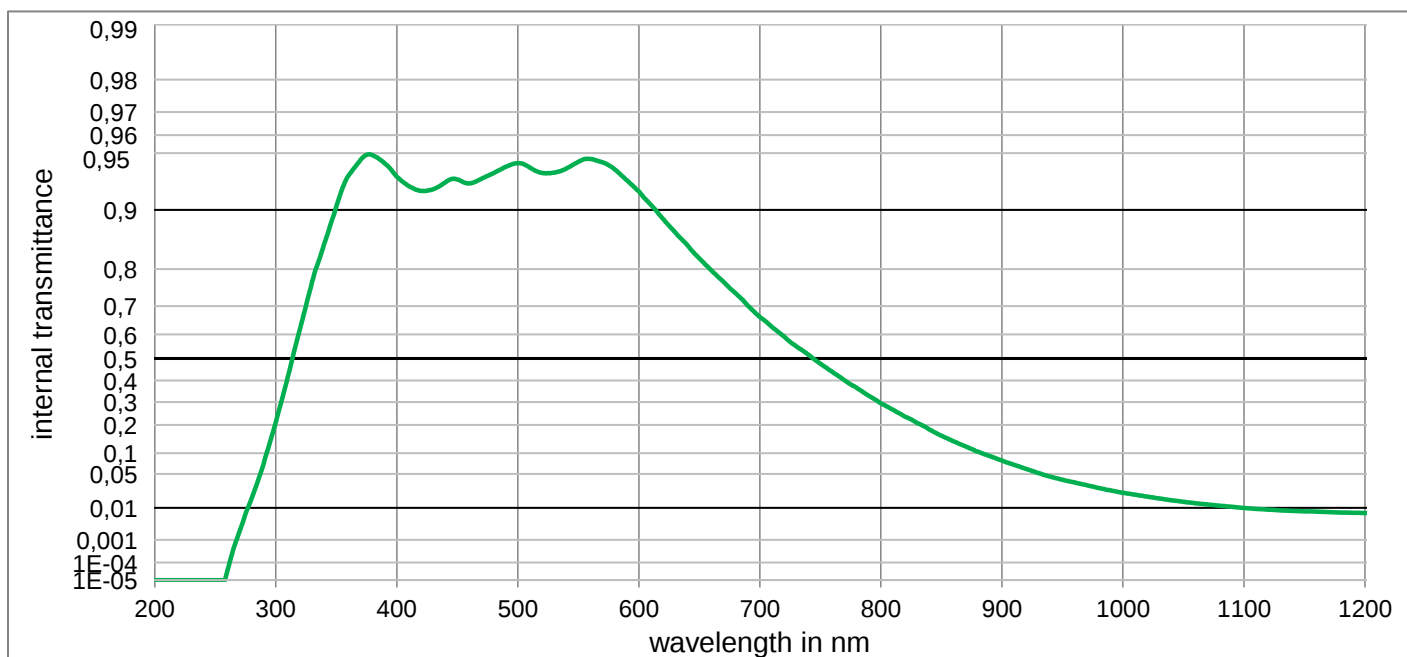

KG1

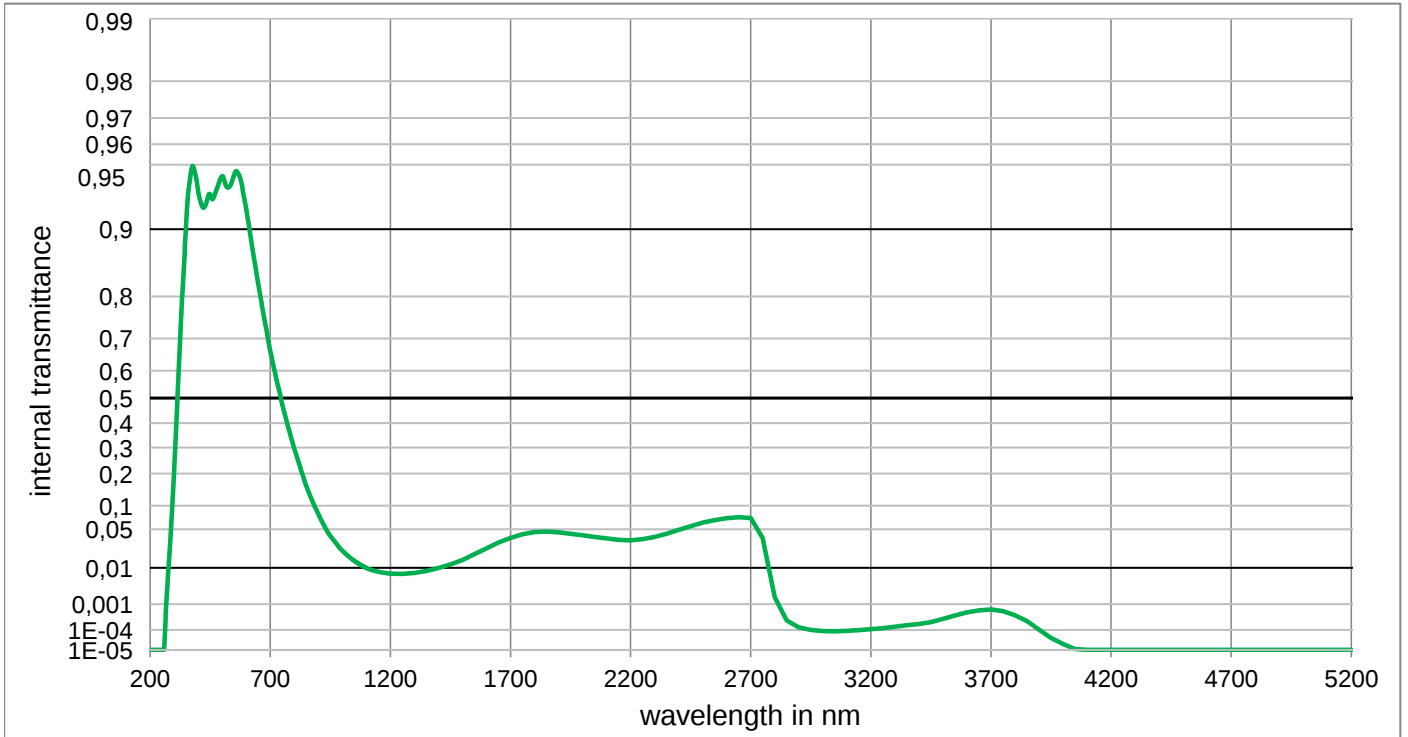Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,434E-01	800	2,936E-01	1100	9,948E-03	2200	3,377E-02	3700	6,632E-04
210	< 1,000E-05	510	9,402E-01	810	2,650E-01	1110	9,410E-03	2250	3,523E-02	3750	5,698E-04
220	< 1,000E-05	520	9,362E-01	820	2,349E-01	1120	8,986E-03	2300	3,829E-02	3800	3,991E-04
230	< 1,000E-05	530	9,364E-01	830	2,082E-01	1130	8,642E-03	2350	4,292E-02	3850	2,350E-04
240	< 1,000E-05	540	9,395E-01	840	1,824E-01	1140	8,360E-03	2400	4,886E-02	3900	1,033E-04
250	< 1,000E-05	550	9,444E-01	850	1,581E-01	1150	8,157E-03	2450	5,536E-02	3950	4,236E-05
260	3,483E-05	560	9,463E-01	860	1,377E-01	1160	7,950E-03	2500	6,181E-02	4000	2,104E-05
270	2,000E-03	570	9,440E-01	870	1,206E-01	1170	7,750E-03	2550	6,692E-02	4050	1,117E-05
280	1,701E-02	580	9,389E-01	880	1,047E-01	1180	7,580E-03	2600	7,069E-02	4100	< 1,000E-05
290	7,300E-02	590	9,302E-01	890	9,150E-02	1190	7,453E-03	2650	7,279E-02	4150	< 1,000E-05
300	2,100E-01	600	9,199E-01	900	7,971E-02	1200	7,350E-03	2700	7,150E-02	4200	< 1,000E-05
310	4,189E-01	610	9,060E-01	910	6,939E-02	1250	7,200E-03	2750	3,692E-02	4250	< 1,000E-05
320	6,222E-01	620	8,887E-01	920	6,017E-02	1300	7,570E-03	2800	1,650E-03	4300	< 1,000E-05
330	7,690E-01	630	8,693E-01	930	5,187E-02	1350	8,490E-03	2850	2,541E-04	4350	< 1,000E-05
340	8,500E-01	640	8,481E-01	940	4,499E-02	1400	9,840E-03	2900	1,282E-04	4400	< 1,000E-05
350	9,040E-01	650	8,230E-01	950	3,971E-02	1450	1,182E-02	2950	9,931E-05	4450	< 1,000E-05
360	9,340E-01	660	7,970E-01	960	3,543E-02	1500	1,472E-02	3000	8,892E-05	4500	< 1,000E-05
370	9,456E-01	670	7,690E-01	970	3,157E-02	1550	1,909E-02	3050	8,612E-05	4550	< 1,000E-05
380	9,487E-01	680	7,380E-01	980	2,790E-02	1600	2,463E-02	3100	9,044E-05	4600	< 1,000E-05
390	9,433E-01	690	7,020E-01	990	2,477E-02	1650	3,097E-02	3150	9,750E-05	4650	< 1,000E-05
400	9,330E-01	700	6,640E-01	1000	2,230E-02	1700	3,707E-02	3200	1,074E-04	4700	< 1,000E-05
410	9,251E-01	710	6,280E-01	1010	2,029E-02	1750	4,196E-02	3250	1,208E-04	4750	< 1,000E-05
420	9,205E-01	720	5,921E-01	1020	1,846E-02	1800	4,558E-02	3300	1,397E-04	4800	< 1,000E-05
430	9,222E-01	730	5,530E-01	1030	1,677E-02	1850	4,635E-02	3350	1,594E-04	4850	< 1,000E-05
440	9,284E-01	740	5,170E-01	1040	1,525E-02	1900	4,488E-02	3400	1,805E-04	4900	< 1,000E-05
450	9,309E-01	750	4,770E-01	1050	1,404E-02	1950	4,284E-02	3450	2,178E-04	4950	< 1,000E-05
460	9,274E-01	760	4,393E-01	1060	1,300E-02	2000	4,076E-02	3500	2,881E-04	5000	< 1,000E-05
470	9,315E-01	770	4,012E-01	1070	1,212E-02	2050	3,830E-02	3550	3,919E-04	5050	< 1,000E-05
480	9,362E-01	780	3,658E-01	1080	1,133E-02	2100	3,616E-02	3600	5,113E-04	5100	< 1,000E-05
490	9,408E-01	790	3,290E-01	1090	1,062E-02	2150	3,447E-02	3650	6,113E-04	5150	< 1,000E-05

Optical properties	
Reflection factor	
P _d = 0,920	
Spectral values guaranteed	
τ _i (365 nm)	≥ 0,93
τ _i (500 nm)	≥ 0,94
τ _i (600 nm)	≥ 0,92
τ _i (700 nm)	≤ 0,83
τ _i (800 nm)	≤ 0,55
τ _i (900 nm)	≤ 0,28
τ _i (1060 nm)	≤ 0,12
τ _i (2200 nm)	≤ 0,2
Refractive indices	
n _d (587,6 nm)	= 1,51
Sellmeier coefficients	
on request	
Internal quality	
Bubble class	3


Mechanical properties	
Reference thickness	
d = 2,00 mm	
Density	
ρ = 2,52 g/cm³	
Knoop hardness	
HK[0.1/20] = 444	

Thermal properties	
Transformation temperature	
T _g = 605 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _[-30°C/+70°C] = 5,4	
α _[20°C/300°C] = 6,3	


Chemical properties	
Chemical resistance	
FR class = 0	
SR class = 2	
AR class = 3	
Resistance against humidity	
Delicate glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colormetric properties				
	1 mm	2 mm	3 mm	
Illuminant D65	x	0,312	0,311	0,310
	y	0,330	0,331	0,331
	Y	89,5	87,1	84,7
	λ _d	501 nm	501 nm	501 nm
	P _e	0,003	0,007	0,010
Illuminant A	x	0,446	0,444	0,442
	y	0,409	0,410	0,411
	Y	89,3	86,7	84,2
	λ _d	506 nm	507 nm	507 nm
	P _e	0,004	0,008	0,012

Notes	
UV	
Transmission changes are possible under the action of intense ultraviolet radiation.	
Ionically colored glass	
Shortpass filter	
Heat protection filter	
ISO 23364:2021	
Disclaimer	
All data without tolerances are to be understood to be reference values.	

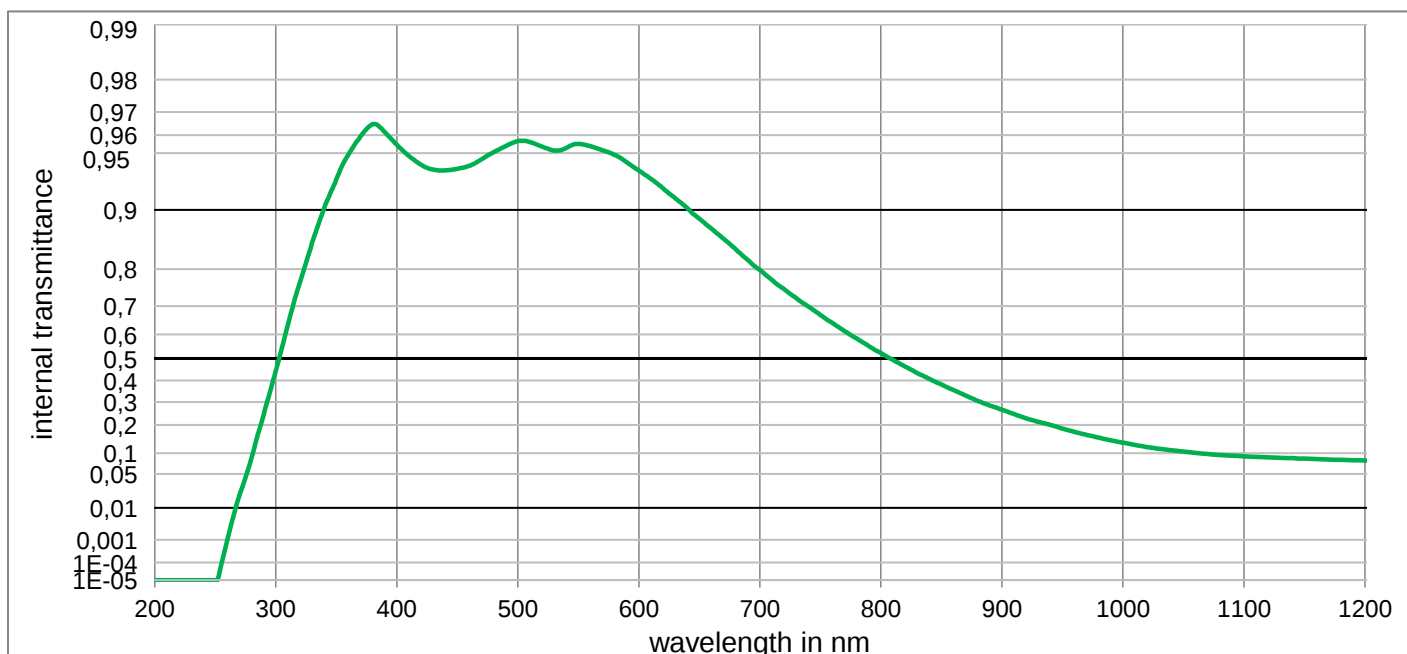


KG2

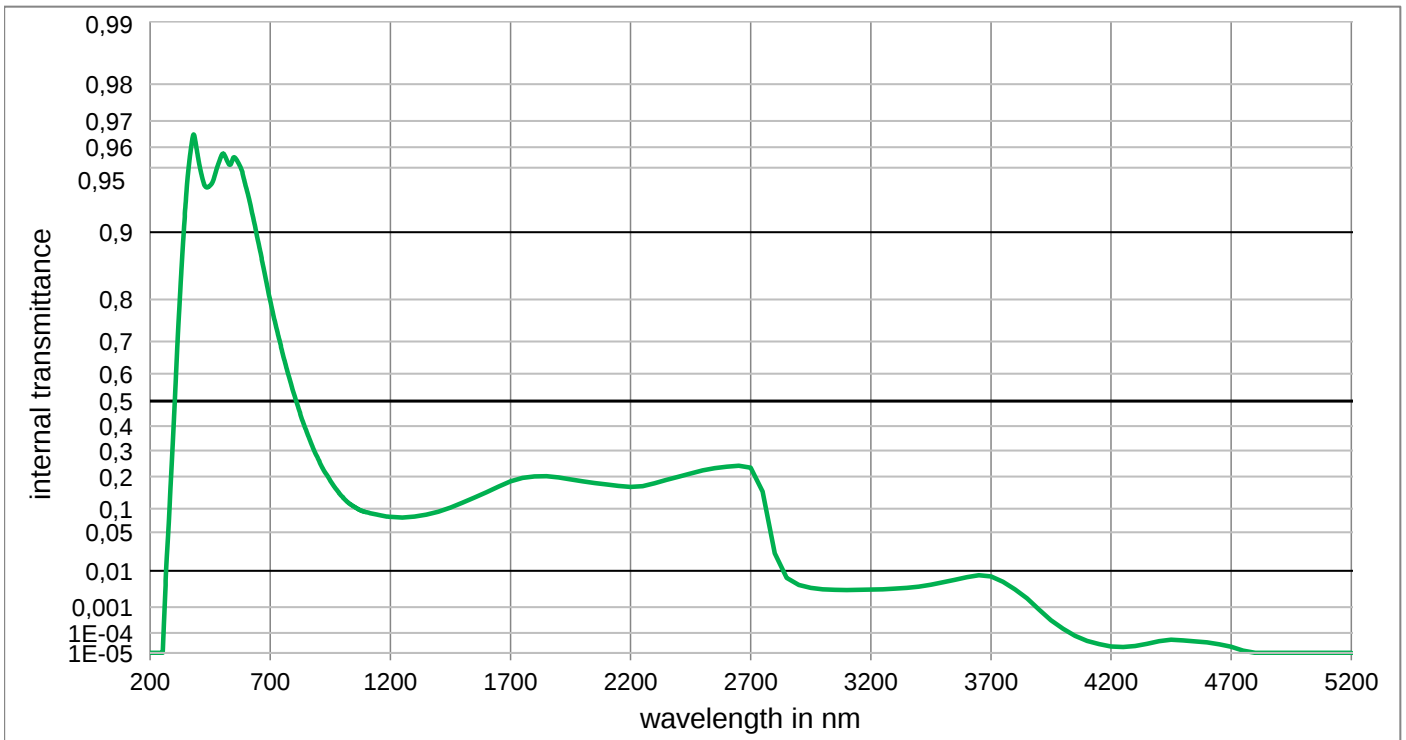Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,569E-01	800	5,237E-01	1100	9,099E-02	2200	1,647E-01	3700	7,376E-03
210	< 1,000E-05	510	9,564E-01	810	4,940E-01	1110	8,975E-02	2250	1,671E-01	3750	5,454E-03
220	< 1,000E-05	520	9,538E-01	820	4,640E-01	1120	8,844E-02	2300	1,764E-01	3800	3,463E-03
230	< 1,000E-05	530	9,516E-01	830	4,342E-01	1130	8,715E-02	2350	1,885E-01	3850	1,917E-03
240	< 1,000E-05	540	9,531E-01	840	4,080E-01	1140	8,600E-02	2400	1,997E-01	3900	8,350E-04
250	< 1,000E-05	550	9,554E-01	850	3,822E-01	1150	8,470E-02	2450	2,114E-01	3950	3,360E-04
260	1,000E-03	560	9,541E-01	860	3,557E-01	1160	8,350E-02	2500	2,227E-01	4000	1,525E-04
270	2,000E-02	570	9,518E-01	870	3,300E-01	1170	8,252E-02	2550	2,311E-01	4050	7,328E-05
280	8,800E-02	580	9,489E-01	880	3,054E-01	1180	8,150E-02	2600	2,370E-01	4100	4,198E-05
290	2,450E-01	590	9,440E-01	890	2,840E-01	1190	8,070E-02	2650	2,404E-01	4150	2,924E-05
300	4,440E-01	600	9,380E-01	900	2,652E-01	1200	8,005E-02	2700	2,327E-01	4200	2,239E-05
310	6,372E-01	610	9,314E-01	910	2,457E-01	1250	7,868E-02	2750	1,493E-01	4250	2,065E-05
320	7,690E-01	620	9,230E-01	920	2,280E-01	1300	8,103E-02	2800	2,260E-02	4300	2,344E-05
330	8,522E-01	630	9,132E-01	930	2,130E-01	1350	8,550E-02	2850	6,823E-03	4350	3,020E-05
340	9,020E-01	640	9,020E-01	940	2,001E-01	1400	9,250E-02	2900	4,519E-03	4400	4,162E-05
350	9,310E-01	650	8,891E-01	950	1,850E-01	1450	1,028E-01	2950	3,811E-03	4450	4,823E-05
360	9,492E-01	660	8,750E-01	960	1,726E-01	1500	1,157E-01	3000	3,483E-03	4500	4,508E-05
370	9,593E-01	670	8,590E-01	970	1,611E-01	1550	1,305E-01	3050	3,357E-03	4550	4,009E-05
380	9,651E-01	680	8,407E-01	980	1,510E-01	1600	1,471E-01	3100	3,334E-03	4600	3,556E-05
390	9,615E-01	690	8,199E-01	990	1,415E-01	1650	1,651E-01	3150	3,357E-03	4650	2,884E-05
400	9,549E-01	700	7,980E-01	1000	1,333E-01	1700	1,835E-01	3200	3,420E-03	4700	2,143E-05
410	9,482E-01	710	7,740E-01	1010	1,259E-01	1750	1,951E-01	3250	3,491E-03	4750	1,346E-05
420	9,423E-01	720	7,499E-01	1020	1,189E-01	1800	2,007E-01	3300	3,614E-03	4800	< 1,000E-05
430	9,388E-01	730	7,250E-01	1030	1,133E-01	1850	2,011E-01	3350	3,793E-03	4850	< 1,000E-05
440	9,382E-01	740	6,990E-01	1040	1,089E-01	1900	1,971E-01	3400	4,130E-03	4900	< 1,000E-05
450	9,393E-01	750	6,710E-01	1050	1,047E-01	1950	1,905E-01	3450	4,645E-03	4950	< 1,000E-05
460	9,416E-01	760	6,428E-01	1060	1,009E-01	2000	1,834E-01	3500	5,333E-03	5000	< 1,000E-05
470	9,461E-01	770	6,130E-01	1070	9,748E-02	2050	1,776E-01	3550	6,109E-03	5050	< 1,000E-05
480	9,506E-01	780	5,840E-01	1080	9,478E-02	2100	1,724E-01	3600	7,119E-03	5100	< 1,000E-05
490	9,542E-01	790	5,530E-01	1090	9,283E-02	2150	1,676E-01	3650	7,893E-03	5150	< 1,000E-05

Optical properties		Mechanical properties		Colorimetric properties				
Reflection factor		Reference thickness		1 mm		2 mm	3 mm	
P _d = 0,920		d = 2,00 mm		Illuminant D65	x	0,309	0,306	0,303
Spectral values guaranteed		Density			y	0,330	0,332	0,333
τ _i (365 nm)	≥ 0,86	ρ = 2,52 g/cm³			Y	87,1	82,4	78,1
τ _i (500 nm)	≥ 0,88	Knoop hardness			λ _d	496 nm	496 nm	496 nm
τ _i (600 nm)	≥ 0,83	HK[0.1/20] = 442			P _e	0,012	0,023	0,033
τ _i (700 nm)	≤ 0,55	Thermal properties		Illuminant A	x	0,442	0,437	0,432
τ _i (800 nm)	≤ 0,14	Transformation temperature			y	0,410	0,413	0,416
τ _i (900 nm)	≤ 0,03	Tg = 581 °C			Y	86,4	81,3	76,6
τ _i (1060 nm)	≤ 0,001	Thermal expansion in 10 ⁻⁶ /K			λ _d	504 nm	505 nm	505 nm
τ _i (2200 nm)	≤ 0,01	α _{-30°C/+70°C} = 5,3			P _e	0,012	0,024	0,035
Refractive indices		α _{20°C/300°C} = 6,1		Notes				
n _F (486 nm)	= 1,522			UV				
n _e (546 nm)	= 1,518			Transmission changes are possible under the action of intense ultraviolet radiation.				
n _d (587,6 nm)	= 1,516			Ionically colored glass				
Sellmeier coefficients				Shortpass filter				
valid from 400 nm to 1600 nm								
B ₁	1,1717	Chemical properties		Heat protection filter				
B ₂	0,0980	Chemical resistance		ISO 23364:2021				
B ₃	0,0713	FR class = 0						
C ₁	6,324E-03 μm²	SR class = 2		Disclaimer				
C ₂	3,1092E-02 μm²	AR class = 4		All data without tolerances are to be understood to be reference values.				
C ₃	10,066 μm²	Resistance against humidity						
Internal quality		Delicate glass						
Bubble class 3		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5						

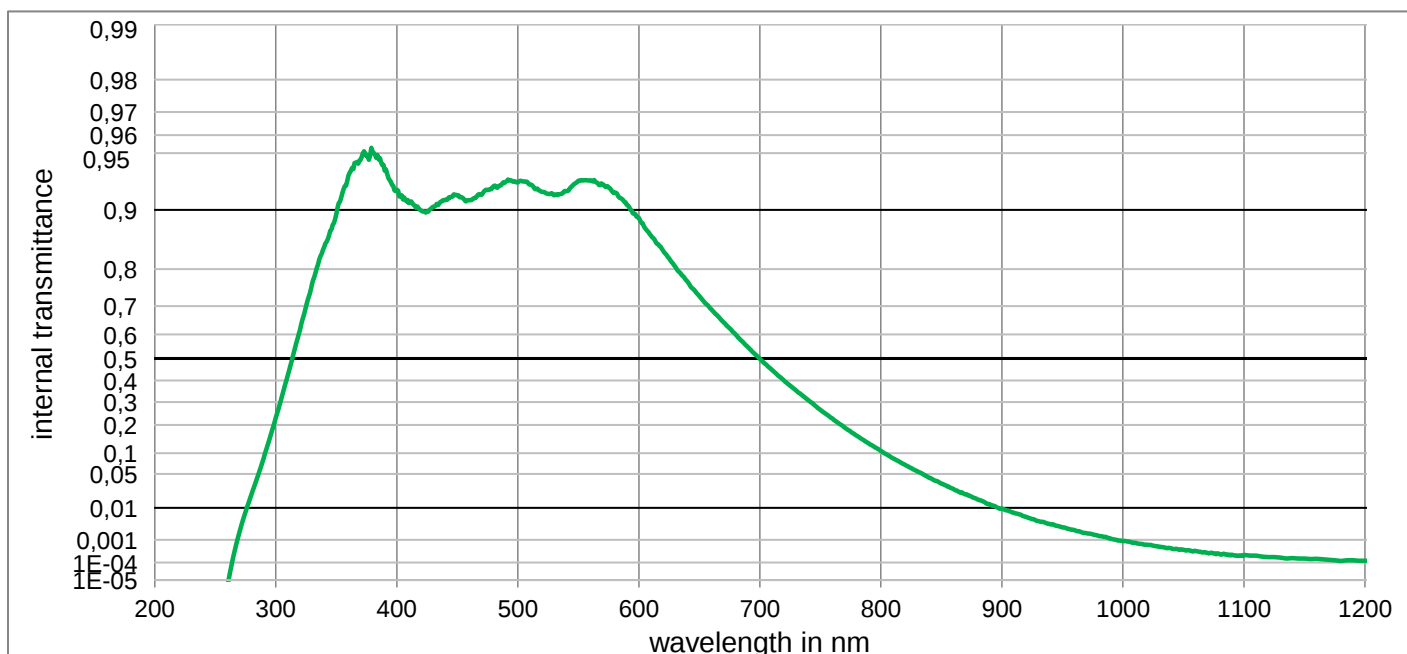


KG3

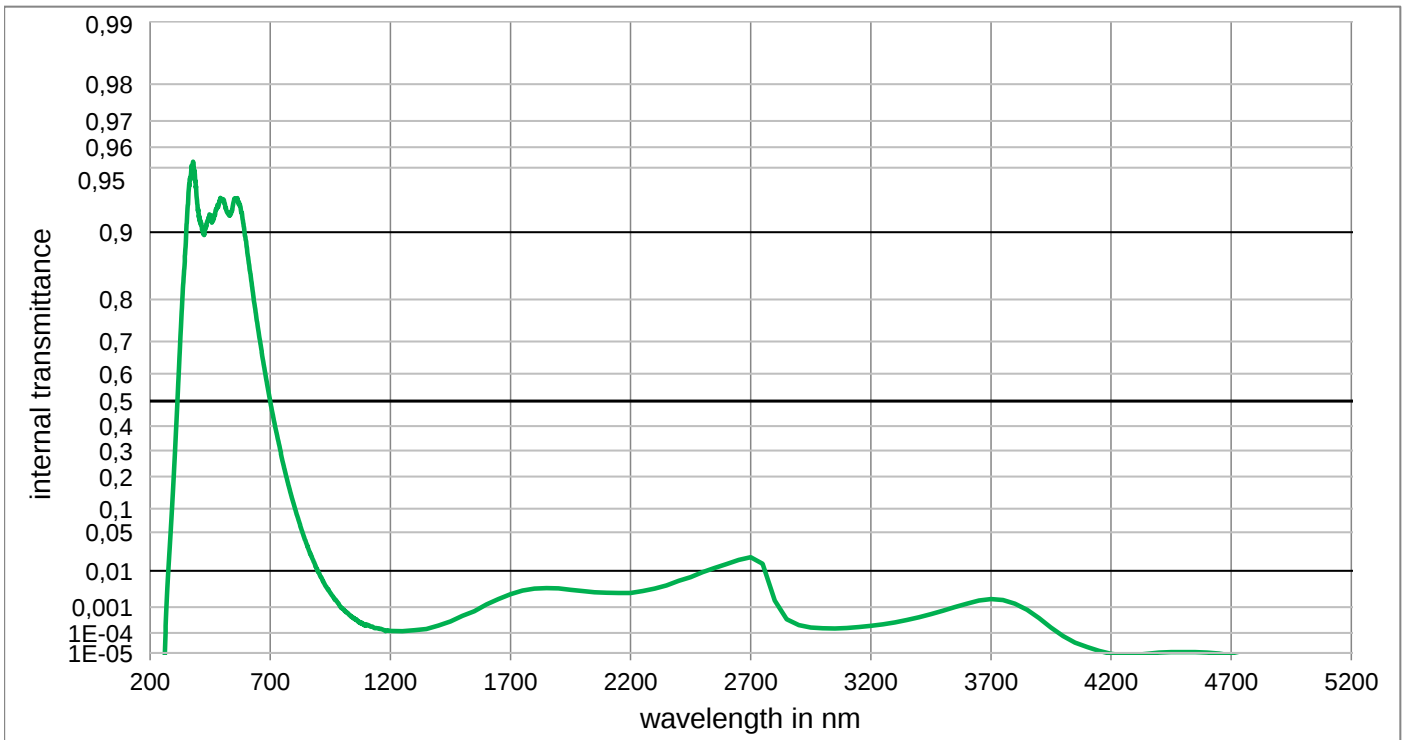Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	9,282E-01	800	1,066E-01	1100	2,334E-04	2200	2,727E-03	3700	1,822E-03
210	< 1,000E-05	510	9,265E-01	810	8,548E-02	1110	2,163E-04	2250	3,103E-03	3750	1,693E-03
220	< 1,000E-05	520	9,194E-01	820	6,913E-02	1120	1,828E-04	2300	3,642E-03	3800	1,292E-03
230	< 1,000E-05	530	9,162E-01	830	5,533E-02	1130	1,729E-04	2350	4,394E-03	3850	8,111E-04
240	< 1,000E-05	540	9,202E-01	840	4,313E-02	1140	1,649E-04	2400	5,839E-03	3900	4,055E-04
250	< 1,000E-05	550	9,298E-01	850	3,387E-02	1150	1,586E-04	2450	7,150E-03	3950	1,710E-04
260	< 1,000E-05	560	9,303E-01	860	2,668E-02	1160	1,510E-04	2500	9,398E-03	4000	7,230E-05
270	1,919E-03	570	9,267E-01	870	2,066E-02	1170	1,379E-04	2550	1,160E-02	4050	3,512E-05
280	2,114E-02	580	9,189E-01	880	1,585E-02	1180	1,201E-04	2600	1,403E-02	4100	2,115E-05
290	8,698E-02	590	9,059E-01	890	1,195E-02	1190	1,309E-04	2650	1,687E-02	4150	1,291E-05
300	2,288E-01	600	8,899E-01	900	9,471E-03	1200	1,227E-04	2700	1,917E-02	4200	< 1,000E-05
310	4,257E-01	610	8,645E-01	910	7,401E-03	1250	1,188E-04	2750	1,420E-02	4250	< 1,000E-05
320	6,184E-01	620	8,381E-01	920	5,677E-03	1300	1,322E-04	2800	1,641E-03	4300	< 1,000E-05
330	7,634E-01	630	8,054E-01	930	4,323E-03	1350	1,495E-04	2850	3,690E-04	4350	< 1,000E-05
340	8,445E-01	640	7,704E-01	940	3,458E-03	1400	2,072E-04	2900	2,146E-04	4400	1,042E-05
350	8,948E-01	650	7,303E-01	950	2,746E-03	1450	3,025E-04	2950	1,725E-04	4450	1,106E-05
360	9,343E-01	660	6,891E-01	960	2,212E-03	1500	4,975E-04	3000	1,586E-04	4500	1,106E-05
370	9,455E-01	670	6,451E-01	970	1,740E-03	1550	7,248E-04	3050	1,571E-04	4550	1,106E-05
380	9,509E-01	680	5,988E-01	980	1,401E-03	1600	1,222E-03	3100	1,649E-04	4600	1,042E-05
390	9,379E-01	690	5,497E-01	990	1,092E-03	1650	1,812E-03	3150	1,794E-04	4650	< 1,000E-05
400	9,217E-01	700	4,982E-01	1000	9,072E-04	1700	2,542E-03	3200	2,000E-04	4700	< 1,000E-05
410	9,079E-01	710	4,482E-01	1010	7,715E-04	1750	3,228E-03	3250	2,324E-04	4750	< 1,000E-05
420	8,992E-01	720	3,989E-01	1020	6,422E-04	1800	3,652E-03	3300	2,755E-04	4800	< 1,000E-05
430	9,037E-01	730	3,535E-01	1030	5,357E-04	1850	3,770E-03	3350	3,430E-04	4850	< 1,000E-05
440	9,112E-01	740	3,084E-01	1040	4,512E-04	1900	3,681E-03	3400	4,356E-04	4900	< 1,000E-05
450	9,159E-01	750	2,645E-01	1050	3,972E-04	1950	3,366E-03	3450	5,699E-04	4950	< 1,000E-05
460	9,109E-01	760	2,263E-01	1060	3,472E-04	2000	3,121E-03	3500	7,511E-04	5000	< 1,000E-05
470	9,167E-01	770	1,901E-01	1070	2,827E-04	2050	2,861E-03	3550	9,992E-04	5050	< 1,000E-05
480	9,250E-01	780	1,584E-01	1080	2,515E-04	2100	2,785E-03	3600	1,302E-03	5100	< 1,000E-05
490	9,288E-01	790	1,302E-01	1090	2,367E-04	2150	2,752E-03	3650	1,630E-03	5150	< 1,000E-05

Optical properties		Mechanical properties		Colormetric properties				
Reflection factor		Reference thickness		1 mm		2 mm	3 mm	
P _d = 0,920		d = 2,00 mm		Illuminant D65	x	0,308	0,304	0,300
Spectral values guaranteed		Density			y	0,331	0,332	0,334
τ _i (365 nm)	≥ 0,8	ρ = 2,53 g/cm³			Y	85,4	79,3	73,7
τ _i (500 nm)	≥ 0,86	Knoop hardness			λ _d	496 nm	496 nm	496 nm
τ _i (600 nm)	≥ 0,8	HK[0.1/20] = 435			P _e	0,015	0,029	0,042
τ _i (700 nm)	≤ 0,43	Thermal properties		Illuminant A	x	0,440	0,434	0,427
τ _i (800 nm)	≤ 0,09	Transformation temperature			y	0,411	0,415	0,418
τ _i (900 nm)	≤ 0,008	T _g = 565 °C			Y	84,6	77,9	71,9
τ _i (1060 nm)	≤ 0,0001	Thermal expansion in 10 ⁻⁶ /K			λ _d	504 nm	505 nm	505 nm
τ _i (2200 nm)	≤ 0,001	α _{-30°C/+70°C} = 5,4			P _e	0,016	0,031	0,045
Refractive indices		α _{20°C/300°C} = 6,2		Notes				
n _F (486 nm)	= 1,518			UV				
n _e (546 nm)	= 1,515			Transmission changes are possible under the action of intense ultraviolet radiation.				
n _d (587,6 nm)	= 1,513			Ionically colored glass				
Sellmeier coefficients				Shortpass filter				
valid from 400 nm to 1550 nm								
B ₁	1,0371	Chemical properties		Heat protection filter				
B ₂	0,2237	Chemical resistance		ISO 23364:2021				
B ₃	33,7882	FR class = 0						
C ₁	9,265E-03 μm²	SR class = 3		Disclaimer				
C ₂	5,0235E-03 μm²	AR class = 4		All data without tolerances are to be understood to be reference values.				
C ₃	3577,611 μm²	Resistance against humidity						
Internal quality		Delicate glass						
Bubble class 3		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5						

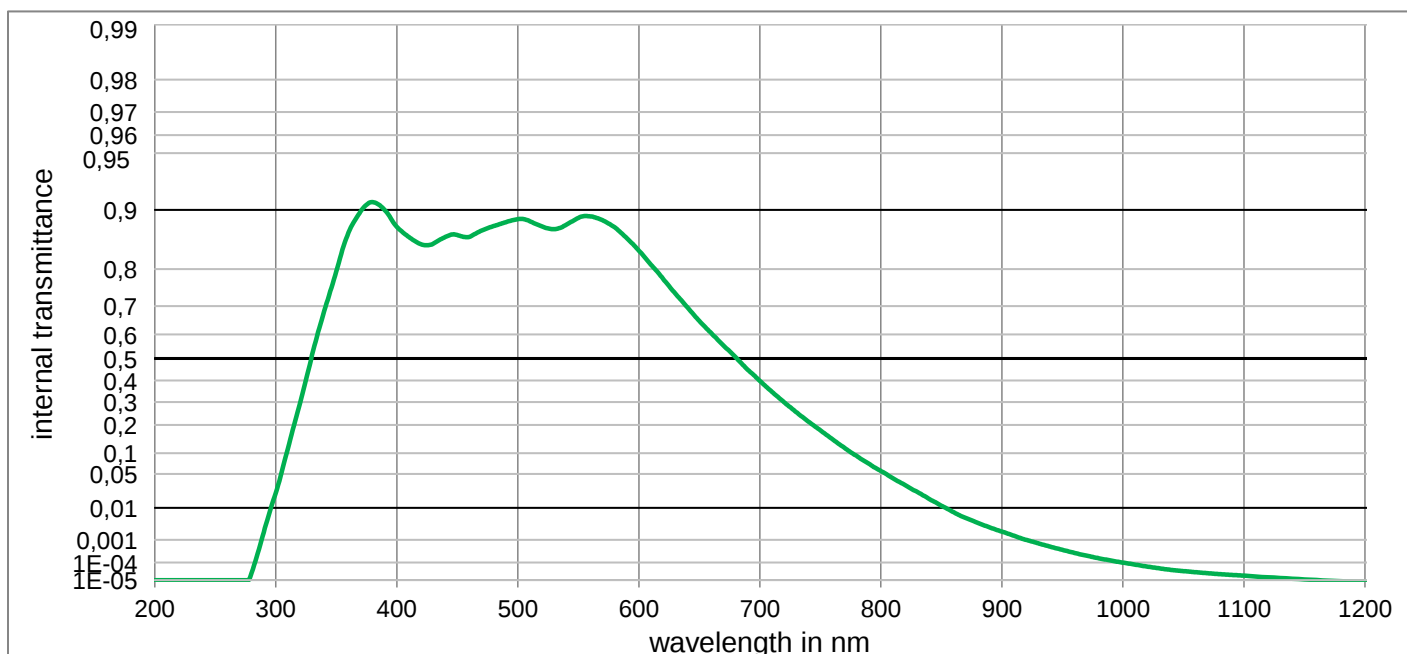


KG5

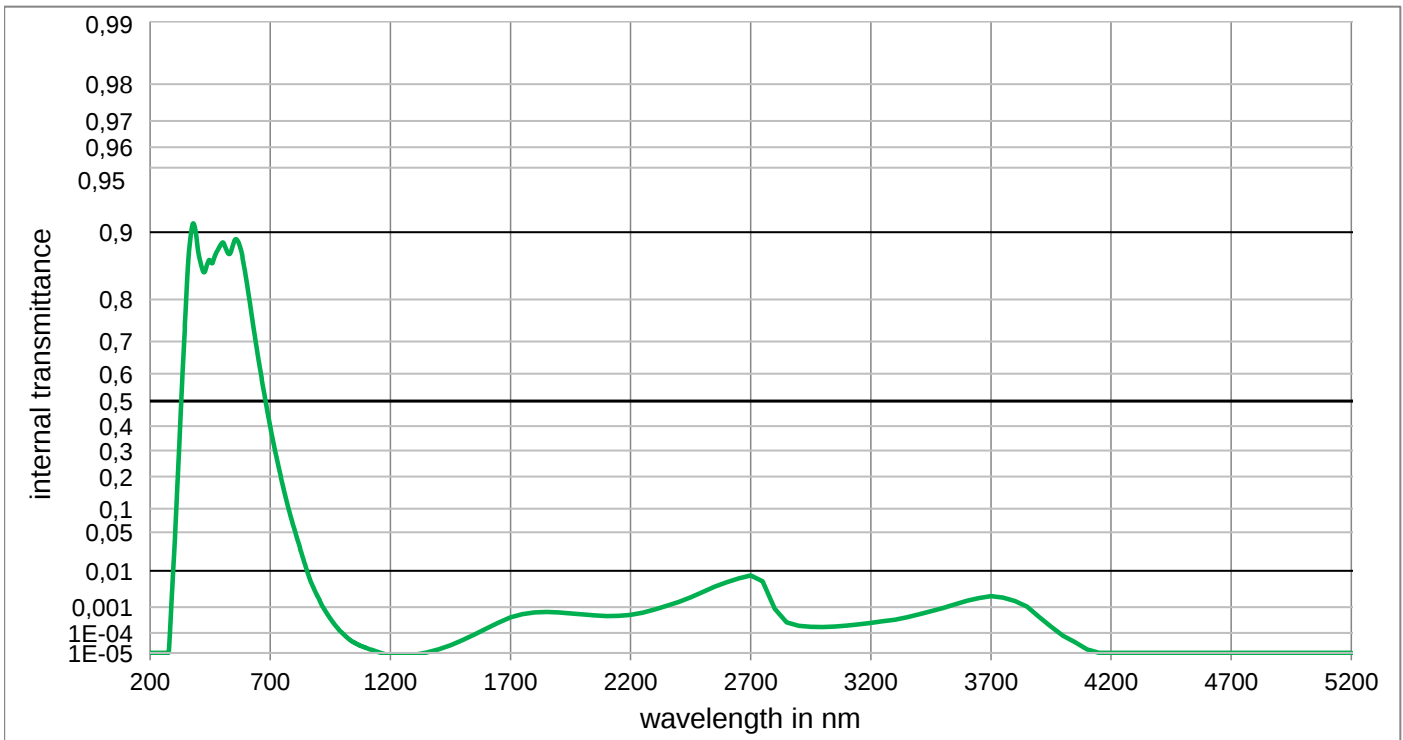Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	8,883E-01	800	5,600E-02	1100	1,875E-05	2200	5,413E-04	3700	2,208E-03
210	< 1,000E-05	510	8,854E-01	810	4,211E-02	1110	1,667E-05	2250	6,482E-04	3750	2,015E-03
220	< 1,000E-05	520	8,781E-01	820	3,171E-02	1120	1,500E-05	2300	8,290E-04	3800	1,577E-03
230	< 1,000E-05	530	8,743E-01	830	2,311E-02	1130	1,370E-05	2350	1,095E-03	3850	1,039E-03
240	< 1,000E-05	540	8,806E-01	840	1,632E-02	1140	1,239E-05	2400	1,479E-03	3900	4,560E-04
250	< 1,000E-05	550	8,900E-01	850	1,135E-02	1150	1,109E-05	2450	2,058E-03	3950	1,861E-04
260	< 1,000E-05	560	8,919E-01	860	7,720E-03	1160	1,007E-05	2500	2,914E-03	4000	7,390E-05
270	< 1,000E-05	570	8,870E-01	870	5,300E-03	1170	< 1,000E-05	2550	4,090E-03	4050	3,650E-05
280	2,793E-05	580	8,770E-01	880	3,839E-03	1180	< 1,000E-05	2600	5,337E-03	4100	1,570E-05
290	1,880E-03	590	8,600E-01	890	2,716E-03	1190	< 1,000E-05	2650	6,620E-03	4150	< 1,000E-05
300	2,200E-02	600	8,380E-01	900	1,990E-03	1200	< 1,000E-05	2700	7,858E-03	4200	< 1,000E-05
310	1,138E-01	610	8,100E-01	910	1,410E-03	1250	< 1,000E-05	2750	5,622E-03	4250	< 1,000E-05
320	2,950E-01	620	7,770E-01	920	1,000E-03	1300	< 1,000E-05	2800	8,872E-04	4300	< 1,000E-05
330	5,160E-01	630	7,380E-01	930	7,311E-04	1350	1,050E-05	2850	2,754E-04	4350	< 1,000E-05
340	6,840E-01	640	6,960E-01	940	5,320E-04	1400	1,549E-05	2900	2,037E-04	4400	< 1,000E-05
350	7,950E-01	650	6,500E-01	950	3,917E-04	1450	2,588E-05	2950	1,856E-04	4450	< 1,000E-05
360	8,690E-01	660	6,040E-01	960	2,877E-04	1500	4,550E-05	3000	1,817E-04	4500	< 1,000E-05
370	8,980E-01	670	5,550E-01	970	2,153E-04	1550	8,507E-05	3050	1,894E-04	4550	< 1,000E-05
380	9,090E-01	680	5,050E-01	980	1,633E-04	1600	1,545E-04	3100	2,083E-04	4600	< 1,000E-05
390	8,998E-01	690	4,500E-01	990	1,256E-04	1650	2,683E-04	3150	2,330E-04	4650	< 1,000E-05
400	8,774E-01	700	3,980E-01	1000	9,931E-05	1700	4,375E-04	3200	2,670E-04	4700	< 1,000E-05
410	8,619E-01	710	3,470E-01	1010	7,816E-05	1750	5,757E-04	3250	3,098E-04	4750	< 1,000E-05
420	8,497E-01	720	2,990E-01	1020	6,166E-05	1800	6,608E-04	3300	3,557E-04	4800	< 1,000E-05
430	8,505E-01	730	2,550E-01	1030	4,932E-05	1850	6,868E-04	3350	4,320E-04	4850	< 1,000E-05
440	8,619E-01	740	2,140E-01	1040	4,055E-05	1900	6,537E-04	3400	5,640E-04	4900	< 1,000E-05
450	8,651E-01	750	1,780E-01	1050	3,467E-05	1950	6,034E-04	3450	7,280E-04	4950	< 1,000E-05
460	8,620E-01	760	1,450E-01	1060	3,006E-05	2000	5,593E-04	3500	9,320E-04	5000	< 1,000E-05
470	8,720E-01	770	1,160E-01	1070	2,630E-05	2050	5,136E-04	3550	1,222E-03	5050	< 1,000E-05
480	8,787E-01	780	9,200E-02	1080	2,323E-05	2100	4,851E-04	3600	1,604E-03	5100	< 1,000E-05
490	8,841E-01	790	7,200E-02	1090	2,075E-05	2150	4,927E-04	3650	1,950E-03	5150	< 1,000E-05

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,918$	$d = 1,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed	Density	x
$\tau_i (546 \text{ nm}) < 0,0001$	$\rho = 2,48 \text{ g/cm}^3$	y
	Knoop hardness	Y
	$HK[0.1/20] = 418$	λ_d
		P_e
	Thermal properties	Illuminant A
	Transformation temperature	x
	$T_g = 461 \text{ }^\circ\text{C}$	y
	Thermal expansion in $10^{-6}/\text{K}$	Y
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 6,5$	λ_d
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 7,0$	P_e
Refractive indices		
$n_F (486 \text{ nm}) = 1,527$		
$n_e (546 \text{ nm}) = 1,526$		
$n_d (587,6 \text{ nm}) = 1,522$		
Sellmeier coefficients	Chemical properties	Notes
valid from 440 nm to 1550 nm	Chemical resistance	
$B_1 = 0,8361$	FR class = 1	Ionically colored glass
$B_2 = 0,4344$	SR class = 2.2	Neutral density filter
$B_3 = 0,8624$	AR class = 1	
$C_1 = 1,081\text{E-}02 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,1185\text{E-}02 \text{ } \mu\text{m}^2$		ISO 23364:2021
$C_3 = 100,000 \text{ } \mu\text{m}^2$		
Internal quality		Disclaimer
Bubble class 2		All data without tolerances are to be understood to be reference values.

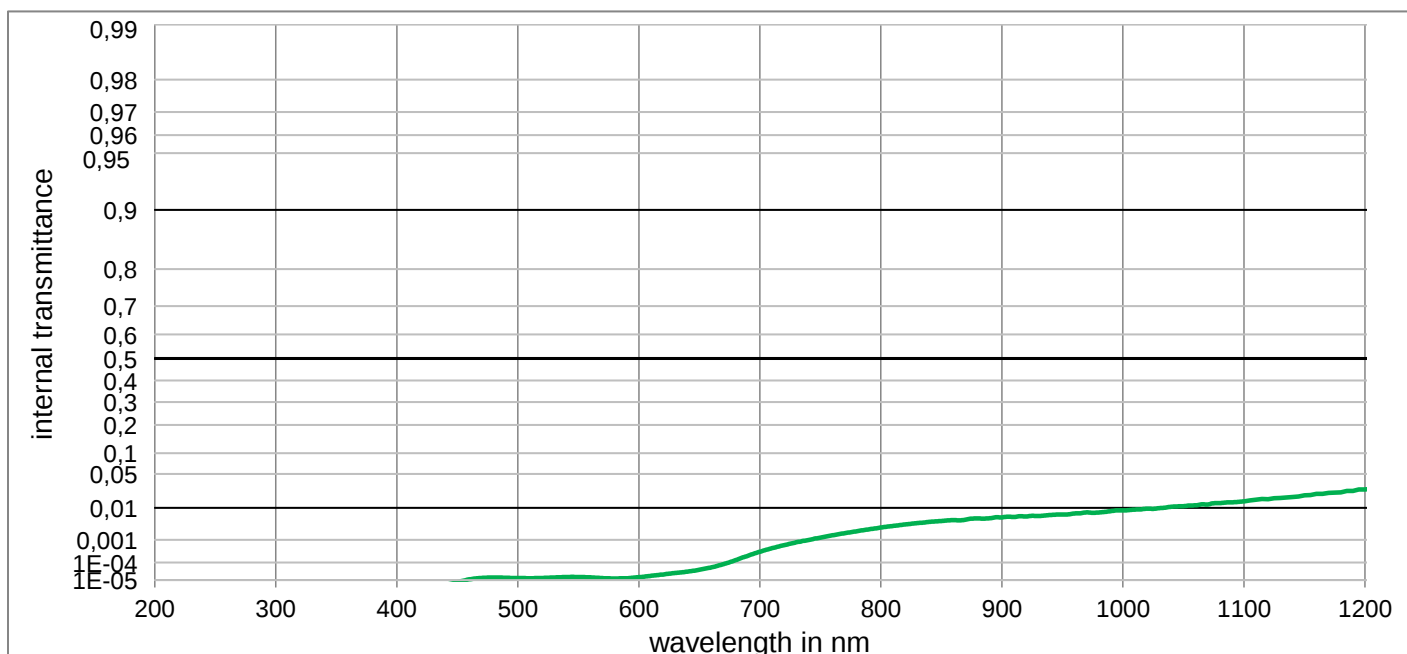


NG1

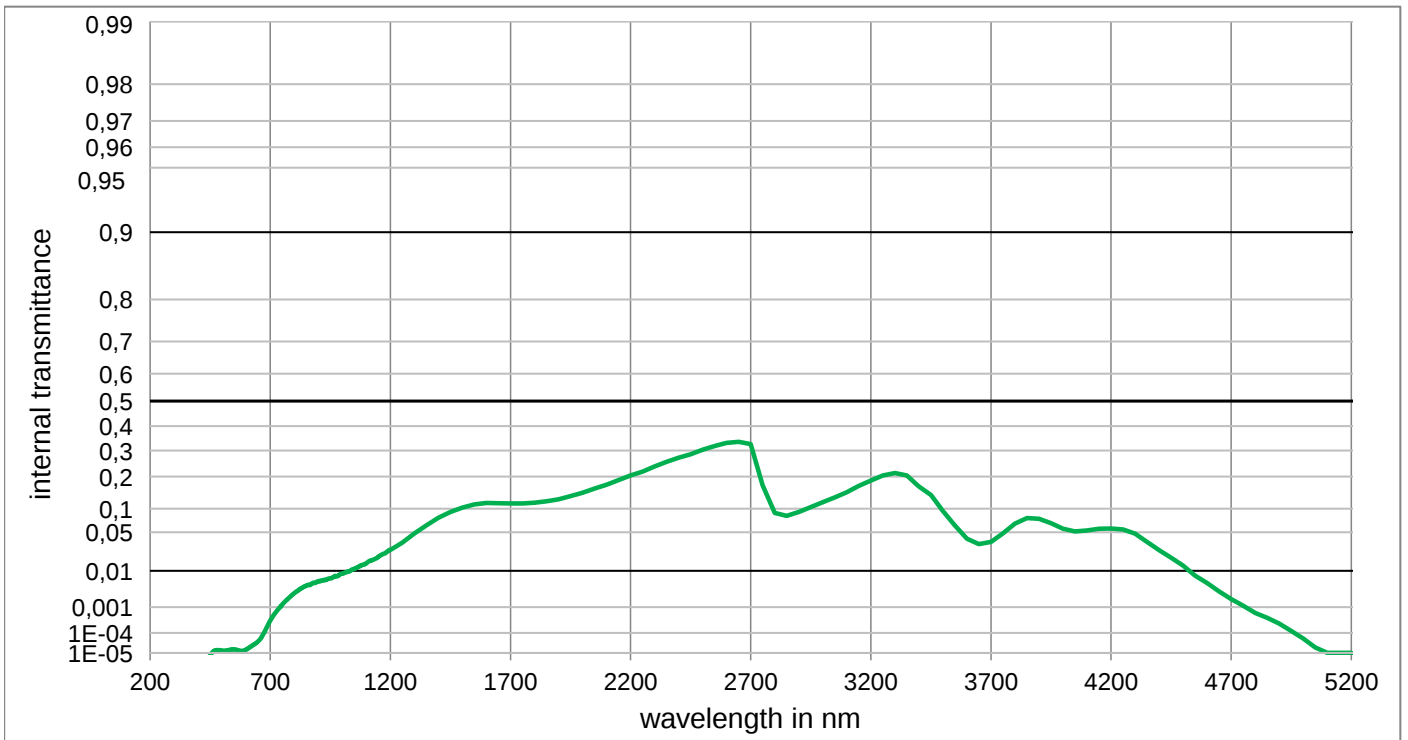Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,000E-05	500	1,340E-05	800	2,710E-03	1100	1,444E-02	2200	2,037E-01	3700	3,550E-02
210	< 1,000E-05	510	1,317E-05	810	3,039E-03	1110	1,580E-02	2250	2,186E-01	3750	4,830E-02
220	< 1,000E-05	520	1,365E-05	820	3,391E-03	1120	1,615E-02	2300	2,378E-01	3800	6,600E-02
230	< 1,000E-05	530	1,459E-05	830	3,730E-03	1130	1,720E-02	2350	2,555E-01	3850	7,740E-02
240	< 1,000E-05	540	1,559E-05	840	4,067E-03	1140	1,811E-02	2400	2,719E-01	3900	7,590E-02
250	< 1,000E-05	550	1,559E-05	850	4,328E-03	1150	1,976E-02	2450	2,853E-01	3950	6,660E-02
260	< 1,000E-05	560	1,482E-05	860	4,614E-03	1160	2,103E-02	2500	3,031E-01	4000	5,590E-02
270	< 1,000E-05	570	1,338E-05	870	4,761E-03	1170	2,212E-02	2550	3,186E-01	4050	5,129E-02
280	< 1,000E-05	580	1,272E-05	880	5,150E-03	1180	2,265E-02	2600	3,308E-01	4100	5,300E-02
290	< 1,000E-05	590	1,315E-05	890	5,234E-03	1190	2,446E-02	2650	3,354E-01	4150	5,610E-02
300	< 1,000E-05	600	1,533E-05	900	5,543E-03	1200	2,600E-02	2700	3,265E-01	4200	5,670E-02
310	< 1,000E-05	610	1,841E-05	910	5,665E-03	1250	3,480E-02	2750	1,700E-01	4250	5,495E-02
320	< 1,000E-05	620	2,208E-05	920	5,865E-03	1300	4,830E-02	2800	8,940E-02	4300	4,786E-02
330	< 1,000E-05	630	2,692E-05	930	6,039E-03	1350	6,230E-02	2850	8,230E-02	4350	3,548E-02
340	< 1,000E-05	640	3,251E-05	940	6,463E-03	1400	7,810E-02	2900	9,160E-02	4400	2,570E-02
350	< 1,000E-05	650	4,074E-05	950	6,682E-03	1450	9,190E-02	2950	1,043E-01	4450	1,862E-02
360	< 1,000E-05	660	5,559E-05	960	7,102E-03	1500	1,029E-01	3000	1,171E-01	4500	1,288E-02
370	< 1,000E-05	670	8,318E-05	970	7,607E-03	1550	1,114E-01	3050	1,313E-01	4550	7,762E-03
380	< 1,000E-05	680	1,321E-04	980	7,578E-03	1600	1,150E-01	3100	1,469E-01	4600	5,129E-03
390	< 1,000E-05	690	2,104E-04	990	8,216E-03	1650	1,143E-01	3150	1,675E-01	4650	3,020E-03
400	< 1,000E-05	700	3,243E-04	1000	8,560E-03	1700	1,136E-01	3200	1,860E-01	4700	1,820E-03
410	< 1,000E-05	710	4,624E-04	1010	9,052E-03	1750	1,136E-01	3250	2,040E-01	4750	1,122E-03
420	< 1,000E-05	720	6,152E-04	1020	9,580E-03	1800	1,157E-01	3300	2,129E-01	4800	6,310E-04
430	< 1,000E-05	730	7,998E-04	1030	9,838E-03	1850	1,200E-01	3350	2,044E-01	4850	4,169E-04
440	< 1,000E-05	740	9,863E-04	1040	1,064E-02	1900	1,256E-01	3400	1,661E-01	4900	2,455E-04
450	< 1,000E-05	750	1,208E-03	1050	1,101E-02	1950	1,349E-01	3450	1,384E-01	4950	1,230E-04
460	1,119E-05	760	1,469E-03	1060	1,158E-02	2000	1,455E-01	3500	9,440E-02	5000	5,495E-05
470	1,365E-05	770	1,738E-03	1070	1,212E-02	2050	1,590E-01	3550	6,250E-02	5050	1,995E-05
480	1,434E-05	780	2,046E-03	1080	1,309E-02	2100	1,718E-01	3600	4,000E-02	5100	< 1,000E-05
490	1,409E-05	790	2,360E-03	1090	1,361E-02	2150	1,876E-01	3650	3,270E-02	5150	< 1,000E-05

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,921$	$d = 1,00 \text{ mm}$	Illuminant D65
Spectral values guaranteed	Density	x
$\tau_i (405 \text{ nm}) = 0,06 \pm 0,02$	$\rho = 2,44 \text{ g/cm}^3$	y
$\tau_i (546 \text{ nm}) = 0,1 \pm 0,02$	Knoop hardness	Y
$\tau_i (694 \text{ nm}) = 0,17 \pm 0,03$	$HK[0.1/20] = 443$	λ_d
		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	Notes
$n_h (404,7 \text{ nm}) = 1,523$	Transformation temperature	
$n_e (546 \text{ nm}) = 1,509$	$T_g = 462 \text{ }^\circ\text{C}$	
$n_d (587,6 \text{ nm}) = 1,507$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 6,5$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 7,3$	
		Ionically colored glass
Sellmeier coefficients	Chemical properties	
valid from 440 nm to 1550 nm	Chemical resistance	
$B_1 = 0,8995$	FR class = 1	
$B_2 = 0,3364$	SR class = 2.2	
$B_3 = 32,4433$	AR class = 1	ISO 23364:2021
$C_1 = 9,703\text{E-}03 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,2385\text{E-}02 \text{ } \mu\text{m}^2$	Resistant glass	
$C_3 = 4153,754 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
Internal quality		
Bubble class 2		Disclaimer
		All data without tolerances are to be understood to be reference values.

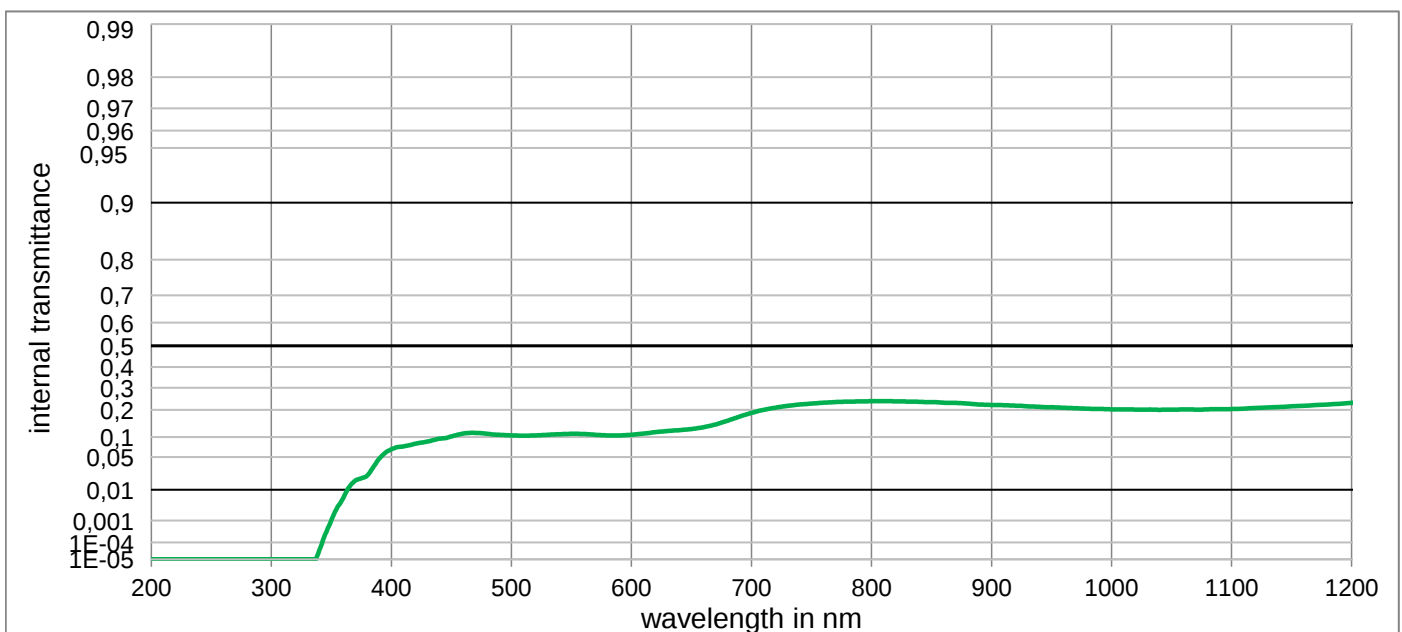

NG3

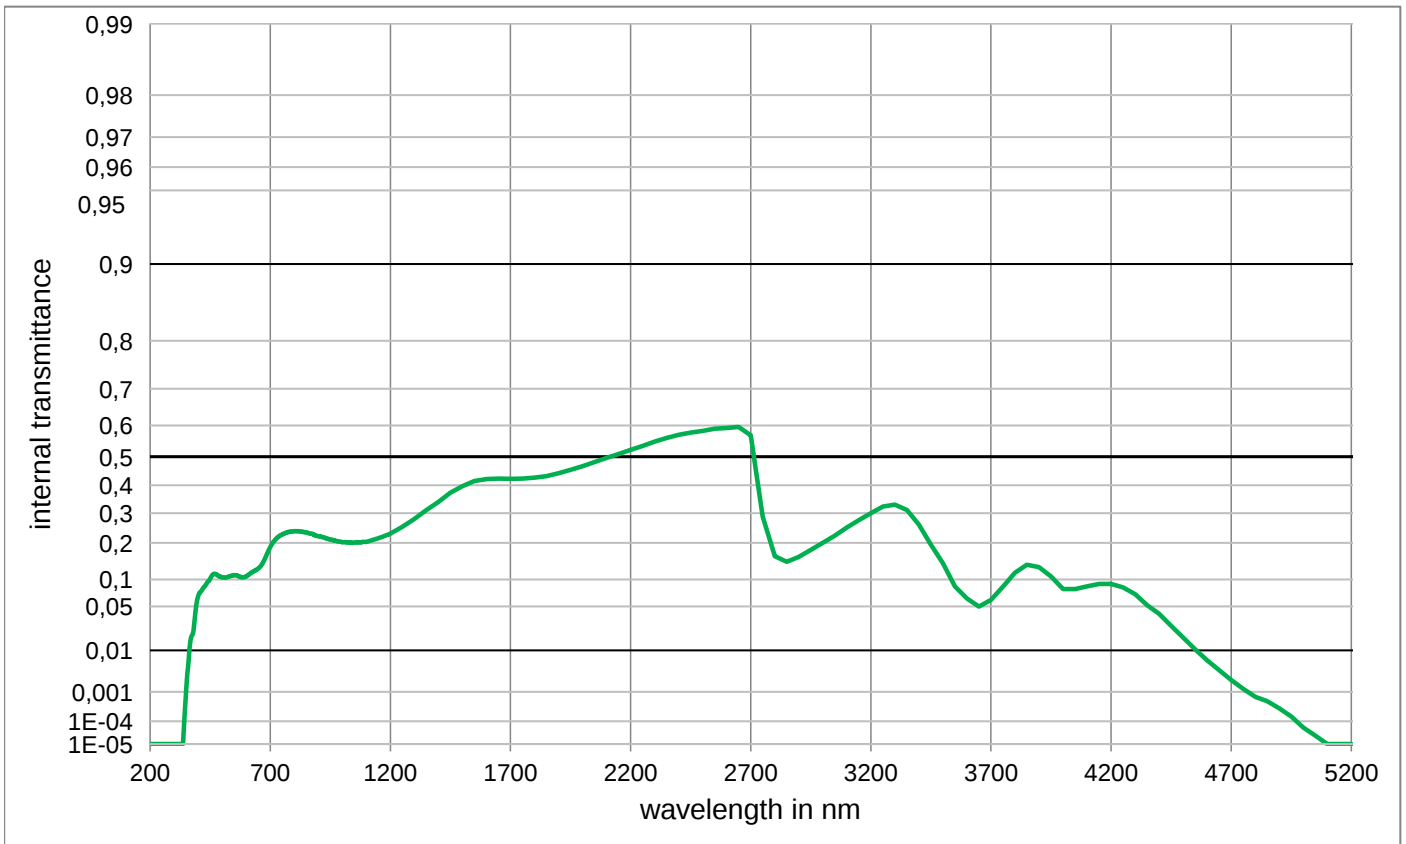Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	1,050E-01	800	2,380E-01	1100	2,034E-01	2200	5,225E-01	3700	6,000E-02
210	< 1,0E-05	510	1,043E-01	810	2,375E-01	1110	2,054E-01	2250	5,360E-01	3750	8,480E-02
220	< 1,0E-05	520	1,050E-01	820	2,370E-01	1120	2,077E-01	2300	5,500E-01	3800	1,156E-01
230	< 1,0E-05	530	1,070E-01	830	2,360E-01	1130	2,100E-01	2350	5,617E-01	3850	1,363E-01
240	< 1,0E-05	540	1,090E-01	840	2,350E-01	1140	2,124E-01	2400	5,711E-01	3900	1,300E-01
250	< 1,0E-05	550	1,100E-01	850	2,340E-01	1150	2,149E-01	2450	5,786E-01	3950	1,068E-01
260	< 1,0E-05	560	1,095E-01	860	2,310E-01	1160	2,175E-01	2500	5,837E-01	4000	8,000E-02
270	< 1,0E-05	570	1,071E-01	870	2,300E-01	1170	2,202E-01	2550	5,900E-01	4050	8,000E-02
280	< 1,0E-05	580	1,050E-01	880	2,270E-01	1180	2,232E-01	2600	5,925E-01	4100	8,511E-02
290	< 1,0E-05	590	1,049E-01	890	2,230E-01	1190	2,263E-01	2650	5,956E-01	4150	9,016E-02
300	< 1,0E-05	600	1,070E-01	900	2,210E-01	1200	2,300E-01	2700	5,700E-01	4200	9,000E-02
310	< 1,0E-05	610	1,110E-01	910	2,200E-01	1250	2,532E-01	2750	2,880E-01	4250	8,318E-02
320	< 1,000E-05	620	1,157E-01	920	2,180E-01	1300	2,800E-01	2800	1,600E-01	4300	7,000E-02
330	< 1,000E-05	630	1,192E-01	930	2,150E-01	1350	3,110E-01	2850	1,439E-01	4350	5,176E-02
340	3,855E-05	640	1,222E-01	940	2,130E-01	1400	3,400E-01	2900	1,574E-01	4400	4,000E-02
350	1,040E-03	650	1,260E-01	950	2,110E-01	1450	3,732E-01	2950	1,784E-01	4450	2,679E-02
360	5,900E-03	660	1,319E-01	960	2,090E-01	1500	3,970E-01	3000	2,000E-01	4500	1,726E-02
370	1,704E-02	670	1,420E-01	970	2,070E-01	1550	4,147E-01	3050	2,224E-01	4550	1,050E-02
380	2,199E-02	680	1,560E-01	980	2,050E-01	1600	4,216E-01	3100	2,500E-01	4600	6,237E-03
390	4,696E-02	690	1,720E-01	990	2,040E-01	1650	4,241E-01	3150	2,752E-01	4650	3,750E-03
400	6,691E-02	700	1,871E-01	1000	2,020E-01	1700	4,230E-01	3200	3,000E-01	4700	2,128E-03
410	7,402E-02	710	2,000E-01	1010	2,022E-01	1750	4,241E-01	3250	3,236E-01	4750	1,222E-03
420	8,105E-02	720	2,094E-01	1020	2,010E-01	1800	4,273E-01	3300	3,300E-01	4800	7,096E-04
430	8,703E-02	730	2,170E-01	1030	2,012E-01	1850	4,325E-01	3350	3,116E-01	4850	5,200E-04
440	9,500E-02	740	2,230E-01	1040	2,000E-01	1900	4,425E-01	3400	2,600E-01	4900	2,985E-04
450	1,019E-01	750	2,270E-01	1050	2,010E-01	1950	4,546E-01	3450	1,948E-01	4950	1,528E-04
460	1,110E-01	760	2,310E-01	1060	2,020E-01	2000	4,674E-01	3500	1,400E-01	5000	5,649E-05
470	1,130E-01	770	2,340E-01	1070	2,010E-01	2050	4,813E-01	3550	8,540E-02	5050	2,518E-05
480	1,100E-01	780	2,360E-01	1080	2,020E-01	2100	4,957E-01	3600	6,220E-02	5100	< 1,000E-05
490	1,070E-01	790	2,370E-01	1090	2,029E-01	2150	5,090E-01	3650	4,960E-02	5150	< 1,000E-05

Optical properties		
Reflection factor		
P _d = 0,922		
Spectral values guaranteed		
τ _i (405 nm)	=	0,27 ± 0,03
τ _i (546 nm)	=	0,31 ± 0,03
τ _i (694 nm)	=	0,39 ± 0,04
Refractive indices		
n _h (404,7 nm)	=	1,517
n _e (546 nm)	=	1,505
n _d (587,6 nm)	=	1,503
Sellmeier coefficients		
valid from 440 nm to 1550 nm		
B ₁		0,6033
B ₂		0,6255
B ₃		54,9099
C ₁		4,261E-03 μm ²
C ₂		1,4068E-02 μm ²
C ₃		5448,332 μm ²
Internal quality		
Bubble class		2


Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,42 g/cm ³	
Knoop hardness	
HK[0.1/20] = 423	

Thermal properties	
Transformation temperature	
T _g = 470 °C	
Thermal expansion in 10 ⁻⁶ /K	
α _(-30°C/+70°C) = 6,5	
α _(20°C/300°C) = 7,1	


Chemical properties	
Chemical resistance	
FR class = 1	
SR class = 2.2	
AR class = 1	
Resistance against humidity	
Resistant glass	
see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	

Colorimetric properties			
	1 mm	2 mm	3 mm
Illuminant D65	x		
	y		
	Y		
	λ _d		
	P _e		
Illuminant A	x		
	y		
	Y		
	λ _d		
	P _e		

Notes
Ionically colored glass
Neutral density filter
ISO 23364:2021
Disclaimer
All data without tolerances are to be understood to be reference values.

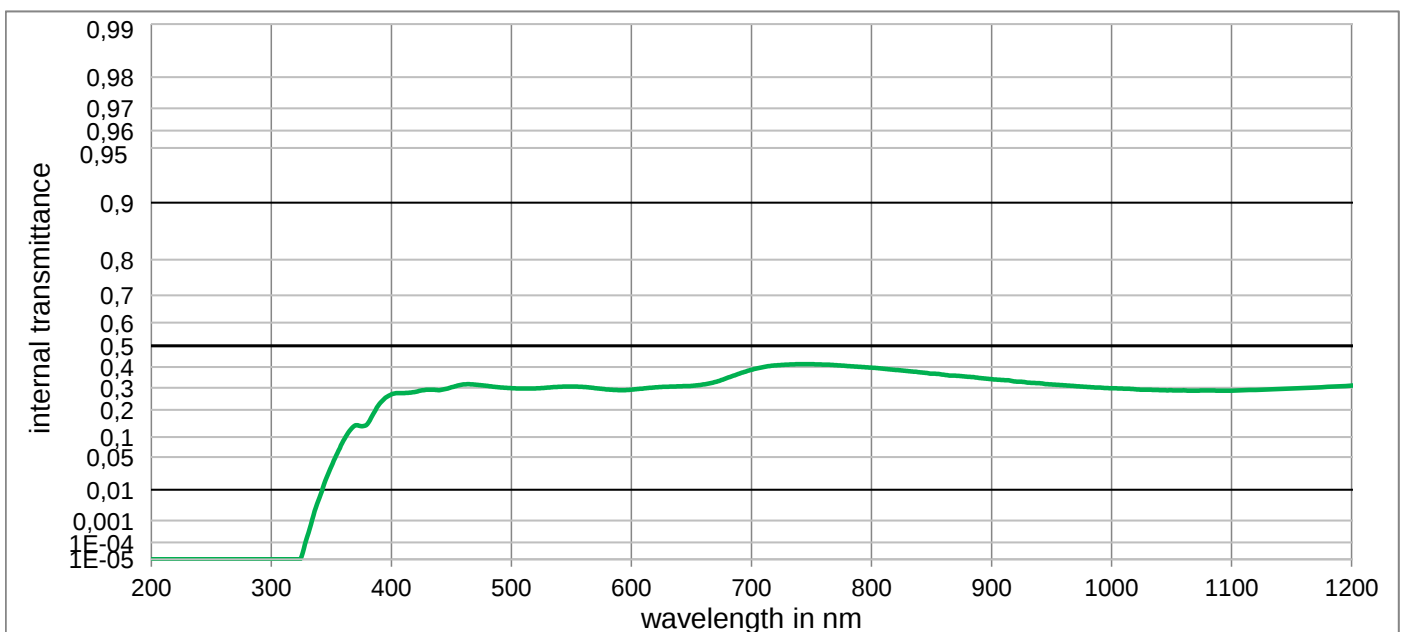


NG4

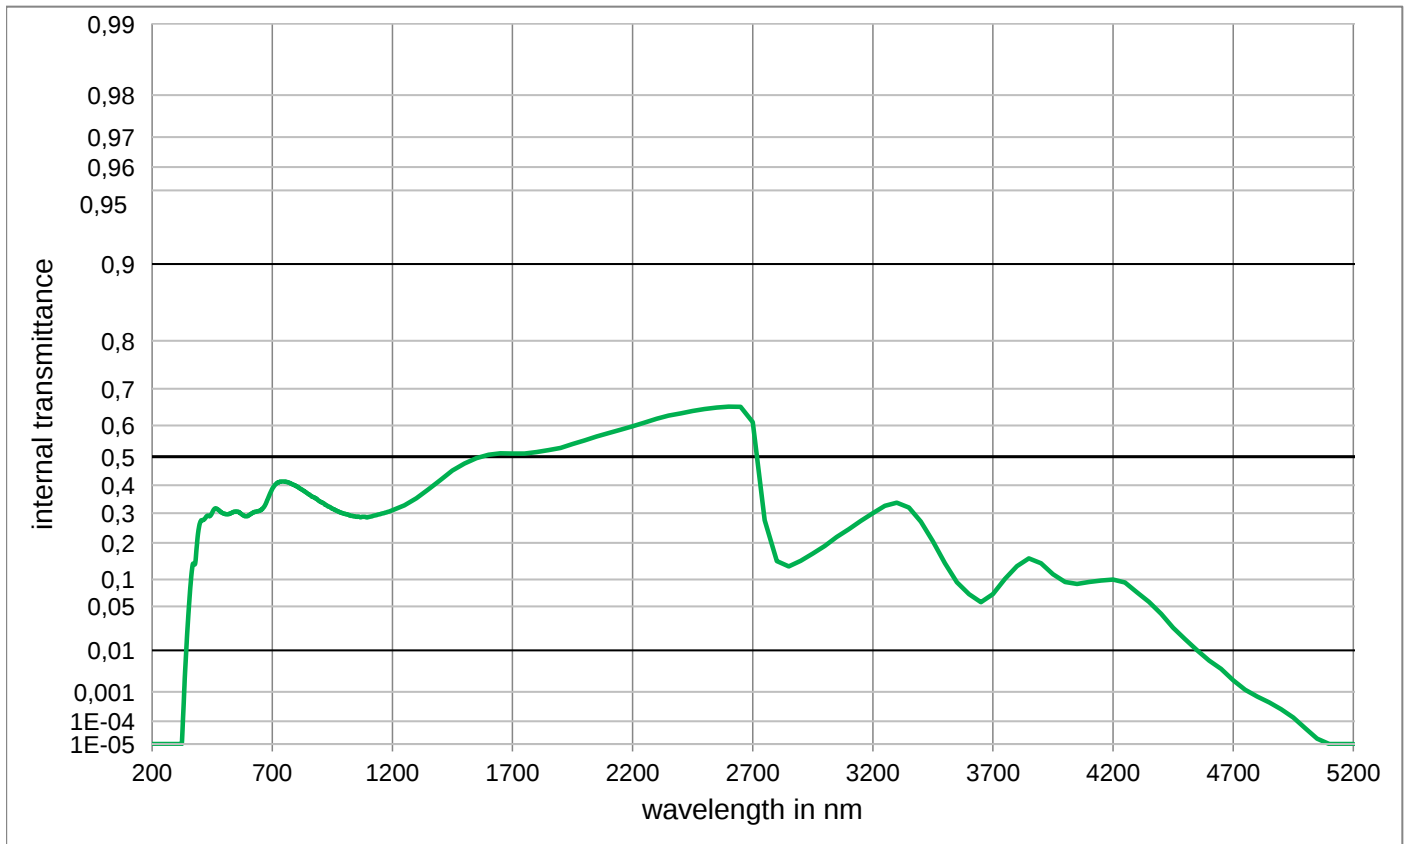Internal transmittance τ_i at reference thickness


The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	2,980E-01	800	3,970E-01	1100	2,860E-01	2200	5,974E-01	3700	7,000E-02
210	< 1,0E-05	510	2,962E-01	810	3,920E-01	1110	2,882E-01	2250	6,084E-01	3750	1,012E-01
220	< 1,0E-05	520	2,971E-01	820	3,860E-01	1120	2,902E-01	2300	6,200E-01	3800	1,327E-01
230	< 1,0E-05	530	3,007E-01	830	3,807E-01	1130	2,924E-01	2350	6,289E-01	3850	1,539E-01
240	< 1,0E-05	540	3,046E-01	840	3,750E-01	1140	2,945E-01	2400	6,355E-01	3900	1,400E-01
250	< 1,0E-05	550	3,060E-01	850	3,680E-01	1150	2,968E-01	2450	6,421E-01	3950	1,121E-01
260	< 1,0E-05	560	3,040E-01	860	3,630E-01	1160	2,991E-01	2500	6,472E-01	4000	9,441E-02
270	< 1,0E-05	570	2,983E-01	870	3,580E-01	1170	3,016E-01	2550	6,516E-01	4050	9,000E-02
280	< 1,0E-05	580	2,920E-01	880	3,530E-01	1180	3,042E-01	2600	6,538E-01	4100	9,441E-02
290	< 1,0E-05	590	2,890E-01	890	3,470E-01	1190	3,069E-01	2650	6,531E-01	4150	9,772E-02
300	< 1,0E-05	600	2,910E-01	900	3,410E-01	1200	3,100E-01	2700	6,100E-01	4200	1,000E-01
310	< 1,0E-05	610	2,966E-01	910	3,370E-01	1250	3,276E-01	2750	2,750E-01	4250	9,333E-02
320	< 1,000E-05	620	3,018E-01	920	3,300E-01	1300	3,533E-01	2800	1,459E-01	4300	7,330E-02
330	1,991E-04	630	3,050E-01	930	3,250E-01	1350	3,855E-01	2850	1,319E-01	4350	5,675E-02
340	6,039E-03	640	3,070E-01	940	3,220E-01	1400	4,185E-01	2900	1,466E-01	4400	4,000E-02
350	3,390E-02	650	3,090E-01	950	3,160E-01	1450	4,523E-01	2950	1,679E-01	4450	2,500E-02
360	8,880E-02	660	3,159E-01	960	3,120E-01	1500	4,764E-01	3000	1,900E-01	4500	1,611E-02
370	1,391E-01	670	3,279E-01	970	3,080E-01	1550	4,948E-01	3050	2,184E-01	4550	1,000E-02
380	1,439E-01	680	3,480E-01	980	3,040E-01	1600	5,065E-01	3100	2,448E-01	4600	6,166E-03
390	2,250E-01	690	3,685E-01	990	3,010E-01	1650	5,116E-01	3150	2,727E-01	4650	4,000E-03
400	2,689E-01	700	3,870E-01	1000	2,980E-01	1700	5,109E-01	3200	3,000E-01	4700	2,104E-03
410	2,750E-01	710	4,000E-01	1010	2,960E-01	1750	5,109E-01	3250	3,262E-01	4750	1,153E-03
420	2,809E-01	720	4,080E-01	1020	2,930E-01	1800	5,153E-01	3300	3,372E-01	4800	7,261E-04
430	2,910E-01	730	4,117E-01	1030	2,910E-01	1850	5,219E-01	3350	3,200E-01	4850	4,688E-04
440	2,890E-01	740	4,134E-01	1040	2,890E-01	1900	5,292E-01	3400	2,700E-01	4900	2,786E-04
450	3,020E-01	750	4,135E-01	1050	2,880E-01	1950	5,417E-01	3450	2,052E-01	4950	1,393E-04
460	3,160E-01	760	4,115E-01	1060	2,880E-01	2000	5,534E-01	3500	1,400E-01	5000	5,212E-05
470	3,150E-01	770	4,090E-01	1070	2,860E-01	2050	5,659E-01	3550	9,380E-02	5050	1,820E-05
480	3,089E-01	780	4,050E-01	1080	2,870E-01	2100	5,769E-01	3600	7,000E-02	5100	< 1,000E-05
490	3,020E-01	790	4,010E-01	1090	2,860E-01	2150	5,871E-01	3650	5,640E-02	5150	< 1,000E-05

Optical properties		Mechanical properties		Colormetric properties		
Reflection factor		Reference thickness		1 mm2 mm3 mm		
P _d = 0,923		d = 1,00 mm		Illuminant D65	x	
Spectral values guaranteed		Density			y	
τ _i (405 nm) = 0,56 ± 0,03		ρ = 2,42 g/cm³			Y	
τ _i (546 nm) = 0,57 ± 0,03		Knoop hardness			λ _d	
τ _i (694 nm) = 0,62 ± 0,03		HK[0.1/20] = 435			P _e	
		Thermal properties		Illuminant A	x	
		Transformation temperature			y	
		T _g = 474 °C			Y	
		Thermal expansion in 10 ⁻⁶ /K			λ _d	
		α _(-30°C/+70°C) = 6,6			P _e	
		α _(20°C/300°C) = 7,1		Notes		
Refractive indices		Chemical properties		Ionically colored glass		
n _h (404,7 nm) = 1,514		Chemical resistance		Neutral density filter		
n _e (546 nm) = 1,502		FR class = 1				
n _d (587,6 nm) = 1,5		SR class = 3.2				
		AR class = 2		ISO 23364:2021		
Sellmeier coefficients		Resistance against humidity <td colspan="3" rowspan="2"> Disclaimer </td>		Disclaimer		
valid from 440 nm to 1550 nm		Resistant glass				
B ₁ 0,7916		see pocket catalogue "Optical Filter Glass 2024", chapter 5.5		All data without tolerances are to be understood to be reference values.		
B ₂ 0,4296						
B ₃ 36,0098						
C ₁ 7,310E-03 μm²						
C ₂ 1,2655E-02 μm²						
C ₃ 3759,685 μm²						
Internal quality						
Bubble class 2						

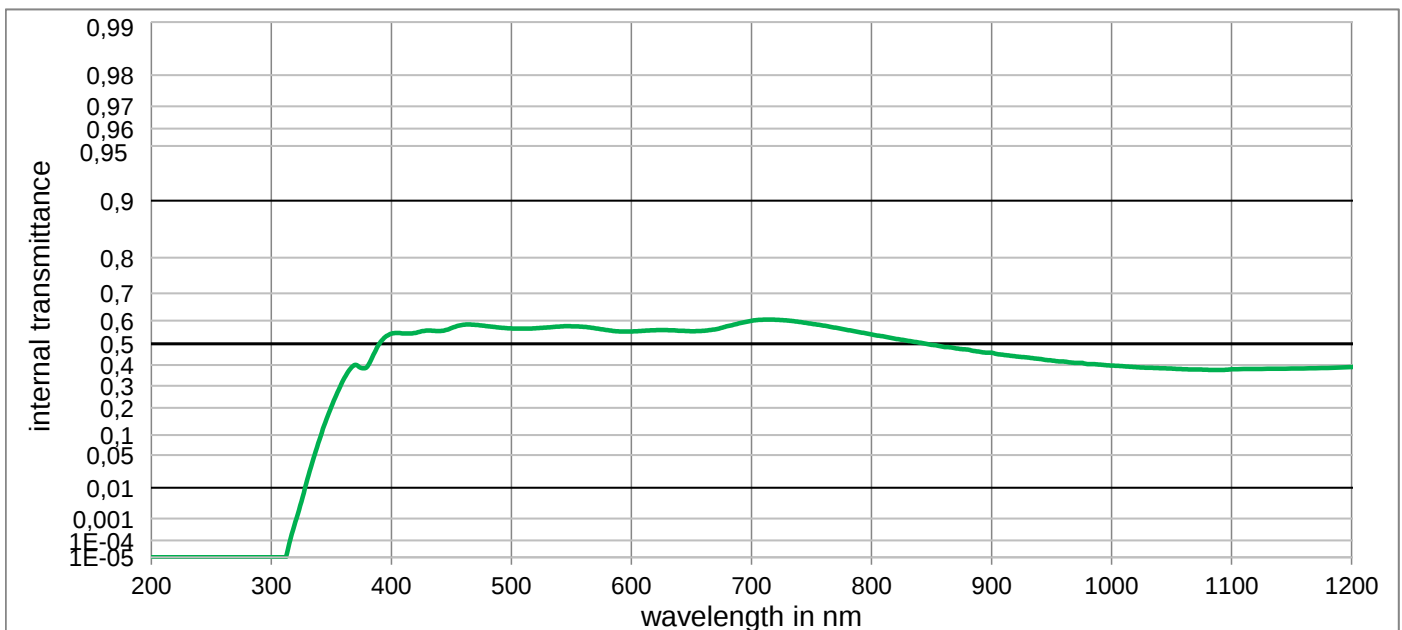


NG5

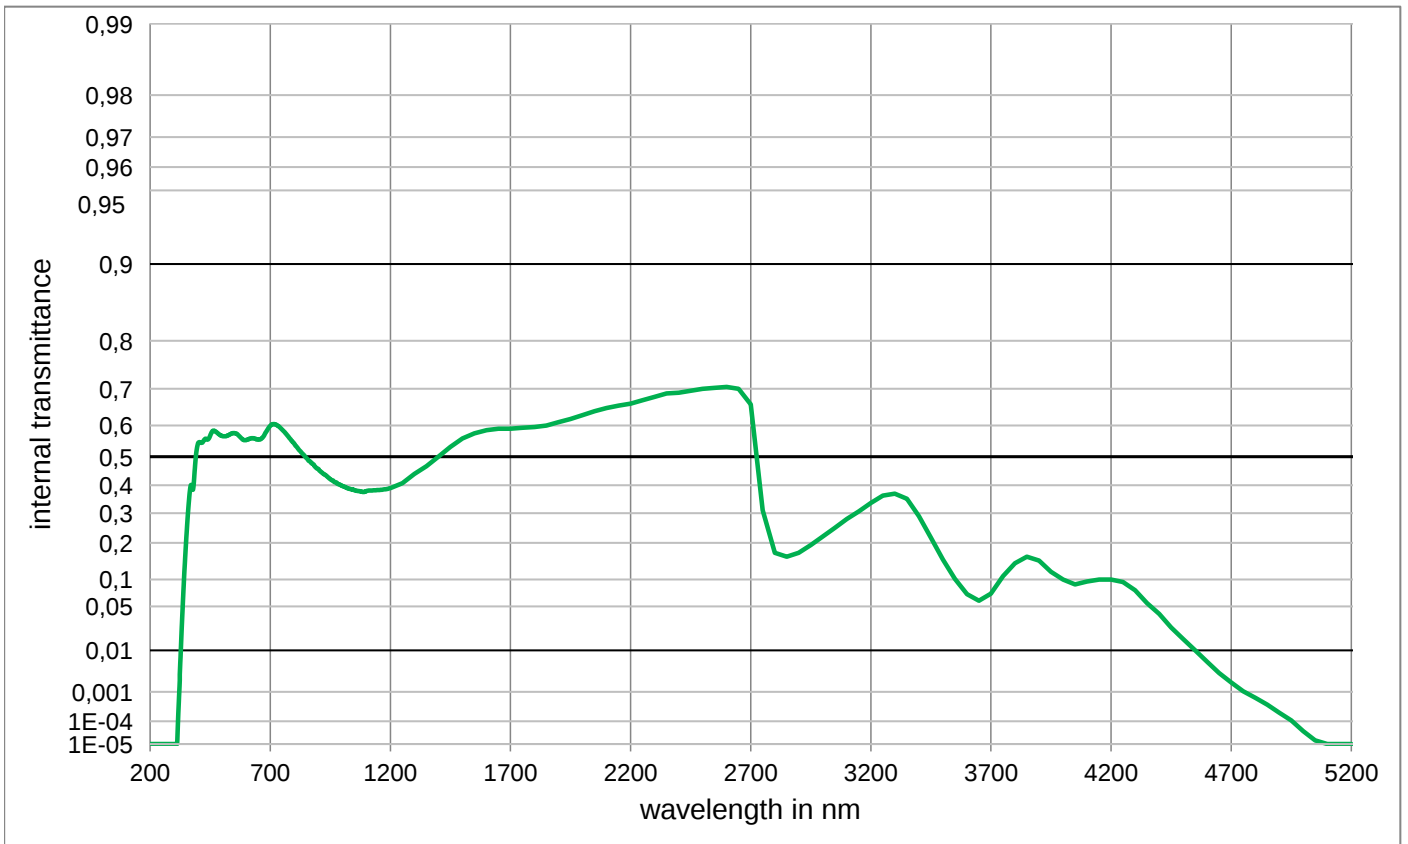
Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	5,677E-01	800	5,424E-01	1100	3,794E-01	2200	6,619E-01	3700	7,110E-02
210	< 1,0E-05	510	5,667E-01	810	5,337E-01	1110	3,808E-01	2250	6,707E-01	3750	1,077E-01
220	< 1,0E-05	520	5,684E-01	820	5,230E-01	1120	3,812E-01	2300	6,800E-01	3800	1,400E-01
230	< 1,0E-05	530	5,717E-01	830	5,142E-01	1130	3,816E-01	2350	6,883E-01	3850	1,583E-01
240	< 1,0E-05	540	5,757E-01	840	5,055E-01	1140	3,821E-01	2400	6,900E-01	3900	1,473E-01
250	< 1,0E-05	550	5,767E-01	850	4,955E-01	1150	3,827E-01	2450	6,949E-01	3950	1,180E-01
260	< 1,0E-05	560	5,747E-01	860	4,857E-01	1160	3,835E-01	2500	7,000E-01	4000	1,000E-01
270	< 1,0E-05	570	5,682E-01	870	4,796E-01	1170	3,845E-01	2550	7,022E-01	4050	8,913E-02
280	< 1,0E-05	580	5,605E-01	880	4,735E-01	1180	3,858E-01	2600	7,044E-01	4100	9,550E-02
290	< 1,0E-05	590	5,549E-01	890	4,636E-01	1190	3,875E-01	2650	7,000E-01	4150	1,000E-01
300	< 1,0E-05	600	5,548E-01	900	4,585E-01	1200	3,900E-01	2700	6,600E-01	4200	1,000E-01
310	< 1,0E-05	610	5,579E-01	910	4,487E-01	1250	4,075E-01	2750	3,108E-01	4250	9,441E-02
320	7,413E-04	620	5,602E-01	920	4,416E-01	1300	4,400E-01	2800	1,700E-01	4300	7,762E-02
330	1,600E-02	630	5,604E-01	930	4,364E-01	1350	4,676E-01	2850	1,583E-01	4350	5,495E-02
340	8,600E-02	640	5,578E-01	940	4,293E-01	1400	5,000E-01	2900	1,700E-01	4400	4,000E-02
350	2,050E-01	650	5,558E-01	950	4,220E-01	1450	5,321E-01	2950	1,935E-01	4450	2,512E-02
360	3,280E-01	660	5,576E-01	960	4,175E-01	1500	5,600E-01	3000	2,200E-01	4500	1,622E-02
370	4,012E-01	670	5,643E-01	970	4,104E-01	1550	5,761E-01	3050	2,485E-01	4550	1,000E-02
380	3,930E-01	680	5,773E-01	980	4,050E-01	1600	5,857E-01	3100	2,800E-01	4600	5,821E-03
390	5,000E-01	690	5,891E-01	990	4,022E-01	1650	5,900E-01	3150	3,057E-01	4650	3,192E-03
400	5,456E-01	700	5,993E-01	1000	3,974E-01	1700	5,900E-01	3200	3,364E-01	4700	1,820E-03
410	5,460E-01	710	6,038E-01	1010	3,941E-01	1750	5,930E-01	3250	3,628E-01	4750	1,038E-03
420	5,487E-01	720	6,035E-01	1020	3,900E-01	1800	5,952E-01	3300	3,700E-01	4800	6,561E-04
430	5,587E-01	730	6,003E-01	1030	3,870E-01	1850	6,000E-01	3350	3,511E-01	4850	3,981E-04
440	5,564E-01	740	5,948E-01	1040	3,850E-01	1900	6,100E-01	3400	2,900E-01	4900	2,104E-04
450	5,690E-01	750	5,873E-01	1050	3,830E-01	1950	6,194E-01	3450	2,170E-01	4950	1,079E-04
460	5,833E-01	760	5,797E-01	1060	3,800E-01	2000	6,300E-01	3500	1,500E-01	5000	3,917E-05
470	5,828E-01	770	5,707E-01	1070	3,790E-01	2050	6,414E-01	3550	1,012E-01	5050	1,503E-05
480	5,770E-01	780	5,610E-01	1080	3,770E-01	2100	6,500E-01	3600	7,000E-02	5100	< 1,000E-05
490	5,715E-01	790	5,511E-01	1090	3,760E-01	2150	6,568E-01	3650	5,860E-02	5150	< 1,000E-05

Optical properties	Mechanical properties	Colormetric properties
Reflection factor	Reference thickness	1 mm 2 mm 3 mm
$P_d = 0,921$	$d = 1,00 \text{ mm}$	
Spectral values guaranteed	Density	Illuminant D65
$\tau_i (405 \text{ nm}) = 0,025 \pm 0,01$	$\rho = 2,44 \text{ g/cm}^3$	x
$\tau_i (546 \text{ nm}) = 0,04 \pm 0,02$	Knoop hardness	y
$\tau_i (694 \text{ nm}) = 0,08 \pm 0,02$	$HK[0.1/20] = 420$	Y
		λ_d
		P_e
		Illuminant A
		x
		y
		Y
		λ_d
		P_e
Refractive indices	Thermal properties	
$n_h (404,7 \text{ nm}) = 1,525$	Transformation temperature	
$n_e (546 \text{ nm}) = 1,511$	$T_g = 469 \text{ }^\circ\text{C}$	
$n_d (587,6 \text{ nm}) = 1,509$	Thermal expansion in $10^{-6}/\text{K}$	
	$\alpha_{(-30^\circ\text{C}/+70^\circ\text{C})} = 6,5$	
	$\alpha_{(20^\circ\text{C}/300^\circ\text{C})} = 7,0$	
Sellmeier coefficients	Chemical properties	
valid from 440 nm to 1550 nm	Chemical resistance	
$B_1 = 0,7032$	FR class = 1	Ionically colored glass
$B_2 = 0,5370$	SR class = 3.2	Neutral density filter
$B_3 = 30,3108$	AR class = 2	
$C_1 = 1,067\text{E-}02 \text{ } \mu\text{m}^2$	Resistance against humidity	
$C_2 = 1,0492\text{E-}02 \text{ } \mu\text{m}^2$	Resistant glass	ISO 23364:2021
$C_3 = 3524,129 \text{ } \mu\text{m}^2$	see pocket catalogue "Optical Filter Glass 2024", chapter 5.5	
Internal quality		Disclaimer
Bubble class 2		All data without tolerances are to be understood to be reference values.

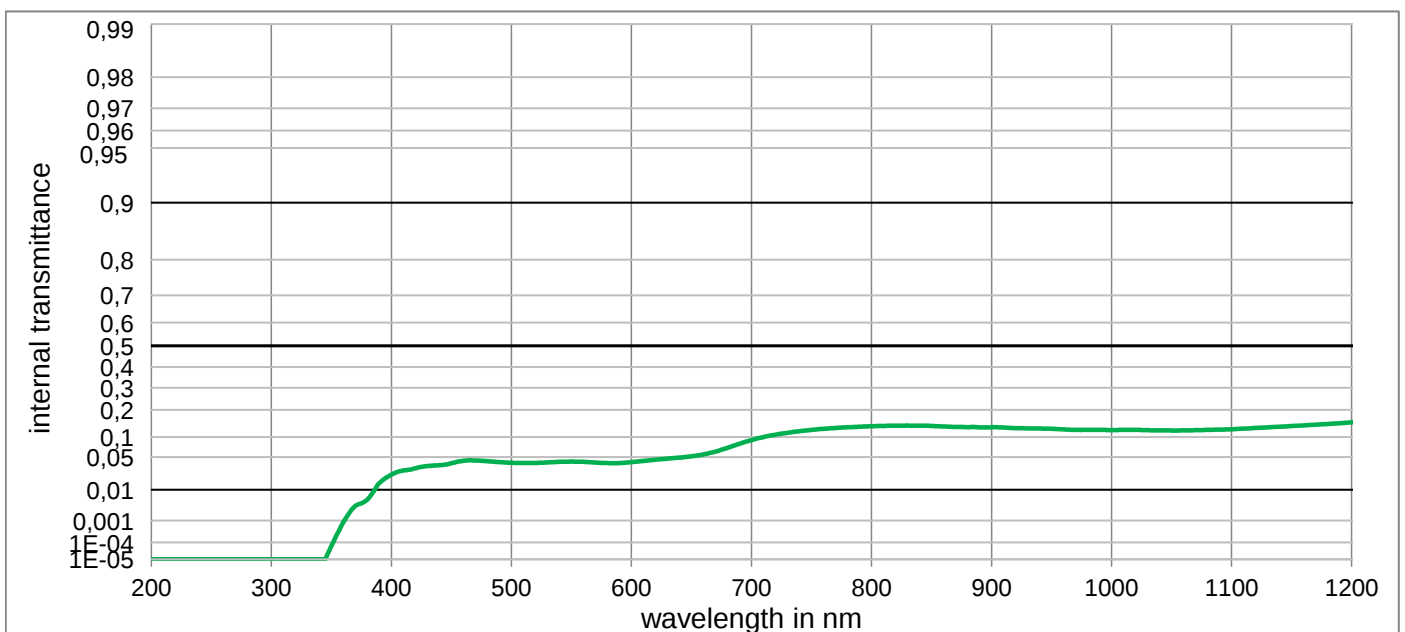

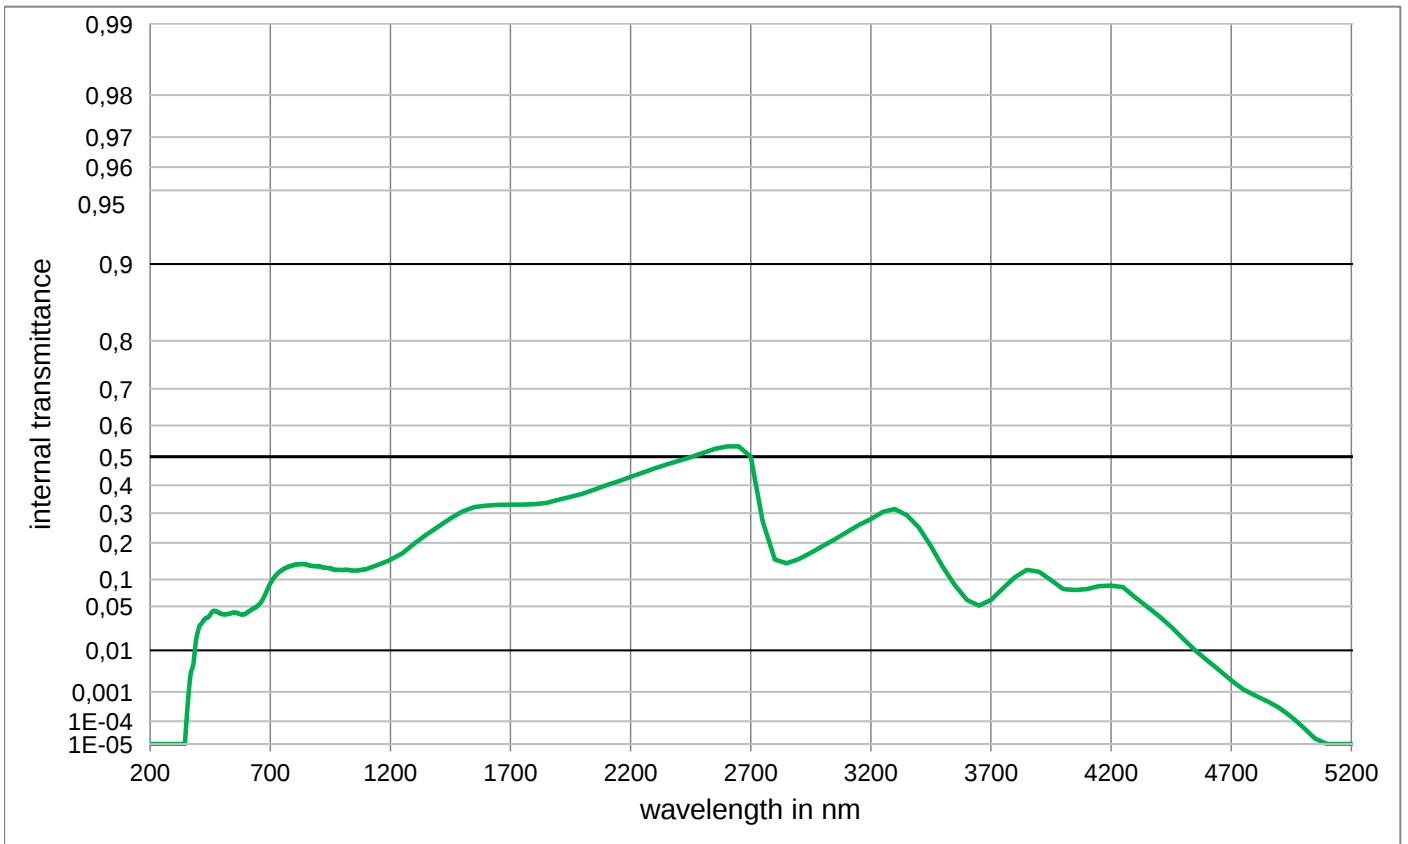Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only


λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	3,959E-02	800	1,359E-01	1100	1,250E-01	2200	4,300E-01	3700	6,000E-02
210	< 1,0E-05	510	3,908E-02	810	1,369E-01	1110	1,273E-01	2250	4,442E-01	3750	8,100E-02
220	< 1,0E-05	520	3,933E-02	820	1,376E-01	1120	1,295E-01	2300	4,600E-01	3800	1,055E-01
230	< 1,0E-05	530	4,021E-02	830	1,381E-01	1130	1,318E-01	2350	4,731E-01	3850	1,231E-01
240	< 1,0E-05	540	4,120E-02	840	1,377E-01	1140	1,340E-01	2400	4,857E-01	3900	1,181E-01
250	< 1,0E-05	550	4,158E-02	850	1,368E-01	1150	1,364E-01	2450	4,982E-01	3950	9,860E-02
260	< 1,0E-05	560	4,120E-02	860	1,350E-01	1160	1,389E-01	2500	5,120E-01	4000	8,000E-02
270	< 1,0E-05	570	3,995E-02	870	1,330E-01	1170	1,414E-01	2550	5,259E-01	4050	7,810E-02
280	< 1,0E-05	580	3,908E-02	880	1,325E-01	1180	1,440E-01	2600	5,340E-01	4100	8,000E-02
290	< 1,0E-05	590	3,908E-02	890	1,319E-01	1190	1,469E-01	2650	5,347E-01	4150	8,590E-02
300	< 1,0E-05	600	4,067E-02	900	1,320E-01	1200	1,501E-01	2700	5,000E-01	4200	8,650E-02
310	< 1,0E-05	610	4,276E-02	910	1,310E-01	1250	1,686E-01	2750	2,710E-01	4250	8,356E-02
320	< 1,000E-05	620	4,500E-02	920	1,290E-01	1300	1,980E-01	2800	1,500E-01	4300	6,457E-02
330	< 1,000E-05	630	4,700E-02	930	1,280E-01	1350	2,268E-01	2850	1,404E-01	4350	4,966E-02
340	< 1,000E-05	640	4,900E-02	940	1,280E-01	1400	2,538E-01	2900	1,514E-01	4400	3,698E-02
350	6,412E-05	650	5,159E-02	950	1,270E-01	1450	2,814E-01	2950	1,700E-01	4450	2,590E-02
360	8,472E-04	660	5,537E-02	960	1,246E-01	1500	3,060E-01	3000	1,900E-01	4500	1,637E-02
370	3,404E-03	670	6,155E-02	970	1,229E-01	1550	3,217E-01	3050	2,112E-01	4550	1,000E-02
380	5,284E-03	680	7,039E-02	980	1,231E-01	1600	3,273E-01	3100	2,347E-01	4600	6,223E-03
390	1,464E-02	690	8,100E-02	990	1,231E-01	1650	3,292E-01	3150	2,582E-01	4650	3,784E-03
400	2,301E-02	700	9,104E-02	1000	1,226E-01	1700	3,300E-01	3200	2,800E-01	4700	2,089E-03
410	2,795E-02	710	1,000E-01	1010	1,231E-01	1750	3,300E-01	3250	3,040E-01	4750	1,186E-03
420	3,108E-02	720	1,074E-01	1020	1,232E-01	1800	3,317E-01	3300	3,149E-01	4800	7,727E-04
430	3,435E-02	730	1,134E-01	1030	1,221E-01	1850	3,368E-01	3350	2,923E-01	4850	5,176E-04
440	3,555E-02	740	1,186E-01	1040	1,214E-01	1900	3,474E-01	3400	2,500E-01	4900	3,148E-04
450	3,872E-02	750	1,228E-01	1050	1,211E-01	1950	3,581E-01	3450	1,900E-01	4950	1,493E-04
460	4,308E-02	760	1,268E-01	1060	1,213E-01	2000	3,700E-01	3500	1,300E-01	5000	5,754E-05
470	4,356E-02	770	1,297E-01	1070	1,220E-01	2050	3,845E-01	3550	8,770E-02	5050	1,820E-05
480	4,231E-02	780	1,320E-01	1080	1,229E-01	2100	4,000E-01	3600	6,000E-02	5100	< 1,000E-05
490	4,069E-02	790	1,340E-01	1090	1,240E-01	2150	4,140E-01	3650	5,110E-02	5150	< 1,000E-05

NG11


Optical properties		
Reflection factor		
P _d = 0,923		
Spectral values guaranteed		
τ _i (405 nm)	=	0,76 ± 0,02
τ _i (546 nm)	=	0,77 ± 0,02
τ _i (694 nm)	=	0,79 ± 0,02
Refractive indices		
n _F (486 nm)	=	1,504
n _e (546 nm)	=	1,5
n _d (587,6 nm)	=	1,499
Sellmeier coefficients		
valid from 365 nm to 1530 nm		
B ₁		1,1839
B ₂		0,0336
B ₃		1,1111
C ₁		7,634E-03 μm ²
C ₂		4,3272E-02 μm ²
C ₃		116,448 μm ²
Internal quality		
Bubble class		2

Mechanical properties	
Reference thickness	
d = 1,00 mm	
Density	
ρ = 2,41 g/cm ³	
Knoop hardness	
HK[0.1/20] = 460	
Thermal properties	
Transformation temperature	
T _g = 481 °C	
Thermal expansion in 10 ⁻⁶ /K	
α (-30°C/+70°C) = 6,7	
α (20°C/300°C) = 7,2	
α (20°C/200°C) = 7	
Chemical properties	
Chemical resistance	
FR class = 1	
SR class = 3.4	
AR class = 2	
Resistance against humidity	
Resistant glass	
see pocket catalogue "Optical Filter Glass 2020", chapter 5.5	

Colormetric properties				
		1 mm	2 mm	3 mm
Illuminant D65	x			
	y			
	Y			
	λ _d			
	P _e			
Illuminant A	x			
	y			
	Y			
	λ _d			
	P _e			
Notes				
Ionically colored glass				
Neutral density filter				
DIN 58131				
Disclaimer				
All data without tolerances are to be understood to be reference values.				

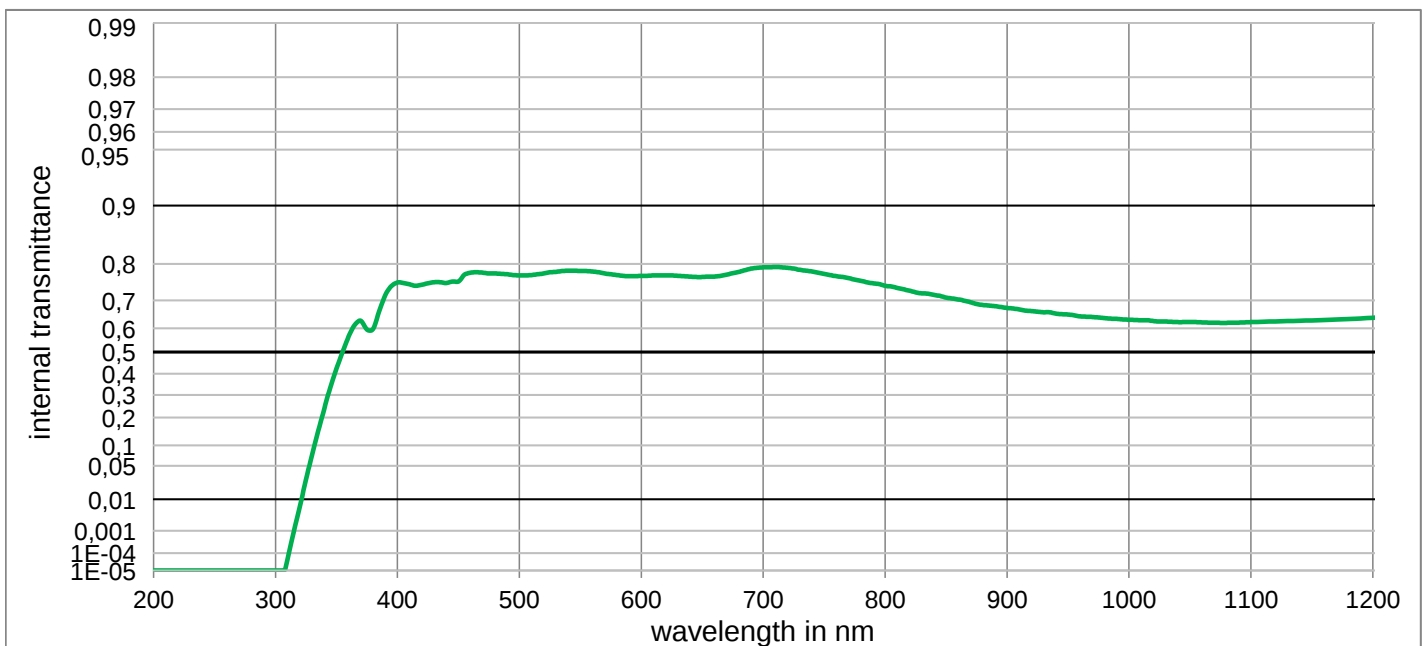

NG11

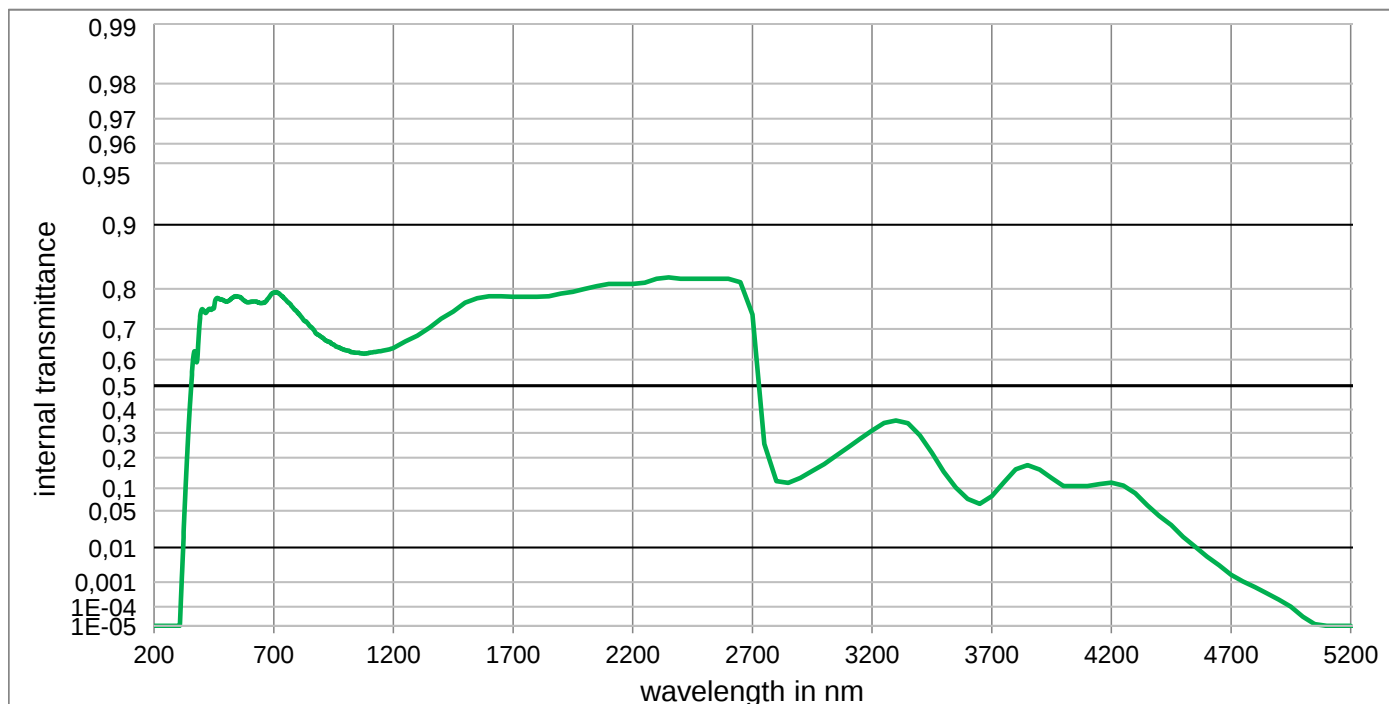Internal transmittance τ_i at reference thickness

The internal transmittance values, tabulated and graphically represented, are reference values only

λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i	λ /nm	τ_i
200	< 1,0E-05	500	7,720E-01	800	7,440E-01	1100	6,240E-01	2200	8,100E-01	3700	8,000E-02
210	< 1,0E-05	510	7,730E-01	810	7,380E-01	1110	6,254E-01	2250	8,124E-01	3750	1,159E-01
220	< 1,0E-05	520	7,770E-01	820	7,300E-01	1120	6,266E-01	2300	8,200E-01	3800	1,583E-01
230	< 1,0E-05	530	7,810E-01	830	7,220E-01	1130	6,278E-01	2350	8,227E-01	3850	1,725E-01
240	< 1,0E-05	540	7,840E-01	840	7,170E-01	1140	6,290E-01	2400	8,200E-01	3900	1,574E-01
250	< 1,0E-05	550	7,830E-01	850	7,090E-01	1150	6,304E-01	2450	8,200E-01	3950	1,300E-01
260	< 1,0E-05	560	7,820E-01	860	7,030E-01	1160	6,318E-01	2500	8,200E-01	4000	1,060E-01
270	< 1,0E-05	570	7,770E-01	870	6,940E-01	1170	6,335E-01	2550	8,200E-01	4050	1,060E-01
280	< 1,0E-05	580	7,730E-01	880	6,850E-01	1180	6,353E-01	2600	8,200E-01	4100	1,058E-01
290	< 1,0E-05	590	7,700E-01	890	6,810E-01	1190	6,375E-01	2650	8,133E-01	4150	1,117E-01
300	< 1,0E-05	600	7,710E-01	900	6,750E-01	1200	6,400E-01	2700	7,400E-01	4200	1,162E-01
310	5,1E-05	610	7,720E-01	910	6,700E-01	1250	6,616E-01	2750	2,545E-01	4250	1,072E-01
320	6,622E-03	620	7,720E-01	920	6,640E-01	1300	6,800E-01	2800	1,200E-01	4300	8,710E-02
330	7,396E-02	630	7,710E-01	930	6,600E-01	1350	7,030E-01	2850	1,150E-01	4350	6,012E-02
340	2,387E-01	640	7,690E-01	940	6,550E-01	1400	7,285E-01	2900	1,300E-01	4400	4,169E-02
350	4,241E-01	650	7,680E-01	950	6,520E-01	1450	7,473E-01	2950	1,527E-01	4450	2,904E-02
360	5,667E-01	660	7,690E-01	960	6,450E-01	1500	7,690E-01	3000	1,762E-01	4500	1,720E-02
370	6,290E-01	670	7,740E-01	970	6,430E-01	1550	7,794E-01	3050	2,073E-01	4550	1,038E-02
380	5,968E-01	680	7,810E-01	980	6,390E-01	1600	7,841E-01	3100	2,400E-01	4600	6,000E-03
390	7,166E-01	690	7,890E-01	990	6,360E-01	1650	7,841E-01	3150	2,752E-01	4650	3,459E-03
400	7,530E-01	700	7,920E-01	1000	6,330E-01	1700	7,831E-01	3200	3,091E-01	4700	1,778E-03
410	7,480E-01	710	7,930E-01	1010	6,310E-01	1750	7,831E-01	3250	3,421E-01	4750	1,052E-03
420	7,470E-01	720	7,910E-01	1020	6,280E-01	1800	7,831E-01	3300	3,525E-01	4800	6,607E-04
430	7,540E-01	730	7,860E-01	1030	6,260E-01	1850	7,841E-01	3350	3,412E-01	4850	3,846E-04
440	7,520E-01	740	7,820E-01	1040	6,240E-01	1900	7,900E-01	3400	2,900E-01	4900	2,089E-04
450	7,559E-01	750	7,760E-01	1050	6,240E-01	1950	7,935E-01	3450	2,186E-01	4950	1,007E-04
460	7,790E-01	760	7,700E-01	1060	6,230E-01	2000	8,000E-01	3500	1,500E-01	5000	3,236E-05
470	7,790E-01	770	7,650E-01	1070	6,220E-01	2050	8,058E-01	3550	1,018E-01	5050	1,271E-05
480	7,770E-01	780	7,580E-01	1080	6,210E-01	2100	8,100E-01	3600	7,350E-02	5100	< 1,000E-05
490	7,750E-01	790	7,510E-01	1090	6,220E-01	2150	8,100E-01	3650	6,310E-02	5150	< 1,000E-05

[schott.com](https://www.schott.com)

Hattenbergstrasse 10, 55122 Mainz, Germany
Phone +49 (0)6131/66-1812, info.optics@schott.com